

Cite this: *J. Mater. Chem. A*, 2024, 12, 25011

Improved ammonia production using Cu₂O@poly-carbazole electrocatalysts in the electrochemical reduction of molecular nitrogen and nitrogen oxoanions†

Luis Herrán,^{‡abc} Diego F. Veliz-Silva,^{‡ab} Colin Poblete,^{ab} Elías Leiva,^{ab} Jessica Honores,^{ab} Esteban Landaeta,^g Mamié Sancy,^{ad} Rodrigo del Río,^{ab} César Sáez-Navarrete,^{ibae} Enrique Dalchiele^f and Mauricio Isaacs^{id*ab}

In the present study, a Cu₂O@PCz electrode for the nitrogen reduction reaction is proposed; this electrode takes advantage of the catalytic properties of Cu₂O in conjunction with conducting polymers such as polycarbazole (PCz). This combination demonstrates an improvement in the catalytic activity and higher stability of this metal oxide in nitrogen electro-reduction reaction (NRR) and nitrogen oxoanion electro-reduction reaction (NORR) processes under aqueous conditions. On this basis, the material synthesized on FTO (SnO₂:F), Cu₂O@PCz, exhibits a faradaic efficiency of around 38.83%, together with an NH₃ productivity of 1.83 μg h⁻¹ cm⁻² in NRR type processes, on applying a potential of -0.8 V (V vs. Ag/AgCl). Similarly, in NORR type processes, the material exhibits NH₃ and N₂H₄ productivity. The latter is the most relevant in terms of the yields obtained. Specifically, using nitrite (NO₂⁻), an efficiency of around 77.72% was obtained, together with a formation rate of 37.02 μg h⁻¹ cm⁻² at a potential of -0.8 V (V vs. Ag/AgCl). Although N₂H₄ is a by-product of ammonia formation, this molecule can be considered an intermediate, which broadens the scope of this study for future research into the production of green chemicals. Finally, this research presents promising new routes for the production of NH₃ at room temperature, highlighting the potential of low-cost materials, easy synthesis, and enhanced stability.

Received 26th April 2024
Accepted 1st August 2024

DOI: 10.1039/d4ta02904f

rsc.li/materials-a

1. Introduction

Ammonia (NH₃) is a fundamental precursor in different chemical processes. This compound plays a crucial role in global food production. In addition, the use of ammonia has become widespread in various fields, being currently a very

studied molecule and of great interest and being proposed as a means of transport and storage of hydrogen due to its hydrogen content of 17.8% by weight, besides remaining in the liquid phase at pressures close to about 8 bars, which allows relatively simple transport and storage processes.¹

The process used for many years for the industrial production of ammonia is known as the Haber-Bosch process.² Currently, this process synthesizes ammonia from N₂ and H₂ in the presence of iron-based catalysts. This synthetic methodology requires a considerable amount of energy and capital, being a very expensive and highly polluting process due to the large amount of greenhouse gases it releases into the environment;³ an example is the hydrogen source of the process, which relies on steam methane reforming of natural gas, which emits more than 300 million tons of carbon dioxide per year.⁴ For this reason, significant efforts have been made to develop environmentally friendly approaches through energy saving and sustainable processes.

One approach with significant potential is the electrochemical nitrogen reduction reaction (NRR), which uses ambient conditions and aqueous solvents as a proton source instead of H₂ gas.^{5,6} Moreover, the energy input in

^aMillenium Institute on Green Ammonia as Energy Vector, Pontificia Universidad Católica de Chile, Santiago, 7820436, Chile. E-mail: misaacs@uc.cl

^bDepartamento de Química Inorgánica, Facultad de Química y de Farmacia, Pontificia Universidad Católica de Chile, Santiago 7820244, Chile

^cDepartamento de Ingeniería Mecánica y Metalúrgica, Escuela de Ingeniería, Pontificia Universidad Católica de Chile, Santiago, 7820436, Chile

^dEscuela de construcción Civil, Facultad de Ingeniería, Pontificia Universidad Católica de Chile, Santiago, 7820436, Chile

^eDepartamento de Ingeniería Química y Bioprocesos, Escuela de Ingeniería, Pontificia Universidad Católica de Chile, Santiago, 7820436, Chile

^fInstituto de Física, Facultad de Ingeniería, Herrera y Reissig 565, C.C. 30, Montevideo, 11000, Uruguay

^gEscuela de Ingeniería, Universidad Central, Av. Santa Isabel 1186, Santiago, 8330563, Chile

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d4ta02904f>

‡ These authors equally contributed to this work.

Electrochemical reactions for ammonia production require the intervention and/or participation of a catalyst to facilitate the reaction. Remarkable progress has been made in this field, with notable advances,¹⁵ such as the development of catalysts synthesized based on Au nanoclusters,¹⁶ Ru nanoparticles¹⁷ and transition metal nitride catalysts.¹⁸ In particular, copper oxide materials have shown great promise for reducing nitrogen compounds to NH_3 by electrocatalysis and photocatalysis.¹⁹ Compared to the precious metal catalysts previously mentioned, a clear advantage of copper oxide materials is their considerably lower cost, specifically cuprous oxide (Cu_2O), that is a low-cost and visible light-sensitive material. Moreover, it has been widely used in electrochemical and photocatalytic conversion processes.^{20,21} This compound possesses conduction and valence band levels suitable for N_2 reduction since it is a p-type semiconductor with a band gap of 2.17 eV and a high electrocatalytic response. Unfortunately, Cu_2O is unstable and could be oxidized, which limits its electrocatalytic activity in aqueous media. It has previously been used to reduce nitrogen derivatives such as NO_3^- (nitrates) and NO_2^- (nitrites) to ammonia and ammonia derivatives; however these electrodes have been shown to be unstable.^{20–24} Moreover, there is little research examining the electrocatalytic performance of Cu_2O for the electrochemical reduction of N_2 , which motivates the possible use of this copper oxide for ammonia generation, in addition to analyzing the possible by-products generated from both N_2 reduction and the reduction of other nitrogen oxoanions on Cu_2O catalysts.^{19,25,26} Given the potential capacity of cuprous oxide in this process, strategies to enhance the stability of this oxide are being explored. Based on the latter, studies have determined, by *in situ*/operating spectroscopy, a direct correlation between changes in the chemical state of the catalyst as a function of potential and time during the $\text{NO}_3\text{RR}/\text{NO}_2\text{RR}$ and the catalytic selectivity of Cu_2O nanocubes, providing information on the main active species involved in the process. From this, it was established that the slow reduction of Cu(I) to metallic Cu at low overpotentials (0.1 V vs. RHE) results in low production rates and efficiencies for NH_3 ,

Based on the above, one of the most promising approaches involves modifying electrodes with a substance that preserves the high stability and durability of Cu₂O while maintaining its excellent catalytic properties. Conductive organic polymers represent a viable option for this purpose. These materials exhibit the typical attributes of conventional polymers, such as solubility, mechanical flexibility, and low production costs, yet they offer conductivity levels comparable to those of semiconductors or even metals.^{33–37} In this instance, the application of carbazole is proposed. This compound belongs to a critical class of heterocycles and offers several advantages, including enhanced stability and a higher redox potential relative to other conducting polymers. Additionally, it exhibits favorable electroactive and photoactive properties.^{38–42} Moreover, although

several methods exist for obtaining polycarbazoles, electrochemical synthesis stands out for its reproducibility and simplicity. On the other hand, this method can be carried out at room temperature with thickness control by varying the current or potential as a function of time.³⁸ Therefore, in this research, the use of copper(i) oxide nanoparticles electrochemically deposited on a polycarbazole (PCz) layer, using an FTO/glass substrate is proposed. This approach is intended to improve the stability of copper oxide nanoparticles to enhance and maintain their potential reducing effect in electrocatalytic reactions for N₂ and nitrogen oxoanion compounds over time.

2. Results and discussion

2.1 Fabrication, characterization and properties

The synthesis of the Cu₂O electrode, stabilized with polycarbazole, was performed using the methodology described in the ESI (S1†). First, the electropolymerization of carbazole on an FTO glass was performed by potential cycling, which leads to the formation of carbamoyl radicals at potentials above 1.2 V against Ag/AgCl.⁴³ The polymerization of carbazole on FTO is a process that occurs with a two-electron transfer and dimerization of the pendant “carbazole” ring through the 3,6-positions (see Fig. S2†).⁴⁴ Subsequently, for Cu₂O deposition, the previously synthesized electrode (FTO/PCz) is subjected to chronopotentiometry using a constant current of −1 mA for 5 min, using a copper lactate solution at pH 12.5. For this process, a current variation is observed as a function of Cu₂O deposition on the electrode (see Fig. S3†).

Fig. 1 illustrates the different morphological and topographical characterization studies of the material. Specifically, in Fig. 1A, transmission electron microscopy (TEM) shows the

copper(i) oxide nanoparticles (black flakes) that are supported on the polycarbazole surface (lighter background).

The size distribution of the copper nanoparticles was observed using a Gaussian distribution with a peak of around 50 nm. Considering 100 nanoparticles, the average size results in a value of 49.91 nm (see Fig. 1B). In Fig. 1C–E, scanning electron microscopy (SEM) images show different material agglomerations on the FTO electrode. These agglomerations of the material are mainly formed by polycarbazole. At the same time, Cu₂O nanoparticles are uniformly deposited all over the surface, which can be seen in Fig. 1C. Fig. 1D shows the EDX (energy dispersive X-ray spectroscopy) mapping; this analysis allows the X-ray generated by the sample to be captured (see ESI, Section S1† for more details). In this case, atomic centers referring to C, O, Cu and Sn are analyzed. Based on the above, the spectrum shows different atomic centers, evidencing the homogeneity of the system with respect to the polymer and the copper nanoparticles. It should be noted that the Sn signals belong to the conductive glass used for the electrodeposition of the catalytic material. On the other hand, the EDX elemental analysis (Fig. 1E) reports a high presence of copper, oxygen, carbon, and tin. The first three elements are given by Cu₂O and polycarbazole deposited on the electrode, while tin is the constituent material of the FTO electrode; it is worth mentioning that the EDX represents the area shown in Fig. 1C. AFM microscopy (Fig. 1F) shows the 3D surface of the synthesized Cu₂O@PCz electrode. The relatively homogeneous deposition of nanoparticles can be observed where the heights and widths of the deposited nanoparticles are close to 100 nm. The cuprous oxide is deposited on the rough surface generated by the polymer. This coincides with the electrode morphology observed in FE-SEM microscopy, as shown in Fig. 1C.

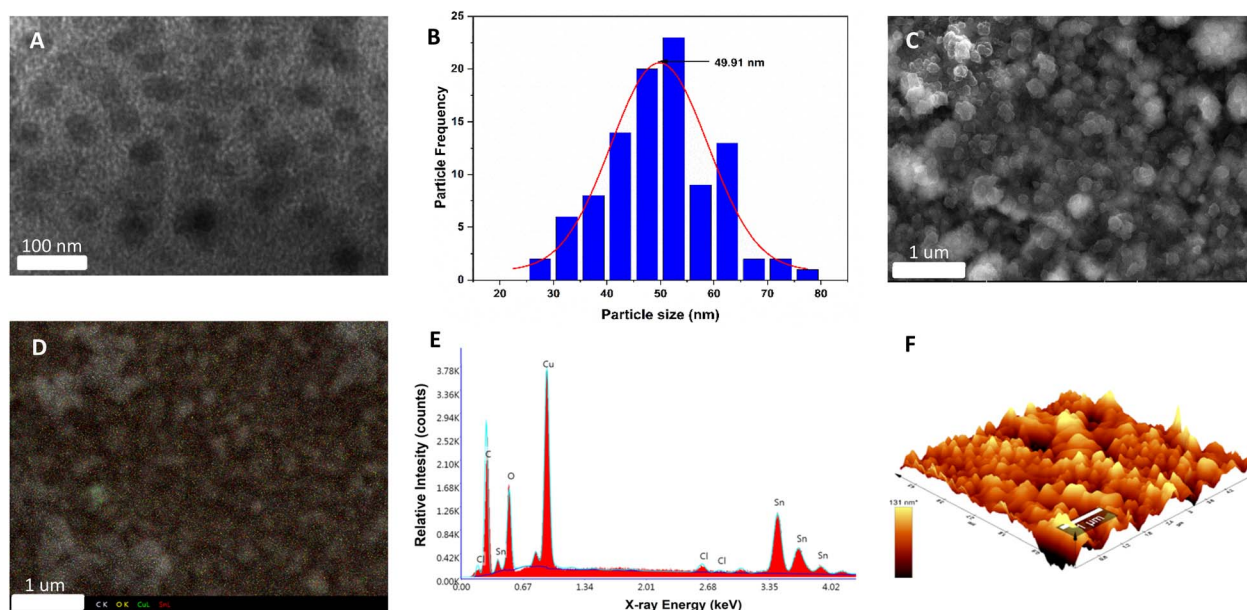


Fig. 1 Morphological and topographical characterization studies of the Cu₂O@PCz electrode surface. (A) TEM image and (B) histogram of the size distribution of Cu₂O nanoparticles on the Cu₂O@PCz electrode surface. (C) FE-SEM image of the Cu₂O@PCz electrode surface. (D) FE-SEM mapping of C, O, Cu and Sn. (E) EDX analysis and (F) AFM image of the Cu₂O@PCz electrode surface.



PCz and Cu₂O@PCz samples were measured, and the characteristic signals of each species were observed separately (Fig. 2B). Specifically, the above 1100 cm⁻¹ signals belonging to PCz and the peaks observed at 1340 and 1603 cm⁻¹ are associated with C=C stretching and C-C aromatic bonds, respectively.⁵² The small peak at 1240 cm⁻¹, appreciable in the PCz spectrum, would correspond to oxidized carbazole,⁵⁰ which disappears upon subsequent deposition of Cu₂O due to the negative potential used. Finally, a peak concerning the conductive glass used (FTO) can be seen at 1090 cm⁻¹.^{53,54}

The characteristic vibrational modes of Cu₂O with A, E and T symmetry can be observed in the region between 100 and 700 cm⁻¹ (see Fig. 3C). The observed shifts are assigned as follows: 221 cm⁻¹ (2_{Eu}), 336 cm⁻¹ (A_{2u}), 412 cm⁻¹ (T_{2g}), 524 cm⁻¹ (T_{1u(TO)}) and 636 cm⁻¹ (T_{1u(LO)}), as reported in the literature.^{50,55} It is worth noting that the areas associated with the polycarbazole (from wavenumber 1000 cm⁻¹) show signs of fluorescence, so that Raman scattering makes it challenging to visualize, both using 532 nm and 785 nm laser excitation. Signals from Cu₂O are present, as shown in Fig. 3B.

Fig. 3D shows 2D Raman spectra, corresponding to a 40 μm × 40 μm region mapped using a filter set to the characteristic band intensity of the T_{1u(LO)} vibrational mode (636 cm⁻¹).^{50,55} The Raman spectrum of Cu₂O reveals a p-type semiconductor character because the observed Raman bands are associated with copper vacancy interactions that conduct electricity through holes; these results agree with those of previously reported investigations.⁵⁶ In addition, a relatively homogeneous deposit of copper oxide nanoparticles is observed, where the signals of greater intensity (yellow color of the 2D spectrum) correspond to the copper nanoparticles. In contrast, the zones represented by black color within the 2D spectrum correspond to polycarbazole zones where the vibration signal analyzed cannot be observed, which indicates that there would not be Cu₂O deposited in those segments.

Fig. 4A shows the existence of Cu, Sn, O, N, and C. The high-resolution XPS spectrum of Cu_{2p} is demonstrated in Fig. 4B. The peak positions of Cu₂O 2p_{1/2} and Cu 2p_{3/2} were 951.99 eV and 932.08 eV, respectively.^{57,58} The peaks adjusted at 935.12 eV and 955.03 eV are attributed to copper(II) oxides, such as CuO, and the two detectable peaks of the shaking satellite indicate the presence of this species in the sample.^{59,60} Unfortunately, it is tough to determine whether the resulting Cu⁺¹ peaks are Cu₂O or metallic Cu due to a slight difference in the peak of the Cu_{2p} core.⁵⁷ As a complementary way, the use of the Cu Auger peak [LMM] is a reliable way to confirm the chemical state in question.⁶¹ Fig. 4C shows that the Auger spectra at 570.03 eV are attributed to Cu₂O and not to metallic Cu due to the lower band energy (568 eV) of Cu.^{57,61,62} Based on the areas obtained from the XPS spectrum, we can identify that 36% corresponds to Cu⁺¹ and 64% to Cu⁺², being in a ratio of approximately 1 : 2.

The high-resolution peaks N_{1s} and C_{1s} are related to the conducting polymer PCz, shown in Fig. 4D and E. The peaks of C_{1s} were divided into six components: the C-C/C-H bond (284.52 eV), C-N bond (285.63 eV), C-O bond (286.86 eV) and C=O bond (288.09 eV).^{63,64} This last peak would correspond to CO₂ adsorbed on the material and the formation of an O-C-O

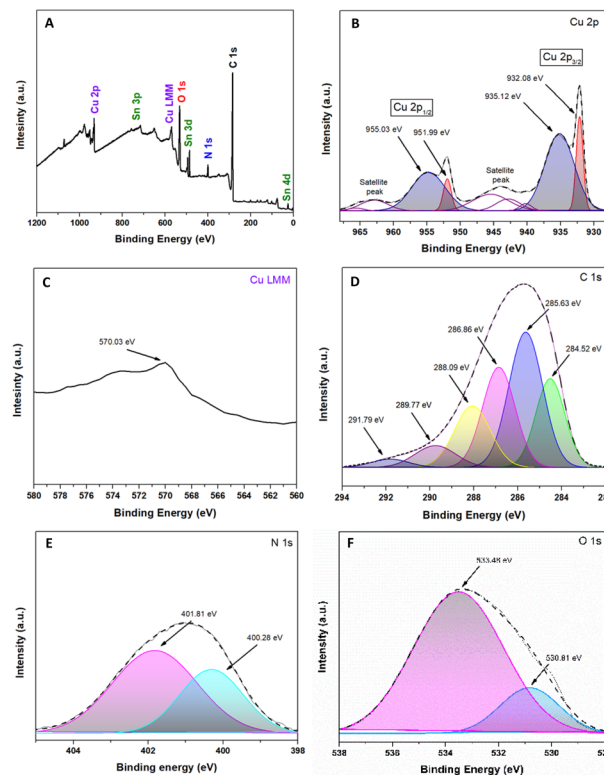


Fig. 4 Spectroscopic analysis XPS of the Cu₂O@PCz electrode. (A) Survey spectra; (B) Cu 2p; (C) Cu 2p AES (Auger electron spectroscopy); (D) C 1s; (E) N 1s; and (F) O 1s.

epoxide group, a product of the interaction between the polymer and the irradiation to which it was exposed, which gives rise to other peaks, such as those originating at 289.77 eV and 291.79 eV.^{63,65} Similarly, among the most important peaks in Fig. 4E, those located at 401.81 eV and 400.28 eV correspond to R₄N⁺ and C-N, respectively.^{63,66} Referring to Fig. 4F, the O_{1s} spectrum can be observed; in particular, the peak located at 530.81 eV corresponds to the presence of Cu-O.⁶⁰ Likewise, the peak at 533.48 eV is attributed to the conductive glass (FTO), which is based on SnO₂.^{67,68}

2.2 Electrocatalytic performance and stability

Once the electrode was characterized, its electrocatalytic performance was evaluated at different potentials (−0.4, −0.6, and −0.8 V; all measurements were performed with respect to a saturated Ag/AgCl reference electrode) for 2 h in 0.1 M Na₂SO₄ aqueous solution at pH 5.95, under room temperature and pressure conditions. A closed H-type cell separated using a Nafion 117 membrane and saturated with N₂ was used; the NH₃ generated and the by-product N₂H₄ were quantified by the indophenol blue method and the method of Watt and Chrisp, respectively. In addition, purity tests of the nitrogen used were carried out to rule out the presence of NO_x *in situ* in the respective procedures, using differential electrochemical mass spectrometry (DEMS) (ESI “S1-DEMS Methodology”†).

Fig. 5 shows the electrochemical results of the linear sweep voltammetry (LSV) curves of the Cu₂O and Cu₂O@PCz







Fig. 5B and C show LSVs obtained with the Cu₂O@PCz electrode, with and without the presence of nitrogen compounds. From this, it can be seen that the blank (LSV in Ar) has a current drop at a potential of -0.7 V, which could be attributed to the HER process. In the presence of NO₃⁻ an onset potential at -0.46 V is observed, revealing that the processes associated with NO₃⁻ reduction are generated at this potential.

Fig. 6A–C show the faradaic efficiency and production rates of ammonia and hydrazine obtained for the electroreduction of NO_2^- , NO_3^- and N_2 , respectively. For the NO_3^- reduction, the faradaic efficiency was around 39% at -0.6 V; this value is lower than that of other reported catalysts, which exceed 90%, mainly due to the presence of other by-products generated from the interaction with Cu, such as NO_2^- , NO, and N_2 .^{69–71} In relation to the electroreduction of the NO_2^- species, the great catalytic capacity of the system for the production of hydrazine can be observed, in parallel to the production of ammonia. From this, a faradaic efficiency of 77.72% and a high production rate ($37.025 \mu\text{g h}^{-1} \text{cm}^{-2}$) can be obtained at a potential of -0.8 V. These results are promising for the electrochemical production of this by-product. Hydrazine can be used as a preliminary step to green ammonia electrowinning, but, like ammonia, it is also considered a green hydrogen source.^{72–74} This fact makes it imperative for a future study of the way to obtain this compound, to identify new areas of study and application for this phenomenon, which has not been possible to identify in other investigations, with such high faradaic efficiencies. The



values obtained for hydrazine production could not be compared with those in other studies in the literature, since hydrazine is not quantified in this type of analysis because it is considered a by-product of ammonia production. When NO_2^- is directly reduced, NH_3 and N_2 are evaluated as reaction products;^{75–77} however, previous studies indicated that copper oxides, together with other transition metals such as Pd, can allow the subsequent reduction of the generated hydrazine to ammonia, generating a faradaic efficiency higher than 90%, considering hydrazine as an intermediate product of the reaction.⁷⁸ For N_2 reduction, a production rate of $1.81 \mu\text{g h}^{-1} \text{cm}^{-2}$ was obtained, together with a faradaic efficiency of 38.82% for ammonia formation, using a potential of -0.8 V . Although this production value is within the average value of the catalysts used in the NRR, the faradaic efficiency obtained is much higher compared to the average faradaic efficiency of the catalysts, which does not exceed 10% of average efficiency, demonstrating the extraordinary capacity of this system for NRR type reactions.^{79–81} Determination of efficiency and comparison data are detailed in the ESI (see Table S2†).

Fig. 7 shows chronoamperometric studies of the $\text{Cu}_2\text{O}@PCz$ electrode at different potentials with the different precursors for the ammonia electrosynthesis. These results reveal that the $\text{Cu}_2\text{O}@PCz$ electrode exhibits stable current densities at various potentials, with constant charge retentions over time for each of the precursors; using a potential of -0.6 V (vs. Ag/AgCl), such stability is close to 92.5% after 2 hours of continuous electrochemical tests (Fig. 7A–C).

On the other hand, using the same potential and observing the highest stability using N_2 as a precursor, both NH_3 production rates and the faradaic efficiency of such a process are analyzed (Fig. 8). The values remained relatively constant during 20 h of continuous NRR electrochemical testing, with a retention of current stability of about 95% up to 10 h of electrolysis (see Fig. 8B). Along with this, the faradaic efficiencies and ammonia generation rate also remained constant up to 10 hours. After that, both a significant variation in current and

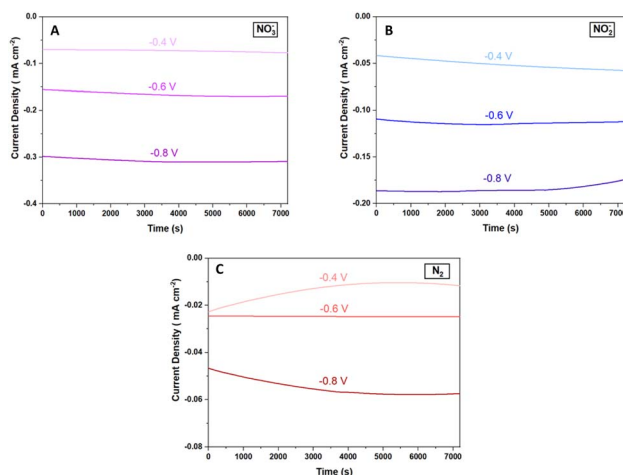


Fig. 7 Galvanostatic curves for the $\text{Cu}_2\text{O}@PCz$ electrode at different potentials using (A) NO_3^- , (B) NO_2^- , and (C) N_2 .

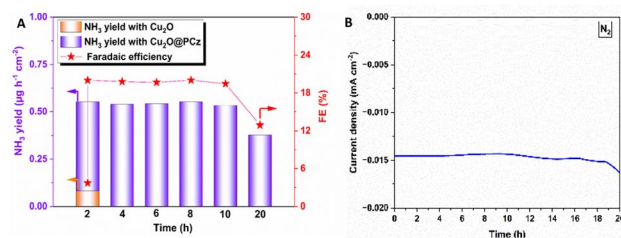


Fig. 8 (A) Faradaic efficiency and generation rate at different potentials for ammonia in the NRR process for 20 hours at -0.6 V vs. Ag/AgCl . The two-hour bar shows a comparison between Cu_2O PCz-stabilized and Cu_2O non-stabilized electrodes. (B) Stability of the NRR process during 20 hours of electrolysis.

a considerable decrease in faradaic efficiency and ammonia formation rate are observed. These results can confirm the high stability of the $\text{Cu}_2\text{O}@PCz$ electrode, both when working at different potentials and when used for prolonged periods of time, without losing its catalytic properties, at least up to 10 hours of continuous work. In addition, the two-hour bar (see Fig. 8A) shows a comparison between the yields and faradaic efficiency for the stabilized $\text{Cu}_2\text{O}@PCz$ and unstabilized Cu_2O electrodes; an increase in ammonia production yield and faradaic efficiency of the catalyst is observed in the presence of the polymer, indicating a higher catalytic activity when Cu_2O nanoparticles are stabilized. This could also indicate that the oxidation of Cu_2O to CuO in the absence of the polymer generates a lower catalytic activity for N_2 reduction, since this species would not be active for the NRR process. This can also be seen in the NO_3^- and NO_2^- reduction processes, by comparing the two 2-hour electrolysis processes, with and without the polymer (Fig. S9†).

2.3 Characterization after electrocatalysis

After the catalytic evaluation, the $\text{Cu}_2\text{O}@PCz$ electrode is characterized, using the nitrogen reduction at -0.6 V (vs. Ag/AgCl) as a model to analyze the proposed electrode.

Regarding the stability of the material, analyzing the different components separately (FTO glass, Cu_2O and PCz respectively) and the $\text{Cu}_2\text{O}@PCz$ electrode. The behaviors of the different currents along the catalysis were plotted (Fig. 9A). From this; it is observed that the FTO conductive glass has a relatively stable current well below that of the final electrode constituents. On the other hand, in the electrode with the respective polymer PCz an initial current increase is observed. Still, it decreases over time, eventually stabilizing and reaching a value similar to that of the conductive glass without deposit, which may be due to the presence of a constant reduction of possible unpolymers oxidized carbazole to a point where the carbazole is completely reduced; this electrode does not present catalytic activity for N_2 .⁸² Similarly, the Cu_2O and $\text{Cu}_2\text{O}@PCz$ currents are relatively stable, but there is an improvement in the cathodic current with the presence of the polymer in the catalyst.

In Fig. 9B, it can be observed that, after the catalytic cycle, in the absence of the polymer, the intensity of the characteristic

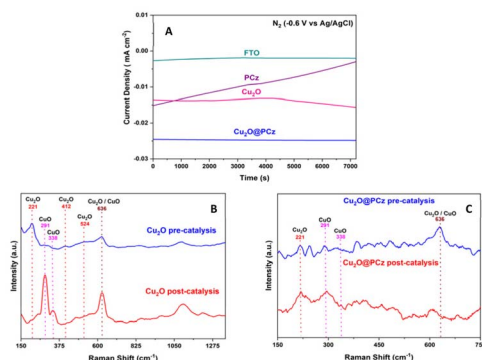


Fig. 9 Stability tests for the $\text{Cu}_2\text{O}@PCz$ electrode and its components on applying a potential of -0.6 V vs. Ag/AgCl in the presence of N_2 : (A) galvanostatic curves for: FTO (green), PCz (purple), Cu_2O (pink), and $\text{Cu}_2\text{O}@PCz$ (blue). (B) Raman spectra of the Cu_2O electrode before and after electrocatalysis. (C) Raman spectra of the $\text{Cu}_2\text{O}@PCz$ electrode before and after electrocatalysis.

signals of Cu_2O decreased, and in turn, two characteristic signals in the presence of CuO in the sample appear (291 and 338 cm^{-1}),⁸³ demonstrating the low stability of Cu_2O nanoparticles in the catalytic cycle. In Fig. 9C, it can be observed that, in the presence of the polymer together with the Cu_2O nanoparticles, there is no increase in the intensity of the signals belonging to CuO , as it occurs when there is no polymer in the catalyst (see Fig. 9B). However, these signals are already present in the system, before catalysis, which indicates that both species are present in the catalyst and that they are stabilized by the polycarbazole present, due to the almost insignificant change in the pre- and post-catalysis signals. This is also demonstrated in the XPS spectrum of the $\text{Cu}_2\text{O}@PCz$ electrode analyzed above (Fig. 4A), where this electrode contains both Cu_2O and CuO species pre-catalysis.

On the other hand, regarding the morphological changes of the $\text{Cu}_2\text{O}@PCz$ cathode, an important change in the morphology of the material can be seen in the TEM after catalysis, where, unlike those seen in Fig. 1, there are clusters of material with different diameters, which exceed 300 nm (see Fig. S11[†]). In parallel, it can be observed in Fig. 10 that the FE-SEM of the material changes after 20 hours of electrolysis, generating clusters of copper species on the surface. This may be because during the electroreduction process, changes in the electrochemical conditions, such as the ion concentration, pH, and applied potential, may favor the nucleation and growth of the particles, generating these structures. In addition, when observing the magnification of these “spherical” structures (Fig. S12[†]), the presence of nanometric structures in the form of flakes is observed on the electrode before catalysis (see Fig. 1).

Similarly, the XPS spectrum of the material shows an important variation in the distribution of copper species. Specifically, before electrolysis, the distribution of $\text{Cu}^{+1}/\text{Cu}^{+2}$ was $1:2$ (Fig. 4), whereas after 20 hours of electrolysis, the distribution changes to about $1:1$ respectively (Fig. S13[†]). The change may be due to several factors, such as the migration of copper ions on the surface, due to the agglomeration evidenced.

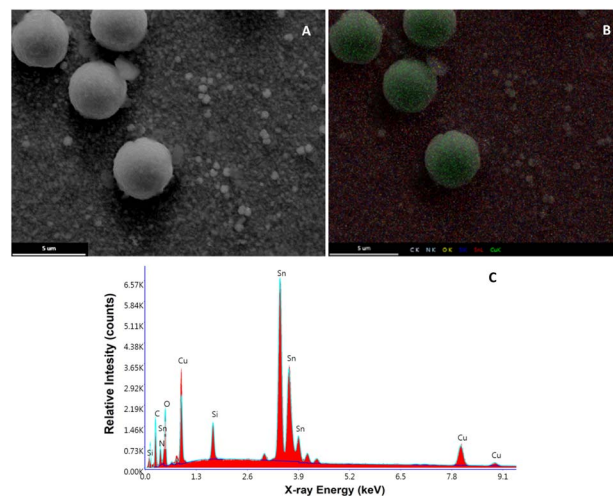


Fig. 10 (A) FE-SEM image of the $\text{Cu}_2\text{O}@PCz$ electrode surface after 10 hours of electrolysis. (B) FE-SEM mapping of C, O, Cu and Sn. (C) EDX analysis.

Along with this, at the surface level, some of the Cu^{2+} ions may have been reduced as a result of the negative potential applied. All these factors may result in some of the energy applied to the system being lost in these processes, generating a drop in the efficiency of nitrogen reduction.

Impedance analysis of Cu_2O and $\text{Cu}_2\text{O}@PCz$ was also performed before and after the NRR process, as shown in Fig. 11. Nyquist diagrams of the Cu_2O deposits reveal several capacitive semicircles between the high-frequency range (HF) and low-frequency domain (MF-LF). The impedance response at HF can be associated with the Cu_2O oxidation reaction previously discussed (see Fig. 9B). The impedance behavior at MF-LF can be related to the diffusion process of N_2 in the solution and Cu_2O because the electrochemical measurements were carried out under static conditions. The NRR did not significantly influence the impedance response of the $\text{Cu}_2\text{O}@PCz$ electrode after 2 h at -0.6 V (vs. Ag/AgCl), also in agreement with the Raman analysis (see Fig. 9C). This suggests that Cu_2O is stabilized when deposited on the PCz layer formed on the FTO glass. However, a change in the resistivity of the material was determined after 20 h of electrolysis (see Fig. 11B), which was attributed to the change in the electrode surface, specifically to

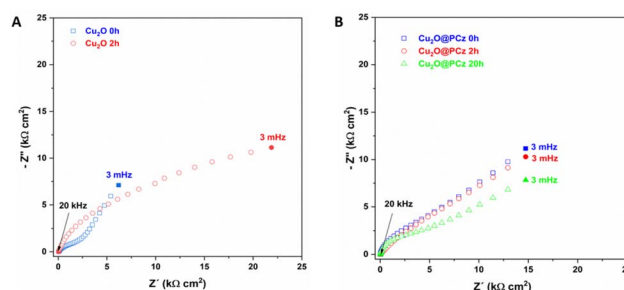


Fig. 11 Nyquist diagram of (A) Cu_2O and (B) $\text{Cu}_2\text{O}@PCz$ at different NRR times, using -0.6 V (vs. Ag/AgCl).

the change in the oxidation state of Cu. Along with this, the change in the electrode surface can be seen in Fig. 10, where after the 20 hours of electrolysis, the copper present on the cathode begins to agglomerate, forming large spheres of copper oxide, which has a direct effect on the electrical resistivity of the material.

3. Conclusion

A Cu₂O@PCz electrode was prepared, and its characteristic vibrational states (ATR-IR and Raman) and chemical bonding characteristics (XPS) were characterized. Thus, homogeneous deposits of these nanoparticles were generated on the electrode surface, which was verified by 2D Raman spectroscopy and EDX. Along with the above, sizes, particle shapes, and deposition thicknesses (≈ 50 nm, flakes, and $0.60\ \mu\text{m}$, respectively) could be identified from AFM, TEM and FE-SEM images. Similarly, stability analyses showed that the polymeric structure affects the long-term stabilization of copper(i) oxide nanoparticles when working between nitrogen reduction potentials, both at short and long electrolysis times (2 and 20 hours, respectively). Finally, it should be noted that the proposed electrodes have great potential to be used in the electrocatalysis of ammonia from molecular nitrogen and nitrogen oxoanions (NO_2^- and NO_3^-), and ammonia production rates around $2\ \mu\text{g h}^{-1}\text{cm}^{-2}$ were obtained, together with a faradaic efficiency of above 30% using NO_3^- and N_2 as precursors. Regarding the latter, the efficiency of other catalysts does not exceed 10%, rendering this material highly promising for future research and application. Similarly, remarkable yields have been achieved in the production of hydrazine, particularly when reducing nitrite at potentials of -0.8 V. This process generated formation rates of $37\ \mu\text{g h}^{-1}\text{cm}^{-2}$ with a faradaic efficiency of approximately 78%. These results, unmentioned in other studies, suggest a possible new research direction in the utilization of copper(i) oxide and nitrite to produce this critical chemical, which tends to be considered a by-product in green ammonia electrowinning.

Data availability

Data are available upon request from the authors.

Author contributions

L. Herrán, D. Veliz-Silva and Colin Poblete conceptualized the idea and experimental design. L. Herrán, D. Veliz-Silva and E. Leiva, with the support of R. del Río, M. Isaacs and C. Saez, prepared the catalysts and evaluated the electrochemical performance of the reduction of nitrogenous compounds. L. Herrán, D. Veliz-Silva E. Landaeta, J. Honores and E. Dalchiele contributed to the material characterization of the catalysts. All the work was supervised by M. Isaacs and M. Sancy. L. Herrán and D. Veliz-Silva contributed equally, and all the authors actively participated in the discussion of the results.

Conflicts of interest

The authors declare no conflict of interest.

Acknowledgements

The authors would like to express their gratitude to Cedenna Project AFB220001, FONDECYT Regular Projects 1221179, FONDEQUIP EQM150020, EQM190016, and EQM150101, the Millennium Institute of Green Ammonia as Energy Vector ICN2021_023(MIGA) and ANID Becas/Doctorado Nacional 21231544.

Notes and references

- 1 R. Lan, J. T. S. Irvine and S. Tao, *Int. J. Hydrogen Energy*, 2012, **37**, 1482–1494.
- 2 M. A. Sutton, D. Simpson, P. E. Levy, R. I. Smith, S. Reis, M. van Oijen and W. de Vries, *Glob Change Biol.*, 2008, **14**, 2057–2063.
- 3 K. Wang, D. Smith and Y. Zheng, *Carbon Resour. Convers.*, 2018, **1**, 2–31.
- 4 Y. Tanabe and Y. Nishibayashi, *Coord. Chem. Rev.*, 2013, **257**, 2551–2564.
- 5 E. Skúlason, T. Bligaard, S. Gudmundsdóttir, F. Studt, J. Rossmeisl, F. Abild-Pedersen, T. Vegge, H. Jónsson and J. K. Nørskov, *Phys. Chem. Chem. Phys.*, 2012, **14**, 1235–1245.
- 6 D. Kim, S. Surendran, Y. Lim, H. Choi, J. Lim, J. Y. Kim, M. K. Han and U. Sim, *Int. J. Energy Res.*, 2022, **46**, 4119–4129.
- 7 C. Tang and S. Z. Qiao, *Chem. Soc. Rev.*, 2019, **48**, 3166–3180.
- 8 T. Mou, J. Long, T. Frauenheim and J. Xiao, *ChemPlusChem*, 2021, **86**, 1211–1224.
- 9 A. R. Singh, B. A. Rohr, J. A. Schwalbe, M. Cargnello, K. Chan, T. F. Jaramillo, I. Chorkendorff and J. K. Nørskov, *ACS Catal.*, 2017, **7**, 706–709.
- 10 B. H. R. Suryanto, H. L. Du, D. Wang, J. Chen, A. N. Simonov and D. R. MacFarlane, *Nat. Catal.*, 2019, **2**, 290–296.
- 11 Y. Liu, M. Cheng, Z. He, B. Gu, C. Xiao, T. Zhou, Z. Guo, J. Liu, H. He, B. Ye, B. Pan and Y. Xie, *Angew. Chem., Int. Ed.*, 2018, **131**, 741–745.
- 12 H. Hirakawa, M. Hashimoto, Y. Shiraishi and T. Hirai, *ACS Catal.*, 2017, **7**, 3713–3720.
- 13 Y. Yao and L. Zhang, *Sci. Bull.*, 2022, **67**, 1194–1196.
- 14 Z. Deng, H. Liu, H. Wang, C. Ma, J. Du and B. Zheng, *Inorg. Chem. Front.*, 2024, **11**, 2339–2345.
- 15 B. H. R. Suryanto, H.-L. Du, D. Wang, J. Chen, A. N. Simonov and D. R. MacFarlane, *Nat. Catal.*, 2019, **2**, 290–296.
- 16 M.-M. Shi, D. Bao, B.-R. Wulan, Y.-H. Li, Y.-F. Zhang, J.-M. Yan and Q. Jiang, *Adv. Mater.*, 2017, **29**, 1606550.
- 17 A. Liu, M. Gao, Y. Gao, X. Ren, Y. Yang, Q. Yang, Y. Li, L. Gao, X. Liang and T. Ma, *Inorg. Chem. Commun.*, 2020, **120**, 108169.
- 18 S. Y. Park, Y. J. Jang and D. H. Youn, *Catalysts*, 2023, **13**, 1–19.
- 19 S. Zhang, Y. Zhao, R. Shi, C. Zhou, G. I. N. Waterhouse, Z. Wang, Y. Weng and T. Zhang, *Angew. Chem., Int. Ed.*, 2021, **60**, 2554–2560.
- 20 M. Madasu, C. F. Hsia, S. Rej and M. H. Huang, *ACS Sustainable Chem. Eng.*, 2018, **6**, 11071–11077.



- 21 F. Matamala-Troncoso, C. Ky Nguyen, D. R. MacFarlane, M. Isaacs and C. Sáez-Navarrete, *Mater. Lett.*, 2021, **293**, 1–4.
- 22 M. García, J. Honores, D. Quezada, C. Díaz, P. Dreyse, F. Celis, C. P. Kubiak, G. Canzi, F. Guzmán, M. J. Aguirre and M. Isaacs, *Electrochim. Acta*, 2016, **192**, 61–71.
- 23 K. Calfumán, M. J. Aguirre, P. Cañete-Rosales, S. Bollo, R. Llusar and M. Isaacs, *Electrochim. Acta*, 2011, **56**, 8484–8491.
- 24 L. Fang, S. Wang, C. Song, S. Lu, X. Yang, X. Qi and H. Liu, *Chem. Eng. J.*, 2022, **446**, 1–10.
- 25 P. E. De Jongh, D. Vanmaekelbergh and J. J. Kelly, *Chem. Mater.*, 1999, **11**, 3512–3517.
- 26 X. Yuan, H. Yuan, L. Ye, J. Hu, Y. Xu and P. Li, *RSC Adv.*, 2015, **5**, 42855–42860.
- 27 L. Bai, F. Franco, J. Timoshenko, C. Rettenmaier, F. Scholten, H. S. Jeon, A. Yoon, M. Rüschler, A. Herzog, F. T. Haase, S. Köhl, S. W. Chee, A. Bergmann and R. C. Beatriz, *J. Am. Chem. Soc.*, 2024, **146**, 9665–9678.
- 28 Y. Cheng, X. Li, P. Shen, Y. Guo and K. Chu, *Energy Environ. Mater.*, 2023, **6**, 1–7.
- 29 Y. Liu, W. Qiu, P. Wang, R. Li, K. Liu, K. M. Omer, Z. Jin and P. Li, *Appl. Catal., B*, 2024, **340**, 1–8.
- 30 C. Li, S. Zhang, Z. Ding, H. Zhou, G. Wang and H. Zhang, *Inorg. Chem. Front.*, 2020, **7**, 3555–3560.
- 31 Z. X. Ge, Y. Ding, T. J. Wang, F. Shi, P. J. Jin, P. Chen, B. He, S. Bin Yin and Y. Chen, *J. Energy Chem.*, 2023, **77**, 209–216.
- 32 Q. Xue, Z. Wang, Y. Ding, F. Li and Y. Chen, *Chin. J. Catal.*, 2023, **45**, 6–16.
- 33 S. Zhang, Q. Li and S. Zhang, *Regener. Ther.*, 2023, **24**, 85–93.
- 34 M. Zhang, L. Wang, H. Xu, Y. Song and X. He, *Nanomicro Lett.*, 2023, **15**, 135.
- 35 T. Zhang, X. Huo, L. Wang, F. Ma and Y. Hou, *J. Phys. D Appl. Phys.*, 2023, **56**, 435503.
- 36 J. Li, H. Sun, S.-Q. Yi, K.-K. Zou, D. Zhang, G.-J. Zhong, D.-X. Yan and Z.-M. Li, *Nanomicro Lett.*, 2022, **15**, 15.
- 37 K. Arjun and B. Karthikeyan, *Appl. Phys. A*, 2023, **129**, 543.
- 38 F. Bekkar, F. Bettahar, I. Moreno, R. Meghabar, M. Hamadouche, E. Hernández, J. L. Vilas-Vilela and L. Ruiz-Rubio, *Polymers*, 2020, **12**, 1–33.
- 39 K. Hoshino, N. Yazawa, Y. Tanaka, T. Chiba, T. Izumizawa and M. Kubo, *ACS Appl. Mater. Interfaces*, 2010, **2**, 413–424.
- 40 W. Sangwan, K. Petcharoen, N. Paradee, W. Lerdwijitjarud and A. Sirivat, *Carbohydr. Polym.*, 2016, **151**, 213–222.
- 41 M. Guzel, Y. Torlak, H. Choi and M. Ak, *Mater. Res. Bull.*, 2023, **167**, 112406.
- 42 T. Soganci, Y. Baygu, N. Kabay, G. Dumlu, Y. Gök and M. Ak, *New J. Chem.*, 2020, **44**, 18616–18624.
- 43 U. Geissler, M. L. Hallensleben, A. Rienecker and N. Rohde, *Soluble Polycarbazoles and Carbazole Motied Electrodes*, 1997, vol. 84.
- 44 A. F. Frau, N. C. Estillore, T. M. Fulghum and R. C. Advincula, *ACS Appl. Mater. Interfaces*, 2010, **2**, 3726–3737.
- 45 S. Bijani, R. Schrebler, E. A. Dalchiele, M. Gabás, L. Martínez and J. R. Ramos-Barrado, *J. Phys. Chem. C*, 2011, **115**, 21373–21382.
- 46 S. Bijani, L. Martínez, M. Gabás, E. A. Dalchiele and J. R. Ramos-Barrado, *J. Phys. Chem. C*, 2009, **113**, 19482–19487.
- 47 B. D. Cullity, *Elements of X-Ray Diffraction*, Addison-Wesley Publishing Company Inc., Reading, USA, 2nd edn, 1978.
- 48 N. G. Elfadill, M. R. Hashim, K. M. Chahrour, M. A. Qaeed and M. Bououdina, *Superlattices Microstruct.*, 2015, **85**, 908–917.
- 49 A. S. Sarac, M. Ates and E. A. Parlak, *J. Appl. Electrochem.*, 2006, **36**, 889–898.
- 50 S. Bouachma, K. Ayouz-Chebout, M. Kechouane, A. Manseri, C. Yaddadene, H. Menari and N. Gabouze, *Appl. Phys. A: Mater. Sci. Process.*, 2022, **128**, 1–13.
- 51 P. T. S. de la Cruz, K. Irikura, A. Lachgar, J. C. Cardoso, H. A. Cavero and M. V. B. Zanoni, *Electrocatalysis*, 2021, **11**, 546–554.
- 52 A. S. Sarac, S. A. M. Tofail, M. Serantoni, J. Henry, V. J. Cunnane and J. B. McMonagle, *Appl. Surf. Sci.*, 2004, **222**, 148–165.
- 53 N. Wang, J. Zhu, X. Zheng, F. Xiong, B. Huang, J. Shi and C. Li, *Faraday Discuss.*, 2014, **176**, 185–197.
- 54 Z. Jiang, D. Yang, N. Wang, F. Zhang, B. Zhao, S. Tan and J. Zhang, *Sci. China Chem.*, 2013, **56**, 1573–1577.
- 55 E. Landaeta, Z. D. Schultz, A. Burgos, R. Schrebler and M. Isaacs, *Green Chem.*, 2018, **20**, 2356–2364.
- 56 P. Choubey, T. Berlijn, A. Kreisel, C. Cao and P. J. Hirschfeld, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2014, **90**, 1–5.
- 57 H. Gong, Y. Zhang, Y. Cao, M. Luo, Z. Feng, W. Yang, K. Liu, H. Cao and H. Yan, *Appl. Catal., B*, 2018, **237**, 309–317.
- 58 S. Karthikeyan, S. Kumar, L. J. Durndell, M. A. Isaacs, C. M. A. Parlett, B. Coulson, R. E. Douthwaite, Z. Jiang, K. Wilson and A. F. Lee, *ChemCatChem*, 2018, **10**, 3554–3563.
- 59 X. Li, W. Kong, X. Qin, F. Qu and L. Lu, *Microchim. Acta*, 2020, **187**, 1–9.
- 60 Z. Dan, Y. Yang, F. Qin, H. Wang and H. Chang, *Materials*, 2018, **11**, 1–14.
- 61 Z. Yin, Y. Xiao, X. Wan, Y. Jiang, G. Chen, Q. Shi and S. Cao, *J. Mater. Sci.*, 2021, **56**, 3874–3886.
- 62 M. Zhang, Z. Chen, Y. Wang, J. Zhang, X. Zheng, D. Rao, X. Han, C. Zhong, W. Hu and Y. Deng, *Appl. Catal., B*, 2019, **246**, 202–210.
- 63 P. Niu, H. Huang, L. Zhao, C. Zhang, Z. Shen and M. Li, *J. Electroanal. Chem.*, 2021, **894**, 1–10.
- 64 M. Majumder, R. B. Choudhary and A. K. Thakur, *Carbon N. Y.*, 2019, **142**, 650–661.
- 65 S. Yamamoto, K. Takeuchi, Y. Hamamoto, R. Y. Liu, Y. Shiozawa, T. Koitaya, T. Someya, K. Tashima, H. Fukidome, K. Mukai, S. Yoshimoto, M. Suemitsu, Y. Morikawa, J. Yoshinobu and I. Matsuda, *Phys. Chem. Chem. Phys.*, 2018, **20**, 19532–19538.
- 66 R. Kessel and J. W. Schultze, *Surface Analytical and Photoelectrochemical Investigations of Conducting Polymers*, 1990, vol. 16.
- 67 W. Liu, Q. Kang, L. Wang, L. Wen and Z. Li, *Environ. Sci. Pollut. Res.*, 2022, **29**, 51989–52002.
- 68 P. G. Choi, N. Izu, N. Shirahata and Y. Masuda, *ACS Appl. Nano Mater.*, 2019, **2**, 1820–1827.



- 69 F. Wang, H. Zhao, G. Zhang, H. Zhang, X. Han and K. Chu, *Adv. Funct. Mater.*, 2023, **34**, 1–9.
- 70 N. Isoda, H. Yokoyama, M. Nojiri, S. Suzuki and K. Yamaguchi, *Bioelectrochemistry*, 2010, **77**, 82–88.
- 71 E. Murphy, Y. Liu, I. Matanovic, M. Rüschler, Y. Huang, A. Ly, S. Guo, W. Zang, X. Yan, A. Martini, J. Timoshenko, B. R. Cuenya, I. V. Zenyuk, X. Pan, E. D. Spörke and P. Atanassov, *Nat. Commun.*, 2023, **14**, 4554.
- 72 X. Liu, W. Sun, X. Hu, J. Chen and Z. Wen, *Chem. Eng. J.*, 2023, **474**, 1–10.
- 73 L. Zhu, J. Huang, G. Meng, T. Wu, C. Chen, H. Tian, Y. Chen, F. Kong, Z. Chang, X. Cui and J. Shi, *Nat. Commun.*, 2023, **14**, 1–13.
- 74 C. Lim, H. Roh, E. H. Kim, H. Kim, T. Park, D. Lee and K. Yong, *Small*, 2023, **19**, 1–11.
- 75 L. Mattarozzi, S. Cattarin, N. Comisso, P. Guerriero, M. Musiani, L. Vázquez-Gómez and E. Verlato, *Electrochim. Acta*, 2013, **89**, 488–496.
- 76 D. Reyter, D. Bélanger and L. Roué, *Electrochim. Acta*, 2008, **53**, 5977–5984.
- 77 J. Choi, J. Choi, H. L. Du, H. L. Du, C. K. Nguyen, C. K. Nguyen, B. H. R. Suryanto, A. N. Simonov, A. N. Simonov, D. R. MacFarlane and D. R. MacFarlane, *ACS Energy Lett.*, 2020, **5**, 2095–2097.
- 78 S. Liu, L. Cui, S. Yin, H. Ren, Z. Wang, Y. Xu, X. Li, L. Wang and H. Wang, *Appl. Catal., B*, 2022, **319**, 1–8.
- 79 S. Giddey, S. P. S. Badwal and A. Kulkarni, *Int. J. Hydrogen Energy*, 2013, **38**, 14576–14594.
- 80 G. Qing, R. Ghazfar, S. T. Jackowski, F. Habibzadeh, M. M. Ashtiani, C. P. Chen, M. R. Smith and T. W. Hamann, *Chem. Rev.*, 2020, **120**, 5437–5516.
- 81 C. J. M. Van Der Ham, M. T. M. Koper and D. G. H. Hetterscheid, *Chem. Soc. Rev.*, 2014, **43**, 5183–5191.
- 82 L. Kortekaas, F. Lancia, J. D. Steen and W. R. Browne, *J. Phys. Chem. C*, 2017, **121**, 14688–14702.
- 83 C. H. Tsai, P. H. Fei, C. M. Lin and S. L. Shiu, *Coatings*, 2018, **8**, 1–13.

