

Covalent, sequence-specific attachment of long DNA molecules to a surface using DNA-templated click chemistry†

Gary R. Abel, Jr., Blessing Huynh Cao, Jason E. Hein and Tao Ye*

Cite this: *Chem. Commun.*, 2014, 50, 8131

Received 19th April 2014,
Accepted 4th June 2014

DOI: 10.1039/c4cc02900c

www.rsc.org/chemcomm

We present a novel method that covalently and sequence-specifically attaches long DNA molecules to a surface that is compatible with high-resolution atomic force microscopy (AFM) imaging. Surfaces prepared with this approach are ideally suited for performing biophysical experiments on single DNA molecules.

Techniques that probe DNA at the single molecule level have provided unique insight into fundamental biological processes, such as gene expression and DNA-protein binding. For many techniques, including AFM force spectroscopy,¹ optical tweezers,² and single molecule fluorescence,³ it is necessary for a long DNA molecule (>100 bp) to be attached at one end to a solid support. The prevalence of surface-tethering can be attributed to the following: tethering restricts the diffusion of the molecule, allowing for extended observation; it isolates the molecule, preventing unwanted interactions with neighboring molecules; and it provides a convenient handle with which the molecule can be manipulated. Going beyond existing approaches, the capability of attaching long DNA molecules with different sequences to specific locations on the surface would potentially allow researchers to perform high throughput, multiplexed single molecule measurements on spatially addressable nanoarrays.⁴ Among the existing strategies to tether DNA to a solid support, such as biotin-avidin recognition,^{2,3} amide coupling,¹ and gold-thiol chemistry,⁵ several limitations remain. Although covalent attachment methods are effective at tethering relatively short DNA to a solid support, they become significantly slower for longer DNA due to orientational constraints and diffusion limitation of the reaction.⁶ Existing covalent attachment chemistries are also not sequence specific, *i.e.*, cannot selectively tether molecules with different sequences, which is important for nanoarrays. Often the surface has significant heterogeneity in topography and chemical functionality, resulting in nonspecific interactions that

introduce artefacts into measurements. Very little is known about the heterogeneity in the local environment of the immobilized molecules, as the surfaces are generally not compatible with high-resolution AFM imaging, the only technique that is potentially capable of characterizing these surfaces with sub 10 nm resolution.^{7,8} Typically, the surface interactions are either too strong to allow for the conformational freedom that is needed for unperturbed reactions, or too weak to immobilize the molecules for imaging.^{7,8} Existing AFM studies have relied on exchanging the buffer solution to switch the binding affinities between DNA and the mica substrate to allow for conformational freedom in a weakly bound state and imaging in a strongly bound state.^{9,10} However, the biochemical reactions are heavily perturbed by surface interactions even in the weakly bound state, as there must be sufficient surface interactions to prevent irreversible desorption of DNA.¹⁰

Here we demonstrate that long DNA can be covalently and sequence-specifically tethered to a surface that is compatible with both high-resolution single molecule imaging and unimpeded biomolecular interactions. This is accomplished by attaching short DNA 'anchor' strands that bear an alkyne group to a surface that can switch DNA-surface interactions on demand, allowing the anchor strands to capture long 'target' DNA with a complementary sequence, and then covalently crosslinking the strands *via* Cu(I)-catalyzed azide-alkyne cycloaddition (CuAAC) (Fig. 1). Base-pairing interactions have been previously used to bring reactive groups into close proximity to facilitate reactions in a homogeneous solution phase.^{13,14} Here we show that the specificity and greater efficiency of the base-pairing process can guide the covalent attachment of long DNA strands to our switchable surface. This novel approach may have broad utility in single molecule techniques that require surface-tethering of long DNA, and may enable the production of single molecule nanoarrays.

We employed the CuAAC reaction to crosslink the DNA strands because it is efficient and orthogonal to a wide range of biochemical reactions.¹⁵ Prior to performing the reaction on the surface, we tested the approach by crosslinking two short, complementary DNA strands in solution. This step was useful not only for identifying conditions that would provide a suitable reaction yield,

Chemistry and Chemical Biology, School of Natural Sciences,
University of California, 5200 N. Lake Rd., Merced, CA 95343, USA.
E-mail: tao.ye@ucmerced.edu

† Electronic supplementary information (ESI) available: Experimental procedures, mass spectrometry and NMR data, and additional AFM results. See DOI: 10.1039/c4cc02900c



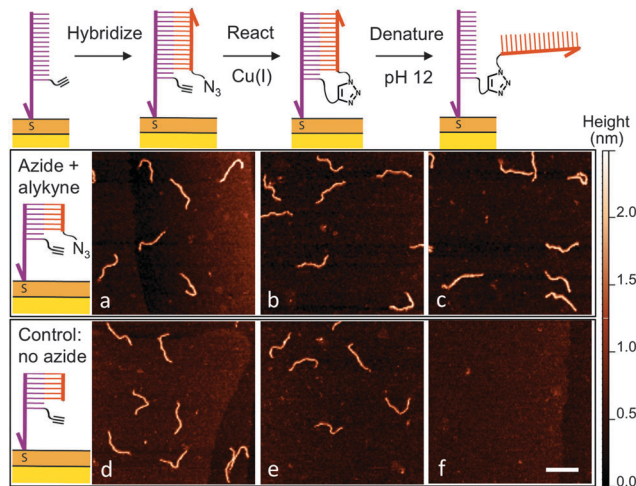


Fig. 3 AFM images taken after each step of attaching 396 bp DNA to the surface. (a) The azide-labeled DNA targets are hybridized with surface anchor strands containing an alkyne group. (b) Next the surface is exposed to Cu(I), catalyzing the formation of the triazole product. (c) To verify that the DNA is covalently crosslinked, the surface is exposed to alkaline conditions so that any unreacted DNA is denatured and rinsed away. (d–f) The same hybridization, reaction, and denaturation steps, respectively, but with the azide group omitted. In this case, >99% of the DNA was removed after denaturing. Scale bar is 100 nm.

with the expected contour length of ~ 120 nm; hence hybridization is facile on this surface. The surface was then exposed to a catalyst solution containing Cu(I), the sodium ascorbate reducing agent, and a Cu(I)-binding ligand. The kinetics of the surface reaction is slower than that in a homogeneous solution and an increased reaction time of 25 minutes was used to ensure a good yield. AFM imaging revealed that the DNA was still present on the surface after the reaction. Statistical analysis of the DNA chain conformations before and after the reaction indicates that oxidative degradation of the DNA during this step is minimal (Fig. S7, ESI[†]). To verify covalent crosslinking, the surface was next exposed to an alkaline NaOH solution (pH 12), which is known to disrupt the hydrogen bonds in base pairs and denature double-stranded DNA.¹⁹ The majority of the molecules remained bound to the surface, consistent with the DNA being linked to the surface through a covalent bond in addition to base pairing. By counting molecules over a large area before and after denaturation, we determined the yield of the crosslinking reaction to be 83%. Note that the denaturing pH was selected such that the base pairing between the single-stranded tail and the anchor strand is melted (Fig. 3c) but the double-stranded segment of the target DNA remains intact due to its higher melting temperature. When a higher pH was used, the anchored target strands were completely melted into single-stranded DNA (Fig. S12, ESI[†]). In control experiments where either the azide or alkyne group is excluded, the targets indeed hybridized with the surface anchors, and were still present on the surface after exposure to the Cu(I) catalyst. However, after exposure to denaturing conditions, >99% of the DNA molecules were rinsed away, confirming that base-pairing alone is not sufficient for stable attachment to the surface under these conditions (Fig. 3f and

Fig. S10, ESI[†]). Finally, to verify the sequence-specificity, we repeated the experiment using sequence-mismatched DNA anchors and target strands containing the alkyne and azide groups. None of the mismatched DNA was found on the surface after hybridization, confirming that the crosslinking reaction can be programmed by the base sequence (Fig. S11, ESI[†]). Using the above strategy, we have attached both single- and double-stranded DNA ranging in size from 396 to 3679 bases to the surface.

Our new approach to link long DNA molecules to highly ordered SAMs will enable AFM studies of biochemical reactions that are difficult on traditional mica substrates. In addition, it potentially has broad utility in other single molecule techniques^{2,3} because it can reduce measurement artefacts that are caused by nonspecific surface interactions and heterogeneity in the local environment. Moreover, our method allows long DNA that are difficult to pattern directly to be crosslinked to short anchor strands that are readily patterned with existing techniques.^{20–22} Therefore, it will pave the way for spatially addressable nanoarrays that can allow the parallel measurement of a large number of single molecules.

The authors acknowledge financial support from the National Science Foundation (CHE-1048651 and CHE-1361066) and UC Cancer Research Coordinating Committee.

Notes and references

- 1 M. Erdmann, R. David, A. Fornof and H. E. Gaub, *Nat. Nanotechnol.*, 2010, **5**, 154.
- 2 K. M. Herbert, W. J. Greenleaf and S. M. Block, *Annu. Rev. Biochem.*, 2008, **77**, 149.
- 3 I. Rasnik, S. A. McKinney and T. Ha, *Acc. Chem. Res.*, 2005, **38**, 542.
- 4 S. Howorka and J. Hesse, *Soft Matter*, 2014, **10**, 931.
- 5 G. J. L. Wuite, S. B. Smith, M. Young, D. Keller and C. Bustamante, *Nature*, 2000, **404**, 103.
- 6 S. C. Huang, M. D. Stump, R. Weiss and K. D. Caldwell, *Anal. Biochem.*, 1996, **237**, 115.
- 7 E. A. Josephs and T. Ye, *J. Am. Chem. Soc.*, 2012, **134**, 10021.
- 8 G. R. Abel Jr, E. A. Josephs, N. Luong and T. Ye, *J. Am. Chem. Soc.*, 2013, **135**, 6399.
- 9 N. Thomson, S. Kasas, B. Smith, H. Hansma and P. Hansma, *Langmuir*, 1996, **12**, 5905.
- 10 M. Guthold, X. Zhu, C. Rivetti, G. Yang, N. H. Thomson, S. Kasas, H. G. Hansma, B. Smith, P. K. Hansma and C. Bustamante, *Biophys. J.*, 1999, **77**, 2284.
- 11 E. A. Josephs and T. Ye, *Nano Lett.*, 2012, **12**, 5255.
- 12 E. A. Josephs and T. Ye, *ACS Nano*, 2013, **7**, 3653.
- 13 X. Li and D. R. Liu, *Angew. Chem., Int. Ed.*, 2004, **43**, 4848.
- 14 P. Kocalka, A. H. El-Sagheer and T. Brown, *ChemBioChem*, 2008, **9**, 1280.
- 15 J. E. Hein and V. V. Fokin, *Chem. Soc. Rev.*, 2010, **39**, 1302–1315.
- 16 P. Y. Liu, N. Jiang, J. Zhang, X. Wei, H. H. Lin and X. Q. Yu, *Chem. Biodiversity*, 2006, **3**, 958.
- 17 Q. Wang, T. R. Chan, R. Hilgraf, V. R. Fokin, K. B. Sharpless and M. G. Finn, *J. Am. Chem. Soc.*, 2003, **125**, 3192.
- 18 S. I. Presolski, V. Hong, S. H. Cho and M. G. Finn, *J. Am. Chem. Soc.*, 2010, **132**, 14570.
- 19 M. Ageno, E. Dore and C. Frontali, *Biophys. J.*, 2009, **9**, 1281.
- 20 L. M. Demers, D. S. Ginger, S. J. Park, Z. Li, S. W. Chung and C. A. Mirkin, *Science*, 2002, **296**, 1836.
- 21 S. K. Kufer, E. M. Puchner, H. Gump, T. Liedl and H. E. Gaub, *Science*, 2008, **319**, 594.
- 22 E. A. Josephs and T. Ye, *J. Am. Chem. Soc.*, 2010, **132**, 10236.

