

Cite this: *CrystEngComm*, 2019, 21, 4501Received 1st April 2019,
Accepted 14th May 2019

DOI: 10.1039/c9ce00485h

rsc.li/crystengcomm

The high-pressure and low-temperature structural behaviour of 2,2,2-trifluoroethanol†

S. A. Barnett  and D. R. Allan *

On cooling to 229 K at ambient pressure, 2,2,2-trifluoroethanol freezes to form a crystal structure characterised by hydrogen-bonded molecular chains in the orthorhombic space group $Pca2_1$ (form 1). On compression to 0.22 GPa at room temperature, however, liquid 2,2,2-trifluoroethanol crystallises in a structure adopting triclinic $P\bar{1}$ symmetry (form 2). Although the form 1 and form 2 polymorphs are both characterised by the formation of hydrogen-bonded chains, the arrangement of the molecules within the chains are significantly different with the high-pressure form appearing to adopt a more strained configuration. The orientation of the molecules in form 2 is such that the hydrogen bonds in neighbouring chains are in close proximity with a bridging interchain $O\cdots O$ contact distance that is of the same order as the $O\cdots O$ distances found for the hydrogen bonds. The resulting close pairing of neighbouring catemeric chains produces molecular pillars in the structure of form 2.

Introduction

In the mono-alcohols (ROH), there is competition between the packing requirements of the relatively bulky R-group and the demand for the small hydroxyl groups to be sufficiently close for hydrogen bonding to occur.¹ The packing motifs adopted for the smaller members of the mono-alcohol series are often relatively 'thin' where the crystal structures show that catemers are formed with the molecules arranged in an approximately coplanar alternating sequence about the central chain of hydrogen bonds. For mono-alcohol systems with bulkier R-groups, steric hindrance often prohibits the molecules from adopting this simple arrangement. If the R-group is particularly bulky then the molecules may no longer form hydrogen-bonded chains or catemers, but cyclic dimers, trimers, tetramers or hexamers can be created instead.

As part of an ongoing programme to study the high-pressure and low-temperature structural behaviour of small molecule systems, we have been examining a range of mono-functional molecular materials. Among the first of these studies was the investigation of the structural behaviour of methanol and ethanol which are the simplest members of the linear alcohol series, $H(CH_2)_nOH$.^{2–5} For methanol, two orthorhombic crystalline phases are formed on cooling, while at pressures above about 4 GPa a triclinic $P\bar{1}$ phase is formed. It is, however, possible to superpress the liquid phase and, if

compression is suitably rapid, crystallisation is suppressed and the liquid becomes a pressure-induced glass. The extremely strained conformation of the hydrogen-bonded molecular chains in the high-pressure $P\bar{1}$ crystal structure offers a partial explanation of why methanol is so difficult to crystallise at high pressure and so readily vitrifies.² Ethanol, in contrast, almost invariably crystallises on compression at pressures above 3 GPa.^{3,4} Conversely, it is the low-temperature ethanol polymorph that exhibits the strained structure.⁵ Below the freezing temperature of ~ 156 K, ethanol crystallises in the monoclinic Pc space group and its crystal structure is characterised by hydrogen-bonded molecular chains where pairs of molecules are linked together in *trans* and *gauche* conformers with the methyl groups of each molecule directed away from the centre of each pair. These molecular pairs alternate such that the molecules are arranged in a relatively strained sequence along the chain. In the high-pressure $P2_1/c$ structure this strain is relieved by the orientations of the molecules about the hydrogen bonds adopting a simple alternating sequence.

More recently, Ridout and Probert⁶ have studied the low-temperature and high-pressure structures of isopropyl alcohol (isopropanol, C_3H_8O) where they found that the more bulky R-group led to the two polymorphs, which both adopt the monoclinic $P2_1/c$ space group, having very different packing motifs and densities. In the low-temperature phase, at 180 K, the molecules are arranged in one-dimensional helical hydrogen-bonded chains while the significantly denser high-pressure phase is characterised by the formation of isolated 8-membered rings, at 1.1 GPa. It appears, therefore, that the R-group in isopropanol exhibits 'thin' behaviour at low-

Diamond Light Source, Harwell Science and Innovation Campus, Chilton, OX11 0RZ, UK. E-mail: David.Allan@diamond.ac.uk

† CCDC Form 1 1906644, form 2 1906643. For crystallographic data in CIF or other electronic format see DOI: 10.1039/c9ce00485h

Herein, we report the crystal structure of the high-pressure phase of 2,2,2-trifluoroethanol ($\text{CF}_3\text{CH}_2\text{OH}$) along

	Form 1	Form 2
Chemical formula	C ₂ H ₃ F ₃ O	C ₂ H ₃ F ₃ O
Molecular weight	100.04	100.04
Temperature (K)/ pressure (GPa)	229/0	295/0.22
Crystal system	Orthorhombic	Triclinic
Space group	<i>Pca</i> 2 ₁	<i>P</i> $\bar{1}$
Unit cell		
<i>a</i> (Å)	8.6040(7)	4.9159(7)
<i>b</i> (Å)	10.0578(8)	8.8894(18)
<i>c</i> (Å)	9.1461(8)	9.226(3)
α (°)	90	111.71(2)
β (°)	90	103.03(2)
γ (°)	90	90.970(10)
<i>V</i> (Å ³)	791.48(11)	362.68(15)
<i>Z</i> / <i>Z'</i>	8/2	4/2
Density (g cm ^{−3})	1.679	1.832
Flack/extinction coefficient	−0.7(10)/0.099(10)	—/—
Reflections collected	9973	2016
Unique reflections/ <i>R</i> _{int}	2767/0.0518	637/0.0290
<i>R</i> ₁ [<i>I</i> > 2σ]	0.0331	0.0478
<i>wR</i> ₂ [all data]	0.1058	0.1430
GoF on <i>F</i> ²	0.875	1.088
Largest diff. peak and hole (e Å ^{−3})	0.157/−0.161	0.142/−0.118

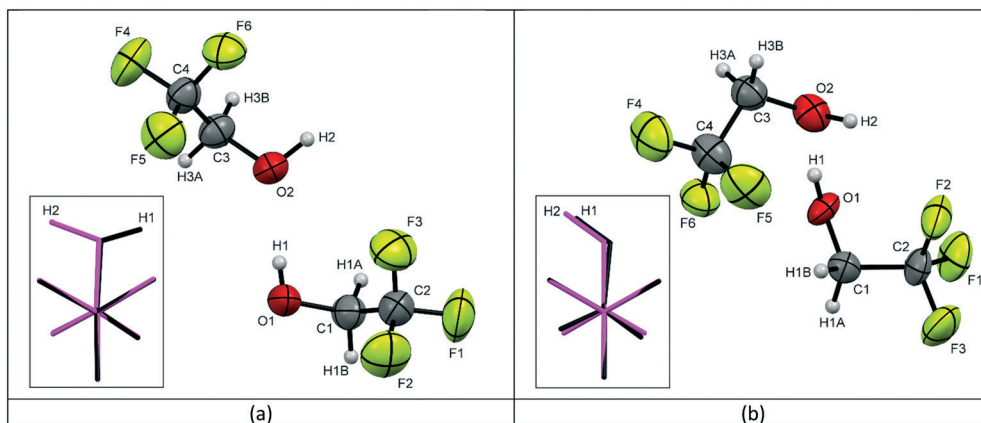


Fig. 1 The labelling schemes used in the crystal structures of TFE for (a) the low temperature form 1 and (b) the high pressure form 2, with thermal ellipsoids drawn at the 50% probability level. The inserted images show the molecular overlay[‡] of the two independent molecules in the asymmetric unit with molecule 1 (O1, C1, C2, F1, F2, F3) shown in black and molecule 2 (O2, C3, C4, F4, F5, F6) shown in pink (C – dark grey, H – light grey, O – red, F – green).

the Newport kappa-geometry 4-circle diffractometer fitted with a Dectris Pilatus 300 K pixel-array photon-counting detector. Both datasets were collected using a wavelength of $\lambda = 0.4895$ Å, with a step size and exposure time of 0.2° and 0.4 seconds respectively. The low-temperature data collection was carried out with a single 360° ϕ scan, in order to minimise the contribution of other crystals, at a cryostream temperature of 229 K. The collected frames were integrated using XIA2¹⁹ on one of the major crystallites, and the data were corrected for absorption effects using AIMLESS,²⁰ an empirical method. The high pressure dataset was collected using a series of ω scans to give the optimal completeness when using a diamond anvil cell. The data were integrated with the program CrysAlisPro²¹ which incorporates routines that omit regions of the detector shaded by the diamond-anvil cell from integration. Both structures were solved by dual-space methods²² and refined by least-squares refinement on all unique measured F^2 values.²³ For both forms, the alkyl hydrogen atoms were placed geometrically and refined using a riding model, whereas the hydroxyl hydrogen atoms were located from the difference map and refined freely. The data collection, integration and refinement statistics for both the low-temperature and high-pressure data sets are presented in Table 1.

Results and discussion

Form 1 of 2,2,2-trifluoroethanol (TFE) was found to crystallise at a temperature of 229 K, at ambient pressure, in the orthorhombic space group $Pca2_1$ with 2 molecules in the asymmetric unit, see Fig. 1a. At a fairly modest pressure of 0.22 GPa, at room temperature, TFE crystallises as form 2 adopting the triclinic $P\bar{1}$ space group, also with $Z' = 2$, see Fig. 1b.

For form 1, the two molecules are conformationally very similar, with the molecular overlay[‡] of the two independent molecules in the asymmetric unit calculated to be 0.0096. The overlay, see Fig. 1a inset, shows that the F–C–C–O torsion

angles for the two molecules are comparable (O1–C1–C2–F1 (black) = $-176.08(17)^\circ$; O2–C3–C4–F4 (pink) = $-177.91(18)^\circ$) and highlights that the fundamental difference between the two molecules is the opposing orientations of the hydroxyl hydrogens. The four remaining F–C–C–O torsion angles for the two molecules average 59.7° , with a variance of 12.0. The structure is characterised by the formation of hydrogen-bonded molecular chains, with a relatively unstrained arrangement similar to that of the monoclinic Pc phase of ethanol,⁵ see Fig. 2a. The chains are aligned parallel with the crystallographic c -axis (Fig. 2b) and these chains, in turn, are arranged in layers stacked orthogonally to the a -axis, see Fig. 2c.

The two independent molecules in the asymmetric unit of the high pressure form of TFE (form 2) have the same hydroxyl hydrogen orientation, but the overlay match[‡] is much poorer with an RMS of 0.0199. Fig. 1b inset also clearly demonstrates that the conformation of molecule 1 (black) is offset from a perfect staggered arrangement with an O1–C1–C2–F3 torsion angle of $-174.6(4)^\circ$ compared to $179.5(5)^\circ$ for O2–C3–C4–F4 (molecule 2, pink). This is exemplified by the greater variance (16.6) for the spread of the F–C–C–O torsion angles, although the average is the same as for form 1 (59.7°). Like form 1, form 2 is also characterised by the formation of hydrogen-bonded chains, see Fig. 2d. However, the arrangement of the trifluoro groups with respect to the plane of hydrogen bonds is quite different to that of the low-temperature phase as they are aligned approximately orthogonally to one another rather than parallel, compare Fig. 2b and e. This arrangement of the trifluoro groups means the hydrogen bond is exposed and, as can be seen in

[‡] The molecular overlay RMS (root mean square) value was calculated using the “molecule overlay” feature of Mercury²⁴ for the two independent molecules in the asymmetric unit. Just the carbon and fluorine atoms were matched up for the calculation in order to emphasise the differences in the orientation of the hydroxyl groups.





Fig. 2 The structure of TFE form 1 showing (a) the hydrogen-bonded chain formed along the *c*-axis, (b) stacking of the hydrogen-bonded chains and (c) the layers formed orthogonal to the *a*-axis; the structure of TFE form 2 showing (d) the hydrogen-bonded chain formed along the *a*-axis, (e) the orthogonal nature of the trifluoro groups within the hydrogen-bonded chain and the exposed hydrogen bond and (f) the double chain pillars. The dashed lines show the hydrogen bonds in light blue and the short O...O contacts in red.

Fig. 2e, a bridging O...O contact of 2.892(7) Å is made with the neighbouring hydrogen-bonded chain. This distance is of the same order as the O...O distances found for the hydrogen bonds in both structures, see Table 2. The resulting close pairing of neighbouring catemeric chains produces pillars in the structure, aligned along the crystallographic *a*-axis, see Fig. 2f.

It is notable that both hydrogen bonds in form 2 exhibit a large deviation from linearity (158° and 140°, although the large uncertainties in these angles mean they are poorly defined), whereas, the angles formed by the hydrogen bonds in the low temperature form 1 are 178° and 179°. It is possible that the weak halogen bond to F2, formed by O2, could be responsible for the significant deviation observed in form 2.

In ethanol, the low temperature phase is unusual as it consists of pairs of molecules which alternate about the

Table 2 Intermolecular hydrogen bond details for forms 1 and 2 of 2,2,2-trifluoroethanol

D-H...A	D-H/Å	H...A/Å	D...A/Å	D-H...A/°
Form 1				
O1-H1...O2	0.77(3)	1.93(3)	2.696(2)	178(3)
O2-H2...O1 ⁱ	0.94(3)	1.77(3)	2.716(2)	179(3)
Form 2				
O1-H1...O2	0.81(10)	1.99(7)	2.762(7)	158(10)
O2-H2...O1 ⁱⁱ	0.92(14)	1.94(7)	2.714(6)	140(12)
O2-H2...F2	0.92(14)	2.68(16)	3.251(11)	121(7)

Symmetry codes: ⁱ = 3/2 - *x*, *y*, *z* - 1/2; ⁱⁱ = *x* - 1, *y*, *z*.



central axis of the hydrogen bonds. The high pressure phase is more closely related to forms I and II of TFE, as individual molecules alternate about the hydrogen-bonded chain. However, in both phases of ethanol the torsion angles are similar, and within the range expected for a staggered conformation, and these are comparable with the torsion angles found for both forms of TFE, thereby indicating that the molecular conformation is not strongly influenced by the molecular packing.

The unusual orientation of the TFE molecules within the hydrogen-bonded chains, combined with the non-linear hydrogen bonds, indicates that the structure is probably highly strained. This suggests that there is potential for the structure to undergo a phase transition on increasing the pressure and that the exposed oxygen atoms, oriented back-to-back between adjacent chains, could be in a favourable position to allow cross-linking hydrogen bonds to be formed.

Conclusions

2,2,2-Trifluoroethanol, a liquid at ambient conditions, has been compressed at room temperature, and cooled at ambient pressure, in order to induce crystallisation. TFE has been shown to be polymorphic with two novel crystal structures determined, both characterised by hydrogen-bonded chains. This behaviour is broadly reminiscent of the high-pressure and low-temperature behaviour of ethanol. The closest structural similarities are between the form 1 TFE structure and the structure of the high-pressure phase of ethanol, which both exhibit a simple alternating arrangement of molecules about the hydrogen bond within each chain. The fluoridation of the methyl group in ethanol, however, is not sufficient to make the R-group bulky enough for the closure of the molecular chains into hydrogen bonded rings.

All of the O–H...O distances are well within the range of standard lengths for hydrogen-bonding in alcohols;^{2–13} *i.e.*, the electronegativity of the fluorine atoms appears to have a very limited effect on the overall structure and the structural differences observed, compared with those of ethanol, are likely to be dominated by steric effects.

As the orientation of the molecular chains in form 2 is such that the hydrogen bonds in neighbouring chains are in close proximity, with a bridging interchain O...O contact distance (2.892 Å) that is of the same order as the O...O distances found for the hydrogen bonds (~2.72 Å), it could be expected that this region of the structure would become unstable under further compression. This instability could potentially lead to either bond formation or a further phase transition. We are currently studying TFE to higher pressures with both single-crystal X-ray diffraction and time-of-flight neutron powder-diffraction.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors would like to thank Dr. Tamas Javorfi for supplying the sample and Dr. Craig Bull for helpful comments and suggestions. They are also grateful to Diamond Light Source Limited for the provision of beamtime on I19.

Notes and references

- 1 C. P. Brock and L. L. Duncan, *Chem. Mater.*, 1994, **6**, 1307.
- 2 D. R. Allan, S. J. Clark, M. J. P. Brugmans, G. J. Ackland and W. L. Vos, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1998, **58**, R11809 (and references therein).
- 3 D. R. Allan and S. J. Clark, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1999, **60**, 6328.
- 4 C. L. Bull, S. A. Barnett, D. R. Allan and W. G. Marshall, *High Pressure Res.*, 2019, **39**(1), 179.
- 5 P.-G. Jönsson, *Acta Crystallogr., Sect. B: Struct. Crystallogr. Cryst. Chem.*, 1976, **32**, 232.
- 6 J. Ridout and M. R. Probert, *CrystEngComm*, 2014, **16**, 7397.
- 7 P. A. McGregor, D. R. Allan, S. Parsons and S. J. Clark, *Acta Crystallogr., Sect. B: Struct. Sci.*, 2006, **62**, 599.
- 8 P. A. McGregor, D. R. Allan, S. Parsons and C. R. Pulham, *Acta Crystallogr., Sect. B: Struct. Sci.*, 2005, **61**, 449.
- 9 D. R. Allan, S. J. Clark, A. Dawson, P. A. McGregor and S. Parsons, *Acta Crystallogr., Sect. B: Struct. Sci.*, 2002, **58**, 1018.
- 10 I. D. H. Oswald, D. R. Allan, W. D. S. Motherwell and S. Parsons, *Acta Crystallogr., Sect. B: Struct. Sci.*, 2005, **61**, 69.
- 11 I. D. H. Oswald, D. R. Allan, G. M. Day, W. D. S. Motherwell and S. Parsons, *Cryst. Growth Des.*, 2005, **5**, 1055.
- 12 S. A. Moggach, D. R. Allan, P. Lozano-Casal and S. Parsons, *J. Synchrotron Radiat.*, 2005, **12**, 590.
- 13 R. M. Ibberson, S. Parsons, D. R. Allan and A. M. T. Bell, *Acta Crystallogr., Sect. B: Struct. Sci.*, 2008, **64**, 573.
- 14 M. Heger, T. Schrage and M. A. Suhm, *Phys. Chem. Chem. Phys.*, 2013, **15**, 16065.
- 15 J. Cosier and A. M. Glazer, *J. Appl. Crystallogr.*, 1986, **19**, 105.
- 16 S. A. Moggach, D. R. Allan, S. Parsons and J. E. Warren, *J. Appl. Crystallogr.*, 2008, **41**, 249.
- 17 H.-K. Mao, J. Xu and P. M. Bell, *J. Geophys. Res.: Solid Earth*, 1986, **91**, 4673.
- 18 H. Nowell, S. A. Barnett, K. E. Christensen, S. J. Teat and D. R. Allan, *J. Synchrotron Radiat.*, 2012, **19**, 435.
- 19 P. Evans, *Acta Crystallogr., Sect. D: Biol. Crystallogr.*, 2006, **62**, 72; P. R. Evans and G. N. Murshudov, *Acta Crystallogr., Sect. D: Biol. Crystallogr.*, 2013, **69**, 1204; M. D. Winn, *et al.*, *Acta Crystallogr., Sect. D: Biol. Crystallogr.*, 2011, **67**, 235; G. Winter, *J. Appl. Crystallogr.*, 2010, **43**, 186; G. Winter, *et al.*, *Acta Crystallogr., Sect. D: Struct. Biol.*, 2018, **74**, 85.
- 20 CCP4 7.0.062: AIMLESS (version 0.7.2), 27/05/18.



- 21 Rigaku Oxford Diffraction, *CrysAlisPro*, Rigaku Europe, Unit B6, Chaucer Business Park, Watery Lane, Kemsing Sevenoaks, Kent TN15 6QY, United Kingdom, 2017.
- 22 G. M. Sheldrick, *Acta Crystallogr., Sect. A: Found. Adv.*, 2015, 71, 3.
- 23 G. M. Sheldrick, *Acta Crystallogr., Sect. C: Struct. Chem.*, 2015, 71, 3.
- 24 C. F. Macrae, P. R. Edgington, P. McCabe, E. Pidcock, G. P. Shields, R. Taylor, M. Towler and J. van de Streek, *J. Appl. Crystallogr.*, 2006, 39, 453.

