


Tian Tian,  <sup>\*a</sup> Jiamin Xu, <sup>b</sup> Ying Xiong, <sup>ac</sup> Nitya Ramanan, <sup>d</sup> Mary Ryan, <sup>b</sup> Fang Xie  <sup>b</sup>  
and Camille Petit  <sup>\*a</sup>

Porous boron nitride (BN) displays promising properties for interfacial and bulk processes, e.g. molecular separation and storage, or (photo)catalysis. To maximise porous BN's potential in such applications, tuning and controlling its chemical and structural features is key. Functionalisation of porous BN with metal nanoparticle represents one possible route, albeit a hardly explored one. Metal-organic frameworks (MOFs) have been widely used as precursors to synthesise metal functionalised porous carbon-based materials, yet MOF-derived metal functionalised inorganic porous materials remain unexplored. Here, we hypothesise that MOFs could also serve as a platform to produce metal-functionalised porous BN. We have used a Cu-containing MOF, *i.e.* Cu/ZIF-8, as a precursor and successfully obtained porous BN functionalised with Cu nanoparticles (*i.e.* Cu/BN). While we have shown control of the Cu content, we have not yet demonstrated it for the nanoparticle size. The functionalisation has led to improved light harvesting and enhanced electron-hole separation, which have had a direct positive impact on the CO<sub>2</sub> photoreduction activity (production formation rate 1.5 times higher than pristine BN and 12.5 times higher than g-C<sub>3</sub>N<sub>4</sub>). In addition, we have found that the metal in the MOF precursor impacts porous BN's purity. Unlike Cu/ZIF-8, a Co-containing ZIF-8 precursor led to porous C-BN (*i.e.* BN with a large amount of C in the structure). Overall, given the diversity of metals in MOFs, one could envision our approach as a method to produce a library of different metal functionalised porous BN samples.

Received 11th July 2022  
Accepted 4th September 2022

DOI: 10.1039/d2ta05515e

[rsc.li/materials-a](http://rsc.li/materials-a)

Porous boron nitride (BN) is a recent addition to the porous materials family.<sup>1-3</sup> With alternating boron and nitrogen atoms linked *via* strong B-N covalent bonds arranged in an hexagonal pattern, the porous BN structure resembles that of activated carbon but its chemical properties differ. Benefiting from features such as a high surface area, *a priori* tunable chemistry and porosity, and high thermal stability, porous BN has recently attracted interests for various applications such as molecular storage and separation,<sup>4-9</sup> catalysis (incl. photocatalysis),<sup>10-13</sup> and drug delivery.<sup>14</sup>

Chemical functionalisation can help tune the adsorptive, catalytic and optoelectronic properties of porous BN, all of which are relevant to the applications mentioned above. The functionalisation of BN-based materials using non-metal heteroatoms (*e.g.* C, O, P, S and Si) has been reported. Alongside this functionalisation route, the addition of metal atoms to porous BN provides an extra dimension to modulate the properties of the material. Metal functionalisation has been investigated in the case of non-porous hBN ( $S_{\text{BET}} < 150 \text{ m}^2 \text{ g}^{-1}$ ) for Ni,<sup>15,16</sup> Pt,<sup>17,18</sup> Cu,<sup>19</sup> Pd,<sup>20,21</sup> Au.<sup>22</sup> Fewer studies exist in the case of porous BN and low surface area is often observed.<sup>23–27</sup> Today, the challenge with metal functionalisation of porous BN remains to ensure distributed functionalisation while maintaining porosity.

We hypothesise that metal-organic frameworks (MOFs), *i.e.* porous crystalline materials obtained *via* self-assembly of metal clusters and organic linkers, could address the above challenge.<sup>28</sup> Their typically high surface area, ordered arrangement of metal nodes, and carbon-rich nature, have made them attractive precursors to design porous materials, especially carbon-based porous materials.<sup>29–31</sup> The use of MOFs as templates means that one could possibly embed well-dispersed metals in the final material.<sup>30</sup> Yet, examples of MOF-derived inorganic porous materials, particularly BN, remain limited.

*"Barrar Centre, Department of Chemical Engineering, Imperial College London, South Kensington Campus, London SW7 2AZ, UK. E-mail: tian.tian11@imperial.ac.uk; camille.petit@imperial.ac.uk"*

<sup>b</sup>Department of Materials, Imperial College London, South Kensington Campus, London SW7 2AZ, UK

*Departamento de Química Inorgánica, Facultad de Ciencias, Universidad Autónoma de Madrid, Campus de Cantoblanco, Madrid 28049, Spain*

<sup>d</sup>Diamond Light Source Ltd., Diamond House, Harwell Science and Innovation Campus, Didcot OX11 0DE, UK

† Electronic supplementary information (ESI) available. See <https://doi.org/10.1039/d2ta05515e>

## 2. Experimental section

Zinc nitrate hexahydrate (99%, CAS# 10196-18-6), copper nitrate trihydrate (99%, CAS# 10031-43-3), cobalt nitrate hexahydrate (99% CAS# 10026-22-9), 2-methylimidazole (99%, CAS# 693-98-1), boric acid ( $\geq 99.5\%$ , CAS# 10043-35-3), ethanol ( $\geq 99.8\%$ , CAS# 64-17-5), and melamine (99%, CAS# 108-78-1) were purchased from Fisher Scientific. All chemicals were used as received. The gases used in this study,  $\text{NH}_3$  (99.98%),  $\text{N}_2$  (99.9995%), and  $\text{CO}_2$  (99.999%) were purchased from BOC.  $\text{H}_2$  (99.9995%) was generated locally from deionized water using a Peak Scientific PH200 hydrogen generator.

Cu/ZIF-8 was synthesised following a method adapted from Scheijn *et al.* work.<sup>33</sup> A methanol solution of  $\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$  and  $\text{Cu}(\text{NO}_3)_2 \cdot 3\text{H}_2\text{O}$  (4 mmol in total with different molar ratios, 45 mL) was mixed with a methanol solution of 2-methylimidazole (2.62 g, 45 mL), and stirred at room temperature under  $\text{N}_2$  flow for 1 h. After centrifugation, the collected solid was washed in ethanol (150 mL, 3 times) and dried at 80 °C overnight. The solid was then transferred to a glass vial and was further dried at 120 °C under vacuum overnight. The derived samples are labelled as X% Cu/ZIF-8, where X indicates the nominal molar percentage of  $\text{Cu}(\text{NO}_3)_2 \cdot 3\text{H}_2\text{O}$  to total metal precursors (*i.e.*  $\text{Cu}(\text{NO}_3)_2 \cdot 3\text{H}_2\text{O} + \text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ ). In this work, 0% (*i.e.* pure ZIF-8), 1%, 5%, and 10% Cu/ZIF-8 were synthesised.

Boric acid (BA) was loaded into Cu/ZIF-8 following a wet impregnation method: 0.5 g of Cu/ZIF-8 powder was added to 20 mL of ethanol solution of BA (1 g) and stirred at room temperature for 24 h. The solution was then heated to 70 °C and the temperature was maintained until ethanol was completely evaporated. The solid was ground in a mortar and further dried at 120 °C under vacuum. The finely ground powder was then placed in an alumina boat crucible and transferred to a tubular furnace. The sample was initially degassed at room temperature under Ar flow (250 mL min<sup>-1</sup>) for 30 min, then heated to 1000 °C (5 °C min<sup>-1</sup>) under pure NH<sub>3</sub> gas flow (100 mL min<sup>-1</sup>) and held isothermally for 3 h. The furnace was cooled naturally under NH<sub>3</sub> down to 600 °C and then to room temperature under Ar. The derived samples are labelled as X% Cu/BN, where X is the same as that of the initial Cu/ZIF-8 sample. The sample obtained from pure ZIF-8 is referred to as BN. Overall the control of the Cu content in the Cu/BN samples results from the Cu content in the initial ZIF-8 structure and thus the ratio between Cu and B-containing species when forming BN. This is because both Cu and B remain during the thermal process.

Graphitic carbon nitride, g-C<sub>3</sub>N<sub>4</sub>, was synthesised by following the method reported by Dias *et al.*<sup>46</sup> Melamine (4 g) was added to an alumina crucible. The crucible was covered with a lid and transferred to a muffle furnace. The sample was heated to 560 °C (5 °C min<sup>-1</sup>) and held isothermally for 4 h. The sample was then cooled naturally to room temperature and a yellow solid was collected.

10% Co/ZIF-8 was synthesised as another MOF precursor.  $\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$  (1.07 g) and  $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$  (0.12 g) was dissolved in 45 mL of methanol. The solution was mixed with a methanol solution of 2-methylimidazole (2.62 g, 45 mL), and stirred at room temperature for 1 h. After centrifugation, the collected solid was washed in ethanol (150 mL, 3 times) and dried at 80 °C overnight. The solid was then transferred to a glass vial and further dried at 120 °C under vacuum overnight.

The content of Co in ZIF-8 was selected solely to reflect one of the contents selected for Cu/ZIF-8 and allow direct comparison.

## 2.6 Synthesis of Co functionalised C-BN

Co/C-BN was synthesised following the same method as that used to synthesise Cu/BN, except for using 0.5 g of Co/ZIF-8 rather than 0.5 g of Cu/ZIF-8.

## 2.7 Material characterisation

**2.7.1 Chemical properties.** The samples were analysed using Fourier transform infrared (FTIR) spectroscopy. Each sample was ground in an agate mortar and spectra were collected using PerkinElmer Spectrum 100 spectrometer equipped with an attenuated total reflectance (ATR) accessory. Sixteen spectra were collected per sample to obtain an averaged spectrum over the frequency range of 650–4000  $\text{cm}^{-1}$  with a resolution of 2  $\text{cm}^{-1}$ .

Inductively coupled plasma mass spectrometry (ICP-MS) was performed on an Agilent 7900 ICP-MS. Prior to analysis, 0.01 g of sample was dispersed in 20 mL of 2%  $\text{HNO}_3$  and then diluted 200 times using 2%  $\text{HNO}_3$ .

Cu K edge (8979 eV) X-ray absorption spectroscopy (XAS) measurements were performed at room temperature at the core X-ray absorption beamline B18 at Diamond Light Source.<sup>47</sup> The samples were pressed into pellets for the measurement. A Si (111) double crystal monochromator was used for energy selection. A set of Pt coated mirrors were used to reject higher harmonics from the X-ray beam. The data were collected in transmission mode for all samples using a set of three ionization chambers placed in series and filled with appropriate mixtures of He and Ar. This allowed to simultaneously measure data on the sample and a reference Cu foil, with an energy resolution of 0.3 eV. Before the test, Cu/BN samples were kept at ambient environment for 20 days.

The relative chemical composition and the valence state of the elements were measured using X-ray photoelectron spectroscopy (XPS) on a Thermo Scientific K-Alpha<sup>+</sup> X-ray photoelectron spectrometer equipped with a MXR3 Al K $\alpha$  monochromated X-ray source ( $h\nu = 1486.6$  eV). The samples were initially ground using an agate mortar and mounted on to a XPS sample holder using a small piece of conductive carbon tape. The X-ray gun power was set to 72 W (6 mA and 12 kV). The high-resolution spectra were obtained using 20 eV pass energy and 0.1 eV step size. We also conducted depth profiling by applying ion gun with energy of 1500 eV. The etch rate was 0.71  $\text{nm s}^{-1}$  and the etch time was maintained at 70 s per etch cycle. XPS scans were taken at the etching depths of 0, 50, 100, 150 and 200 nm. The adventitious carbon (C-C) peak set at 284.8 eV was used for binding energy calibration. Thermo Avantage software was used to analyse the data.

**2.7.2 Textural properties and morphology.** Powder X-ray diffraction (PXRD) patterns were recorded on a PANalytical X'Pert PRO diffractometer using Cu K $\alpha$  irradiation ( $\lambda = 1.54178$  Å) with a step of 0.01° at a scanning speed of 10 s per step. An anode voltage of 40 kV and emission current of 20 mA were

chosen as the operating condition. All samples were ground prior to measurement using an agate mortar.

$\text{N}_2$  and  $\text{CO}_2$  adsorption isotherms were collected at 77 K and 298 K, respectively, using a Micromeritics 3Flex volumetric sorption analyser. The samples were initially degassed overnight at 120 °C at 0.2 mbar, followed by degas *in situ* at 120 °C for 4 h at around 0.003 mbar. The equivalent specific surface areas of the samples were determined using Brunauer–Emmett–Teller (BET) method.<sup>48</sup> The micropore volume was determined using the Dubinin–Radushkevich model.<sup>49</sup> The pore size distribution was derived from the build-in software from Micromeritics, using DFT model for carbon slit shape pores.

Scanning electron microscope (SEM) images were taken using a Zeiss Auriga microscope with an accelerating voltage of 5 kV. The samples were ground using an agate mortar, deposited on carbon tape and sputter-coated with 10 nm of chromium. To calculate the particle size distribution, 100 particles were randomly selected and measured by using ImageJ. Transmission electron microscope (TEM) images were taken using a FEI Titan 80-300 Cs image-corrected microscope. The samples were dispersed in ethanol and then drop-deposited on to a holey carbon film on 300 mesh copper grids.

**2.7.3 Optoelectronic properties.** UV-vis diffuse reflectance spectra (DRS) were collected using a Shimadzu UV-2600 UV-vis spectrophotometer equipped with an integrating sphere. The spectral bandwidth was set to 2 nm, with  $\text{BaSO}_4$  as a reference. Photoluminescence (PL) spectra were collected for an excitation wavelength of 280 nm using a Fluorolog-3 photoluminescence spectrometer from Horiba.

Valence band X-ray photoelectron spectroscopy (XPS) and work function measurements were carried out on a Thermo Scientific K-Alpha<sup>+</sup> X-ray photoelectron spectrometer equipped with a MXR3 Al K $\alpha$  monochromated X-ray source ( $h\nu = 1486.6$  eV). Samples were ground and mounted on the XPS holder using a conductive carbon tape. The spectra were obtained by using 15 eV pass energy and 0.05 eV step size. The work function was determined by measuring the secondary electron cut-off in the low kinetic energy region. A clean gold standard sample was used as a reference material for calibration. A sample bias of −29.47 eV was applied to the sample using an ion gun and 10 eV pass energy was used to obtain the cut-off spectra. To account for potential variations across the surface of the material, the work function was measured at four different locations and the average was taken.

**2.7.4 Photocatalytic reduction of  $\text{CO}_2$ .**  $\text{CO}_2$  photoreduction experiments were conducted in a home-made photoreactor setup (17.7  $\text{cm}^3$ ). The photoreactor was made off stainless steel and equipped with a fused quartz window for irradiation. In a typical experiment, 0.01 g of finely ground sample previously activated at 120 °C under vacuum overnight was deposited on a stainless-steel Petri-dish and transferred to the photoreactor. The sample was first vacuumed for 20 min, and then exposed to a flow of research grade  $\text{CO}_2$  (80  $\text{mL min}^{-1}$ ) and  $\text{H}_2$  (40  $\text{mL min}^{-1}$ ) simultaneously for 20 min. The photoreactor was then sealed and filled with 2 bar of a  $\text{CO}_2$  :  $\text{H}_2$  mixture (2 : 1 v/v ratio) and irradiated for 5 h. A Xenon arc lamp (100 W, LCS-100





Scheme 1 Schematic representation of Cu/BN synthesis.

solar simulator, Newport) was used as the irradiation source with the distance from the lamp to the sample being 15 cm, providing the intensity at the catalyst surface to be  $1000 \text{ W m}^{-2}$ . A long pass UV filter ( $\lambda < 400 \text{ nm}$ ) and a long pass visible filter ( $\lambda < 550 \text{ nm}$ ) were used to conduct the test under visible light irradiation. The evolved gases were detected and analysed using a Shimadzu GCMS-QP2020 NX equipped with Q-Bond

(Shimadzu Rt-Q-Bond Plot Column 30 m, 0.32 mm ID, 10  $\mu\text{m}$ ) and molecular sieve columns (Shimadzu SH-Msieve 5A plot, 30 m, 0.32 mm ID, 30  $\mu\text{m}$ ) in series. The tests were repeated twice on new samples obtained from different synthesis batches. We also conducted control experiments to confirm the origin of the products, namely: (i) without irradiation, (ii) under  $\text{N}_2/\text{H}_2$  atmosphere and (iii) under  $^{13}\text{CO}_2/\text{H}_2$  atmosphere ( $^{13}\text{CO}_2$  from



Fig. 1 Appearance and structural features of ZIF-8 and Cu/ZIF-8 samples: (a) optical images; (b) XRD patterns; (c) XRD patterns of BA-impregnated Cu/ZIF-8 samples.





BOC, 99 at%  $^{13}\text{C}$ ). During the recyclability tests, the aforementioned process was repeated after each 5 h UV-vis irradiation cycle without opening the photoreactor. Between each cycle, the sample was activated under vacuum for 30 min at room temperature.

### 3. Results and discussion

#### 3.1 Characterisation of Cu/ZIF-8

In this study, we synthesised porous Cu/BN samples using Cu/ZIF-8 samples as precursors (Scheme 1). We first analysed the composition, structure, and morphology of the precursors, *i.e.* ZIF-8, 1% Cu/ZIF-8, 5% Cu/ZIF-8, and 10% Cu/ZIF-8. The percentage refers to the molar percentage of  $\text{Cu}(\text{NO}_3)_2 \cdot 3\text{H}_2\text{O}$  to

total metal precursors (*i.e.*  $\text{Cu}(\text{NO}_3)_2 \cdot 3\text{H}_2\text{O} + \text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ ) of used to synthesise Cu/ZIF-8.

Fig. 1a presents the optical images of the Cu/ZIF-8 samples which progressively changed colour from white to darker yellow with increasing Cu content. The PXRD patterns (Fig. 1b) indicate that both pure ZIF-8 and Cu/ZIF-8 samples exhibit the expected crystalline structure of ZIF-8. Upon adsorbing boric acid (BA), the PXRD patterns of BA-impregnated Cu/ZIF-8 did not change (Fig. 1c), confirming the MOF crystalline structure was maintained. This result differs from that reported by Cao *et al.*<sup>32</sup> who instead observed the formation of a new phase.<sup>32</sup> We attribute this difference to the milder soaking conditions used in this project (*i.e.* room temperature and ambient pressure). Despite their similar crystalline structures, ZIF-8 showed



Fig. 2 Appearance, structural features and chemical features of BN and Cu/BN samples with varying Cu contents: (a) optical images; (b) FTIR spectra; (c) XRD patterns; (d) high resolution XPS and peak fittings of the B 1s core level; (e) high resolution XPS and peak fittings of the N 1s core level.



smaller particle size compared to Cu/ZIF-8 (Fig. S1†). We speculate that this difference relates to a change in nucleation rate in the presence of  $\text{Cu}^{2+}$ .<sup>50</sup> The porosity of the prepared samples was assessed using  $\text{N}_2$  sorption at 77 K (Fig. S2†). All samples showed a type I isotherm, indicating a predominantly microporous character. As shown in Table S1,† we did not observe differences in surface area and pore volume between each sample, suggesting the characteristic porosity of ZIF-8 was retained after the incorporation of  $\text{Cu}^{2+}$ .

### 3.2 Characterisation of Cu/BN

We used BA-impregnated Cu/ZIF-8 samples as self-sacrificial templates to form Cu/BN samples upon pyrolysis at 1000 °C under an  $\text{NH}_3$  atmosphere (Scheme 1). The ZIF-8 linker, along with  $\text{NH}_3$ , provided the N source while BA provided the B source to form BN. We hypothesized that  $\text{NH}_3$  would also reduce  $\text{Cu}^{2+}$  inducing *in situ* Cu nanoparticles growth, while Zn ( $T_{\text{boiling}} = 907$  °C) from ZIF-8 would be removed at high temperature.


Fig. 2a shows the optical images of the Cu/BN samples and highlights the change of colour with different Cu contents: we observed a more pronounced pink/red colour with increasing Cu content (Cu content measured by ICP-MS analyses, Table 1). To gain further insight into the composition and structure of Cu/BN, we collected FTIR spectra. As shown in Fig. 2b, all

samples displayed two main IR bands at  $\sim 1375$   $\text{cm}^{-1}$  (B–N stretching) and  $\sim 800$   $\text{cm}^{-1}$  (B–N–B bending),<sup>45</sup> confirming the formation of BN. We noted an additional peak at  $\sim 1100$   $\text{cm}^{-1}$ , which we attribute to B–O bending, an impurity commonly found in porous BN.<sup>51,52</sup> Fig. 2c shows the PXRD patterns. All samples displayed two broad peaks corresponding to BN (002) and (100) planes, indicating the presence of turbostratic/amorphous BN.<sup>9</sup> Cu/BN samples exhibited two additional sharp peaks at  $43.5^\circ$  and  $50.5^\circ$ , corresponding to Cu (111) and (200) planes, respectively.<sup>53</sup> We did not observe any peak from copper oxide suggesting that  $\text{Cu}^{2+}$  from the template was reduced to metallic Cu, as hypothesised. To provide further support and evidence on the chemical nature and structure of the samples, we conducted high resolution XPS (Fig. 2d and e). The analysis of the core level spectra of B 1s and N 1s confirmed the formation of BN, evidenced by the peaks at  $\sim 190.8$  and  $\sim 398.4$  eV, respectively.<sup>9</sup> The additional peaks at 192.2 eV on the B 1s spectrum and 399.5 eV on N 1s spectrum belong to the B–O–N bonds.<sup>9,54</sup> Oxygen is a known and unavoidable impurity of porous BN due to surface oxidation. We noticed a low carbon content in all samples (Table S2†), most or part of which we attribute to adventitious impurities. The absence of Zn (Fig. S3 and S4†) together with the ICP-MS results suggest that all Zn atoms were removed during the high-temperature synthesis, due to the lower boiling point of Zn (907 °C) compared to the synthesis temperature (1000 °C). In addition, we did not observe any Cu peak on the XPS spectra of the Cu/BN samples (Fig. S3 and S4†). We speculate that this is because Cu particles are located within the bulk of the samples rather than their surface and/or because of the low Cu content in the samples.

As we could not identify the chemical state of Cu using XPS, we instead performed X-ray absorption spectroscopy (XAS) measurements at Cu K edge on samples. Cu foil, CuO,  $\text{Cu}_2\text{O}$  and CuPc (copper phthalocyanine) were used as reference samples. From the normalised Cu K-edge X-ray absorption near-edge (XANES) spectra in Fig. 3a, all the Cu/BN samples show the characteristic absorption edge and shape of metallic Cu

**Table 1** Cu content and textural properties of the Cu/BN samples. The Cu content was obtained from ICP-MS analyses. BET area ( $S_{\text{BET}}$ ), micropore volume ( $V_{\text{mic}}$ ) and total pore volume ( $V_{\text{tot}}$ ) were derived from  $\text{N}_2$  sorption isotherms at 77 K and calculated as described in the experimental section

Sample	Cu content [wt%]	$S_{\text{BET}}$ [ $\text{m}^2 \text{g}^{-1}$ ]	$V_{\text{mic}}$ [ $\text{cm}^3 \text{g}^{-1}$ ]	$V_{\text{tot}}$ [ $\text{cm}^3 \text{g}^{-1}$ ]
BN	0	508	0.68	1.02
1% Cu/BN	0.5	478	0.68	1.07
5% Cu/BN	2.5	493	0.68	0.93
10% Cu/BN	4.4	471	0.67	0.74

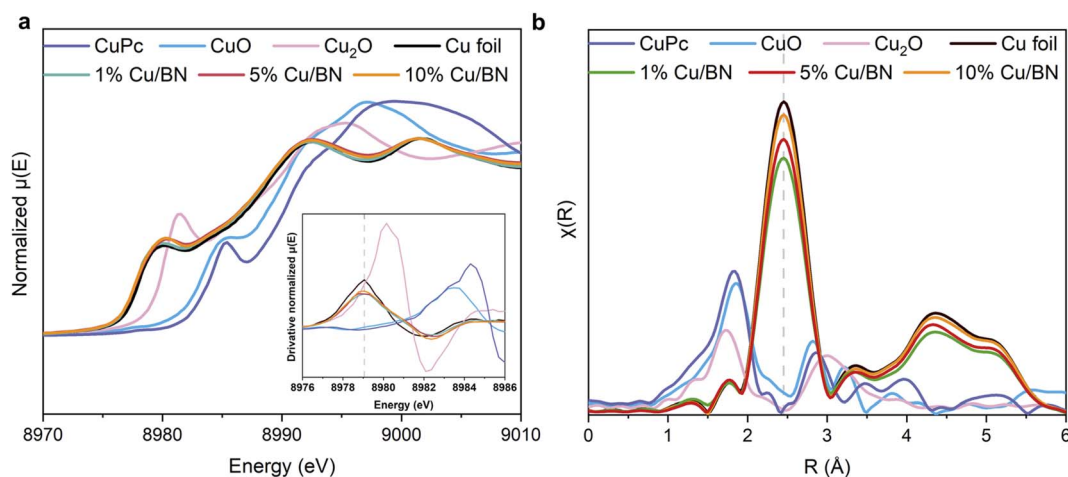

**Fig. 3** XAS characterisation of Cu/BN samples with varying Cu contents and reference samples. (a) Normalised Cu K-edge XANES spectra; inset: derivative Cu K-edge spectra; (b) phase corrected  $k^2$ -weighted Fourier transformed EXAFS spectra, using  $k$ -range 3–11  $\text{\AA}^{-1}$ .





(Cu<sup>0</sup>).<sup>55,56</sup> The Fourier-transformed extended X-ray absorption fine structure (EXAFS) spectra (Fig. 3b) of all Cu/BN samples featured a peak at 2.45 Å, similar to that in Cu foil, and can be attributed to Cu–Cu bonds in the first coordination sphere.<sup>56</sup> Both results indicated that the metallic Cu was the major component in Cu/BN and no oxidized Cu was observed, thereby supporting the XRD analyses. Here, our analyses indicated that Cu nanoparticles were sufficiently stabilized (*i.e.* surface oxidation remained below the detection limit of XAS) over a period of weeks under the protection of porous BN, suggesting the composite is likely to be useful for practical applications.

We characterised the morphology of BN and Cu/BN samples using SEM and TEM. The SEM images in Fig. S6† show that all

samples presented a similar morphology: a densely packed flake structure, which is different from that of the template (*i.e.* MOF nanoparticles, Fig. S1†). Interestingly, we observed many pores ranging from 50–100 nm on the surface of the Cu/BN samples, possibly obtained upon removal of the MOF template. These macropores could facilitate mass transfer. TEM images with the fast Fourier transform (FFT) are shown in Fig. 4. All samples exhibited the disordered structure of BN, confirming the XRD analyses (Fig. 2c). The concentration of Cu particles on BN increased with increasing Cu content, while the particle size did not change noticeably. The particle sizes ranged from 30 to 300 nm, with an average diameter of ~130 nm, as shown in Fig. S7.† The wide particle size



Fig. 4 TEM images of Cu/BN with varied Cu contents (a–d); zoom-in HRTEM images with FFT patterns on corresponding BN of Cu/BN samples (a'–d'). (a) and (a') BN; (b) and (b') 1% Cu/BN; (c) and (c') 5% Cu/BN; (d) and (d') 10% Cu/BN.





Fig. 5  $N_2$  sorption isotherms at 77 K for BN samples in (a) linear scale; (b) semi-log scale. Filled symbols: adsorption. Empty symbols: desorption.

distribution might result from the diffusion of Cu atoms across the BN surface, leading to heterogeneous Cu particle growth (or agglomeration).

We evaluated the porosity of the samples using  $N_2$  sorption isotherms at 77 K. All samples displayed a type IV isotherm with H3 hysteresis loop (Fig. 5), indicating the presence of slit-shaped micro- and mesopores. Doping with Cu particles did not significantly change the BET surface area ( $\sim 500 \text{ m}^2 \text{ g}^{-1}$ ) and the micropore volume ( $\sim 0.7 \text{ cm}^3 \text{ g}^{-1}$ ) of the derived BN. However, the total pore volume reduced upon doping, possibly due to Cu particles occupying the larger pores of BN (Table 1). The porosity in BN is linked to the formation and release of N- and C-containing porogens derived from the precursors.<sup>9,52,57</sup>

Finally, we investigated the optoelectronic properties of the Cu/BN samples using UV/vis diffuse reflectance spectroscopy (UV/vis DRS). The samples displayed two main absorption peaks at  $\sim 210$  and  $\sim 250$  nm, respectively, and these peaks remained almost unchanged upon addition of Cu particles (Fig. 6a). We link the first peak to residual hBN, the 2D non-porous analogue to porous BN, as a small portion of BN might be crystalline (Fig. 4a'–d'). This is supported by the moderate surface area of porous BN in the current work. The second peak with an absorption edge at 295 nm resembled that

previously observed in highly porous (and amorphous) BN.<sup>45</sup> Overall, the BN samples exhibited an estimated optical gap of 4.2 eV based on the band edge from the optical spectra. In addition, the spectra of the Cu/BN samples featured a broad band between 450 and 600 nm (Fig. 6b), attributed to the local surface plasmon resonance (LSPR) of Cu nanoparticles.<sup>58–60</sup>

### 3.3 $CO_2$ photoreduction

We tested the BN and Cu/BN samples for  $CO_2$  photoreduction gas phase without adding any co-catalyst or photosensitizer. We used graphitic carbon nitride ( $g\text{-}C_3N_4$ ) as a reference sample due to its well-known visible light photocatalytic properties as well as its chemical and structural similarity to porous BN. Under UV-vis irradiation for 5 h, all BN samples led to both CO and  $CH_4$  formation, with CO as the primary product (Fig. 7). The CO production rate of Cu/BN samples increased by a factor of 6 or more compared to the reference sample. Although 5% Cu/BN had the highest CO production rate among all BN samples, its performance was only 10% higher than that of pure BN, indicating the limited impact of Cu particles on CO production. On the other hand, all Cu/BN presented a much higher  $CH_4$  production rate compared to pristine BN, particularly 5% Cu/BN (3 times higher performance, Fig. 7b). We link the higher



Fig. 6 Optoelectronic properties Cu/BN with different Cu contents. (a) DRS UV-vis absorption spectra compared to that of hBN; (b) zoom of the panel (a) spectra in the range of 400–700 nm wavelength; (c) PL spectra obtained using a 250 nm excitation wavelength.







Fig. 7 CO<sub>2</sub> photoreduction testing of Cu/BN compared to g-C<sub>3</sub>N<sub>4</sub> under UV-vis irradiation for 5 h. (a) CO production rate; (b) CH<sub>4</sub> production rate; (c) normalised production rate; (d) schematic representation of CO<sub>2</sub> photoreduction mechanism. The error bars correspond to the standard deviation from 2 tests.

CH<sub>4</sub> production to the interactions between Cu(111) surface and CO and/or reaction intermediates, which can facilitate the formation of products like CH<sub>4</sub> and limit the direct desorption of CO from the catalyst surface.<sup>39,61,62</sup> The normalised total product formation rate (*i.e.* both CO and CH<sub>4</sub>) is shown in Fig. 7c. 5% Cu/BN performed the best among all samples, with a production rate 12.5 times and 1.5 times higher than those of g-C<sub>3</sub>N<sub>4</sub> and pristine BN, respectively. We further tested the recyclability of 5% Cu/BN sample over 5 cycles (Fig. S9†). We observed a 12% decrease in product formation rate, which may be due to the degradation of the porous BN.<sup>45</sup> We confirmed the origin of CO *via* a series of control tests: (i) test under dark, (ii) test under a N<sub>2</sub>/H<sub>2</sub> atmosphere and (iii) test under a <sup>13</sup>CO<sub>2</sub>/H<sub>2</sub> atmosphere. We did not observe CO formation in the absence of light or CO<sub>2</sub>, while we detected <sup>13</sup>CO when using <sup>13</sup>CO<sub>2</sub> (Fig. S10†). These results provide direct evidence that CO resulted from the reduction of CO<sub>2</sub>.

We attribute the enhanced CO<sub>2</sub> photoreduction efficiency of 5% Cu/BN compared to pristine BN to two aspects, namely, the plasmonic effect of the Cu nanoparticles and electron-hole separation through Cu–BN heterojunction. We focus first on the

plasmonic effect. Plasmonic effect induced by metal nanoparticles, incorporated into semiconductor nanostructures, can modulate photocatalysis through three mechanistic pathways: light scattering, hot electron transfer, and plasmonic resonance induced energy transfer (PRIET).<sup>63,64</sup> We here hypothesise that both light scattering and hot electron transfer contributed to the Cu/BN system. Light scattering is dominant in the LSPR band for large particles (typically larger than 50 nm in diameter).<sup>65–67</sup> The Cu particles in 5% Cu/BN (123 ± 49 nm) are able to scatter the incident light, resulting in increased photon flux and thus enhanced light absorption. Hot electron transfer, a two-step energy transfer process is another mechanistic pathway due to the surface plasmon from Cu nanoparticles (step 1: hot electrons produced by Cu nanoparticle; step 2: hot electrons injected into other species).<sup>68</sup> PRIET, which includes transferring plasmonic energy non-radiatively from plasmonic particles to semiconductor through dipole–dipole interactions in the near-field, is negligible in the Cu/BN system because we do not observe any characteristic plasmonic response from Cu particles above the bandgap of porous BN. We now look at the second aspect enhancing CO<sub>2</sub>



photoreduction efficiency electron, *i.e.* electron-hole separation. Indeed, the formation of Cu–BN heterojunction improves electron-hole separation compared to pristine BN as suggested by the PL emission spectrum of BN samples (Fig. 6c). Cu/BN samples displayed lower PL intensities compared to BN, suggesting a lower electron-hole recombination rate.<sup>69</sup> This phenomenon is mainly attributed to the electron transfer from the conduction band of porous BN to Cu nanoparticles due to the lower work function of porous BN compared to Cu nanoparticles (3 eV vs. 4.65 eV). The higher work function of 5% Cu/BN compared to pristine BN (Fig. S11†) further suggests the

electron transfer from BN to Cu, agreeing well with other Cu/semiconductor composites.<sup>39,70</sup> The band structures of both pristine BN and 5% Cu/BN are displayed in Fig. S13.† Overall, the above discussion demonstrates the proposed mechanism of CO<sub>2</sub> photoreduction using Cu/BN, which is illustrated in Fig. 7d. We provide further details on the photocatalytic activity of the materials in the ESI (Fig. S14–S16†).

### 3.4 Use of a different metal

To further study how our synthesis approach would extend to other MOFs, we used 10% Co/ZIF-8 as a precursor while keeping



**Fig. 8** Synthesis and characterisation of 10% Co/C-BN. (a) Synthesis process of 10% Co/C-BN; (b) XPS survey spectra; (c) high resolution XPS in the region of C 1s; (d) XRD patterns; (e) N<sub>2</sub> sorption isotherms at 77 K.



This journal is © The Royal Society of Chemistry 2022





- 66 T. G. U. Ghobadi, A. Ghobadi, E. Ozbay and F. Karadas, *ChemPhotoChem*, 2018, **2**, 161–182.
- 67 S. K. Cushing, A. D. Bristow and N. Wu, *Phys. Chem. Chem. Phys.*, 2015, **17**, 30013–30022.
- 68 M. Kim, M. Lin, J. Son, H. Xu and J.-M. Nam, *Adv. Opt. Mater.*, 2017, **5**, 1700004.
- 69 L. Xiao, Q. Zhang, P. Chen, L. Chen, F. Ding, J. Tang, Y. J. Li, C. T. Au and S. F. Yin, *Appl. Catal., B*, 2019, **248**, 380–387.
- 70 C. De Melo, M. Jullien, Y. Battie, A. En Naciri, J. Ghanbaja, F. Montaigne, J. F. Pierson, F. Rigoni, N. Almqvist, A. Vomiero, S. Migot, F. Mücklich and D. Horwat, *ACS Appl. Mater. Interfaces*, 2018, **10**, 40958–40965.
- 71 X. Yuan, X.-X. Hu, X.-L. Ding, H.-C. Kong, H.-D. Sha, H. Lin, W. Wen, G. Shen, Z. Guo, Z.-F. Ma and Y. Yang, *Nanoscale Res. Lett.*, 2013, **8**, 478.
- 72 S. Esconjauregui, C. M. Whelan and K. Maex, *Carbon*, 2009, **47**, 659–669.

