



Cite this: *EES Batteries*, 2025, **1**, 242

Metal-incorporated interphases formed between inorganic solid electrolytes and Li metal: beneficial or detrimental?

Han Su,^{†a,b} Jiamin Fu,^{†b} Sufu Liu,^a Yu Zhong,^{id} ^{*a,c} Yang Hu,^{id} ^b Juner Kuang,^a Minkang Wang,^a Xiuli Wang,^a Xueliang Sun,^{id} ^{*b,d} and Jiangping Tu,^{id} ^{*a}

Most inorganic solid electrolytes (ISEs) undergo reduction when in contact with Li metal to form a new interphase. Traditionally, it was suggested that such interphases should ideally be metal-free, since metals with high electronic conductivity may contribute to the generation of mixed conducting interphases, thereby leading to continuous reduction of the ISE and significant consumption of Li metal. However, recent studies challenge this viewpoint, showing that certain metal-incorporated interphases (MIs) can suppress Li intrusion and improve lithium reversibility compared to metal-free interphases. In this perspective, we aim to address the ongoing debate surrounding the role of metal incorporation at the interphase formed between ISEs and Li metal. We first propose a protocol for critically assessing the MI based on Li asymmetric cells. Throughout the comparative analysis, we discover that the use of conventional Li symmetric cells yields misleading results when evaluating MIs. In contrast, our proposed Li asymmetric cells can more accurately reflect the impact of MIs on Li reversibility. Furthermore, we observe that when the metal volume fraction in the MI is sufficiently low, the MI significantly enhances lithium reversibility compared to its metal-free counterparts. We explain this phenomenon through percolation theory. Lastly, we provide insights into future design strategies for MIs, aiming to offer guidance for the progress of Li/ISE interface design.

Received 6th February 2025,

Accepted 4th March 2025

DOI: 10.1039/d5eb00024f

rsc.li/EESBatteries

Broader context

The integration of lithium metal anodes (LMAs) with non-flammable inorganic solid electrolytes (ISEs) offers a promising route toward next-generation energy-storage devices, combining high energy density with enhanced safety. Nonetheless, most ISEs tend to undergo reduction reactions when in contact with lithium metal, resulting in the formation of a new interphase that plays a critical role in battery performance. Based on conducting properties, interphases can be categorized into two types: one that conducts only ions, known as the solid electrolyte interphase (SEI), and another that conducts both ions and electrons, known as the mixed conducting interphase (MCI). Traditional views suggested that to ensure high Li metal reversibility, interphases should conduct only ions, as the presence of metals could promote MCI formation, leading to continuous ISE reduction. However, recent findings have challenged this traditional view, suggesting that metal incorporation within the interphase can sometimes enhance the stability of the Li/ISE interface. This perspective aims to critically review the evolving role of metal incorporated interphases formed between ISE and Li metal, proposing a new methodology for evaluating their performance and shedding light on the underlying mechanisms that govern their impact on Li metal reversibility.

Introduction

Lithium metal, with its lowest electrochemical potential of -3.04 V vs. SHE (standard hydrogen electrode) and high specific capacity of 3860 mA h g^{-1} , is considered one of the most promising negative electrode materials for next-generation energy storage devices.^{1,2} However, the pairing of inflammable organic electrolytes with highly reactive Li metal poses significant safety risks.^{3,4} Substituting non-flammable inorganic solid electrolytes (ISEs) for conventional organic electrolytes to construct all-solid-state lithium metal batteries (ASSLMBs) can alleviate these safety concerns, paving the way

^aState Key Laboratory of Silicon and Advanced Semiconductor Materials, Key Laboratory of Advanced Materials and Applications for Batteries of Zhejiang Province, School of Materials Science and Engineering, Zhejiang University, Hangzhou 310027, China

^bDepartment of Mechanical and Materials Engineering, University of Western Ontario, London, Ontario, N6A 5B9, Canada

^cKey Laboratory of Advanced Energy Materials Chemistry (Ministry of Education), Nankai University, Tianjin 300071, China

^dEastern Institute for Advanced Study, Eastern Institute of Technology, Ningbo, Zhejiang 315020, China

[†]These authors contributed equally to this work.



for the practical application of lithium metal electrodes in battery devices.^{5,6}

Given the exceedingly high Fermi level of metallic Li, most ISEs will be reduced by Li metal through chemical or electrochemical processes to form a new interphase.^{7–10} This reaction is more pronounced for industrially promising sulfide and halide electrolytes due to their high reduction potentials.^{11–13} Previously, it was thought that the prerequisite for achieving high Li metal reversibility was to impede the continuous reduction of ISEs by ensuring only Li^+ conduction throughout the interphase. Therefore, a metal-incorporated interphase (MII) is proposed to be avoided, as the high electronic conductivity of metals promotes the formation of a mixed conducting interphase (MCI), which induces continuous reduction of ISEs and significant consumption of Li metal.^{14–16} Considering this, the conventional standpoint is that metallic phases in the interphase would only play a detrimental role in the reversibility of lithium (Fig. 1a).

However, recently some researchers have proposed that the inclusion of metallic phases into the interphase can introduce beneficial effects on enhancing Li reversibility. In comparison to the solid electrolyte interphase (SEI) composed solely of non-metallic phases (e.g., Li_2O , Li_3P , LiCl , Li_2S) characterized by relatively low Li^+ conductivity and high lithiophobicity, interphases with metals may offer the following advantages to promote a more regulated Li^+ plating (Fig. 1b).^{17,18} (1) Enhanced Li metal affinity. Studies have shown that metals, even those that do not form alloys with Li (e.g., Cu), generally

exhibit better Li wettability compared to highly lithiophobic non-metallic phases.^{19–21} (2) Facilitated Li^+ transfer kinetics (limited to Li alloys). In contrast to ion-insulating compounds, Li atoms can diffuse more readily within alloys through mechanisms such as vacancy migration or direct hopping. Particularly, in recent investigations into ISE design, it has been observed that certain MII configurations diverge from the classical MCI by not promoting continuous reactions between Li and ISEs during galvanostatic discharging/charging tests in Li symmetric cells.^{22,23} Moreover, some MIIs even demonstrate enhanced capacity to restrain Li intrusion and extend the battery lifespan compared to the typical SEI (Fig. 1c). For instance, though $\text{Li}_6\text{PS}_5\text{Cl}$ (LPSC) electrolytes doped with metal cations (e.g., Cu^+ , Mg^{2+}) or LPSC mixed with some ISEs possessing considerable metal cations (e.g., $\text{Li}_{10}\text{GeP}_2\text{S}_{12}$, Li_3InCl_6) would generate the MII, Li symmetric cells using these electrolytes exhibited no obvious increase of overpotential during galvanostatic discharging/charging tests and exhibited a significant enhancement in the cycle life compared to their counterparts using pristine LPSC.^{24–27}

Currently, there is a growing proposal that the proper introduction of metals into the interphase may be a promising strategy to realize high Li reversibility. Nevertheless, some still maintain the view that the introduction of metals inevitably leads to an increase in electronic conductivity, which will adversely affect lithium reversibility. Therefore, a comprehensive analysis addressing the above debate is highly necessary.

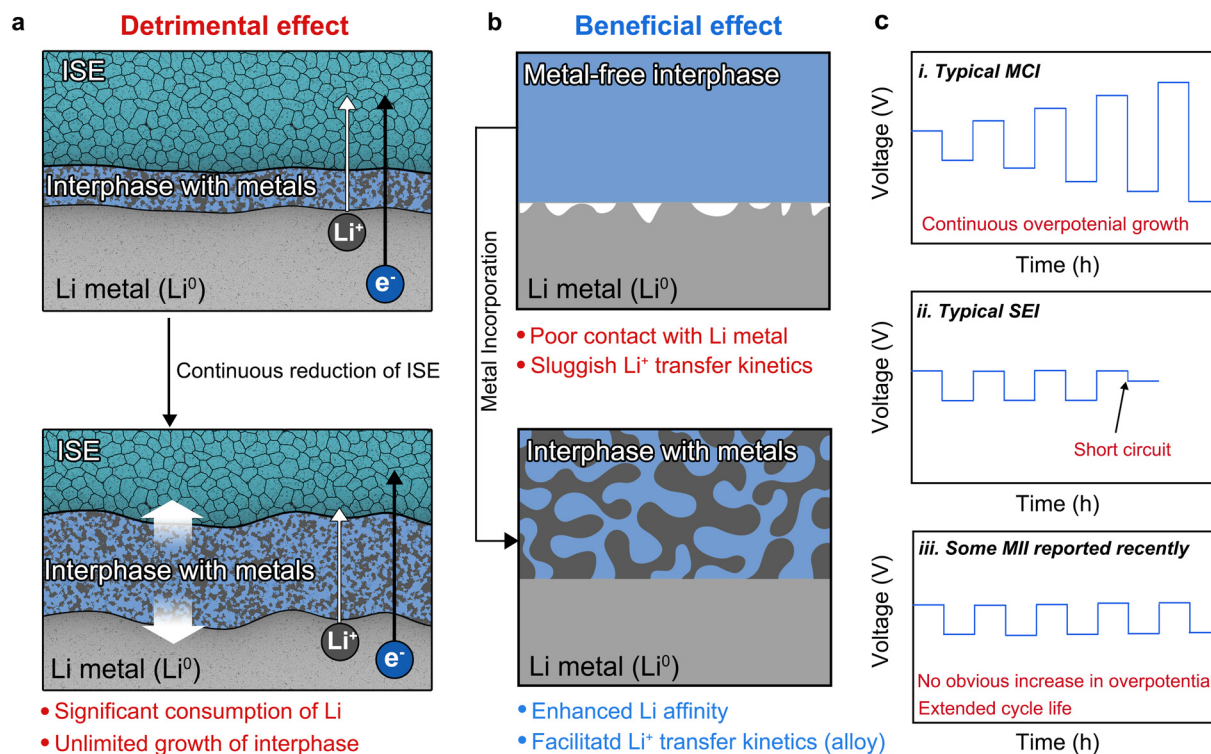


Fig. 1 (a) The schematic diagram of the detrimental effect. (b) The schematic diagram of the beneficial effect. (c) The schematic comparison between Li symmetric cells employing a typical mixed-conducting interphase, a typical solid electrolyte interphase and some metal-incorporated interphases reported recently during galvanostatic discharging/charging tests.



Next, to address the question of whether the detrimental effects of MIIs can be reduced to negligible levels, we evaluated MII-3 with a very low V_{FM} (generated from the reduction of LPSC:LGPS = 16:1) using both symmetric and asymmetric cells. Encouragingly, both the symmetric and asymmetric cells paired with MII-3 (Fig. 2h-j) demonstrated lower polarization and extended cycle life compared to symmetric cells paired with metal-free SEIs (Fig. 2k-m). Moreover, no Li depletion

We then compare the difference between the use of conventional Li symmetric cells and our proposed Li asymmetric cells on the evaluation of interphases with varying V_{FM} . The evaluated interphase was attained by *in situ* reactions between Li metal and a recently reported LPSC/Li₁₀GeP₂S₁₂ (LGPS) composite electrolyte.²⁶ The modulation of LGPS's molar ratio in this composite electrolyte enabled the deliberate generation of interphases with varying V_{FM} . The Li symmetric cells consisted of two Li electrodes with the same areal capacity of 20.5 mA h

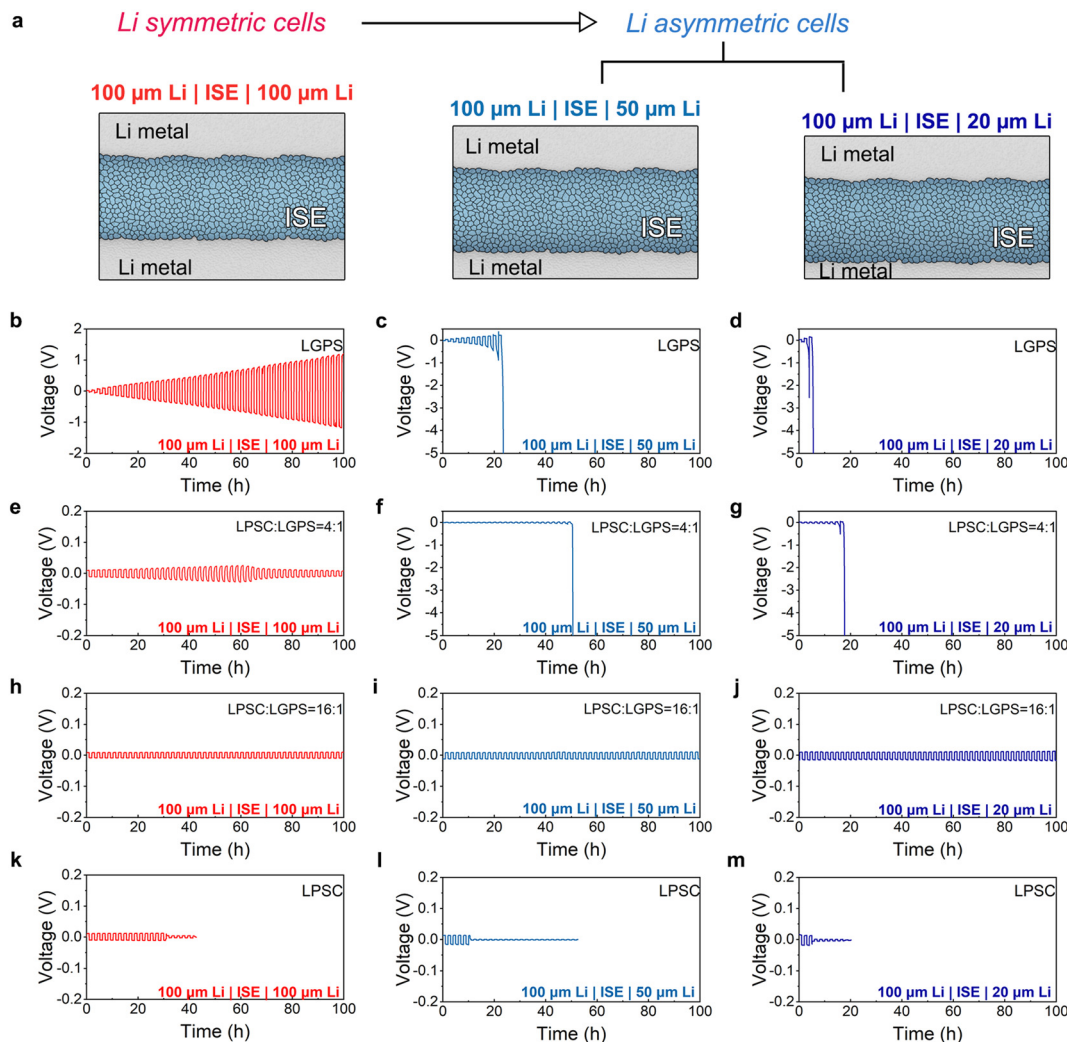


Fig. 2 (a) The schematic diagram of Li symmetric and asymmetric cells used in the evaluation. (b–d) Voltage profiles of the 100 μm thick Li|LGPS|100 μm thick Li symmetric cell (b), 100 μm thick Li|LGPS|50 μm thick Li (c) and 100 μm thick Li|LGPS|20 μm thick Li asymmetric cells (d). (e–g) Voltage profiles of the 100 μm thick Li|LPSC : LGPS = 4 : 1|100 μm thick Li symmetric cell (e), 100 μm thick Li|LPSC : LGPS = 4 : 1|50 μm thick Li (f) and 100 μm thick Li|LPSC : LGPS = 4 : 1|20 μm thick Li asymmetric cells (g). (h–j) Voltage profiles of the 100 μm thick Li|LPSC : LGPS = 16 : 1|100 μm thick Li symmetric cell (h), 100 μm thick Li|LPSC : LGPS = 16 : 1|50 μm thick Li (i) and 100 μm thick Li|LPSC : LGPS = 16 : 1|20 μm thick Li asymmetric cells (j). (k–m) Voltage profiles of the 100 μm-thick Li|LPSC|100 μm thick Li symmetric cell (k), 100 μm Li|LPSC|50 μm thick Li (l) and 100 μm thick Li|LPSC|20 μm thick Li asymmetric cells (m).

was observed during the evaluation based on asymmetric cells. These results experimentally confirm that MIIs with an appropriately low V_{FM} can virtually eliminate their detrimental effects while retaining their beneficial properties, thus enhancing lithium reversibility. Based on this, we support the view that MIIs have the potential to enhance lithium reversibility, provided that its V_{FM} is sufficiently low. The following section will explore, from a theoretical perspective, why the detrimental effects nearly vanish at an appropriately low V_{FM} value and discuss what constitutes an “appropriate” low V_{FM} .


The relationship between V_{FM} and the electronic conductivity of MIIs

Based on the simple mixing rule (eqn (1)), given that the intrinsic electronic conductivity of metals (σ_{M}) is orders of

magnitude higher than that of non-metallic components (σ_{NM}), even a minimal introduction of metals can lead to a substantial increase in electronic conductivity of the MII (σ_{MII}). This forms the basis of the argument against the MII’s potential to enhance Li reversibility. However, this theoretical view contradicts our experimental observations presented above. Therefore, a more scientific and accurate theoretical framework is needed to explain the relationship between the metal content and the electronic conductivity of the interphase.

$$\sigma_{\text{MII}} = V_{\text{f}}\sigma_{\text{M}} + (1 - V_{\text{f}})\sigma_{\text{NM}} \quad (1)$$

As there is currently no dedicated research systematically establishing such a relationship, we draw insights from the studies on composites of electronically insulating polymers and electronically conductive agents, which share considerable



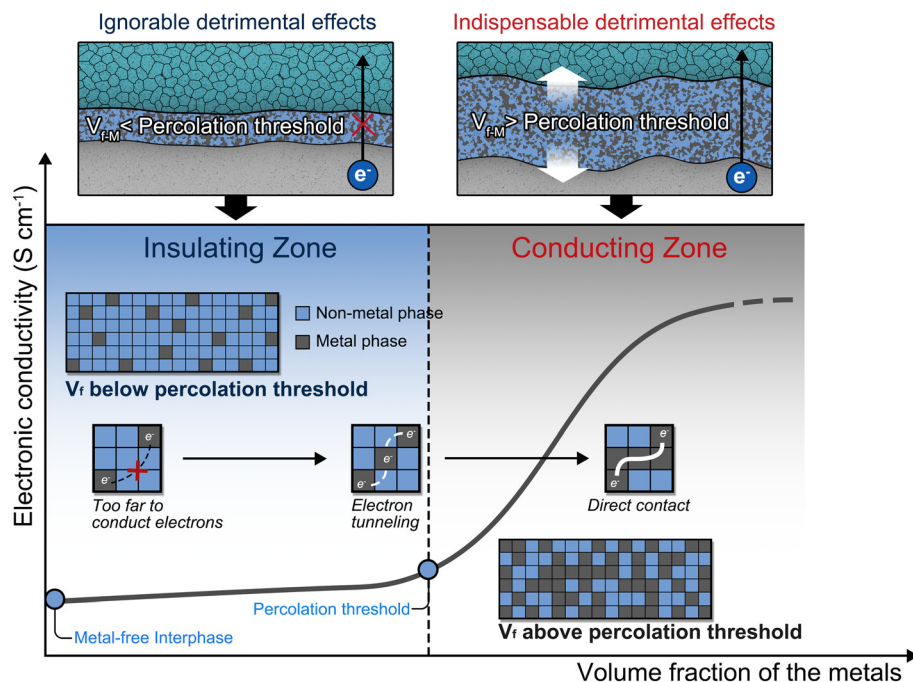


Fig. 3 The application of the percolation theory in the metal-incorporated interphase.

similarities with MIIs.^{28,29} In these composites, the correlation between the volume fraction (V_f) of electronically conductive agents and the electronic conductivity of composites can be determined using the percolation theory. In percolation theory, a crucial concept is the percolation threshold, representing the fraction of points that must be filled to establish a continuous path of nearest neighbors from one side to another. As for the composite of electronically conductive and electronically insulating agents, when the V_f of electronically conductive agents surpasses the percolation threshold, either through direct contact or electron tunneling effects, electronically conductive agents gradually form a continuous electron-conducting network. At this point, the electronic conductivity of the composite increases exponentially with the introduction of electronically conductive agents. At a V_f lower than the percolation threshold, electronically conductive agents are separated by substantial amounts of electronically insulating agents, and a continuous percolation network for electron conduction does not form. In this situation, the electronic conductivity of the composite approaches that of electronically insulating agents. This theory provides a plausible explanation for why the detrimental effects of MII-3 are nearly eliminated, despite the presence of metals (Fig. 3). The key lies in the fact that the V_{f-M} of MII-3 is below the percolation threshold, and thus the electron transport is entirely hindered by the insulating phase.

Typically, the measurement of the percolation threshold in mixed conducting composites is achieved by iteratively incorporating the V_f of the conductive agent and the electronic conductivity into the percolation equation (eqn (2)), where σ_0 is the bulk electronic conductivity of the conducting agent, V_p is

the percolation threshold, σ is the electronic conductivity of the composite, and n is the fitting exponent.

$$\sigma = \sigma_0 \cdot (V_f - V_p)^n \quad (2)$$


Nevertheless, within the framework of ASSLMBs, ascertaining the percolation threshold presents a formidable challenge attributed to the intricacy associated with independently measuring the electronic conductivity of the interphase.³⁰ Therefore, we look forward to the development of advanced electrochemical measurement techniques to address this challenge.

Outlook: future directions in designing metal incorporated-SEIs

Based on the above discussion, when the V_{f-M} falls below the percolation threshold, the MII almost loses its electron transport capability. Similar to the SEI, this type of MII also exhibits the characteristics of self-limiting growth through our critical evaluations. Therefore, we suggest referring to this type of MII as the “metal incorporated-SEI (MI-SEI)” to distinguish it from other MIIs. Due to its promising capability of enhancing Li reversibility, the MI-SEI is poised to become the focal point in the ongoing research of Li/ISE interfaces. We attempt to depict the following directions in the future design of the MI-SEI (Fig. 4).

Elevating the percolation threshold

Below the percolation threshold, the detrimental effects of metals are suppressed to an ignorable level, and the beneficial



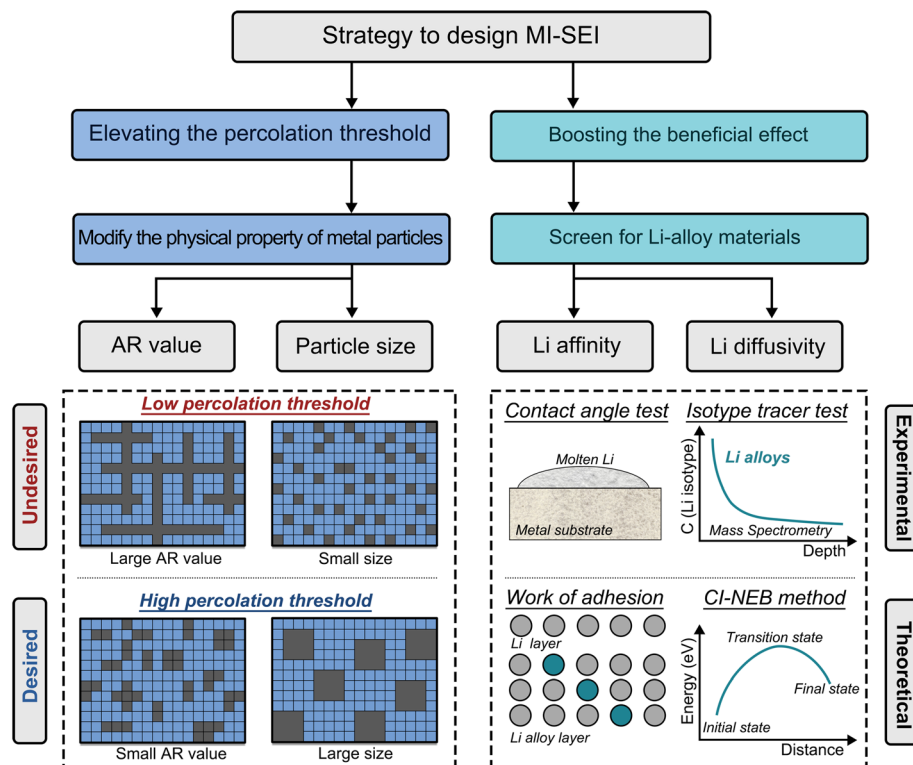


Fig. 4 Future directions in designing the MI-SEI.

effects increase with the enhancing V_{F-M} . Based on this, the MI-SEI theoretically reaches its maximum potential in enhancing Li reversibility when its V_{F-M} approaches the percolation threshold. Consequently, raising the percolation threshold can further augment the maximum V_{F-M} within the MI-SEI, thereby enhancing MI-SEI's capacity to improve the reversibility of Li. Previous studies on polymer/conductive agent composites can provide valuable insights into methods for increasing the percolation threshold.³¹ For instance, different metal particles may exhibit varying aspect ratios (AR), where AR is defined as the ratio between the longest and shortest dimensions of a particle, serving as a parameter to describe its shape. As particles approach a spherical shape, their AR values decrease, resulting in higher achievable percolation thresholds. Additionally, the percolation threshold is closely linked to the size of conductive particles. Under the same V_f of particles, larger particle sizes lead to higher percolation thresholds. In addition to those techniques, we assert that the distribution pattern of metals can influence the percolation threshold of the resulting MII. In our mind, if metals and non-metal particles are not randomly distributed in the interphase but rather designed such that the non-metal particles envelop the metal particles, the formation of a percolation network for metals may become more challenging. Given the current lack of understanding regarding the microstructure and distribution of the metallic phase within MIIs, it is crucial to employ advanced characterization techniques to study the MII

in order to facilitate the successful implementation of the strategies mentioned above.

Promoting the beneficial effects

Li alloys commonly demonstrate higher Li affinity than metallic phases that cannot alloy with Li.³² In addition, Li alloys additionally offer the merit of high Li diffusivity compared to their non-alloyed counterparts. Therefore, we recommend prioritizing the introduction of Li alloys into the MI-SEI. To boost the beneficial effects, one should screen for Li alloys that simultaneously possess high Li affinity and high Li diffusivity. The simplest method to assess Li affinity is testing the contact angle between Li and the Li alloy substrate. Li alloy materials with a higher Li affinity will show a lower contact angle with molten Li.³² For Li diffusivity, isotope tracer tests can determine the Li diffusion coefficient.³³ Aside from experimental methods, high-throughput theoretical calculations of the work of adhesion between Li and the alloy, as well as the lithium diffusion barrier in Li alloys calculated by the climb image-nudged elastic band (CI-NEB) method, can assist in screening Li alloy materials with high Li affinity and high Li diffusivity, respectively.^{21,34,35}

Conclusions

In summary, we propose that the use of Li asymmetric cells offers a more accurate and reliable method for evaluating MIIs



compared to conventional Li symmetric cells. Through a comparative analysis of the evaluation results from Li symmetric and asymmetric cells, we discover that when assessing MIIs with a very high V_{F-M} , Li symmetric cells only exhibit increased polarization, while the voltage of Li asymmetric cells exceeds the test range of the instrument rapidly due to Li depletion. Moreover, when evaluating MIIs with a relatively high V_{F-M} , testing results from Li symmetric cells can be highly misleading, whereas the use of Li asymmetric cells effectively avoids such misleading outcomes. Additionally, we observed that MIIs with sufficiently low V_{F-M} can significantly improve Li reversibility. Drawing insights from percolation theory, we argue that when V_{F-M} is below the percolation threshold, the undesirable electronic conduction of MIIs can be effectively suppressed. Therefore, we advocate for the design of MIIs as an effective approach to enhance lithium reversibility, provided that the V_{F-M} is below the percolation threshold. Lastly, we propose two strategies for MII design: one aimed at increasing the percolation threshold and another focused on promoting beneficial effects. We believe that this perspective provides valuable guidance for future evaluations of MIIs and offers insights for the design of Li/ISE interfaces in upcoming research.

Experimental section

Preparation of LPSC, LGPS and LPSC/LGPS composite electrolytes

The LPSC and LGPS electrolytes were prepared *via* the following approach. As for the LPSC electrolytes, stoichiometric Li_2S (99.99%, Sigma-Aldrich), P_2S_5 (99.9%, Sigma-Aldrich) and LiCl (99.9%, Sigma-Aldrich) were mechanically milled at 550 rpm for 20 h. Then, as-milled precursors obtained from the ball milling process was further annealed at 550 °C for 5 h to yield the final LPSC products. As for the LGPS electrolytes, stoichiometric Li_2S (99.99%, Sigma-Aldrich), P_2S_5 (99.9%, Sigma-Aldrich) and GeS_2 (99.9%, Sigma-Aldrich) were mechanically milled at 550 rpm for 20 h. Then, as-milled precursors obtained from the ball milling process was further annealed at 550 °C for 24 h to yield the final LGPS products. The LPSC/LGPS composite electrolytes were prepared by mechanically milling the LPSC and LGPS electrolytes with an appropriate ratio together at 110 rpm for 1 h.

Cell assembly and electrochemical tests

Both the Li symmetric and Li asymmetric cells were assembled in the Ar-filled glovebox ($\text{H}_2\text{O} < 0.1$ ppm, $\text{O}_2 < 0.1$ ppm). For Li symmetric cells, electrolyte pellets were prepared by cold pressing electrolyte powder (150 mg) at 360 MPa inside the poly (ether-ether-ketone) (PEEK) mold with a diameter of 10 mm.³⁶ Then, two 100 μm thick Li foils with a diameter of 10 mm were pressed onto both sides of the electrolyte layer under 30 MPa for 5 min. For the preparation of Li asymmetric cells, one electrode side of the Li asymmetric cell employed a 50 μm thick or 20 μm thick Li foil, while the other electrode

side used a 100 μm thick Li foil. Apart from this, all other assembly processes remained consistent with those of Li symmetric cells. The galvanostatic discharging/charging tests were conducted on the Neware CT-4008 battery test system.

Author contributions

J.P.T. and H.S. conceived the perspective article. H.S. and J.M.F. conducted relevant literature reviews and wrote the initial manuscript. H.S., J.M.F. and Y.Z. proposed the protocol to evaluate the metal-incorporated interphase. The verification experiments were carried out by S.F.L., J.E.K., M.K.W., H.S., J.M.F., Y.H. and X.L.W.. Y.Z. designed the figures. Y.Z., X.L.S. and J.P.T. provided supervision throughout the manuscript-writing process. H.S. and J.M.F. contributed equally to this work.

Data availability

The data in Fig. 2 are available in Google Sheets at https://docs.google.com/spreadsheets/d/1qj_Bzgz2x1pPs0qyI5Fpgko2Ket-gBHRyXM9SJLH70/edit?usp=sharing.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work is supported by the National Natural Science Foundation of China (Grant No. U20A20126, 52103350, 52472109), the “Pioneer” and “Leading Goose” R&D Program of Zhejiang (grant. no. 2025C01181), and the Key Research and Development Program of Zhejiang Province (2022C01071). Prof. X. L. Sun acknowledges the support from the Natural Sciences and Engineering Research Council of Canada (NSERC), the Canada Research Chair Program (CRC), the Canada Foundation for Innovation (CFI), the Ontario Research Fund, and the University of Western Ontario.

References

- 1 J. G. Zhang, W. Xu, J. Xiao, X. Cao and J. Liu, *Chem. Rev.*, 2020, **120**, 13312–13348.
- 2 N. Nitta, F. X. Wu, J. T. Lee and G. Yushin, *Mater. Today*, 2015, **18**, 252–264.
- 3 Y. Li, X. Feng, D. Ren, M. Ouyang, L. Lu and X. Han, *ACS Appl. Mater. Interfaces*, 2019, **11**, 46839–46850.
- 4 J. X. Hou, L. G. Lu, L. Wang, A. Ohma, D. S. Ren, X. Feng, Y. Li, Y. L. Li, I. Ootani, X. B. Han, W. N. Ren, X. He, Y. Nitta and M. G. Ouyang, *Nat. Commun.*, 2020, **11**, 5100.
- 5 J. Janek and W. G. Zeier, *Nat. Energy*, 2016, **1**, 141.



- 6 A. Manthiram, X. W. Yu and S. F. Wang, *Nat. Rev. Mater.*, 2017, **2**, 16103.
- 7 T. Famprikis, P. Canepa, J. A. Dawson, M. S. Islam and C. Masquelier, *Nat. Mat.*, 2019, **18**, 1278–1291.
- 8 T. Krauskopf, F. H. Richter, W. G. Zeier and J. Janek, *Chem. Rev.*, 2020, **120**, 7745–7794.
- 9 Y. H. Xiao, Y. Wang, S. H. Bo, J. C. Kim, L. J. Miara and G. Ceder, *Nat. Rev. Mater.*, 2019, **5**, 105–126.
- 10 Z. Wang, J. Zhao, X. Zhang, Z. Rong, Y. Tang, X. Liu, L. Zhu, L. Zhang and J. Huang, *eScience*, 2023, **3**, 100087.
- 11 Y. Z. Zhu, X. F. He and Y. F. Mo, *ACS Appl. Mater. Interfaces*, 2015, **7**, 23685–23693.
- 12 N. Kamaya, K. Homma, Y. Yamakawa, M. Hirayama, R. Kanno, M. Yonemura, T. Kamiyama, Y. Kato, S. Hama, K. Kawamoto and A. Mitsui, *Nat. Mat.*, 2011, **10**, 682–686.
- 13 Z. H. Zhang, S. J. Chen, J. Yang, J. Y. Wang, L. L. Yao, X. Y. Yao, P. Cui and X. X. Xu, *ACS Appl. Mater. Interfaces*, 2018, **10**, 2556–2565.
- 14 H. Su, Z. Jiang, Y. Liu, J. R. Li, C. D. Gu, X. L. Wang, X. H. Xia and J. P. Tu, *Energy Mater.*, 2022, **2**, 200005.
- 15 S. Wenzel, D. A. Weber, T. Leichtweiss, M. R. Busche, J. Sann and J. Janek, *Solid State Ionics*, 2016, **286**, 24–33.
- 16 B. B. Chen, J. W. Ju, J. Ma, J. Zhang, R. Xiao, G. Cui and L. Chen, *Phys. Chem. Chem. Phys.*, 2017, **19**, 31436–31442.
- 17 Y. Lu, C. Z. Zhao, J. K. Hu, S. Sun, H. Yuan, Z. H. Fu, X. Chen, J. Q. Huang, M. G. Ouyang and Q. Zhang, *Sci. Adv.*, 2022, **8**, eadd0510.
- 18 H. L. Wan, Z. Y. Wang, S. F. Liu, B. Zhang, X. Z. He, W. R. Zhang and C. S. Wang, *Nat. Energy*, 2023, **8**, 473–481.
- 19 J. S. Yoon, D. W. Liao, S. M. Greene, T. H. Cho, N. P. Dasgupta and D. J. Siegel, *ACS Appl. Mater. Interfaces*, 2024, **16**, 18790–18799.
- 20 H. Su, Y. Liu, Y. Zhong, J. R. Li, X. L. Wang, X. H. Xia, C. D. Gu and J. P. Tu, *Nano Energy*, 2022, **96**, 107104.
- 21 T. R. Wang, J. Duan, B. Zhang, W. Luo, X. Ji, H. H. Xu, Y. Huang, L. Q. Huang, Z. Y. Song, J. Y. Wen, C. S. Wang, Y. H. Huang and J. B. Goodenough, *Energy Environ. Sci.*, 2022, **15**, 1325–1333.
- 22 Y. C. Yin, J. T. Yang, J. D. Luo, G. X. Lu, Z. Huang, J. P. Wang, P. Li, F. Li, Y. C. Wu, T. Tian, Y. F. Meng, H. S. Mo, Y. H. Song, J. N. Yang, L. Z. Feng, T. Ma, W. Wen, K. Gong, L. J. Wang, H. X. Ju, Y. Xiao, Z. Li, X. Tao and H. B. Yao, *Nature*, 2023, **616**, 77–83.
- 23 Z. X. Wang, Y. Jiang, J. Wu, Y. Jiang, W. C. Ma, Y. R. Shi, X. Y. Liu, B. Zhao, Y. Xu and J. J. Zhang, *Nano Energy*, 2021, **84**, 105906.
- 24 C. Liu, B. T. Chen, T. R. Zhang, J. C. Zhang, R. Y. Wang, J. Zheng, Q. J. Mao and X. F. Liu, *Angew. Chem., Int. Ed.*, 2023, **62**, e202302655.
- 25 B. W. Taklu, W. N. Su, Y. Nikodimos, K. Lakshmanan, N. T. Temesgen, P. X. Lin, S. K. Jiang, C. J. Huang, D. Y. Wang, H. S. Sheu, S. H. Wu and B. J. Hwang, *Nano Energy*, 2021, **90**, 106542.
- 26 S. Li, S. J. Yang, G. X. Liu, J. K. Hu, Y. L. Liao, X. L. Wang, R. Wen, H. Yuan, J. Q. Huang and Q. Zhang, *Adv. Mater.*, 2024, **36**, 2307768.
- 27 H. Duan, C. H. Wang, R. Z. Yu, W. H. Li, J. M. Fu, X. F. Yang, X. T. Lin, M. Zheng, X. N. Li, S. X. Deng, X. G. Hao, R. Y. Li, J. T. Wang, H. Huang and X. L. Sun, *Adv. Energy Mater.*, 2023, **13**, 2300815.
- 28 T. Khan, M. S. Irfan, M. Ali, Y. Dong, S. Ramakrishna and R. Umer, *Carbon*, 2021, **176**, 602–631.
- 29 J. Doh, S. I. Park, Q. Yang and N. Raghavan, *Carbon*, 2021, **172**, 308–323.
- 30 P. Bron, B. Roling and S. Dehnen, *J. Power Sources*, 2017, **352**, 127–134.
- 31 L. D. S. Vieira, E. G. R. dos Anjos, G. E. A. Verginio, I. C. Oyama, N. F. Braga, T. F. da Silva, L. S. Montagna and F. R. Passador, *Nano Sel.*, 2021, **3**, 248–260.
- 32 S. H. Wang, J. Yue, W. Dong, T. T. Zuo, J. Y. Li, X. Liu, X. D. Zhang, L. Liu, J. L. Shi, Y. X. Yin and Y. G. Guo, *Nat. Commun.*, 2019, **10**, 4930.
- 33 M. Siniscalchi, J. Liu, J. S. Gibson, S. J. Turrell, J. Aspinall, R. S. Weatherup, M. Pasta, S. C. Speller and C. R. M. Grovenor, *ACS Energy Lett.*, 2022, **7**, 3593–3599.
- 34 X. Liang, Q. Pang, I. R. Kochetkov, M. S. Sempere, H. Huang, X. Sun and L. F. Nazar, *Nat. Energy*, 2017, **2**, 17119.
- 35 R. Wang, J. Yu, J. T. Tang, R. J. Meng, L. F. Nazar, L. Z. Huang and X. Liang, *Energy Storage Mater.*, 2020, **32**, 178–184.
- 36 Z. Wu, S. He, C. Zheng, J. Gan, L. She, M. Zhang, Y. Gao, Y. Yang and H. Pan, *eScience*, 2024, **4**, 100247.

