

Stacked porous tin phosphate nanodisk anodes†

Sanghan Lee and Jaephil Cho


Received (in Cambridge, UK) 20th November 2009, Accepted 14th January 2010

First published as an Advance Article on the web 28th January 2010

DOI: 10.1039/b924381j

Stacked porous octahedral tin phosphate $\text{Sn}_2\text{P}_2\text{O}_7$ nanodisks, with a thickness and a width of 20 nm and 200 nm, respectively, were prepared from quenching hydrothermally prepared $(\text{SnHPO}_4)_2 \cdot \text{H}_2\text{O}$ at 600 °C. The first discharge capacity was 600 mA h g⁻¹ while the capacity retention, even after 220 cycles, was 93%.

Since SnO_2 shows a theoretical gravimetric capacity that is more than twice than that of graphite carbon (~ 376 mA h g⁻¹), and with relatively low average working potential (< 1.5 V),^{1–10} a lot of research has been devoted to this material. Upon lithium reaction, SnO_2 causes the formation of a Li_2O matrix phase according to eqn (1).



However, SnO_2 has some critical problems in its practical application to the Li secondary battery because of very large irreversible capacity (> 700 mA h g⁻¹), and severe capacity fading although a buffer Li_2O matrix phase is formed due to a large volume change between Sn and $\text{Li}_{4.4}\text{Sn}$.^{11,12} Consequently, fracturing and a loss of contact among the bulk Li_2O matrix leads to the destruction of the electrode conduction, which decreases the capacity retention. In order to reduce such problems, nanostructured SnO_2 has been intensively investigated. For instance, nanotubes,^{13–15} hollow nanoparticles,^{8,9,16} nanowires,¹⁷ mesopores,^{18,19} and nanorods²⁰ have been demonstrated to have relatively good capacity retention and a high rate capability, compared to the bulk counterparts. However, these SnO_2 materials show a very large irreversible capacity and eventual catastrophic capacity failure after 100 cycles.¹⁶ On the other hand, when substantial amounts of other spectator atoms, such as B and P atoms, were present in SnO_2 , Sn aggregation was apparently prevented for a couple of cycles.^{1,21,22} However, these tin phosphates also exhibited a rapid capacity fade that was accompanied by a high irreversible capacity (> 500 mA h g⁻¹).²³

In this study, we report on stacked porous octahedral tin phosphate ($\text{Sn}_2\text{P}_2\text{O}_7$) nanodisk anodes that have a reversible capacity of > 600 mA h g⁻¹ and a capacity retention of 93%, even after 220 cycles, in coin-type half cells.

School of Energy Engineering and Converging Research Center for Innovative Battery Technologies and Ulsan National Institute of Science & Technology Ulsan, Korea, 689-805.
E-mail: jpcho@unist.ac.kr

† Electronic supplementary information (ESI) available: A typical experimental procedure for the samples, and XRD, SEM, TEM images of SnO_2 and reference $\text{Sn}_2\text{P}_2\text{O}_7$ anodes. See DOI: 10.1039/b924381j

Fig. 1(a) exhibits the XRD patterns of the as-prepared and quenched samples. The as-prepared sample shows the presence of a $(\text{SnHPO}_4)_2 \cdot \text{H}_2\text{O}$ phase but after quenching at 600 °C, the sample transformed into an amorphous phase. An inductively coupled plasma–mass spectroscopy (ICP-MS) analysis of the quenched sample confirmed a $\text{Sn}_{1.99}\text{P}_2\text{O}_7$ phase, and therefore water loss led to the formation of the $\text{Sn}_2\text{P}_2\text{O}_7$ phase, according to $(\text{SnHPO}_4)_2 \cdot \text{H}_2\text{O} \rightarrow \text{Sn}_2\text{P}_2\text{O}_7 + 2\text{H}_2\text{O}$. Fig. 1(b) and (c) show the SEM images of the as-prepared and quenched samples at 600 °C from which it is seen that the as-prepared sample consists of stacked nanodisks in which each nanodisk has a thickness and diameter of ~ 20 nm and ~ 250 nm, respectively. Also, note that even after the quenching process the pristine octahedral shape of the nanodisk appears to be maintained.

Fig. 1(d) and (e) show TEM images of the stacked nanodisks while randomly distributed mesopores with a diameter of < 4 nm in the amorphous matrix can be observed. However, a lattice fringe that is indicated by the white circle shows the possible presence of the crystalline phase, although its XRD pattern shows a dominant amorphous phase. The N_2

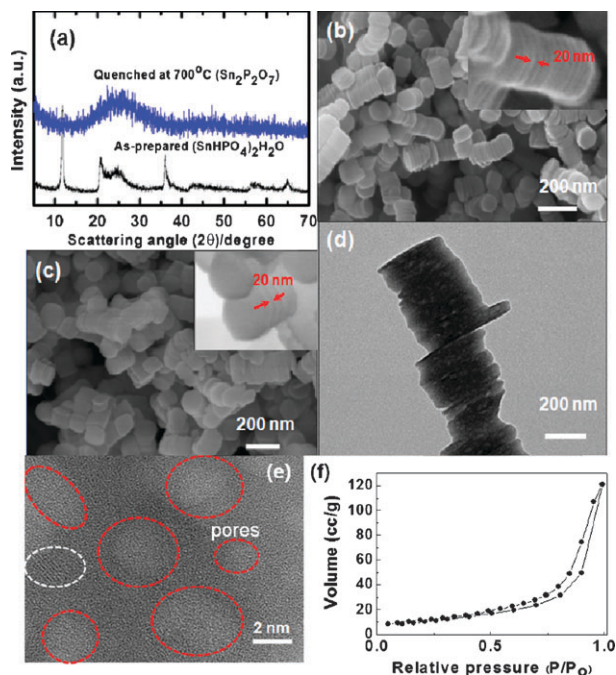


Fig. 1 (a) XRD patterns of as-prepared and quenched nanodisks at 700 °C. (b, c) SEM images of as-prepared and quenched nanodisks at 700 °C (insets: expanded images of b and c). (d) TEM image of the quenched nanodisk where white spots indicate the mesopores. (e) Expanded image of (d) where red circles indicate the mesopores and the white circle indicates a possible crystalline domain. (f) N_2 isotherm of the quenched sample.

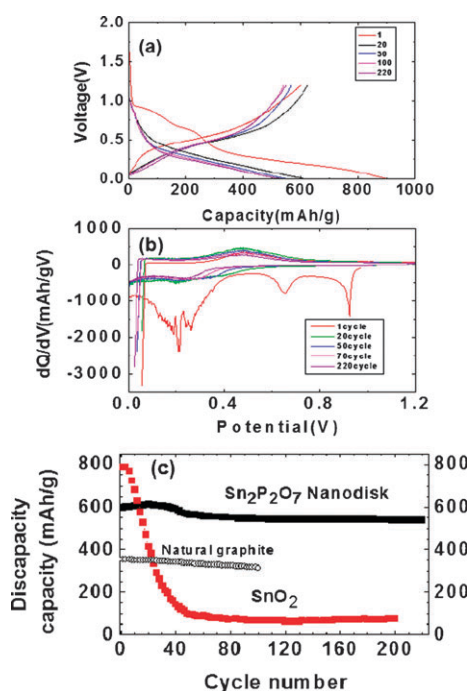


Fig. 2 (a) Voltage profiles of the quenched nanodisks in a coin-type half cell between 0 and 1.2 V at 0.5 C rate ($= 350 \text{ mA g}^{-1}$) after 1, 20, 50, 100, 220 cycles. (b) Differential curves of (a). (c) Discharge capacity (after lithium removal) vs. cycle number in nanodisk. References are natural graphite and SnO_2 nanoparticles.

adsorption–desorption isotherms of the annealed samples in Fig. 1(f) show the typical curves that are observed in aggregated layered materials with irregular slit-like pores²⁴ while the Brunauer–Emmett–Teller (BET) surface area is found to be $38 \text{ m}^2 \text{ g}^{-1}$.

Fig. 2(a) exhibits the voltage profiles of the porous stacked nanodisks after 1, 2, 50, 100 and 220 cycles between 0 and 1.2 V. The first discharge capacity (lithium extraction) is found to be 600 mA h g^{-1} with a coulombic efficiency of 68%. The decomposed $\text{Sn}_2\text{P}_2\text{O}_7$ led to amorphous Li_3PO_4 and LiPO_3 matrix phase, according to $12.8\text{Li} + \text{Sn}_2\text{P}_2\text{O}_7 \rightarrow 2\text{Li}_{4.4}\text{Sn} + \text{Li}_3\text{PO}_4 + \text{LiPO}_3 \leftrightarrow 8.8\text{Li} + 2\text{Sn} + \text{Li}_3\text{PO}_4 + \text{LiPO}_3$.²³ Compared to the SnO_2 nanoparticles (ESI 1†), the coulombic efficiency of the nanodisks was improved by 28% in spite of the BET surface area being similar to each other (SnO_2 was $43 \text{ m}^2 \text{ g}^{-1}$).

This means that the amorphous Li_3PO_4 and LiPO_3 matrix phase is less reactive with the electrolytes than the Li_2O matrix of the SnO_2 . The discharge capacity of the nanodisk anode gradually increased and reached a maximum value of 620 mA h g^{-1} after 20 cycles, after which it slowly decreased to 547 mA h g^{-1} after 220 cycles, showing a 91% capacity retention. Compared with natural graphite (pitch-coated), the overall discharge capacity of the nanodisks (after lithium extraction) during cycling was maintained as high as $> 200 \text{ mA h g}^{-1}$. In terms of coulombic efficiency, its value was increased to 99% after two cycles, which was identical to that of natural graphite (see ESI 2†). Similar crystalline $\text{Sn}_2\text{P}_2\text{O}_7$ (obtained by heating SnHPO_4 to 550°C) exhibited an initial charge capacity of 519 mA h g^{-1} , which decreased rapidly to 148 mA h g^{-1} after 30 cycles.²⁷ On the other hand, amorphous Sn-P-B-O composites lost 50% of their pristine capacity after 45 cycles.¹²

The differential capacity plots in Fig. 2(b) of the coin-type half-cell that contained nanodisks were constructed from the corresponding cycling curves in Fig. 2(a). The peaks at around 0.2 and 0.7 V are lithium insertion/extraction reactions associated with the lithium–tin alloy phases of different compositions.²⁶ As the differential capacity plots are sensitive detectors of change in the voltage profiles from cycle to cycle, the constancy of the plots is indicative of the good reversibility of the electrode material in repetitive charge and discharge operations. However, maintaining broad peaks out to 220 cycles indicates that the tin nanoparticles were confined in the matrix without growing into large clusters. This observation contrasts with that of the tin and tin oxide composite glasses, which were smooth for the first six cycles but gave strong sharp peaks after 15 cycles, indicating the formation of large tin clusters.¹²

On the other hand, the SnO_2 nanoparticles exhibited rapid capacity decay to 80 mA h g^{-1} only after 40 cycles (ESI 3†). In order to understand the differences in the capacity retention, nanodisk electrodes after the 1st, 50th, 100th and 220th cycles were extracted and TEM analyses were carried out, as shown in Fig. 3. After the 1st cycle, the pores in the nanodisks collapsed, and the amorphous nanoparticles with a size of $\sim 2 \text{ nm}$ were embedded in the nanorod-shaped amorphous matrix, which was believed to be Li_3PO_4 and LiPO_3 . After 50 cycles (Fig. 3(e)), such nanoparticles grew to 5 nm. In these conditions, restricted electronic and Li ion conducting pathway between the tin atoms may occur, as proposed by Kim *et al.*²⁵ and therefore, the gradual capacity increase of the nanodisks may occur until tin atoms moved over a greater distance in order to aggregate to a certain size, and thus the distance between the Sn clusters became short enough to produce percolation pathways for conduction. Similar behaviour was observed in mesocellular foam tin phosphates.²⁵ After 100 cycles, without the particle size changing, the Sn nanoparticle population significantly increased and covered the rectangular-shaped matrix particles.

Even after 220 cycles, while some particles grew to 10 nm, most of them appeared to be confined to 5 nm. In addition, the rectangular shape was sustained and all the nanoparticles became encapsulated in the rectangular rod-shaped matrix. On the other hand, SnO_2 nanoparticles that had a particle size of $\sim 10 \text{ nm}$ were pulverized after the 20th cycle (ESI 4b†). The HREM image (ESI 4c†) shows the formation of an amorphous layer on the Sn particles, which is believed to be the Li_2O matrix. However, we could not find the Sn nanoparticles that were dispersed in the matrix. After 100 cycles (ESI 4d and e†), the particles were severely pulverized and the Sn particle size was $\sim 5 \text{ nm}$.

Similar to SnO_2 , Sn-P-M-O composites showed a rapid capacity fade and their capacity retention was below 40% after 40 cycles.^{1,22,27,28} Although there was no description of the particle sizes of these materials, the methods described in these studies resulted in bulk particles. For comparison, bulk amorphous $\text{Sn}_2\text{P}_2\text{O}_7$ particles showed a rapid capacity fade after 40 cycles, and pristine $5 \mu\text{m}$ -sized particles were completely pulverized to 10 nm-sized particles (ESI 5†). We believe this difference could be due to the surface area to volume ratio that increased dramatically when the size decreased to the

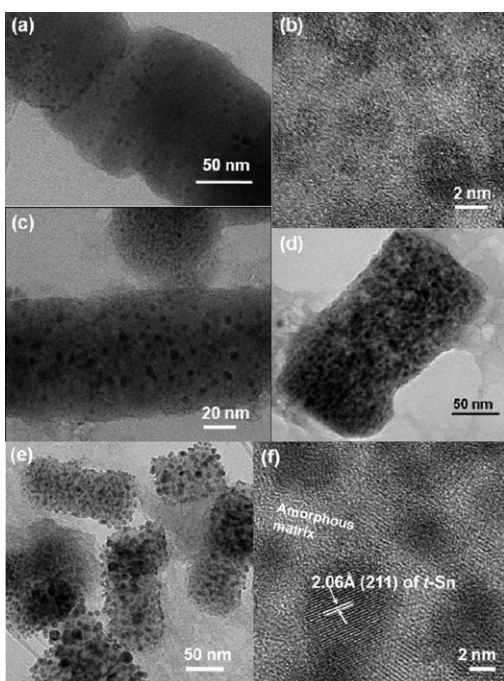


Fig. 3 *Ex situ* TEM images of nanodisks after the 1st cycle (a and b), after 50 cycles (c), after 100 cycles (d) and after 220 cycles (e and f); (f) is an expanded image of (e).

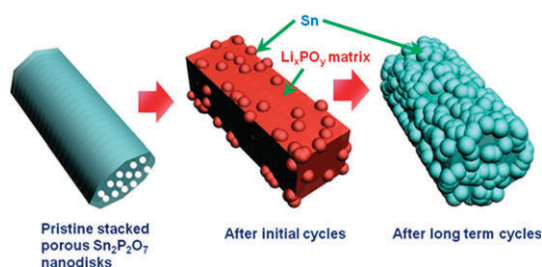


Fig. 4 Schematic view of morphology evolution of pristine stacked porous nanodisks.

nanometre range, and that any dislocations induced by the volume change during lithium alloy and dealloy may have been quickly drawn to the surface.^{29,30} A similar result was also observed in SnHPO_4 nanoparticles that had a mesocellular form structure.²⁵

Overall, Fig. 4 shows schematic views of the morphology evolution of the stacked porous tin phosphate ($\text{Sn}_2\text{P}_2\text{O}_7$) nanodisks upon lithium reaction. Porous nanodisks with a thickness of 20 nm led to confinement of the Sn nanoparticle growth in the Li_xPO_y matrix particle pulverization. Even after extended cycles, Sn nanoparticles grew but were confined in the matrix of which the size was similar to that after initial cycles.

In conclusion, stacked amorphous $\text{Sn}_2\text{P}_2\text{O}_7$ nanodisks demonstrated excellent reversible capacity and capacity retention, even after 200 cycles. In the nanodisks, the matrix phases that consisted of lithium phosphates (Li_3PO_4 and LiPO_3) as a reaction product could play a role as a “glue” that keeps the

Li–Sn particles mechanically connected during the large volume changes of Sn during the alloying/dealloying processes. One of the biggest concerns of the lithium reactive metals relates to the volume change during the lithium alloy and dealloy process. However, the fact that the pristine nanodisk particle size was retained without pulverization even after extended cycling indicated no problem with the mechanical stability of the nanodisk anodes.

This research was supported by the Converging Research Center Program through the National Research Foundation of Korea (NRF) funded by the Ministry of Education, Science and Technology (2009-0082083).

Notes and references

- 1 I. A. Courtney and J. R. Dahn, *J. Electrochem. Soc.*, 1997, **144**, 2045.
- 2 S. Panero, G. Savo and B. Scrosati, *Electrochem. Solid-State Lett.*, 1999, **2**, 365.
- 3 J. Zhu, Z. Lu, Z. S. T. Aruna, D. Aurbach and A. Gedanken, *Chem. Mater.*, 2000, **12**, 2557.
- 4 S. C. Nam, T. H. Kim, W. I. Cho, B. W. Cho, H. S. Chun and K. S. Yun, *Electrochem. Solid-State Lett.*, 1999, **2**, 9.
- 5 C. Kim, M. Noh, M. Choi, J. Cho and B. Park, *Chem. Mater.*, 2005, **17**, 3297.
- 6 M. Winter and J. Besenhard, *Electrochim. Acta*, 1999, **45**, 31.
- 7 S. Han, B. Jang, T. Kim, S. M. Oh and T. Hyeon, *Adv. Funct. Mater.*, 2005, **15**, 1845.
- 8 W. Lou, Y. Wang, C. Yuan, J. Y. Lee and L. A. Archer, *Adv. Mater.*, 2006, **18**, 2325.
- 9 Y. Wang, F. Su, J. Y. Lee and X. S. Zhao, *Chem. Mater.*, 2006, **18**, 1347.
- 10 D. Deng, M. G. Kim, J. Y. Lee and J. Cho, *Energy Environ. Sci.*, 2009, **2**, 818.
- 11 G.-A. Nazri and G. Pistoia, *Lithium Batteries Science and Technology*, Kluwer, Boston, MA, 2004.
- 12 I. A. Courtney, W. R. Mckinnon and J. R. Dahn, *J. Electrochem. Soc.*, 1999, **146**, 59.
- 13 Y. Wang and J. Y. Lee, *J. Phys. Chem. B*, 2004, **108**, 17832.
- 14 Y. Wang, H. C. Zeng and J. Y. Lee, *Adv. Mater.*, 2006, **18**, 645.
- 15 Y. Wang, J. Y. Lee and H. C. Zeng, *Chem. Mater.*, 2005, **17**, 3899.
- 16 M. G. Kim and J. Cho, *Adv. Funct. Mater.*, 2009, **19**, 1497.
- 17 M. S. Park, G.-X. Wang, Y.-M. Kang, D. Wexler, S.-X. Dou and H.-K. Liu, *Angew. Chem., Int. Ed.*, 2007, **46**, 750.
- 18 F. Chen and M. Liu, *Chem. Commun.*, 1999, 1829.
- 19 H. Kim and J. Cho, *J. Mater. Chem.*, 2008, **18**, 771.
- 20 D.-F. Zhang, L.-D. Sun, J.-L. Yin and C.-H. Yan, *Adv. Mater.*, 2003, **15**, 1022.
- 21 Y. Idota, T. Kubota, A. Matsufuji, Y. Maekawa and T. Miyasaka, *Science*, 1997, **276**, 1395.
- 22 I. A. Courtney and J. R. Dahn, *J. Electrochem. Soc.*, 1997, **144**, 2943.
- 23 Y. W. Xiao, J. Y. Lee, A. S. Yu and Z. L. Liu, *J. Electrochem. Soc.*, 1999, **146**, 3623.
- 24 K. S. Sing, D. H. Everett, R. A. W. Haul, L. Moscou, R. A. Pierotti, J. Rouquerol and T. Siemieniewska, *Pure Appl. Chem.*, 1985, **57**, 603.
- 25 E. Kim, M. G. Kim and J. Cho, *Electrochem. Solid-State Lett.*, 2006, **9**, A311.
- 26 H. Kim, G.-S. Park, E. Kim, J. Kim, S.-G. Doo and J. Cho, *J. Electrochem. Soc.*, 2006, **153**, A1633.
- 27 M. Behm and J. T. S. Irvine, *Electrochim. Acta*, 2002, **47**, 1727.
- 28 M. L. E. Moubtassim, J. I. Corredor, J. L. Tirado and C. P. Vicente, *Electrochim. Acta*, 2001, **47**, 489.
- 29 J. Graetz, C. C. Ahn, R. Yazami and B. Fultz, *Electrochem. Solid-State Lett.*, 2003, **6**, A194.
- 30 H. Kim and J. Cho, *Nano Lett.*, 2008, **8**, 3688.