

Cite this: *Chem. Sci.*, 2019, 10, 1549

All publication charges for this article have been paid for by the Royal Society of Chemistry

Metal–salen molecular cages as efficient and recyclable heterogeneous catalysts for cycloaddition of CO₂ with epoxides under ambient conditions†

Chee Koon Ng,^{a,b} Ren Wei Toh,^a Ting Ting Lin,^b He-Kuan Luo,^b T. S. Andy Hor^{*c} and Jie Wu^{*a}

A salen based molecular cage, salen@cage, was synthesized and complexed with Co and Al to yield metal–salen molecular cages, Co(II)@cage, Co(III)@cage and Al(III)@cage. These cages were demonstrated to be efficient heterogeneous catalysts for the cycloaddition of CO₂ with styrene oxide, achieving full conversion at 25 °C and 1 atm CO₂. Good to excellent yields of various cyclic carbonates were also achieved under mild conditions. Al(III)@cage can be reused up to five times without any significant loss of its high catalytic activity. The capability to access a variety of heterogeneous organometallic catalysts with salen@cage offers new prospects for practical CO₂ utilization and chemical manufacturing.

Received 11th November 2018
Accepted 24th November 2018

DOI: 10.1039/c8sc05019h

rsc.li/chemical-science

Introduction

Molecular cages have been of much interest over the past decade as these materials have a wide range of applications from molecular recognition¹ to chemical sensors.² Moreover, their high surface area and porous structure allow them to find applications in gas separation and storage.³ The reactive sites found within these porous molecular cages are suitable for catalytic applications as they can be used to stabilize metal nanoparticles like Pd⁴ and Rh,⁵ increasing their catalytic activities towards organic transformations. Molecular cages can also trap both homogeneous catalysts and substrates *via* specific binding sites. This preorganization brings the encapsulated substrates and catalyst into a confined cavity which promotes the catalytic process.⁶

Salen ligands and their metal complexes have been well studied over the last two decades in homogeneous catalysis.⁷ These ligands are versatile as they can coordinate with many transition metals, main group metals, and even lanthanides. Their complexes have been employed as catalysts in a wide variety of organic transformations, *e.g.* epoxidation of alkenes, Diels–Alder reactions, oxidation, ring opening of epoxides,

Michael addition and reduction of ketones.⁸ One of the most important application of these metal salen complexes is to catalyze the cycloaddition of CO₂ with epoxides to form cyclic carbonates. The increasing anthropogenic emissions of CO₂ have resulted in excessive global warming, and thus the efficient utilization of CO₂ as a C₁ source is an appealing subject of investigation.⁹ Co(III) and Al(III) salen complexes were effective catalysts for the cycloaddition of CO₂ to epoxides and the reaction usually proceeds under mild conditions.¹⁰ The cyclic carbonate products obtained have a range of different applications, including being used as green solvents,¹¹ electrolytes in lithium-ion batteries¹² and precursors in organic synthesis as intermediates to important chemicals like glycols, polyurethanes, dialkyl carbonates, carbamates, purines and pyrimidines. Although homogeneous catalysts like Co(III) and Al(III) salen complexes¹³ were effective at coupling CO₂ with epoxides,¹⁴ they suffer from poor catalyst separation and low recyclability. On the other hand, heterogeneous catalysts like metal oxides,¹⁵ supported metal complexes,¹⁶ metal organic frameworks (MOFs)¹⁷ and porous polymers¹⁸ have been investigated for the production of cyclic carbonates from CO₂, but many of these catalysts require elevated temperatures and pressures or long reaction durations. Therefore, heterogenization of these metal salen complexes to obtain highly efficient catalysts is important not only for the CO₂ cycloaddition, but also for shedding light on the diverse metal salen-mediated chemical transformations.⁸

We herein report that by utilizing dynamic imine condensation,¹⁹ molecular cages incorporated with the salen moiety (salen@cage) can be conveniently synthesized in moderate yields, which can undergo complexation with different metal

^aDepartment of Chemistry, National University of Singapore, 3 Science Drive 3, Singapore 117543, Singapore. E-mail: andyhor@hku.hk; chmjie@nus.edu.sg

^bInstitute of Materials Research and Engineering, Agency for Science, Technology and Research, #08-03, 2 Fusionopolis Way, Innovis, Singapore 138634, Singapore

^cDepartment of Chemistry, The University of Hong Kong, Pokfulam, Hong Kong SAR, China

† Electronic supplementary information (ESI) available: Synthesis and characterization details, computational methods and supplementary catalytic data. See DOI: 10.1039/c8sc05019h

precursors to give $\text{Co(II)}@cage$, $\text{Co(III)}@cage$ and $\text{Al(III)}@cage$. These cages show excellent catalytic reactivity for the cycloaddition of epoxide with CO_2 , giving full conversions of styrene oxide at room temperature and 1 atm CO_2 , probably because porous molecular cages serve to concentrate CO_2 in the pores of the catalyst.


Results and discussion

Synthesis and characterization of salen@cage


The imine-based organic salen@cage was synthesized by the Schiff base reaction as shown in Scheme 1.²⁰ In the ESI-MS spectrum, the salen@cage compound showed only one sharp signal at m/z 1447.83 with the expected isotopic pattern which corresponded to the cation of $[2 + 3]$ salen@cage (Fig. S1 in the ESI†). MALDI-TOF MS in the m/z range of 750–8000 illustrated no further signals other than m/z 1448.0, which excluded the formation of smaller (*e.g.* $[2 + 1]$ and $[2 + 2]$) or larger (*e.g.* $[4 + 6]$ or up to $[10 + 15]$) condensation cages (Fig. S2 in the ESI†). The formation of salen@cage was further corroborated by high resolution mass spectroscopy, solid state ^{13}C cross polarization magic angle spinning NMR and FT-IR (Fig. S3 and S4a in the ESI†). According to dynamic covalent chemistry, the reversible nature of the imine bonds, high reaction temperature and long reaction duration allowed for the most thermodynamically stable product to be selectively formed in equilibrium.^{19c,21} The $[2 + 3]$ molecular prism⁴ was the most enthalpically favoured (least bond angle strain) and entropically favoured (least number of reactants).^{3d} The use of other lower boiling point solvents (*e.g.* CHCl_3 and THF) and shorter reaction durations resulted in the formation of smaller $[2 + 2]$, $[2 + 1]$ and $[1 + 2]$ cages detected by ESI-MS.

Synthesis and characterization of $\text{Co(II)}@cage$, $\text{Co(III)}@cage$ and $\text{Al(III)}@cage$

Considering the high catalytic activity of Co and Al salen complexes in cycloaddition of CO_2 with epoxides,^{13a,18a,22} Co and Al were subsequently coordinated onto salen@cage *via* reactions with Co(OAc)_2 and Al(OEt)_3 , respectively (Scheme 2). Further purification of the compounds was done by Soxhlet extraction. $\text{Co(II)}@cage$, $\text{Co(III)}@cage$ and $\text{Al(III)}@cage$ were all insoluble in common organic solvents, similar to salen@cage. Upon metalation, the characteristic $\text{C}=\text{N}$ stretching of the imine bond shifts from 1630 cm^{-1} in salen@cage to 1607 cm^{-1}

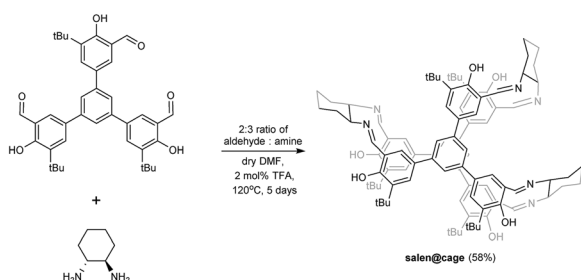

Scheme 1 Synthesis of salen@cage.

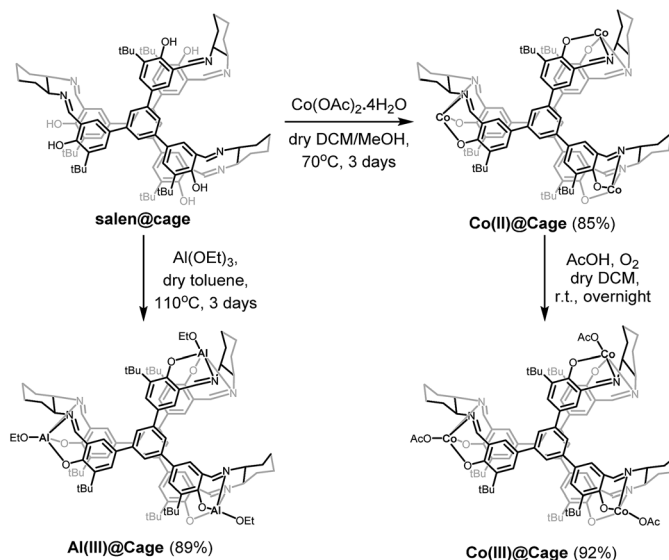

Scheme 2 Synthesis of $\text{Co(II)}@cage$, $\text{Co(III)}@cage$ and $\text{Al(III)}@cage$.

in $\text{Co(II)}@cage$, 1609 cm^{-1} in $\text{Co(III)}@cage$ and 1627 cm^{-1} in $\text{Al(III)}@cage$ (Fig. S4b in the ESI†). The shifts to a lower frequency in FT-IR indicates that Co and Al have been coordinated onto the salen@cage.²³ However, a small shoulder at around 1630 cm^{-1} can still be seen for $\text{Co(II)}@cage$ and $\text{Co(III)}@cage$, which may suggest incomplete metalation for these two cage complexes which was confirmed by elemental analysis (Table S1 in the ESI†). In addition, the positive shifts of the N 1s peak in $\text{Co(II)}@cage$, $\text{Co(III)}@cage$ and $\text{Al(III)}@cage$ as compared to salen@cage in XPS (Fig. S5, ESI†) corroborates the coordination of Co and Al onto the salen@cage.²⁴ The Al 2p peak in the XPS spectrum (Fig. S6a, ESI†) indicates that aluminium is in the +3 oxidation state in $\text{Al(III)}@cage$. The binding energies of the Co 2p peaks in the XPS spectrum (Fig. S6b, ESI†), together with the presence of observable satellite peaks,²⁵ corroborate the +2 oxidation state of cobalt in $\text{Co(II)}@cage$ while the slightly higher binding energies of the Co 2p peaks (Fig. S6c, ESI†) and the absence of satellite peaks indicate that the cobalt in $\text{Co(III)}@cage$ is in the +3 oxidation state.²⁶

We then studied the porosity and CO_2 adsorption of these materials as these properties would affect the CO_2 uptake and conversion. The porosity of these materials was studied by gas sorption experiments with N_2 at 77 K and CO_2 at 298 K (Fig. S9 and S10 in the ESI†). All the cages showed type I nitrogen gas adsorption isotherms according to the IUPAC classifications,²⁷ indicating that these cage complexes consisted of both micropores and mesopores. DFT calculations of the molecular structure of $\text{Al(III)}@cage$ suggested that the micropores ($<2\text{ nm}$) likely originated from the intramolecular space within the cage compound (Fig. S11 in the ESI†), while the mesopores ($2\text{--}50\text{ nm}$) might have originated from the intermolecular packing between each cage molecule (Fig. S12 in the ESI†). All the synthesized cage complexes were considered to be moderately porous, with $\text{Al(III)}@cage$ displaying a higher BET surface area ($771\text{ m}^2\text{ g}^{-1}$) as compared to the other cage complexes ($610\text{--}635\text{ m}^2\text{ g}^{-1}$) (Table S2 in the ESI†). The CO_2 adsorption capability of



salen@cage (35.8 mg g⁻¹) increased once it was coordinated to a metal (Co or Al). This was likely due to the Lewis acidic metal sites which polarized CO₂ and led to greater adsorption.²⁸ Due to the larger surface area, Al(III)@cage displayed a larger CO₂ adsorption capability (70.4 mg g⁻¹) as compared to the rest of the cage complexes (35.8–49.2 mg g⁻¹), which was comparable to that of the conjugated microporous polymers synthesized by Deng *et al.*^{18a}

Cycloaddition of CO₂ with epoxides


We then investigated the cycloaddition of styrene oxide (SO) with CO₂ to give styrene carbonate (SC) using our cage complexes at 25 °C and 1 atm CO₂. Only 9% conversion was achieved after 24 hours in the absence of a catalyst (entry 1, Table 1). Using salen@cage as a catalyst did not improve the conversion (8%, entry 2). This proved that the metal centres in the metal cages were the active catalytic sites and the salen@cage served as the framework to support the metal salen complexes and to increase the surface area of the catalyst for the efficient diffusion of substrates (CO₂ and SO). The heterogeneous Co(III)@cage proved to be more active than Co(II)@cage (100% vs. 55%, entries 4 and 3 respectively), because the more electrophilic Co(III) could coordinate strongly with the epoxide and activated it for ring opening.^{13a} Co(III)@cage was also more efficient than Al(III)@cage (100% vs. 75%, entries 4 and 7 respectively), although Al(III)@cage could also achieve full conversion after 48 h (entry 8). DFT calculations by Deng and co-workers suggested that the Co–salen catalysts gave better catalytic activity as compared to the Al–salen catalysts due to the lower activation barrier of the Co–salen catalysts.²⁹ When the catalyst loading of Co(III)@cage was reduced to 0.17 mol%, the conversion of SO to SC decreased to 76% (entry 5). A longer

reaction duration (48 instead of 24 h) at this reduced catalyst loading could achieve 98% conversion (entry 6). The homogeneous metal salts Co(OAc)₂·4H₂O and Al(OEt)₃ exhibited much lower reactivity (59% and 24%, entries 9 and 10) as compared to the heterogeneous Co(III)@cage and Al(III)@cage. Previous reports on utilizing molecular cage complexes for CO₂ cycloaddition are rare, although some molecular cages showed selective uptake of CO₂^{20,30} and were able to trap CO₂ as carbonate anions within the cage framework.³¹ In 2014, Martinez and Dufaud demonstrated that an azaphosphatrane–hemicyclopentane cage complex was able to catalyze the CO₂ cycloaddition to give styrene carbonate in 82% yield at 100 °C and 1 atm CO₂.³²

We also investigated the enantioselectivity of the CO₂ cycloaddition as the metal cage complexes were synthesized with chiral (*S,S*)-*trans*-1,2-diaminocyclohexane, which might impart a chiral environment to the heterogeneous catalysts. A low selectivity (13.6% ee) was obtained during the cycloaddition of CO₂ with propylene oxide. However, the ee decreased to 2.3% when styrene oxide was used as the substrate (Fig. S15 and S16, ESI†).^{22b,33}

The recyclability of the metal cage complexes was subsequently evaluated. Al(III)@cage retained most of its catalytic activity even after five runs, with the conversions dropping only slightly from 100% to 94% (Fig. 1). ICP-OES analysis of the reaction mixture after filtering shows only 52 ppm of Al, indicating negligible leaching of Al into the reaction mixture. However, Co(III)@cage performed less convincingly in its recyclability testing, with conversions dropping from 100% to 67% (Fig. S17 in the ESI†). Finally, we investigated the epoxide scope with Al(III)@cage under optimized conditions (Fig. 2). Good to excellent yields of the cyclic carbonates were achieved under mild conditions, illustrating that this catalytic system was effective with both alkyl and aryl epoxides, tolerating functionalities including halides, ethers, alkenes and alkynes. The modest yield for propylene carbonate was due to the high volatility of propylene oxide even at room temperature. In

Table 1 Catalyst screening for cycloaddition of CO₂ with styrene oxide to produce styrene carbonate at 25 °C^a

			
Entry	Catalyst	Catalyst loading/mol%	Conversion ^b /%
1	NIL	NIL	9
2	salen@cage	0.33	8
3	Co(II)@cage	0.33 ^d	55
4	Co(III)@cage	0.33 ^d	>99
5	Co(III)@cage	0.17 ^e	76
6	Co(III)@cage	0.17 ^e	98 ^c
7	Al(III)@cage	0.33 ^f	75
8	Al(III)@cage	0.33 ^f	>99 ^c
9	Co(OAc) ₂ ·4H ₂ O	1	59
10	Al(OEt) ₃	1	24

^a Typical reaction conditions: 5.0 mmol styrene oxide, 0.5 mmol TBAB, and catalyst under 1 atm CO₂ pressure at 25 °C for 24 h. ^b Conversions calculated from the crude ¹H NMR spectra. ^c Reaction time = 48 h. ^d Corresponding to approximately 1 mol% of Co. ^e Corresponding to approximately 0.5 mol% of Co. ^f Corresponding to approximately 1 mol% of Al.

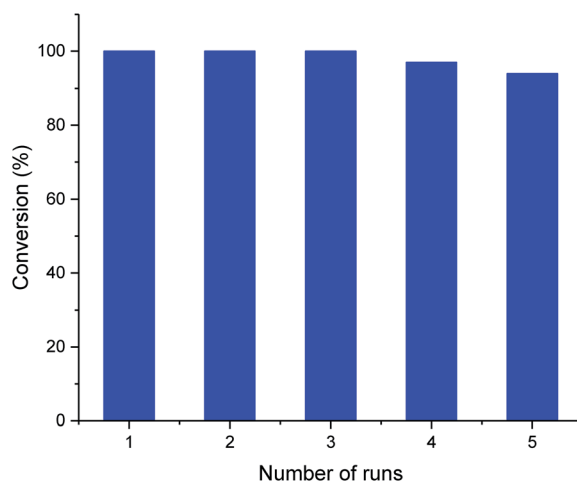


Fig. 1 Recyclability of Al(III)@cage. Typical reaction conditions: 5.0 mmol styrene oxide, 10 mol% TBAB and 0.33 mol% Al(III)@cage under 1 atm CO₂ pressure at 25 °C for 48 h.



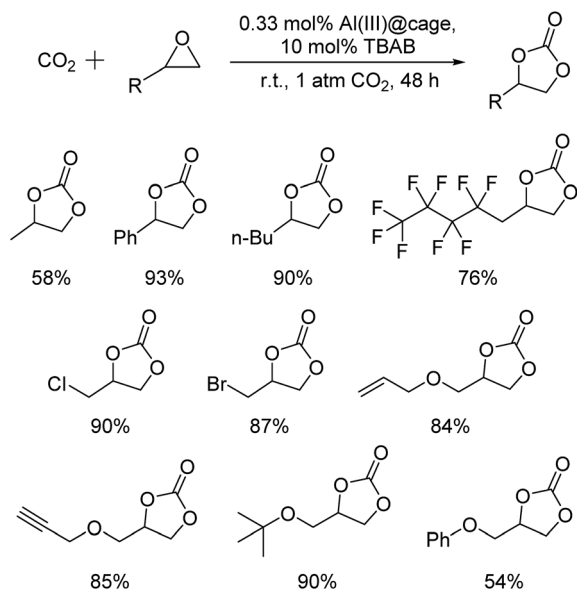


Fig. 2 Isolated yields of cyclic carbonates formed by the cycloaddition of CO₂ with epoxides catalyzed by Al(III)@cage; reaction conditions: 1 mmol epoxide, 0.33 mol% Al(III)@cage, 10 mol% TBAB, r.t., 1 atm CO₂, and 48 h.

comparison with other high performing heterogeneous catalysts for this transformation, the catalytic activity of metal salen cages outperforms that of many supported metal complexes,^{16b-d,34} porous polymers³⁵ and MOFs,³⁶ but there have been recent reports of some MOFs³⁷ and metalated porous organic polymers (POPs)^{18a,d-f,38} with similar or higher catalytic activities. The advantages of these cages include high stability, ease of synthesis, use of readily available materials, ability to adapt to different metals, and good recyclability with high productivity. Further optimisation can be focused on the control of porosity through molecular manipulation of the salen framework and its metal compatibility.

Conclusions

We have successfully synthesized and characterized a salen-based [2 + 3] molecular cage, salen@cage. As a proof of concept for the heterogenization of metal salen complexes, Co and Al were coordinated onto the salen@cage to give Co(II)@cage, Co(III)@cage and Al(III)@cage in excellent yields. Co(III)@cage and Al(III)@cage proved to be excellent heterogeneous catalysts for the cycloaddition of CO₂ with styrene oxide, giving full conversions of styrene oxide to styrene carbonate at 25 °C and 1 atm CO₂ with only 0.33 mol% catalyst loading. Al(III)@cage could be reused up to five times without any significant decrease in its catalytic activity. The catalytic performances of molecular cage catalysts exceed that of many other heterogeneous CO₂ cycloaddition catalysts under mild conditions which makes them suitable heterogeneous catalysts for CO₂ conversion under ambient conditions. Moreover, our study opens the possibility of utilizing other metals with the salen@cage framework to yield a variety of efficient heterogeneous metal

salen catalysts without the use of external heterogeneous supports like silica. These heterogeneous metal salen catalysts can potentially be applied in a variety of other transformations and also can be fitted for continuous-flow synthesis as a packed-bed catalyst. These studies are currently underway in our laboratory.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

We are grateful for the financial support provided by GSK-EDB (R-143-000-687-592), A*STAR RIE2020 AME (A1783c0013). We would like to acknowledge the A*STAR Computational Resource Centre for their support of the computation work through the use of its high performance computing facilities.

Notes and references

- (a) F. Hof, S. L. Craig, C. Nuckolls and J. J. Rebek, *Angew. Chem., Int. Ed.*, 2002, **41**, 1488–1508; (b) A. V. Leontiev and D. M. Rudkevich, *Chem. Commun.*, 2004, 1468–1469; (c) J. Rebek, *Angew. Chem., Int. Ed.*, 2005, **44**, 2068–2078; (d) S. M. Biroš and J. J. Rebek, *Chem. Soc. Rev.*, 2007, **36**, 93–104.
- (a) A. P. Bisson, V. M. Lynch, M.-K. C. Monahan and E. V. Anslyn, *Angew. Chem., Int. Ed.*, 1997, **36**, 2340–2342; (b) Y. Ferrand, M. P. Crump and A. P. Davis, *Science*, 2007, **318**, 619–622.
- (a) J. L. Atwood, L. J. Barbour and A. Jerga, *Science*, 2002, **296**, 2367–2369; (b) K. Swaminathan Iyer, M. Norret, S. J. Dalgarno, J. L. Atwood and C. L. Raston, *Angew. Chem., Int. Ed.*, 2008, **47**, 6362–6366; (c) T. Tozawa, J. T. A. Jones, S. I. Swamy, S. Jiang, D. J. Adams, S. Shakespeare, R. Clowes, D. Bradshaw, T. Hasell, S. Y. Chong, C. Tang, S. Thompson, J. Parker, A. Trewin, J. Bacsá, A. M. Z. Slawin, A. Steiner and A. I. Cooper, *Nat. Mater.*, 2009, **8**, 973–978; (d) Y. Jin, B. A. Voss, A. Jin, H. Long, R. D. Noble and W. Zhang, *J. Am. Chem. Soc.*, 2011, **133**, 6650–6658; (e) M. Petryk, J. Szymkowiak, B. Gierczyk, G. Spólnik, Ł. Popenda, A. Janiak and M. Kwit, *Org. Biomol. Chem.*, 2016, **14**, 7495–7499.
- B. Mondal, K. Acharyya, P. Howlader and P. S. Mukherjee, *J. Am. Chem. Soc.*, 2016, **138**, 1709–1716.
- J.-K. Sun, W.-W. Zhan, T. Akita and Q. Xu, *J. Am. Chem. Soc.*, 2015, **137**, 7063–7066.
- (a) W. Cullen, M. C. Misuraca, C. A. Hunter, N. H. Williams and M. D. Ward, *Nat. Chem.*, 2016, **8**, 231; (b) Q.-Q. Wang, S. Gonell, S. H. A. M. Leenders, M. Dürr, I. Ivanović-Burmazović and J. N. H. Reek, *Nat. Chem.*, 2016, **8**, 225; (c) C. Tan, J. Jiao, Z. Li, Y. Liu, X. Han and Y. Cui, *Angew. Chem., Int. Ed.*, 2017, **57**, 2085–2090; (d) J. Jiao, C. Tan, Z. Li, Y. Liu, X. Han and Y. Cui, *J. Am. Chem. Soc.*, 2018, **140**, 2251–2259.
- S. J. Wezenberg and A. W. Kleij, *Angew. Chem., Int. Ed.*, 2008, **47**, 2354–2364.



- 8 (a) P. G. Cozzi, *Chem. Soc. Rev.*, 2004, **33**, 410–421; (b) K. C. Gupta and A. K. Sutar, *Coord. Chem. Rev.*, 2008, **252**, 1420–1450.
- 9 (a) D. Yu, S. P. Teong and Y. Zhang, *Coord. Chem. Rev.*, 2015, **293–294**, 279–291; (b) Q. Liu, L. Wu, R. Jackstell and M. Beller, *Nat. Commun.*, 2015, **6**, 5933; (c) J. Klankermayer, S. Wesselbaum, K. Beydoun and W. Leitner, *Angew. Chem., Int. Ed.*, 2016, **55**, 7296–7343; (d) Q. W. Song, Z. H. Zhou and L. N. He, *Green Chem.*, 2017, **19**, 3707–3728.
- 10 (a) A. Decortes, A. M. Castilla and A. W. Kleij, *Angew. Chem., Int. Ed.*, 2010, **49**, 9822–9837; (b) M. Cokoja, M. E. Wilhelm, M. H. Anthofer, W. A. Herrmann and F. E. Kuhn, *ChemSusChem*, 2015, **8**, 2436–2454; (c) F. D. Bobbink, D. Vasilyev, M. Hulla, S. Chamam, F. Menoud, G. Laurenczy, S. Katsyuba and P. J. Dyson, *ACS Catal.*, 2018, **8**, 2589–2594; (d) R. R. Shaikh, S. Pornpraprom and V. D'Elia, *ACS Catal.*, 2018, **8**, 419–450.
- 11 (a) M. North, F. Pizzato and P. Villuendas, *ChemSusChem*, 2009, **2**, 862–865; (b) B. Schäffner, F. Schäffner, S. P. Verevkin and A. Börner, *Chem. Rev.*, 2010, **110**, 4554–4581.
- 12 S. S. Zhang, *J. Power Sources*, 2006, **162**, 1379–1394.
- 13 (a) A. Decortes, A. M. Castilla and A. W. Kleij, *Angew. Chem., Int. Ed.*, 2010, **49**, 9822–9837; (b) X.-B. Lu and D. J. Darensbourg, *Chem. Soc. Rev.*, 2012, **41**, 1462–1484.
- 14 C. Martín, G. Fiorani and A. W. Kleij, *ACS Catal.*, 2015, **5**, 1353–1370.
- 15 W.-L. Dai, S.-L. Luo, S.-F. Yin and C.-T. Au, *Appl. Catal., A*, 2009, **366**, 2–12.
- 16 (a) N. A. M. Razali, K. T. Lee, S. Bhatia and A. R. Mohamed, *Renewable Sustainable Energy Rev.*, 2012, **16**, 4951–4964; (b) T. Ema, Y. Miyazaki, T. Taniguchi and J. Takada, *Green Chem.*, 2013, **15**, 2485–2492; (c) A. A. L. Gonçalves, A. C. Fonseca, J. F. J. Coelho and A. C. Serra, *Curr. Green Chem.*, 2015, **2**, 43–65; (d) V. D'Elia, H. Dong, A. J. Rossini, C. M. Widdifield, S. V. C. Vummaleti, Y. Minenkov, A. Poater, E. Abou-Hamad, J. D. A. Pelletier, L. Cavallo, L. Emsley and J.-M. Basset, *J. Am. Chem. Soc.*, 2015, **137**, 7728–7739.
- 17 (a) A. C. Kathalikkattil, R. Babu, J. Tharun, R. Roshan and D.-W. Park, *Catal. Surv. Asia*, 2015, **19**, 223–235; (b) H. He, J. A. Perman, G. Zhu and S. Ma, *Small*, 2016, **12**, 6309–6324; (c) J. W. Maina, C. Pozo-Gonzalo, L. Kong, J. Schütz, M. Hill and L. F. Dumée, *Mater. Horiz.*, 2017, **4**, 345–361.
- 18 (a) Y. Xie, T.-T. Wang, X.-H. Liu, K. Zou and W.-Q. Deng, *Nat. Commun.*, 2013, **4**, 1960; (b) T.-T. Liu, J. Liang, Y.-B. Huang and R. Cao, *Chem. Commun.*, 2016, **52**, 13288–13291; (c) G. Ji, Z. Yang, H. Zhang, Y. Zhao, B. Yu, Z. Ma and Z. Liu, *Angew. Chem., Int. Ed.*, 2016, **55**, 9685–9689; (d) Z. Dai, Q. Sun, X. Liu, C. Bian, Q. Wu, S. Pan, L. Wang, X. Meng, F. Deng and F.-S. Xiao, *J. Catal.*, 2016, **338**, 202–209; (e) Y. Chen, R. Luo, Q. Xu, J. Jiang, X. Zhou and H. Ji, *ChemSusChem*, 2017, **10**, 2534–2541; (f) S. Wang, K. Song, C. Zhang, Y. Shu, T. Li and B. Tan, *J. Mater. Chem. A*, 2017, **5**, 1509–1515.
- 19 (a) S. J. Rowan, S. J. Cantrill, G. R. L. Cousins, J. K. M. Sanders and J. F. Stoddart, *Angew. Chem., Int. Ed.*, 2002, **41**, 898–952; (b) M. Mastalerz, *Angew. Chem., Int. Ed.*, 2010, **49**, 5042–5053; (c) Y. Jin, Q. Wang, P. Taynton and W. Zhang, *Acc. Chem. Res.*, 2014, **47**, 1575–1586.
- 20 S. M. Elbert, F. Rominger and M. Mastalerz, *Chem.–Eur. J.*, 2014, **20**, 16707–16720.
- 21 Y. Jin, C. Yu, R. J. Denman and W. Zhang, *Chem. Soc. Rev.*, 2013, **42**, 6634–6654.
- 22 (a) J. Meléndez, M. North and R. Pasquale, *Eur. J. Inorg. Chem.*, 2007, **2007**, 3323–3326; (b) T. Roy, R. I. Kureshy, N.-u. H. Khan, S. H. R. Abdi and H. C. Bajaj, *Catal. Sci. Technol.*, 2013, **3**, 2661–2667; (c) J. W. Comerford, I. D. V. Ingram, M. North and X. Wu, *Green Chem.*, 2015, **17**, 1966–1987.
- 23 (a) D. Gong, B. Wang, X. Jia and X. Zhang, *Dalton Trans.*, 2014, **43**, 4169–4178; (b) H. Keypour, S. G. Saremi, H. Veisi and R. Azadbakht, *RSC Adv.*, 2016, **6**, 77020–77029.
- 24 (a) J. H. Burness, J. G. Dillard and L. T. Taylor, *J. Am. Chem. Soc.*, 1975, **97**, 6080–6088; (b) H. Liu, X. Xue, T. Li, J. Wang, W. Xu, M. Liu, P. Chen and Y. Wu, *RSC Adv.*, 2016, **6**, 84815–84824.
- 25 (a) S. Laokroekiat, M. Hara, S. Nagano and Y. Nagao, *Langmuir*, 2016, **32**, 6648–6655; (b) J. Li, Y. Fan, Y. Ren, J. Liao, C. Qi and H. Jiang, *Inorg. Chem.*, 2018, **57**, 1203–1212.
- 26 D. Patel, G. R. Kurrey, S. S. Shinde, P. Kumar, G.-J. Kim and S. S. Thakur, *RSC Adv.*, 2015, **5**, 82699–82703.
- 27 S. Brunauer, L. S. Deming, W. E. Deming and E. Teller, *J. Am. Chem. Soc.*, 1940, **62**, 1723–1732.
- 28 Z. Zhang, Z.-Z. Yao, S. Xiang and B. Chen, *Energy Environ. Sci.*, 2014, **7**, 2868–2899.
- 29 T.-T. Wang, Y. Xie and W.-Q. Deng, *J. Phys. Chem. A*, 2014, **118**, 9239–9243.
- 30 (a) S.-T. Zheng, J. T. Bu, Y. Li, T. Wu, F. Zuo, P. Feng and X. Bu, *J. Am. Chem. Soc.*, 2010, **132**, 17062–17064; (b) B. X. Dong, S. Y. Zhang, W. L. Liu, Y. C. Wu, J. Ge, L. Song and Y. L. Teng, *Chem. Commun.*, 2015, **51**, 5691–5694; (c) W.-P. Chen, P.-Q. Liao, Y. Yu, Z. Zheng, X.-M. Chen and Y.-Z. Zheng, *Angew. Chem., Int. Ed.*, 2016, **55**, 9375–9379.
- 31 (a) D. Sun, G.-G. Luo, N. Zhang, R.-B. Huang and L.-S. Zheng, *Chem. Commun.*, 2011, **47**, 1461–1463; (b) S. K. Dey, R. Chutia and G. Das, *Inorg. Chem.*, 2012, **51**, 1727–1738; (c) A. M. Garcia-Deibe, C. Portela-Garcia, M. Fondo, A. J. Mota and J. Sanmartin-Matalobos, *Chem. Commun.*, 2012, **48**, 9915–9917.
- 32 B. Chatelet, L. Joucla, J.-P. Dutasta, A. Martinez and V. Dufaud, *Chem.–Eur. J.*, 2014, **20**, 8571–8574.
- 33 (a) P. Yan and H. Jing, *Adv. Synth. Catal.*, 2009, **351**, 1325–1332; (b) S. Zhang, Y. Huang, H. Jing, W. Yao and P. Yan, *Green Chem.*, 2009, **11**, 935–938; (c) D. Chen, R. Luo, M. Li, M. Wen, Y. Li, C. Chen and N. Zhang, *Chem. Commun.*, 2017, **53**, 10930–10933.
- 34 S. Kumar, S. L. Jain and B. Sain, *Catal. Today*, 2012, **198**, 204–208.
- 35 (a) Y. Xie, R.-X. Yang, N.-Y. Huang, H.-J. Luo and W.-Q. Deng, *J. Energy Chem.*, 2014, **23**, 22–28; (b) Y. Xie, T.-T. Wang, R.-X. Yang, N.-Y. Huang, K. Zou and W.-Q. Deng, *ChemSusChem*, 2014, **7**, 2110–2114.



- 36 (a) M. H. Beyzavi, R. C. Klet, S. Tussupbayev, J. Borycz, N. A. Vermeulen, C. J. Cramer, J. F. Stoddart, J. T. Hupp and O. K. Farha, *J. Am. Chem. Soc.*, 2014, **136**, 15861–15864; (b) Z.-R. Jiang, H. Wang, Y. Hu, J. Lu and H.-L. Jiang, *ChemSusChem*, 2015, **8**, 878–885.
- 37 (a) W.-Y. Gao, L. Wojtas and S. Ma, *Chem. Commun.*, 2014, **50**, 5316–5318; (b) W.-Y. Gao, Y. Chen, Y. Niu, K. Williams, L. Cash, P. J. Perez, L. Wojtas, J. Cai, Y.-S. Chen and S. Ma, *Angew. Chem., Int. Ed.*, 2014, **53**, 2615–2619; (c) W.-Y. Gao, C.-Y. Tsai, L. Wojtas, T. Thiounn, C.-C. Lin and S. Ma, *Inorg. Chem.*, 2016, **55**, 7291–7294; (d) H. He, Q. Sun, W. Gao, J. A. Perman, F. Sun, G. Zhu, B. Aguila, K. Forrest, B. Space and S. Ma, *Angew. Chem., Int. Ed.*, 2018, **57**, 4657–4662.
- 38 Y. Chen, R. Luo, Q. Xu, W. Zhang, X. Zhou and H. Ji, *ChemCatChem*, 2017, **9**, 767–773.

