


Cite this: *RSC Adv.*, 2023, 13, 26357

Estimation of spectroscopic parameters and TL glow curve analysis of Eu^{3+} -activated CaY_2O_4 phosphor

Tirath Ram,^a Neeraj Verma,^a Jagjeet Kaur,^a Abhishek Kumar Misra,^a Vikas Dubey,^{id} ^{*b} Neha Dubey,^{id} ^a Marta Michalska-Domańska,^{id} ^{*c} Janita Saji,^{id} ^d and Ram Sagar Yadav,^{id} ^e

The solid-state reaction method was utilised to create a down-conversion phosphor in an air environment in $\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$ nanocrystalline material. The calcination temperature was set at 1000 °C, and the sintering temperature was set at 1300 °C. Following annealing, confirmation of the crystallinity quality of the phosphor was accomplished by the use of X-ray diffraction analysis. The particle size was predicted to be 43.113 nm using Scherrer's formula. To produce down-conversion luminescence spectra, an excitation wavelength of 247 nm was applied with a fluorescence spectrophotometer. The PL got increasingly intense as the concentration of the dopant increased. The maximum intensity was measured at 2.0 mol% of Eu^{3+} ion, which gradually decreased as the concentration increased because of concentration quenching. To analyse spectrophotometric peak determinations, the approach developed by the Commission Internationale de l'Éclairage (CIE) was used. Thermoluminescence (TL) glow curve analysis of the $\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$ -doped phosphor manufactured here revealed a wide TL centred at 225 °C, which comprised of so many peaks that may be extracted by the computerised glow curve deconvolution (CGCD) approach using glow-fit software. The associated kinetic parameters were then determined. The prepared phosphor may be useful for application in various display devices upon excitation by 247 nm; the prominent 613 nm peak of the Eu^{3+} ion ($^5\text{D}_0 \rightarrow ^7\text{F}_2$) electric dipole transition features a red component. $\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$ phosphors show promise as materials for potential use in phosphor-converted white LEDs in the field of solid-state lighting technology. The linear connection that the TL glow curve has with UV dose provides evidence for its possible use in dosimetry.

Received 14th May 2023
Accepted 4th August 2023

DOI: 10.1039/d3ra03200k

rsc.li/rsc-advances

1. Introduction

Phosphorescence, also known as persistent luminescence (PersL) or long-lasting afterglow, refers to a fascinating occurrence of light emission that persists for several minutes or even hours after the cessation of the initial light excitation, whether it be from UV or visible sources.¹ Long persistent phosphors (LPPs) continue to provoke researchers' curiosity due to their unexplained optical nature and broad applicability. LPPs have found diverse applications in specialised technical fields, such as road signs, decoration, emergency lighting, security displays,

radiation detection, information storage, and imaging displays. These applications have seen increased the utilization of LPPs in recent decades.^{2–5} Materials that can store energy in this way also go by the name of electron/hole traps.^{6–9} High-energy radiation (e.g., gamma rays, X-rays, or ultraviolet light) creates either electrons or holes, which are then trapped by lattice defects or impurities. After absorbing phonons or infrared photons,^{10–14} the bound electrons/holes are slowly freed. Understanding the presence and distribution of these traps presents a significant challenge. It has not been determined yet how charge carriers go from emission centres to traps.^{3,15} Lattice imperfections are not just trap centres, but may also act as emission sources.

P. Tadge *et al.* studied the downshifting, frequency up-conversion, and intrinsic optical bi-stability in $\text{CaY}_2\text{O}_4:\text{Ho}^{3+}/\text{Yb}^{3+}$ and $\text{CaSc}_2\text{O}_4:\text{Ho}^{3+}/\text{Yb}^{3+}$ phosphors that were synthesised by a complex-based precursor solution method. The X-ray powder diffraction confirmed the formation of highly crystalline phosphors with a pure orthorhombic phase. Fourier transform infrared studies showed vibrational bands and diffuse reflectance spectra. The $\text{Ho}^{3+}/\text{Yb}^{3+}$ co-doped CaSc_2O_4

^aDepartment of Physics, Government Vishwanath Yadav Tamaskar Post Graduate Autonomous College, Durg, C.G., India

^bDepartment of Physics, North Eastern Hill University (NEHU), Shillong, Meghalaya, 793022, India. E-mail: jsvikasdubey@gmail.com

^cInstitute of Optoelectronics, Military University of Technology, Kaliskiego 2, 00-908 Warsaw, Mazovia, Poland

^dDepartment of Sciences and Humanities, School of Engineering and Technology CHRIST (Deemed to be University), Bangalore, India

^eDepartment of Statistics, Institute of Science, Banaras Hindu University, Varanasi, 221005, India





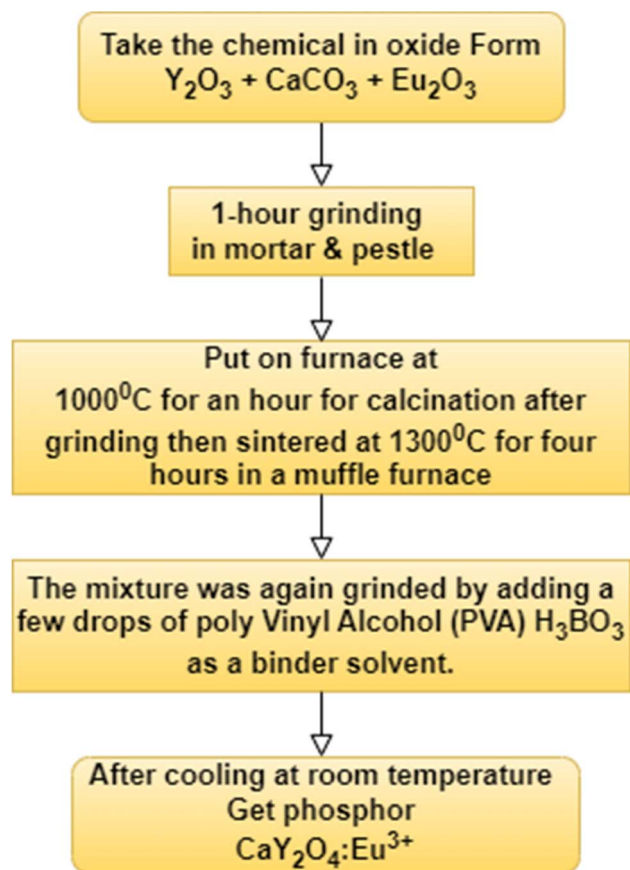
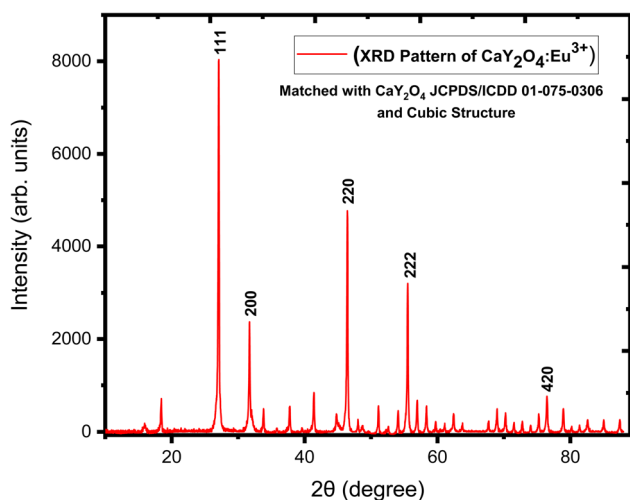


Fig. 1 Flow chart of sample preparation.

for (0.5–2.5 mol%) is shown in Fig. 2. At different values of 27.077, 31.715, 46.443, 55.526, and 76.488, five different peaks were obtained, which correspond to diffraction at the (111), (200), (220), (222), and (420) planes, respectively. In compliance with (JCPDS/ICDD 01-075-0306 & 00-019-0265), the spectrum indicates the predicted cubic structure crystalline process for

Fig. 2 XRD pattern of CaY₂O₄:Eu³⁺.Table 1 Calculation of crystallite size of CaY₂O₄:Eu³⁺ phosphor

<i>hkl</i>	Peak position (2θ)	FWHM	Crystallite size <i>D</i> (nm)	Average size <i>D</i> (nm)
111	27.07759	0.19309	42.32714752	43.113
200	31.7155	0.21663	38.1304235	
220	46.44312	0.19783	43.70569803	
222	55.52602	0.19785	45.38561618	
420	76.4881	0.21986	46.01642362	

the nanopowders. A simple Debye–Scherrer's formula was used to determine a crystallite size that was estimated at 43.113 nm because full width at half maximum (FWHM) of the intense peak; they were matched to the JCPDS card number 01-075-0306.²⁴

Scherrer's formula for the calculation of crystallite size is as follows:

$$D = \frac{0.9\lambda}{\beta \cos \theta}$$


In this context, the size of the crystallites is represented in this situation by the variable *D*. The FWHM is represented by the symbol β . The wavelength of the X-ray source is indicated by the symbol λ , while the diffraction angle is shown by the symbol θ . According to Table 1,

$$D = (0.9 \times 0.15409) / (\text{RADIANS}(0.19309) \times \text{COS}(\text{RADIANS}(27.07759)/2))$$

The average crystallite size is 43.113 nm.

3.2 Fourier transform-infrared spectroscopy (FTIR) analysis

The FTIR spectra of the Eu³⁺-doped CaY₂O₄ phosphor are shown in Fig. 3. It is observed that strong peaks occur at 415–447 cm^{−1} which are a characteristic of the Y–O vibrations.⁴⁰ The medium sharp peak at 704 cm^{−1} corresponds to the O–Y–O

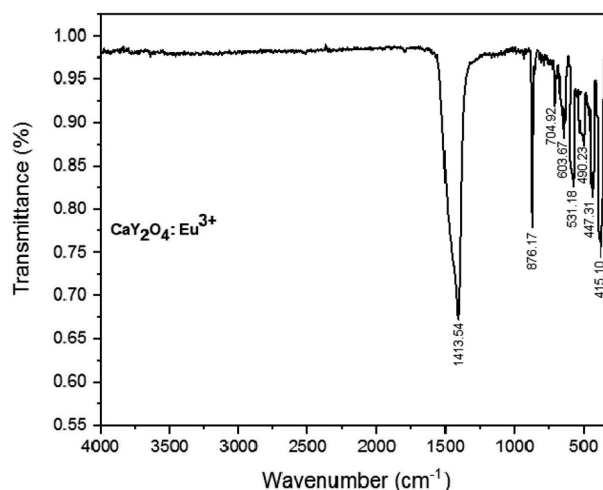Fig. 3 FTIR spectra of CaY₂O₄:Eu³⁺.

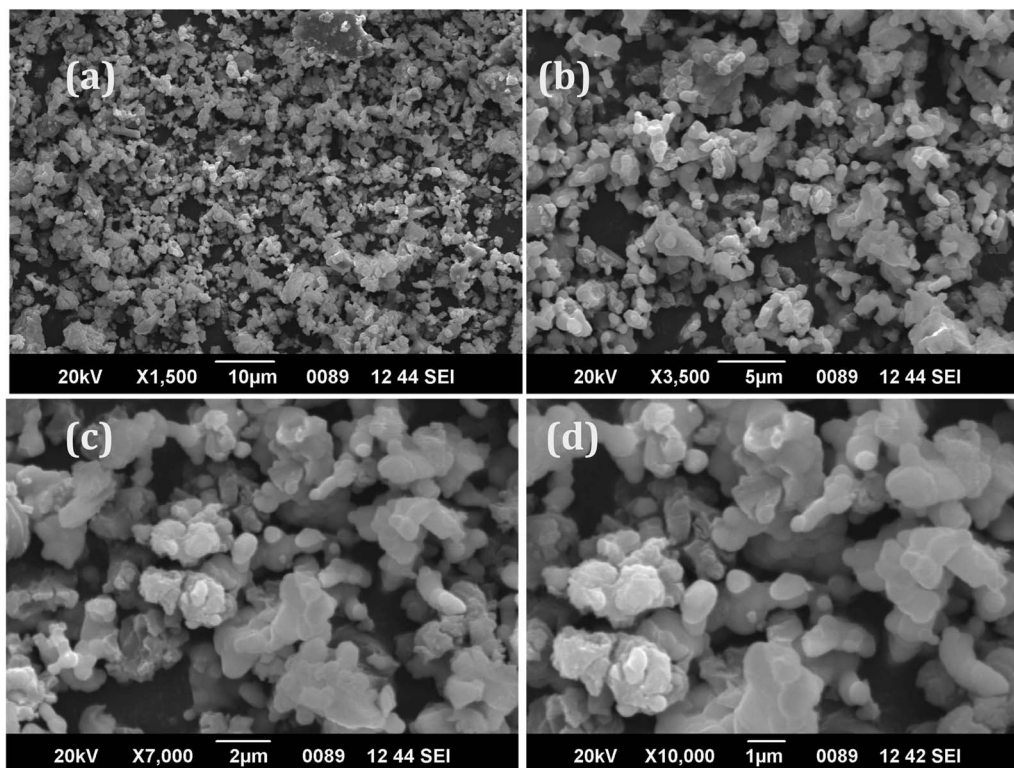


Fig. 4 (a–d) SEM images of phosphor CaY_2O_4 -doped with of Eu^{3+} (2.5 mol%) ion prepared here.

deformation bond owing to the enlargement in the lattice of CaY_2O_4 after calcination. It can be noted that in the presence of O–Y–O, there is a vibration peak at 603 cm^{-1} , Y–O vibration at 531 cm^{-1} , and a stretching vibration at 490 cm^{-1} .^{41,42} The sample showed a strong peak at 876 cm^{-1} , which was assigned to the formation of CaY_2O_4 .⁴²

3.3 SEM analysis

Fig. 4a–d show the SEM images collected under different resolutions of the Eu^{3+} (2.0 mol%)-doped CaY_2O_4 phosphor. From the images, the shape and size of the synthesised phosphors were studied. The diagram depicts a diverse morphology and noticeably large grain size.^{23,26} The powders exhibit an uneven surface structure, indicating a propensity for grain growth and agglomeration at elevated temperatures. The distribution of grain sizes was wide, ranging from approximately $1\text{ }\mu\text{m}$ to 100 nm , with an average size falling within this range. Phosphor materials were synthesised at very high temperatures, which led to the formation of aggregates. The efficacy of luminescence may be reduced due to aggregation, which causes considerable dispersion of light. To increase the quality of phosphors and make them appropriate for use in solid-state lighting, a lengthy ball milling process is required to break up the aggregates. Here, at different resolutions of $1500\text{--}10\,000\times$, the morphology of the phosphor exhibited a distinctive cubic structure, providing compelling evidence supporting the structural

analysis conducted on the synthesised phosphor using XRD analysis (Fig. 2).

3.4 Energy dispersive X-ray analysis (EDAX)

EDAX analysis can show the formation of elemental analysis in prepared phosphor. Fig. 5 shows an intense Ca (calcium) peak, an intense Y (yttrium) peak, and a peak from O (oxygen) with doping-ion Eu (europium), which confirmed that the phosphor was formed properly.

3.5 PL studies

The excitation and emission spectra of CaY_2O_4 phosphor doped with Eu^{3+} are depicted in Fig. 6a and b, which represent the oxide forms of inorganic elements. An excitation spectrum was observed at 613 nm , with a significant peak at 247 nm . Upon excitation, the phosphor emitted a broad range of wavelengths spanning from 535 to 631 nm , with notable high-intensity peaks at 613 and 631 nm resulting from energy transfers.

The excitation spectra of $\text{CaY}_2\text{O}_4\cdot\text{Eu}^{3+}$ phosphor were recorded by monitoring the $\text{Eu}^{3+}\text{ }^5\text{D}_0 \rightarrow ^7\text{F}_2$ transition at 613 nm . A large peak at 247 nm was seen in the excitation spectra, followed by another broad peak at 344 nm due to the $^7\text{F}_0 \rightarrow ^5\text{D}_4$ transition. The maximum absorption intensity was observed at these two wavelengths. The excitation spectra (shown in Fig. 6a) included a prominent wide band with a peak at 247 nm , which is attributed to the charge transfer band (CTB) between Eu^{3+}



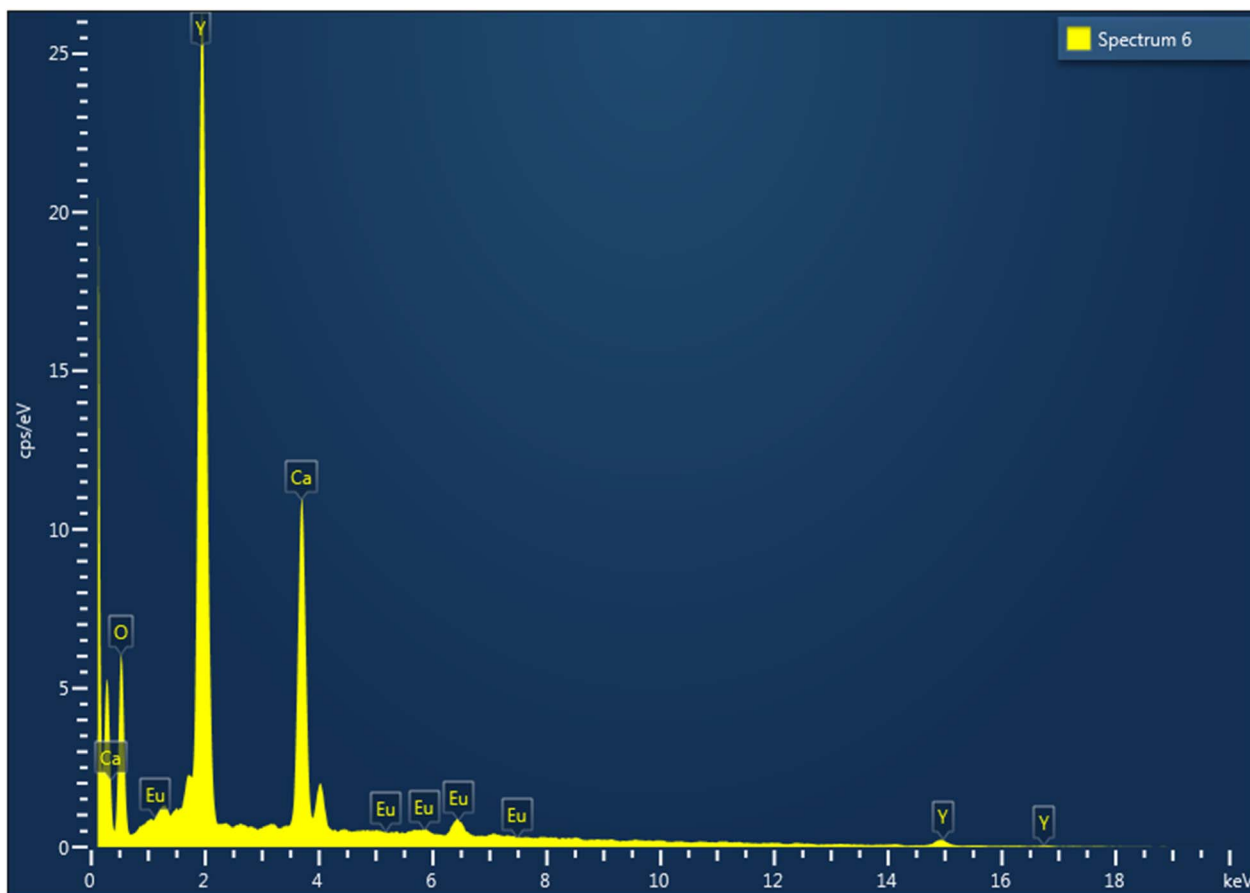


Fig. 5 EDAX analysis of the phosphor $\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$ prepared here.

and O^{2-} neighbouring ions. Lines owing to the f-f transitions in the $\text{Eu}^{3+} 4f^6$ arrangement were also seen at longer wavelengths.^{29,30}

The emission spectrum of the phosphor was measured by exciting them with 247 nm, and the results are depicted in Fig. 6b. The spectrum comprises $^5\text{D}_0 \rightarrow ^7\text{F}_j$ ($j = 1, 2$, and 3) emission lines of Eu^{3+} . When Eu^{3+} occupies a crystallographic position devoid of inversion symmetry, the red-forced electric-dipole transition $^5\text{D}_0 \rightarrow ^7\text{F}_2$ often dominates the emission spectrum. On the other hand, if the Eu^{3+} site has an inversion centre, the $^5\text{D}_0 \rightarrow ^7\text{F}_1$ orange emission dominates.³¹ The transitions from excited $^5\text{D}_0$ to the $^7\text{F}_j$ ($j = 0-3$) levels of Eu^{3+} ions produce distinctive emission lines within the 535–650 nm range. The placement of the Eu^{3+} ion in the CaY_2O_4 lattice, in combination with the selection criteria, determines the kind of transition from the emission levels to the terminating levels.^{32,33,36–39}

The prominent peak at 613 nm is due to the electric dipole (ED) transition between the $^5\text{D}_0$ and $^7\text{F}_2$ levels, whereas the faint emission at 593 nm is due to a forced magnetic dipole (MD) transition process. The emission spectrum of the $\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$ sample displays peaks ranging from 535–650 nm, which arise from the $^5\text{D}_0 \rightarrow ^7\text{F}_j$ ($j = 1, 2$) transitions of Eu^{3+} ions upon excitation at 247 nm. The 535 nm, 613 nm, and 631 nm

peaks are attributed to the ED transition of $^5\text{D}_0 \rightarrow ^7\text{F}_1$ and ($^5\text{D}_0 \rightarrow ^7\text{F}_2$), respectively, with the 613 nm peak having twice the intensity of the 593 nm peak. The ratio of the 593 nm peak intensity to the 613 and 631 nm peaks is half, which differs from previous research findings. This suggests that the Eu^{3+} ions are located at a site with low symmetry in the CaY_2O_4 host, as the MD transition has a lower intensity than the ED transition. However, at a concentration of 2.0 mol% of Eu^{3+} , concentration quenching occurs as a consequence of energy transfer between Eu^{3+} ions, and the peak locations of the emission spectra alter. Therefore, the $\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$ (2.0 mol%) phosphor could be a promising candidate for use in compact fluorescent lamps (CFLs) with excitation at 247 nm.

3.6 CIE coordinate

The peaks determined in spectrophotometry are put to the test by the CIE (Fig. 6c). Using a spectrophotometric technique and the spectrum energy distribution of the $\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$ sample, the CIE coordinates were calculated (Fig. 6). The Eu^{3+} -doped sample has the colour coordinates of $x = 0.5169$ and $y = 0.4782$, which are near the orange-red spectrum of visible light. In accordance with the recommendations of the International Commission on Illumination (1931), a cross has been placed in the relevant area in Fig. 6c.^{27,28,34}

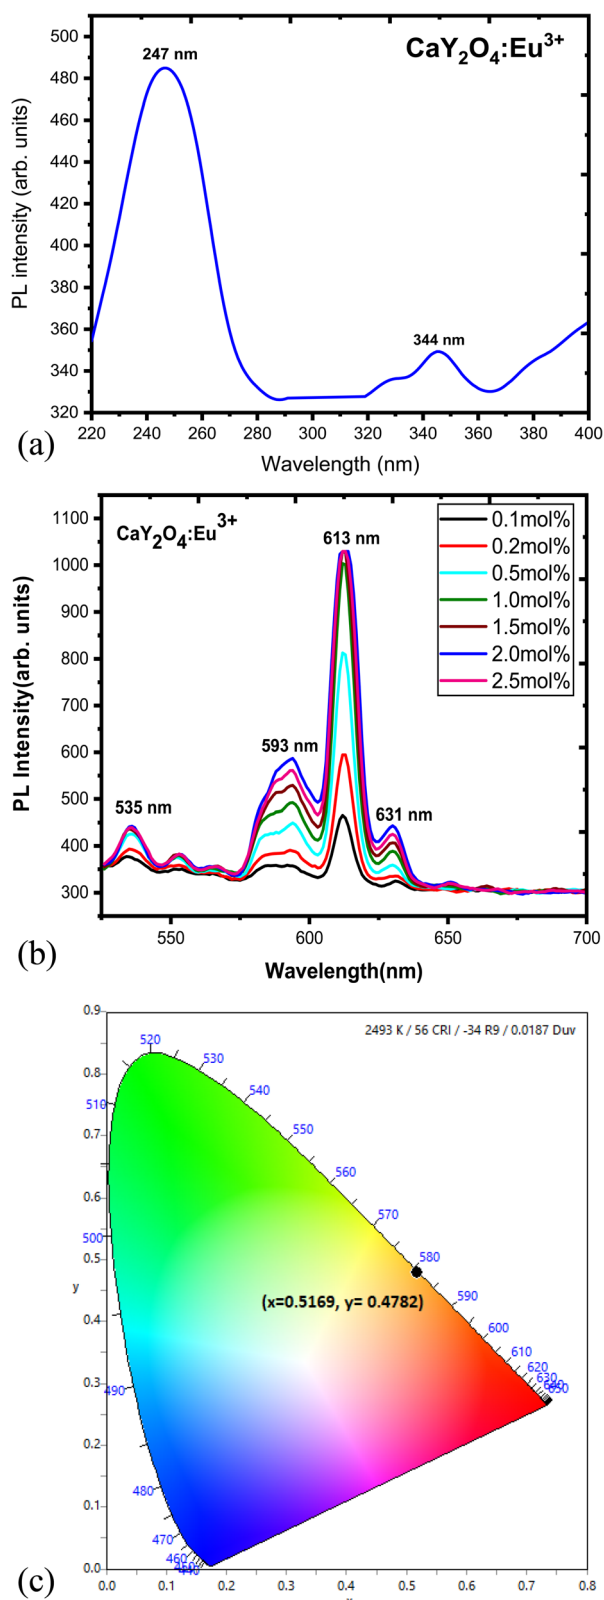


Fig. 6 (a) PL excitation spectra of $\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$ at 2.0 mol%. (b) PL emission curve of $\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$ for (0.1–2.5) mol%. (c) Commission Internationale de l'Eclairage (CIE 1931) of $\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$ for 2.5 mol% ($x = 0.5169$, $y = 0.4782$).

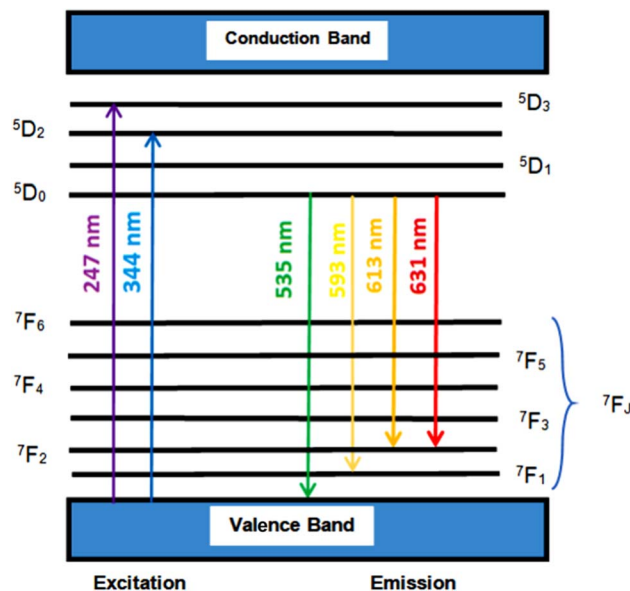


Fig. 7 Energy level diagram of $\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$.

Fig. 7 shows the energy-level diagram of the Eu^{3+} ion in terms of the ED transition peak at 613 nm ($5\text{D}_0 \rightarrow 7\text{F}_2$) and the dominant MD transition peak at 593 nm ($5\text{D}_0 \rightarrow 7\text{F}_1$).

4. TL glow curve analysis

The TL glow curve of the $\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$ phosphor illustrates a linear response to UV treatment at a constant heating rate of 6.7°C s^{-1} (Fig. 8). A good TL dosimeter peak can be seen at 225°C as the TL intensity increases with UV exposure time (Fig. 8). This curve can be successfully theoretically and experimentally fitted using the CGCD method.

Fig. 8 presents a distinct and wide TL glow curve with its peak centred at 225°C . The intensity of the TL glow curve

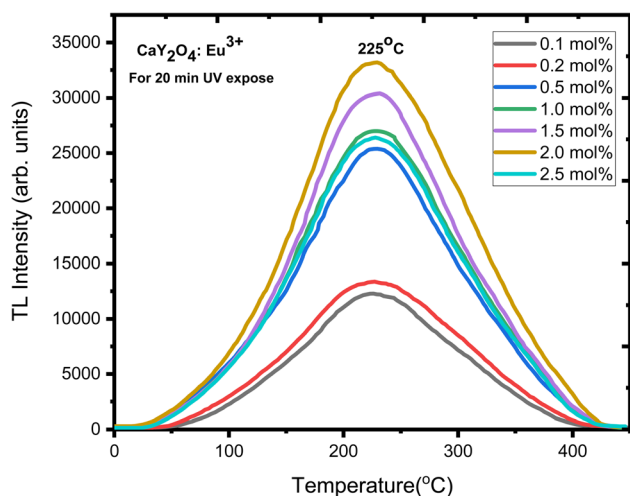


Fig. 8 TL glow curve analysis of $\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$.

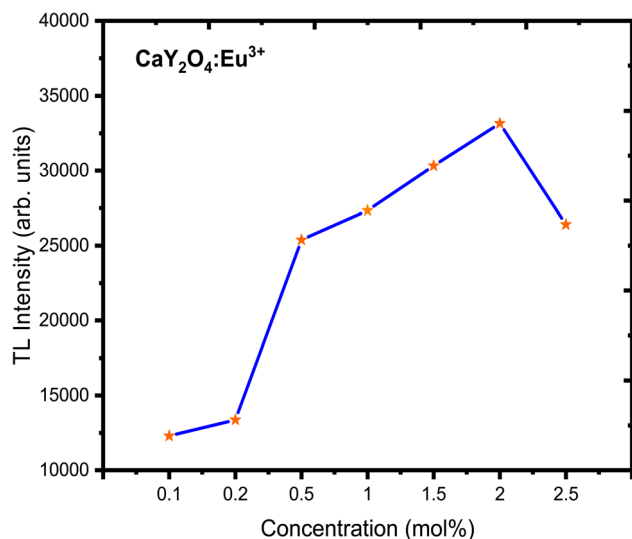


Fig. 9 $\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$ concentration vs. intensity.

demonstrates an upward trend as the concentration of doping ions increases, reaching its highest point at 2 mol%. Concentration quenching caused a loss of intensity after going over the highest point. This particular TL glow curve was obtained after a 20 minute exposure to UV radiation and is considered suitable for dosimetry applications. The concentration *versus* intensity plot is shown in Fig. 9 for better understanding.

As well-resolved broad TL glow curve was monitored in the dose *versus* intensity plot with various UV doses and 5–25 min UV exposure time (Fig. 10). Here, the intensity of the glow curve was measured at a fixed (optimised) concentration of 2.0 mol% of doping ion; it increased with increasing UV radiation exposure (Fig. 11). The well-resolved peak showed good linearity with the dose which showed the prepared phosphor could be useful for dosimetric applications.

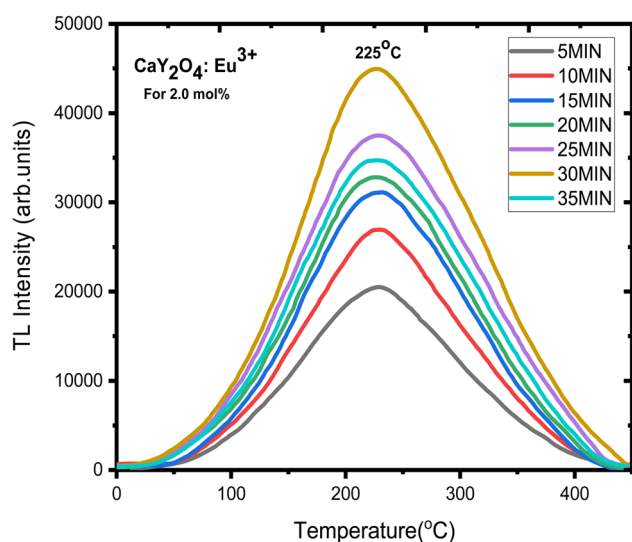


Fig. 10 TL glow curve analysis of $\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$ for 2.0 mol%.

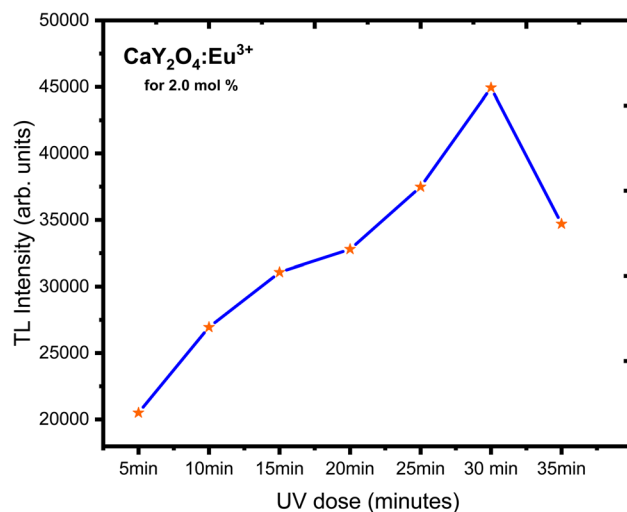


Fig. 11 $\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$ phosphor TL glow curve dose vs. intensity plot.

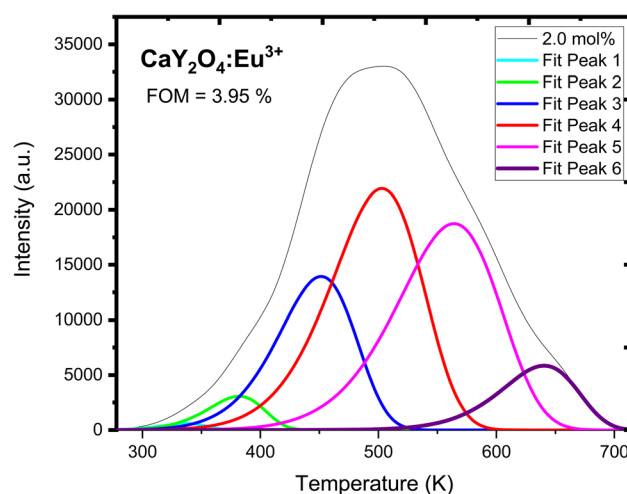


Fig. 12 CGCD of UV-induced $\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$ -doped phosphor for optimised UV dose and 2.0 mol% concentration.

CGCD-fitted TL glow curves of $\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$ phosphor (Fig. 12) that were exposed to UV radiation for 20 minutes are shown in Fig. 10. Table 2 displays a variety of trapping characteristics, including activation energy, order of kinetics, and frequency factors. After being exposed to UV light, the prepared sample's trap depth decreased from 0.5 to 1.0412 eV as shown by the fit, suggesting the creation of shallower traps. Irradiation by the UV rays from a lower energy source would have resulted in the formation of shallow trap levels, where electrons need less energy to tunnel through the barrier and recombine; hence, activation energy is lower for UV-irradiated samples. Fig. 12 shows the CGCD pattern of the optimised concentration (2 mol%) of the dopant with 25 min of UV exposure time; this pattern was composed of five distinct peaks, and Table 2 shows the calculated trap parameters of the CGCD pattern (a value of merit is 1.09%). It shows that the first order of kinetic and activation energies vary from 0.5 to 1.0412 eV, and the frequency

Table 2 Calculation of the kinetic parameters using the CGCD programme for UV-induced $\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$ -doped phosphor

T_1 (K)	T_m (K)	T_2 (K)	τ	δ	ω	$\mu = \delta/\omega$	Activation energy (eV)	Frequency factor (s^{-1})
311	338	359	27	21	48	0.4375	0.5	2.18×10^8
350	382	406	32	24	56	0.4285714	0.5001	2.14×10^8
406	452	485	46	33	79	0.4177215	0.5002	2.08×10^8
452	503	543	51	40	91	0.4395604	0.5275	2.31×10^8
505	564	608	59	44	103	0.4271845	0.5902	2.52×10^8
597	640	673	43	33	76	0.4342105	1.0412	4.52×10^8

factor values are very high, *i.e.*, $4.52 \times 10^8 \text{ s}^{-1}$ for the second fitted peak.

5. Conclusion

$\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$ is a newly synthesised phosphor; the XRD analysis confirmed the existence of a single cubic crystalline phase with nanocrystalline behaviour. The surface morphology of the prepared phosphors was fine with a cube-like shape. Some vibration modes of Y–O, Ca–O, and Eu–O were observed in the FTIR spectra. Broad excitation for photoluminescence may be shown in the spectra with maxima at 247 and 344 nm. In the 247 nm-excited emission spectra, peaks at 535 nm, 593 nm, 613 nm, and 631 nm could be seen clearly, and the emission peaks were found to have corresponding transitions at 535 nm ($^5\text{D}_0 \rightarrow ^7\text{F}_0$) and 593 nm ($^5\text{D}_0 \rightarrow ^7\text{F}_1$), where the strongest peak was observed at 613 nm ($^5\text{D}_0 \rightarrow ^7\text{F}_2$) and 631 nm ($^5\text{D}_0 \rightarrow ^7\text{F}_2$). As a result, the phosphor exhibits remarkable colour constancy throughout its emission of light in the orange-to-red spectrum. The TL glow curve showed that the intensity of thermoluminescence increases with increasing UV exposure time and peaks at 225 °C, showing a good TL dosimeter peak. The kinetic parameters that were calculated for $\text{CaY}_2\text{O}_4:\text{Eu}^{3+}$ phosphor by the CGCD technique were fitted using the CGCD technique, which resulted in a successful theoretical and experimental fit¹⁶ (Table 2).

Conflicts of interest

There are no conflicts to declare.

References

- 1 F. Clabau, X. Rocquefelte, S. Jobic, M. H. Whangbo, *et al.*, *Chem. Mater.*, 2005, **17**(15), 3904–3912.
- 2 Y. Li, M. Gecevicius and J. Qiu, *Chem. Soc. Rev.*, 2016, **45**(8), 2090–2136.
- 3 Y. Liu, B. Lei and C. Shi, *Chem. Mater.*, 2005, **17**(8), 2108–2113.
- 4 B. Liu, C. Shi and Z. Qi, *Appl. Phys. Lett.*, 2005, **86**(19), 191111.
- 5 J. Zhong, J. Chen, Q. Yang, C. Hu, J. Li and R. Duan, *Appl. Phys. A: Mater. Sci. Process.*, 2018, 124.
- 6 F. Clabau, X. Rocquefelte, T. Le Mercier, P. Deniard, S. Jobic and M. H. Whangbo, *Chem. Mater.*, 2006, **18**(14), 3212–3220.
- 7 D. Jia and W. M. Yen, *J. Lumin.*, 2003, **101**(1), 115–121.
- 8 J. Kuang, Y. Liu and J. Zhang, *J. Solid State Chem.*, 2006, **179**(1), 266–269.
- 9 J. Qiu and K. Hirao, *Solid State Commun.*, 1998, **106**(12), 795–798.
- 10 B. Zhang, X. Yu, T. Wang, S. Cheng, J. Qiu and X. Xu, *J. Am. Ceram. Soc.*, 2015, **98**(1), 171–177.
- 11 F. Liu, W. Yan, Y.-J. Chuang, Z. Zhen, J. Xie and Z. Pan, *Sci. Rep.*, 2013, **3**, 1554.
- 12 A. S. Pradhan and R. C. Bhatt, *Phys. Status Solidi A*, 1981, **68**(2), 405–411.
- 13 Y. Liu, J. Kuang, B. Lei and C. Shi, *J. Mater. Chem.*, 2005, **15**(37), 4025–4031.
- 14 K. Van den Eeckhout, P. F. Smet and D. Poelman, *Materials*, 2010, **3**(4), 2536–2566.
- 15 T. Wang, J. Gou, X. Xu, D. Zhou, J. Qiu and X. Yu, *Opt. Express*, 2015, **23**(10), 12595–12604.
- 16 Y. Parganiha, J. Kaur, V. Dubey and K. V. R. Murthy, *Mater. Sci. Semicond. Process.*, 2015, **31**, 715–719.
- 17 V. Dubey, J. Kaur, S. Agrawal, N. S. Suryanarayana and K. V. R. Murthy, *Superlattices Microstruct.*, 2014, **67**, 156–171.
- 18 P. Tadge, I. R. Martín, S. B. Rai, S. Sapra, T. M. Chen, V. Lavín, R. S. Yadav and S. Ray, *J. Lumin.*, 2022, **252**, 119261.
- 19 Y. S. Jeon, S. Hwangbo and K. S. Hwang, *J. Nanosci. Nanotechnol.*, 2019, **19**(3), 1709–1713.
- 20 K. S. Hwang, Y. S. Jeon, S. Hwangbo and J. T. Kim, *J. Nanosci. Nanotechnol.*, 2019, **19**(4), 2431–2434.
- 21 A. R. Krasnaya, B. M. Nosenko, L. S. Revzin and V. Y. Yaskolko, *Sov. Atom. Energy*, 1962, **10**, 625–626.
- 22 B. E. Bjärngard, J.-S. Tsai, R. K. Rice and B. E. Bjärngard, *Radiat. Res.*, 1989, **118**, 195.
- 23 T. Yamashita, N. Nada, H. Onishi and S. Kitamura, *Health Phys.*, 1971, **21**, 295–300.
- 24 R. Tamrakar, D. Bisen, K. Upadhyay and N. Bramhe, *Superlattices Microstruct.*, 2015, **81**, 34–48.
- 25 S. Ghorpade, R. Hari Krishna, R. Melavanki, V. Dubey and N. Patil, *Optik*, 2020, **208**, 164533.
- 26 J. Kaur, Y. Parganiha, V. Dubey, D. Singh and D. Chandrakar, *Superlattices Microstruct.*, 2014, **73**, 38–53.
- 27 V. Dubey and N. S. Suryanarayana, *J. Miner. Mater. Charact. Eng.*, 2010, **9**(12), 1101–1111.
- 28 V. Dubey, J. Kaur, N. S. Suryanarayana and K. V. R. Murthy, *Res. Chem. Intermed.*, 2013, **39**, 3689–3697.
- 29 G. R. Dillip, S. J. Dhoble, L. Manoj, C. M. Reddy and B. D. Raju, *J. Lumin.*, 2012, **132**, 3072.



- 30 K. N. Shinde, S. J. Dhoble and A. Kumar, *J. Rare Earths*, 2011, **29**, 527.
- 31 K. G. Lee, B.-Y. Yu, C.-H. Pyun and S.-I. Mho, *Solid State Commun.*, 2002, **122**, 485–488.
- 32 V. Dubey, J. Kaur, S. Agrawal, N. S. Suryanarayana and K. V. R. Murthy, *Superlattices Microstruct.*, 2014, **67**, 156–171.
- 33 M. R. Rao, *et al.*, PL Studies of Eu Doped YPO₄ Phosphor, *Proc. of NCAPMS*, 2013, pp. 212–213.
- 34 A. N. Yerpude and S. J. Dhoble, Luminescence Properties and Concentration Quenching of Sr₅SiO₄Cl₆:Eu³⁺ Phosphor, *Proc. of NCAPMS*, 2013, pp. 157–159.
- 35 S. Shigeo and M. William, *Phosphor Handbook*, CRC Press, Washington, D.C., 1998.
- 36 S. Lu and J. Zhang, *J. Lumin.*, 2007, **122–123**, 500–502.
- 37 P. A. M. Berdowski, J. VanKeulen and G. Blasse, *J. Solid State Chem.*, 1986, **63**, 86.
- 38 X. Zhang and H. J. Seo, *J. Alloys Compd.*, 2010, **503**, L14.
- 39 V. Dubey, J. Kaur and S. Agrawal, *Mater. Sci. Semicond. Process.*, 2015, **31**, 27–37.
- 40 P. Apte, H. Burke and H. Pickup, Synthesis of yttrium aluminum garnet by reverse strike precipitation, *J. Mater. Res.*, 1992, **7**, 706–711.
- 41 M. Maheshwary, B. P. Singh and R. A. Singh, *New J. Chem.*, 2015, **39**, 4494–4507.
- 42 M. Chroma, J. Pinkas, I. Pakutinskiene, A. Beganskiene and A. Kareiva, *Ceram. Int.*, 2005, **31**, 1123–1130.

