



Cite this: *Soft Matter*, 2023, 19, 1109

Microphase separation assisted reduction in the percolation threshold of MWCNT/block polymer composites†

Gokhan Topcu,^a David Reinoso Arenas,^b Tony McNally^b and C. Remzi Becer^a

Block copolymers continue to attract a great deal of interest since they allow the formation of microphase-separated domains, useful for nanopatterning/templating. Herein, we present the drastic effect of microphase separation of a diblock copolymer on the electrical properties of polymer nanocomposites. Microphase-separated poly(styrene-*b*-2-ethylhexyl acrylate) (P(St-*b*-EHA)) block copolymers having different block lengths were synthesized and utilized as templates for multi-walled carbon nanotubes (MWCNTs). The percolation threshold of the films decreased from 0.46 to 0.19 vol% with decreasing styrene phase fraction. More importantly, we observed a non-linear and unique reduction in percolation threshold with transforming the phase into lamellar structures.

Received 20th September 2022,
Accepted 4th January 2023

DOI: 10.1039/d2sm01277d

rsc.li/soft-matter-journal

Introduction

The incorporation of carbon nanotubes (CNTs) in polymeric materials to obtain enhanced electrical properties has been of significant interest from both the fundamental and engineering points of view for the last couple of decades. The improvement in electrical performance of the composites makes them potential candidates for various applications in the area of electronics, such as dielectrics for charge-storage capacitors,¹ antistatic materials,² electromagnetic shielding,³ piezoresistive sensors,⁴ and shape-memory polymer (SMP) materials.^{5,6} Nanocomposites of polymers and CNTs exhibit a sharp increase in their electrical conductivity with increasing nanofiller content above a percolation threshold that is described as a critical value to form an interconnected touching conductive network in 3D space.

Additionally, the insulator-conductor transition of polymers by the incorporation of CNTs can be achieved at a low percolation threshold depending on the degree of CNT alignment and uniform spatial distribution of individual CNTs. Nevertheless, MWCNTs tend to form agglomerates and bundles in either liquid or solid media due to high electron delocalization induced by van der Waals interactions between nanotubes.

Therefore, the vast majority of the studies have focused on reducing the percolation threshold *via* advanced chemical and manufacturing approaches.^{7,8} To eliminate CNT agglomeration, surface modification has been widely studied and can be grouped into two categories: covalent bonding of functional groups,^{9,10} non-covalent wrapping, or adsorption of mediating molecules onto the CNT surfaces.^{11–13} Covalent functionalization such as with acid treatment, esterification, or amidation reactions facilitates the separation of nanotube bundles into individual tubes or smaller bundles. However, the translational symmetry of the CNTs is disrupted by changing the hybridization of carbon atoms from sp^2 to sp^3 , which leads to an interruption in electronic and transport properties. In contrast, the non-covalent functionalization approaches typically use π - π interactions to homogenize CNTs without creating defect sites on the CNT surface. Further approaches in attempts to achieve homogeneous CNT spatial distribution, such as double percolation, have been widely reported to reduce the percolation threshold by taking advantage of selective localization of CNTs in multi-component immiscible polymer systems.¹⁴ Compared to the homogenous distribution of CNTs in a single medium, this approach leads to two respective scenarios requiring co-continuous polymer morphologies; (i) the localization of fillers directly at the interface and (ii) the selective filling of only one of the phases. Even though the former case may be a theoretical ideal state to reach the lowest possible percolation threshold, to date it has been difficult to achieve due to the very high aspect ratio of CNTs. Therefore, the latter scenario is considered more practical to govern particle distribution. In this sense, the double percolation concept has been extensively implemented

^a Department of Chemistry, University of Warwick, Coventry, CV4 7AL, UK.

E-mail: Gokhan.Topcu@warwick.ac.uk, gt162@leicester.ac.uk

^b International Institute for Nanocomposites Manufacturing (IINM), WMG, University of Warwick, Coventry, CV4 7AL, UK

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d2sm01277d>



for a wide variety of polymer systems including physical blends or block copolymers which enables the formation of conductive pathways with significantly reduced CNT content within the continuous phase.^{15–19} To tailor composite morphology, the utilisation of melt mixing and application of shear forces has been effectively adopted.^{14,20,21}

Block copolymers offer remarkable high-ordered architectures with readily designed chemical structures; therefore, they are good candidates for templating CNTs. Upon appropriate conditions, polymer chains spontaneously self-assemble to form nanostructures in various geometry. From this perspective, the self-organization properties enable a possible route to the elimination of additional processing methods due to fabrication being relatively easy and reproducible. The thermodynamic driving force leading to the separation of the two (or more) chemically discrete blocks is the main reason for self-assembly on the nanoscale. The geometry, size, and symmetry of the structure are highly governed by the volume fraction of blocks, overall degree of polymerization, and incompatibility of the constituent monomers (Flory–Huggins parameter, χ). Recently, several studies of CNTs with block copolymer composites were reported, which examine the dispersion of CNTs and the electrical properties of composites.^{22–25} Staudinger *et al.* reported styrene–butadiene–styrene (SBS) triblock copolymer and MWCNT composites.²² They stated that shortened MWCNTs are more easily to be localised in one phase/interface but also tend to aggregate easier. Tzounis *et al.* showed that the CNTs can be aligned through the phase separation of SBS by applied shear force.²⁴ On the other hand, Santos *et al.* presented MWCNT/SBS composites showing enhanced conductivity with a concentration of 0.1 vol%, which indicates block copolymers may enhance the percolation threshold.²⁵ Nevertheless, the vast majority of recent studies only rely on the composites based on SBS, which are restricted in terms of phase control due to constant block fractions. A systematic investigation of block copolymers to enhance the electrical properties of CNT composites by controlling morphology hasn't been attempted. Therefore, to further examine this electrical improvement, control over the microphase of block copolymers by using a precise chemical toolbox (*i.e.* controlled living radical polymerisation) is crucial which leads to the design of new types of polymers having better performance.

In this study, we enable a decrease in percolation threshold and a slight increase in electrical conductivity by controlling the microphase of diblock copolymers from one to another. As a template, P(St-*b*-EHA) diblock copolymers were synthesized in various block fractions to control MWCNT percolation. By tailoring the volume fraction and dimensions of the continuous phase, we examine the change in morphology from spherical to lamellar and AC conductivity of the nanocomposite. Our work suggests a generalizable strategy to improve the electrical properties of composites of block copolymers and CNTs having microphase separation and selective localization, thus, it may guide the way for the effective use of CNTs at optimum levels.

Experimental

Materials

Styrene (97%, Acros Organics) and 2-ethylhexyl acrylate (98%, Sigma-Aldrich) were purchased and purified by passing through basic aluminium oxide before usage as a monomer. BlocBuilder MA (Nitroxide initiator, Arkema) was supplied and used as received. All solvents including toluene, methanol, acetone, and chloroform used were in analytical grade. The MWCNTs (>98% carbon basis, Sigma-Aldrich, O.D. \times L 6–13 nm \times 2.5–20 μ m) were used as a dispersion in chloroform. Before use, the conductive nanotubes were vigorously dispersed in an ultrasonic bath for 4 h.

Synthesis of polystyrene macroinitiator

Polystyrene (PSt) macroinitiator (MI) was synthesized using NMP in an oil bath. Monomer (10 mmol), initiator (0.2 mmol), and toluene (2 ml) were mixed and loaded into a glass reactor. The mixture was degassed under nitrogen for 30 min. The reaction was maintained at 110 °C for various time scales for kinetic studies in different batches, and each was stopped at different time intervals. To use as MI, the reaction was stopped after 150 min to have more active radical end-groups that correspond to approximately 50% conversion according to kinetic studies. The reaction mixture was precipitated in cold methanol, dried under vacuum at room temperature for 8 h, and stored in a freezer.

Synthesis of P(St-*b*-EHA) copolymers

The molar concentration of EHA is varied between 25 to 200 equivalent to MI. The monomer from (0.13 ml to 1 ml), MI (200 mg), and toluene (2 ml) were mixed and degassed under nitrogen for 30 min. Subsequently, the reaction was conducted at 110 °C in an oil bath for 4 h. All reaction mixtures were cooled down to end the reaction. The polymers were precipitated in excess cold methanol, filtered, and dried at 40 °C under a vacuum overnight.

Preparation of composite films

All synthesized block copolymers (BCPs) were prepared as a solution (in chloroform, 20%) to fabricate as a film by using a spin coater. The desired concentration of MWCNTs in the composites was calculated and the MWCNT dispersion was diluted with chloroform to mix with the BCPs. The mixture was sonicated for 4 h to obtain surface-modified nanotubes. The surface cleaning procedure is as follows: placing an ultrasonic bath in a detergent solution for 15 min, rinsing with deionized water, washing with acetone, and finally drying under nitrogen. An aliquot of the polymer solution was either spun cast (250 μ l, 1000 rpm, 1 min) or drop-cast (1 ml) onto glass slides. Afterwards, thin films were dried in ambient conditions overnight and then annealed in a sealed chamber filled with solvent chloroform vapour for 2 days.



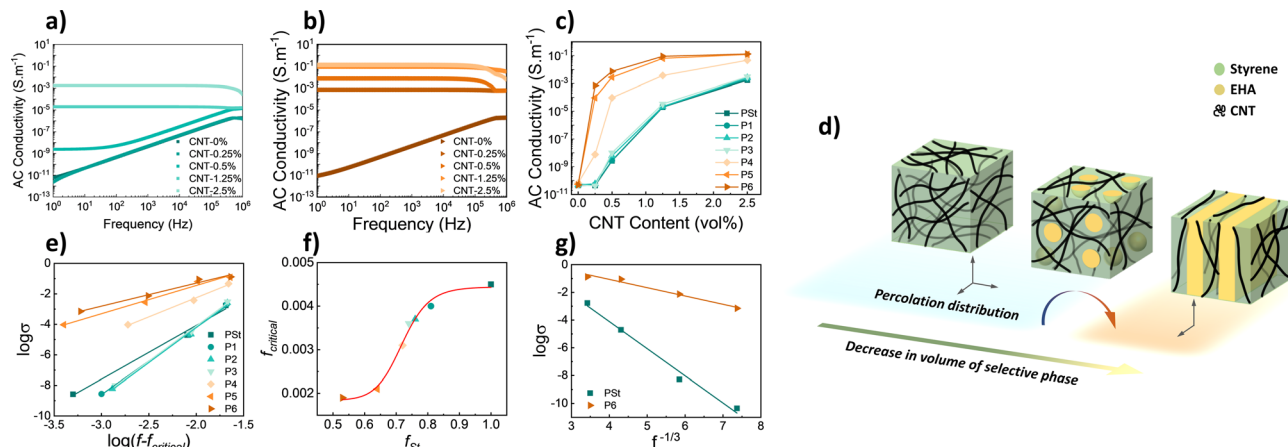


Fig. 3 AC conductivity of (a) PS/MWCNT and (b) P(St-*b*-EHA)/MWCNT (P6) composite films between 1 Hz–1 MHz, (c) conductivity at 10 Hz for composites as a function of CNT content. (d) Schematic representation of possible CNT particle distribution forming percolation with changing phase-type. (e) Logarithmic plot of conductivity versus reduced CNT content, (f) relation between percolation threshold (f_{critical}) and f_{St} , and (g) relation between conductivity per unit volume styrene.

interpretations and approaches were performed. The relation between the composite conductivity (σ), CNT conductivity (σ_{CNT}), and CNT volume fraction f_{CNT} can be given by a power law as below;

$$\sigma = \sigma_{\text{CNT}} (f_{\text{CNT}} - f_{\text{critical}})^t \quad (2)$$

here, the f_{critical} is the critical volume fraction, in other words, the percolation threshold, t is the critical exponent that depends on the electron transport mechanism. The logarithmic plot of σ versus $(f - f_{\text{critical}})$ has a linear correlation, from which the slope of the line is an estimate of the percolation threshold of each P(St-*b*-EHA)/MWCNT composite. In Fig. 3e, all data points are linearly fitted with $R^2 > 0.99$ for each data set. The calculated f_{critical} values are given as a function of f_{St} of block copolymers in Fig. 3f. The percolation threshold of the PSt homopolymer composites was found as 0.0046 (or 0.46 vol%), similar to CNT-filled many other polymers. The percolation threshold decreases to 0.0019 (or 0.19 vol%) while f_{St} reaches 0.53. With a double percolation strategy, a decrease in the volume of the continuous phase enables densification and controlled localisation of the CNTs that allows percolation at lower CNT content. More importantly, this correlation follows a significantly sigmoidal-like pattern instead of a linear one. In the beginning, the percolation threshold slightly decreases with decreasing f_{St} . With changing phase change to a lamellar structure, the decrease in percolation threshold becomes more prominent. This sharp decrease can be attributed to this change in block copolymer geometry that results in the preferential dispersion of the CNTs more unidirectionally in the conduction axis. Please note that a further decrease in f_{St} only slightly reduces the percolation threshold after reaching the lamellar phase. In order to validate the uniformity of the CNTs in both homopolymer and block copolymers, a plot of $\log \sigma$ versus $f_{\text{CNT}}^{-1/3}$ was constructed (Fig. 3g), which yielded R^2 : 0.9942 and 0.9776, respectively. This linearity confirms the applicability of the theory for selective localization since there

is a uniform dispersion of MWCNT in both cases. However, decreasing linearity as in P6 may hint that the CNTs in the composite are mildly selective to styrene and can also slightly involve the EHA phase.

Conclusions

In summary, P(St-*b*-EHA) copolymers were synthesized in various block length and their self-assembly characteristics were examined. The copolymers were used to obtain electrically conductive films by the inclusion of MWCNTs. By selectivity of styrene phase, MWCNTs were templated in microphase separation and their effect on electrical properties was studied. The distinct microphase separation properties of P(St-*b*-EHA) by changing the volume fraction of blocks were successfully visualized from disordered to ordered lamellar phase with decreasing styrene fraction. The AC conductivity measurement of P(St-*b*-EHA)/MWCNT composites showed that the phase separation results in higher conductivity values by using lower CNT content. Furthermore, the percolation threshold decreases with decreasing styrene fraction. This suggests selective localization of the CNTs in the continuous styrene phase, in other words, an increase of particles per unit styrene volume. Importantly and uniquely, the shape of block copolymer morphology has an additional effect on conductivity. The change in phase to a lamellar structure amplifies the conductivity of the composites as the CNTs are forced to align through-plane, *i.e.* throughout the percolation direction. Using microphase separation as a strategy, more useful carbon-filled polymer conductors may be possible for use in microelectronics.

Author contributions

G. Topcu – investigation, methodology, writing-original draft and conceptualization D. Reinoso Arenas – EIS measurements, editing manuscript T. McNally – review & editing manuscript



C. R. Becer – conceptualization, writing – review and editing, supervision.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

G. Topcu acknowledges the Scientific and Technological Research Council of Turkey (TUBITAK) for supporting the Postdoctoral Research Fellowship (2219) “No. 1059B191900073”.

Notes and references

- Z. Wang, M. Zhu, Z. Pei, Q. Xue, H. Li, Y. Huang and C. Zhi, *Mater. Sci. Eng., R*, 2020, **139**, 100520.
- R. Yadav, M. Tirumali, X. Wang, M. Naebe and B. Kandasubramanian, *Def. Technol.*, 2020, **16**, 107–118.
- S. N. Sultana, S. P. Pawar and U. Sundararaj, *Ind. Eng. Chem. Res.*, 2019, **58**, 11576–11584.
- K. Ke, P. Pötschke, S. Gao and B. Voit, *ACS Appl. Mater. Interfaces*, 2017, **9**, 5437–5446.
- M. Behl, M. Y. Razzaq and A. Lendlein, *Adv. Mater.*, 2010, **22**, 3388–3410.
- H. Meng and G. Li, *Polymer*, 2013, **54**, 2199–2221.
- V. D. Punetha, S. Rana, H. J. Yoo, A. Chaurasia, J. T. McLeskey Jr, M. S. Ramasamy, N. G. Sahoo and J. W. Cho, *Prog. Polym. Sci.*, 2017, **67**, 1–47.
- S. W. Kim, T. Kim, Y. S. Kim, H. S. Choi, H. J. Lim, S. J. Yang and C. R. Park, *Carbon*, 2012, **50**, 3–33.
- J. Chen, L. Yan, W. Song and D. Xu, *Composites, Part A*, 2018, **114**, 149–169.
- S. Banerjee, T. Hemraj-Benny and S. S. Wong, *Adv. Mater.*, 2005, **17**, 17–29.
- Y.-T. Liu, Z.-L. Zhang, W. Zhao, X.-M. Xie and X.-Y. Ye, *Carbon*, 2009, **47**, 1883–1885.
- Y.-T. Liu, W. Zhao, Z.-Y. Huang, Y.-F. Gao and X.-M. Xie, *Carbon*, 2006, **44**, 1613–1616.
- Z. Liu, S. M. Tabakman, Z. Chen and H. Dai, *Nat. Protoc.*, 2009, **4**, 1372–1381.
- X.-d. Qi, J.-h. Yang, N. Zhang, T. Huang, Z.-w. Zhou, I. Kühnert, P. Pötschke and Y. Wang, *Prog. Polym. Sci.*, 2021, **123**, 101471.
- X. Zhao, J. Zhao, J.-P. Cao, D. Wang, G.-H. Hu, F. Chen and Z.-M. Dang, *Mater. Des.*, 2014, **56**, 807–815.
- D. Wu, Y. Zhang, M. Zhang and W. Yu, *Biomacromolecules*, 2009, **10**, 417–424.
- F. Wode, L. Tzounis, M. Kirsten, M. Constantinou, P. Georgopoulos, S. Rangou, N. E. Zafeiropoulos, A. Avgeropoulos and M. Stamm, *Polymer*, 2012, **53**, 4438–4447.
- N. K. Shrivastava, S. Suin, S. Maiti and B. Khatua, *RSC Adv.*, 2014, **4**, 24584–24593.
- Q. Li, J. Sun, J. Wang, G.-X. Chen, F. Li and Y. Zhang, *RSC Adv.*, 2012, **2**, 6637–6644.
- A. Göldel, G. Kasaliwal and P. Pötschke, *Macromol. Rapid Commun.*, 2009, **30**, 423–429.
- J.-F. Gao, D.-X. Yan, B. Yuan, H.-D. Huang and Z.-M. Li, *Compos. Sci. Technol.*, 2010, **70**, 1973–1979.
- U. Staudinger, A. Janke, C. Steinbach, U. Reuter, M. Ganß and O. Voigt, *Polymers*, 2022, **14**, 2715.
- U. Staudinger, B. K. Satapathy and D. Jehnichen, *Polymers*, 2019, **11**, 1831.
- L. Tzounis, S. Pegel, N. E. Zafeiropoulos, A. Avgeropoulos, A. S. Paipetis and M. Stamm, *Polymer*, 2017, **131**, 1–9.
- J. P. Ferreira Santos, G. H. Franca Melo, A. M. Gonçalves, J. A. Eiras and R. E. Suman Bretas, *J. Appl. Polym. Sci.*, 2018, **135**, 46650.
- C. R. Becer, R. M. Paulus, R. Hoogenboom and U. S. Schubert, *J. Polym. Sci., Part A: Polym. Chem.*, 2006, **44**, 6202–6213.
- C. R. Becer, C. Haensch, S. Hoepfener and U. S. Schubert, *Small*, 2007, **3**, 220–225.
- S. H. Kim, M. J. Misner, T. Xu, M. Kimura and T. P. Russell, *Adv. Mater.*, 2004, **16**, 226–231.
- C. Jin, B. C. Olsen, E. J. Luber and J. M. Buriak, *Chem. Mater.*, 2017, **29**, 176–188.
- G. Topcu, D. R. Arenas, S. Huband, T. McNally and C. R. Becer, *J. Mater. Chem. C*, 2022, **10**, 9356–9363.
- F. S. Bates and G. H. Fredrickson, *Annu. Rev. Phys. Chem.*, 1990, **41**, 525–557.
- E. W. Cochran, C. J. Garcia-Cervera and G. H. Fredrickson, *Macromolecules*, 2006, **39**, 2449–2451.
- M. W. Matsen and M. Schick, *Phys. Rev. Lett.*, 1994, **72**, 2660.
- W. S. Loo, G. K. Sethi, A. A. Teran, M. D. Galluzzo, J. A. Maslyn, H. J. Oh, K. I. Mongcopa and N. P. Balsara, *Macromolecules*, 2019, **52**, 5590–5601.
- L. Leibler, *Macromolecules*, 1980, **13**, 1602–1617.
- W. Zha, C. D. Han, D. H. Lee, S. H. Han, J. K. Kim, J. H. Kang and C. Park, *Macromolecules*, 2007, **40**, 2109–2119.
- M. M. Arras, B. He and K. D. Jandt, *Polymer*, 2017, **127**, 15–27.

