



Cite this: *RSC Appl. Interfaces*, 2025, 2, 397

Uncovering interfacial electron transfer kinetics of WO₃ biophotoelectrodes for food waste treatment†

Chun Hong Mak,^{ace} Yong Peng,^{ae} Man Hin Chong,^a Jinhua Mou,^a Guohua Jia,^f Shella Permatasari Santoso,^g Wenxin Niu,^h Duu-Jong Lee,^{*c} Chang-Ping Yu,ⁱ Carol Sze Ki Lin^{id a} and Hsien-Yi Hsu^{id *abde}

An effective approach to enhance bioelectrochemical systems' performance involves leveraging semiconductors' light-harvesting capabilities alongside the catalytic properties of bacteria. Here, we demonstrate a food waste removal method using the integration of *Shewanella oneidensis* MR-1 with a tungsten(vi) oxide (WO₃) nanoplate photoanode in a solar-assisted microbial photoelectrochemical cell (S-MPEC) combined with silicon-based photovoltaics (SiPV). The S-MPEC integrates the technologies of bioelectrochemical cells with photoelectrochemical cells (PEC) to enhance the degradation of food waste. The bare WO₃ photoelectrode exhibits a photocurrent of 0.749 A m⁻² at 0.8 V under visible light, whereas the WO₃-MR-1 biophotoelectrode reveals a significantly higher photocurrent of 2.94 A m⁻². Under visible light exposure at an intensity of less than 100 mW cm⁻², the power densities of the WO₃ photoelectrode with and without MR-1 bacterial coating are 2.36 W m⁻² and 0.599 W m⁻², respectively. To further improve performance, the S-MPEC was connected with a SiPV. This combined system, PV-S-MPEC, achieved a power density of 21.99 W m⁻² and a chemical oxygen demand (COD) removal rate of 8167 mg L⁻¹ per day, demonstrating its effectiveness in degrading food waste hydrolysate. Additionally, the study of heterogeneous electron transfer kinetics indicated that the WO₃-MR-1 system exhibits more efficient diffusion coefficients and enhanced rate constants for reduction and oxidation reactions. These findings highlight the significant impact of photoexcited charge carriers on degradation performance in this complex hybrid electricigen system, underscoring its potential for developing S-MPECs for waste degradation. This study also demonstrates significant potential for reducing environmental impact through enhanced COD removal rates and energy-efficient waste processing, making it a viable solution for large-scale applications in urban waste management.

Received 15th August 2024,
Accepted 17th September 2024

DOI: 10.1039/d4lf00291a

rsc.li/RSCApplInter

^a School of Energy and Environment, City University of Hong Kong, Kowloon Tong, Hong Kong SAR. E-mail: sam.hyhsu@cityu.edu.hk

^b Department of Materials Science and Engineering, City University of Hong Kong, Kowloon Tong, Hong Kong SAR

^c Department of Mechanical Engineering, City University of Hong Kong, Kowloon Tong, Hong Kong SAR. E-mail: tuclee@cityu.edu.hk

^d Centre for Functional Photonics (CFP), City University of Hong Kong, Kowloon Tong, Hong Kong SAR

^e Shenzhen Research Institute of City University of Hong Kong, Shenzhen, 518057, China

^f Curtin Institute of Functional Molecules and Interfaces, School of Molecular and Life Sciences, Curtin University, GPO Box U1987, Perth, WA 6845, Australia

^g Department of Chemical Engineering, Faculty of Engineering, Widya Mandala Surabaya Catholic University, Kalijudan No. 37, Surabaya 60114, East Java, Indonesia

^h State Key Laboratory of Electroanalytical Chemistry, Changchun Institute of Applied Chemistry, Chinese Academy of Sciences, 5625 Renmin Street, Changchun, Jilin 130022, P. R. China

ⁱ Graduate Institute of Environmental Engineering, National Taiwan University, Taipei, 10617, Taiwan

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d4lf00291a>

1. Introduction

Biomass is a vital fuel source with numerous applications driven by advanced methods.^{1–5} Food waste, a significant component of biomass derived from human activities, constitutes a considerable portion of municipal solid waste.⁶ Currently, most food waste is managed through traditional methods such as landfilling, composting, and incineration. These practices can contaminate groundwater, attract pests, and emit toxic gases. Additionally, they are unsustainable and economically inefficient, as they do not fully utilize the valuable nutrients and energy stored in food waste. The microbial fuel cell (MFC) represents a promising anaerobic waste treatment technology that employs microorganisms as catalysts to generate electricity from various organic wastes, including domestic and industrial wastewater and excess sludge.^{7–12} MFCs can efficiently produce clean, direct electricity while simultaneously removing organic matter, offering a more sustainable and practical approach to waste management.

Tungsten(vi) oxide (WO_3) has been identified as a robust candidate for photoelectrodes.¹⁴ Recently, WO_3 has been utilized as a bioanode in MFCs due to its biocompatibility and enhanced conductivity, promoting improved adhesion and charge transfer between bacteria and the electrode material.¹⁵ However, an in-depth investigation of the heterogeneous electron transfer dynamics and the interaction between photoelectrode and bacteria remains largely unexplored. Our work extends these findings by employing WO_3 as a superior photoanode material. Our research confirms the synergistic effects observed in earlier studies and quantifies the increase in photocurrent and degradation rates, providing a clearer understanding of the kinetics involved. This study employs electrochemical methods to explore heterogeneous electron transfer and electrochemical redox activity. Furthermore, we explore the integration of this system using silicon-based photovoltaics (SiPV) with S-MPEC. This novel addition significantly enhances both the anodic electron transfer and the COD removal efficiency beyond the capabilities previously reported in the literature.¹⁶⁻²² This advancement offers a promising direction for scaling up bio-photoelectrochemical systems for practical waste management and renewable energy production applications. The findings from this research lay a solid foundation for developing highly efficient S-MPECs that generate electricity and simultaneously address wastewater treatment and solar fuel production.

2.1. Preparation of tungsten(vi) oxide (WO₃) photoelectrode

To complete the assembly of the photoelectrodes, titanium (Ti) wires were affixed to the FTO surfaces using silver glue to ensure electrical connectivity. The wires were then encapsulated with epoxy resin to protect the connections and dried on a hot plate at 65 °C for 30 minutes.

Photoluminescence (PL) spectra of the samples were recorded using a Shimadzu RF-5301 PC spectrometer equipped with a 390 nm long-pass filter. The samples were excited using an excitation wavelength of 375 nm. Additionally, time-resolved PL measurements were conducted using a time-correlated single photon counting setup from PicoQuant GmbH. For these measurements, the sample excitation was performed with a laser head delivering pulses shorter than 200 ps, with a fluence of approximately 30 nJ cm^{-2} , to study the photophysical dynamics of the samples.

Luria-Bertani (LB) (*i.e.*, 10 g NaCl, 5 g yeast extract, and 10 g tryptone in 1000 mL ultrapure water) was chosen as the

In the assembly of the S-MPEC, the as-prepared photoelectrode was positioned such that the WO_3 nanoplate faced inward toward the interior of the chamber. This orientation ensured optimal interaction between the electrode surface and the chamber's environment. The chamber was modified to maintain anaerobic conditions within the cell, which are crucial for accurately simulating specific environmental and biological processes. Two holes at the top of the S-MPEC, designed for inserting the counter and reference electrodes, were sealed with drilled stoppers. Additionally, an argon gas stream was continuously supplied to displace any oxygen present, preserving the anaerobic atmosphere. Cyclic voltammetry of S-MPEC was measured by a CHI660E electrochemical workstation.

2.7. Photoelectrochemical (PEC) measurements

All photoelectrochemical (PEC) measurements within the S-MPEC were conducted at room temperature using a CHI660E electrochemical workstation. Linear sweep voltammetry (LSV) was employed, covering a potential range from -0.2 to 1.0 V *versus* Ag/AgCl, with a sweep rate of 10 mV s^{-1} , to examine the electrochemical characteristics of the system.^{27–31} Cyclic voltammetry (CV) experiments were executed at a scan rate of 1 mV s^{-1} , with a potential window from -1.0 V to 0.2 V *versus* Ag/AgCl for detailed analysis of the electrochemical processes in the bacteria/electrode interfaces. The 300 W xenon light source (6258, Newport Corporation) with 420 nm cutoff filter was used as a light source. The light intensity was precisely controlled at 100 mW cm^{-2} , with measurements verified by an optical power meter (Model 19180R, Newport Corporation).^{32–35} Amperometric measurements were performed at a constant applied voltage of 0.8 V *versus* Ag/AgCl to evaluate the system's long-term stability. This measurement was sustained over 24 hours under continuous illumination at 100 mW cm^{-2} , providing critical insights into the endurance and operational reliability of the S-MPEC under simulated operational conditions.^{36–41}

2.8. Preparation of food waste hydrolysate

Food waste was collected from a university canteen and stored at $-20\text{ }^{\circ}\text{C}$ before enzymatic hydrolysis. Briefly, 1 kg of food waste was blended with 500 mL of deionised water using a kitchen blender, and then subjected to enzymatic hydrolysis using 1% (v/m, enzyme/food waste) dosage of glucoamylase, protease, and cellulase (Sunson, China). The hydrolysis broth was centrifuged at $8000 \times g$ for 30 min, and the supernatant was collected, filtered using $1\text{ }\mu\text{m}$ pore size of filter paper, and stored at $-20\text{ }^{\circ}\text{C}$ until further processing. The final glucose concentrations are $98 \pm 20\text{ g L}^{-1}$. The food waste hydrolysate was sterilise-filtered by a $0.22\text{ }\mu\text{m}$ pore size membrane filter (Sartorius, Germany) for microbial

The electrochemical measurements within the S-MPEC were conducted using a three-electrode configuration setup. This setup included a WO_3 nanoplate electrode serving as the working electrode, an Ag/AgCl electrode saturated with 3 M

cultivation. The food waste hydrolysate was transferred to the anodic chamber of PV-S-MPEC.

2.9. Chemical oxygen demand analysis and performance analysis

Chemical oxygen demand was determined by Hach Method 8000. The COD digestion vials (testing range 20 to 1500 mg L⁻¹ COD, HACH USA) with solution were used. The 2 mL diluted analyte was transferred to the digestion vials and underwent digestion according to the method. The resulting solutions were analysed by UV-vis spectroscopy (Shimadzu, UV3600).

3. Results and discussions

3.1. Characterization of *Shewanella oneidensis* MR-1 coated tungsten(vi) oxide (WO₃)

The WO₃ nanoplate photoelectrodes were fabricated on 1 cm × 2.5 cm glass substrates coated with fluorine-doped tin oxide (FTO), serving as the photoanode in a *Shewanella*-mediated photoelectrochemical cell (S-MPEC). These photoelectrodes were connected using titanium (Ti) wire (Fig. S1a†). High-magnification scanning electron microscopy (SEM) images were obtained for MR-1 coated carbon cloth (CC), MR-1 coated WO₃, and bare WO₃ (Fig. 1a–c). The morphology of bare WO₃ was consistent with previously reported

structures.⁴² The appearance of the WO₃ photoelectrode and the attachment of MR-1 biofilm after (bio) photoelectrochemical reaction were documented (Fig. S1b†). The dimensions of the WO₃ nanowires were significantly smaller than the bacteria, with an average length of 1 μm and 100 nm thick, as evident in the SEM images after the dehydration process (Fig. 1b and c). The X-ray diffraction (XRD) patterns of WO₃ and FTO were compared with the Joint Committee on Powder Diffraction Standards (JCPDS) Card File No. 33-0664 and 00-005-0467, confirming the presence of a nanowire arrayed WO₃ on the FTO substrate.

The optical properties of the WO₃ photoelectrodes were also investigated. The UV-vis absorption spectrum (Fig. S2a†) showed minimal changes in WO₃ before and after photoelectrochemical testing. However, the presence of MR-1 bacteria on WO₃ led to increased absorption between 500 nm and 700 nm, indicating biofilm formation on the photoelectrode surface. Meanwhile, the Tauc plot, a graphical representation derived from UV-vis absorption spectra, allows us to estimate the bandgap energy of semiconductors by extrapolating the linear portion of the $(\alpha h\nu)^2$ vs. $h\nu$ curve, where α is the absorption coefficient, and $h\nu$ is the photon energy. Also showed a reduction in bandgap from 2.84 eV to 2.5 eV after biofilm formation on the photoelectrode (Fig. S2b†). Photoluminescence (PL) characterization was

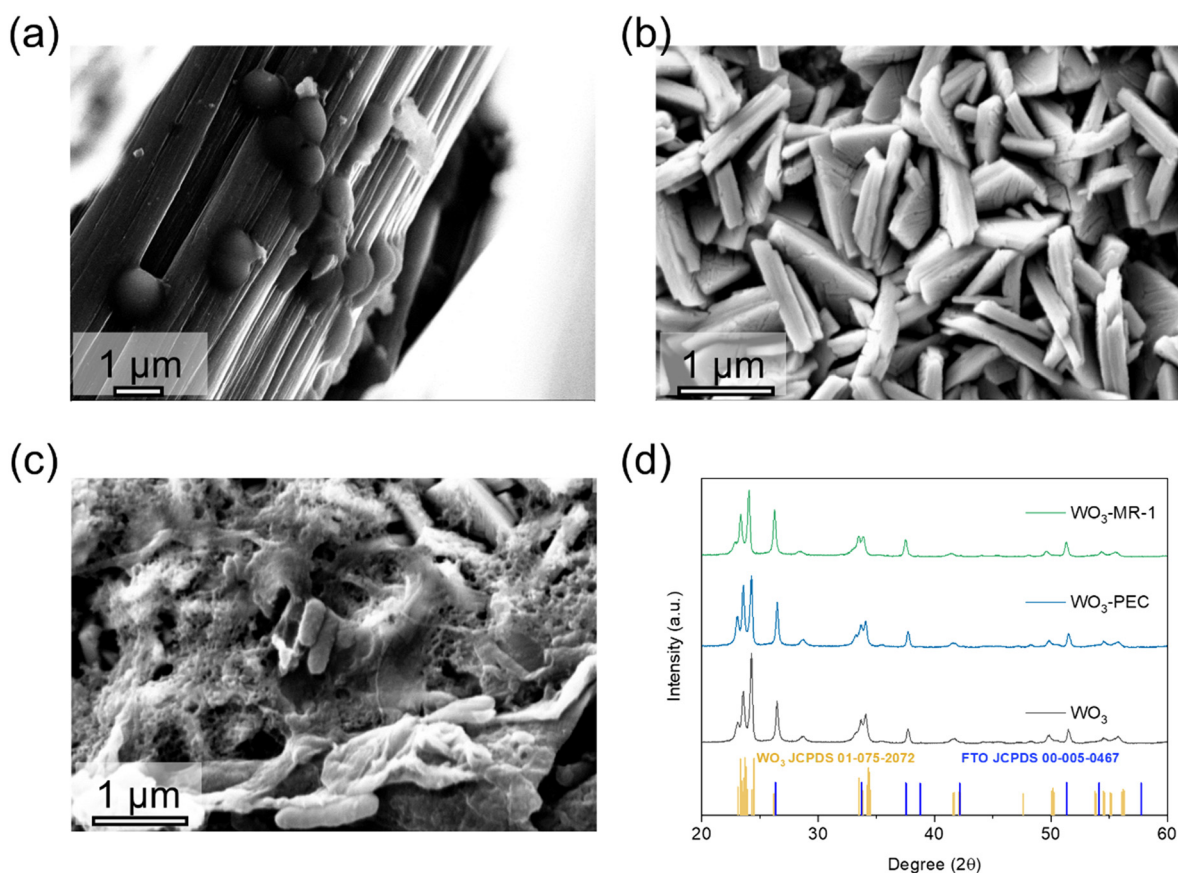


Fig. 1 SEM image of (a) carbon cloth (CC) with MR-1, (b) WO₃ and (c) WO₃ with MR-1. The white rectangular bar on the bottom left-hand corner of each graph indicates the dimensions with 1 μm. (d) XRD patterns of WO₃, WO₃ photoelectrode, and WO₃-MR-1 biophotoelectrode.



performed to further confirm the changes in the optical properties of WO_3 after (bio)photoelectrochemical reactions (Fig. S3a†). The results indicated no shift in the emission peaks at 468 nm post-reaction. The decrease in PL intensity can be attributed to electron transfers from WO_3 to impurities (in photoelectrochemical reaction) and MR-1 (in biophotoelectrochemical reaction). Fig. S3b† shows the time-resolved PL analysis. Bare WO_3 exhibits the highest average lifetime of 1.875 ns, indicating moderate recombination dynamics with significant surface recombination. In contrast, WO_3 -PEC shows reduced recombination lifetimes compared to bare WO_3 , suggesting improved recombination dynamics through reduced surface and bulk recombination. WO_3 -MR-1 reveals the shortest lifetimes and the lowest average lifetime of 0.601 ns, indicating significantly enhanced recombination dynamics. MR-1 bacteria substantially reduces surface and bulk recombination, likely due to enhanced charge separation and transfer facilitated by the bacteria.

3.2. Photoelectrochemical characterization

The LSV for the WO_3 photoanode was performed to establish a baseline photoelectrochemical response without biological influence, focusing on the inherent material properties and light-induced electron dynamics. In contrast, LSV on the S-MPEC incorporated the biological components, specifically targeting the interactions between the WO_3 photoanode and the *Shewanella oneidensis* MR-1 biofilm. This comparative approach allowed us to directly assess the enhancement in photocurrent and electrochemical activity due to the synergistic effects of the semiconductor-bacteria interface. The WO_3 photoanode achieved a photocurrent density of 0.68 mA cm^{-2} at +0.2 V vs. Ag/AgCl 3.5 M KCl, corresponding to +1.23 V vs. RHE at pH 13.6. This performance is in agreement with established literature values. To mitigate photocurrent and overpotential losses, hydrogen peroxide (H_2O_2) was utilized as a sacrificial reducing agent. Subsequently, we enhanced the system by adding 100 mM H_2O_2 to a 1 M NaOH electrolyte. This modification increased the photocurrent to approximately 1.3 mA cm^{-2} , as shown in Fig. S4†. This improvement suggests the activation of surface species capable of hole trapping and enhancing water photo-oxidation on the WO_3 nanoplate.

In the solar-assisted microbial photoelectrochemical cell (S-MPEC) context, LSV experiments were carried out using the WO_3 photoelectrode as the working electrode, with a platinum wire as the counter electrode. The experiments were conducted at a scan rate of 10 mV s^{-1} , focusing on a potential window from -0.2 V to 1.0 V to elucidate the effects of illumination on the electrochemical interactions between WO_3 and MR-1. As depicted in Fig. 2a, the electrochemical activity was minimal under dark conditions, with the WO_3 photoelectrodes showing negligible current. However, under illuminated conditions, there was a significant enhancement in photocurrent

density, aligning with findings reported in the literature. Interestingly, in the absence of light, the presence of *S. oneidensis* cells contributed to a notable increase in current density. The dark current density observed with the WO_3 -MR-1 biophotoelectrode reached 0.826 A m^{-2} , which was considerably higher than the 0.289 A m^{-2} recorded for the bare WO_3 photoelectrode at 0.8 V. This increase indicates that under an external bias, the high interfacial energy barrier typically associated with the WO_3 electrode is effectively surpassed, facilitating the transfer of bioelectrons from MR-1 cells to the WO_3 anode and into the external circuit.

Additionally, Fig. 2a illustrates that the photocurrent of the bare WO_3 photoelectrode reached 2.97 A m^{-2} at 0.8 V, which was significantly higher than the 0.749 A m^{-2} observed at the same potential for the WO_3 -MR-1 biophotoelectrode. The power density of the microbial electrochemical cell (MEC) with the CC-MR-1 bioelectrode was recorded at 0.680 W m^{-2} . Under visible light illumination, the power densities for the bare WO_3 and WO_3 -MR-1 photoelectrodes were 0.599 W m^{-2} and 2.375 W m^{-2} , respectively. These findings indicate that the efficiency of substrate utilization by the exoelectrogenic bacteria MR-1 substantially enhances the performance of the S-MPEC system, regardless of the lighting conditions. This suggests that the intrinsic resistance of the WO_3 photoelectrode can be effectively mitigated by applying an external bias. Under solar illumination, photoexcited holes in the valence band of the photoanodes potentially recombine with bioelectrons from MR-1, which transforms the substrate into bioelectrons, thereby increasing the photocurrent density and promoting greater electron flow to the cathode via the external circuit.

Additionally, cyclic voltammetry provided further insights into the reversible and irreversible processes occurring at the electrode surfaces, showing a distinguish between the electrochemical behaviors of the WO_3 photoanode in the absence and presence of the biofilm. The CV experiments involved a series of working electrodes—CC-MR-1, bare WO_3 , and WO_3 -MR-1—with Ag/AgCl (3.5 M KCl) as the reference electrode and platinum (Pt) as the counter electrode. CV scans were performed in LB medium supplemented with $10 \text{ }\mu\text{M}$ riboflavin, spanning a potential range from -1.0 V to +0.2 V versus SCE for the CC-MR-1, WO_3 , and WO_3 -MR-1 electrodes. For the CC-MR-1 electrode, cathodic and anodic peak potentials (E_{pc} and E_{pa}) were observed at -0.441 V and -0.098 V versus Ag/AgCl, respectively. Similarly, for the WO_3 -MR-1 electrode, E_{pc} and E_{pa} were -0.301 V versus Ag/AgCl and -0.158 V versus Ag/AgCl, respectively. The midpoint potentials (E_0), calculated as $E_0 = (E_{\text{pc}} + E_{\text{pa}})/2$, were -0.230 V for WO_3 -MR-1 and -0.270 V for CC-MR-1. These results correlate with the well-defined redox potentials of c-type cytochromes, which have a midpoint potential of around -0.410 V versus Ag/AgCl. The shuttle-mediated catalytic potential matches previous findings.^{43–45} Our experimental analysis confirms that the interaction between MR-1 electrocogens and WO_3 involves



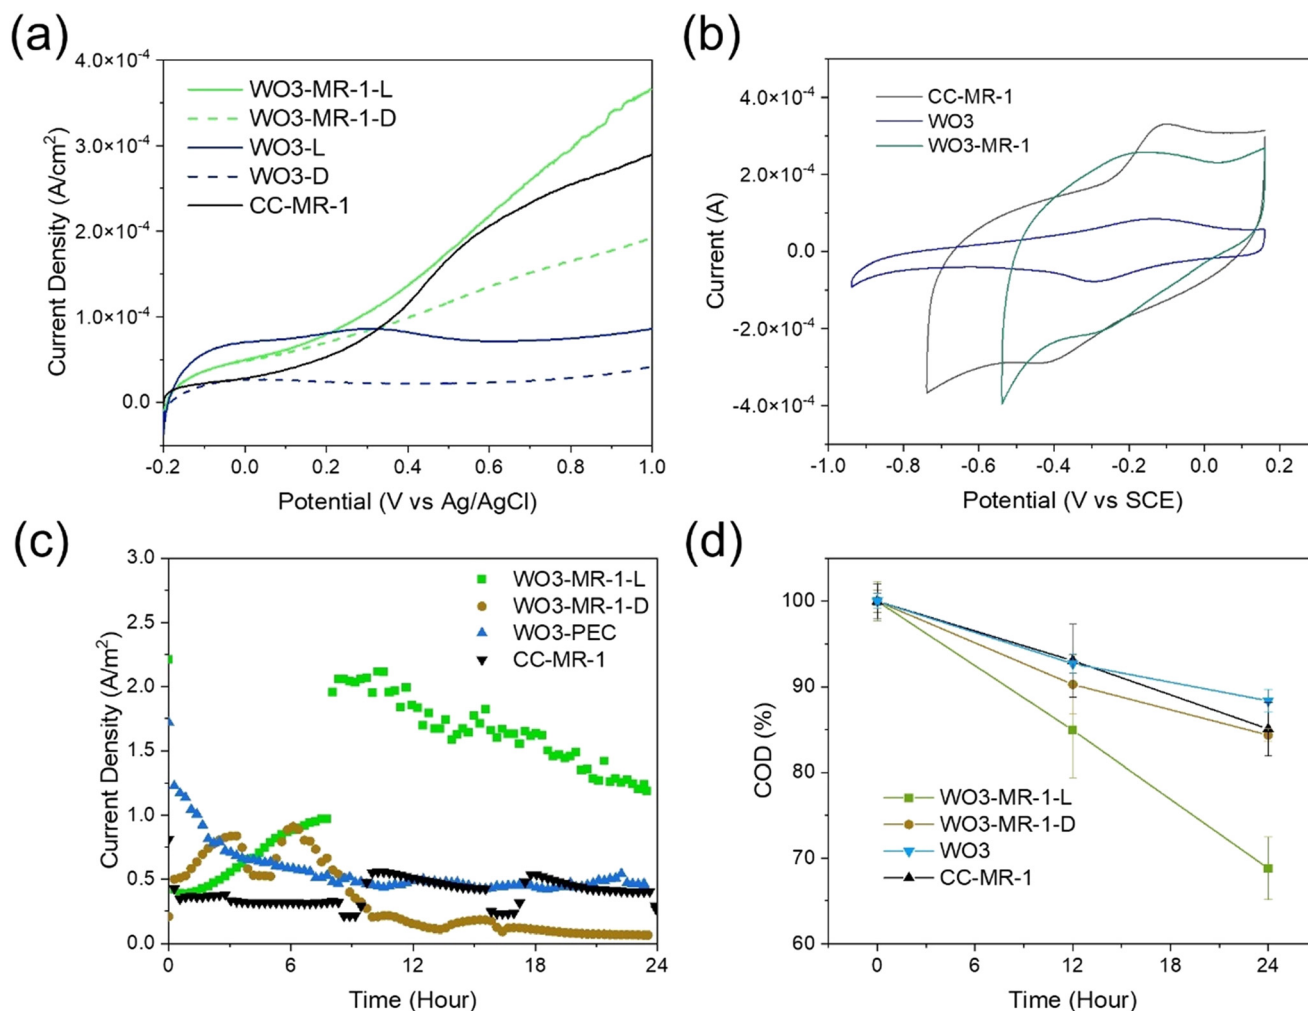


Fig. 2 (a) LSV, (b) CV, and (c) *i-t* curve under external bias of 0.8 V of S-MPEC using CC-MR-1, WO₃, and WO₃-MR-1 as anode under dark and light conditions. (d) Record of COD in the percentage of S-MPEC using CC-MR-1, WO₃, and WO₃-MR-1 as anode.

c-type cytochromes, facilitating extracellular electron transfer.

The long-term stability of the solar-assisted microbial photoelectrochemical cell (S-MPEC) system was evaluated using current-time (*i-t*) measurements over 24 hours. The test was conducted and a bias voltage of 0.8 V vs. Ag/AgCl. The current-time response for various experimental setups is illustrated in Fig. 2c. For the WO₃-MR-1 biophotocathode under illumination, an initial increase in current density was observed from 0 to 3 hours, followed by a decline from 6 to 8 hours. This pattern suggests the ongoing formation and possibly the self-regulation of the biofilm on the WO₃ photocathode under the combined influence of irradiation and electrical bias. In contrast, under irradiated conditions, the photocurrent density of the WO₃-MR1 electrode not only increased but sustained higher levels for up to 8 hours, indicating more robust biofilm activity and electron transfer processes. Comparatively, the current density in the WO₃-MR-1 setup was fourfold higher than that of the bare WO₃ under similar irradiated conditions and four

times greater than that observed in the CC-MR-1 under dark conditions. These results underscore the enhanced durability and electrochemical efficiency of the MR-1 when interfaced with WO₃ in the photoelectrochemical system.

To understand the relationship between bioelectron production and the operation of S-MPEC, the chemical oxygen demand (COD) was monitored at 12-hour intervals, as shown in Fig. 2d. The COD reduction exhibited a rapid decline during the initial 12 hours, aligning with the active growth phase of the microbial cells.⁴² The initial COD was approximately 13 000 mg L⁻¹, as detailed in Table S1.† After 24 hours, the COD for the CC-MR-1 setup decreased from 12 490 mg L⁻¹ to 10 623 mg L⁻¹, which corresponds to a removal rate of 1811 mg L⁻¹ per day. For the WO₃-MR-1 configuration, the COD reduced from 13 207 mg L⁻¹ to 11 140 mg L⁻¹, achieving a notable removal rate of 3867 mg L⁻¹ per day.

These findings demonstrate that the WO₃-MR-1 setup enhances the photocurrent density and significantly improves the COD consumption rate under irradiated conditions. This suggests that photoexcited holes in the WO₃



contribute effectively to the oxidation processes, thereby driving the efficient electron transfer from MR-1.

3.3. Extracellular electron transfer kinetics

Cyclic voltammetry was conducted at different scan rates to investigate the heterogeneous electron transfer kinetics of

different electrodes. To facilitate the analysis, 10 μM Riboflavin was added to each electrode system, serving as a redox shuttle. This addition enables the observation of shuttle-mediated catalytic currents and provides insights into the electron transfer kinetics at the electrode|electrolyte interfaces for the CC-MR-1, WO_3 , and WO_3 -MR-1. In Fig. 3a, c, and e, significant peak broadening and peak

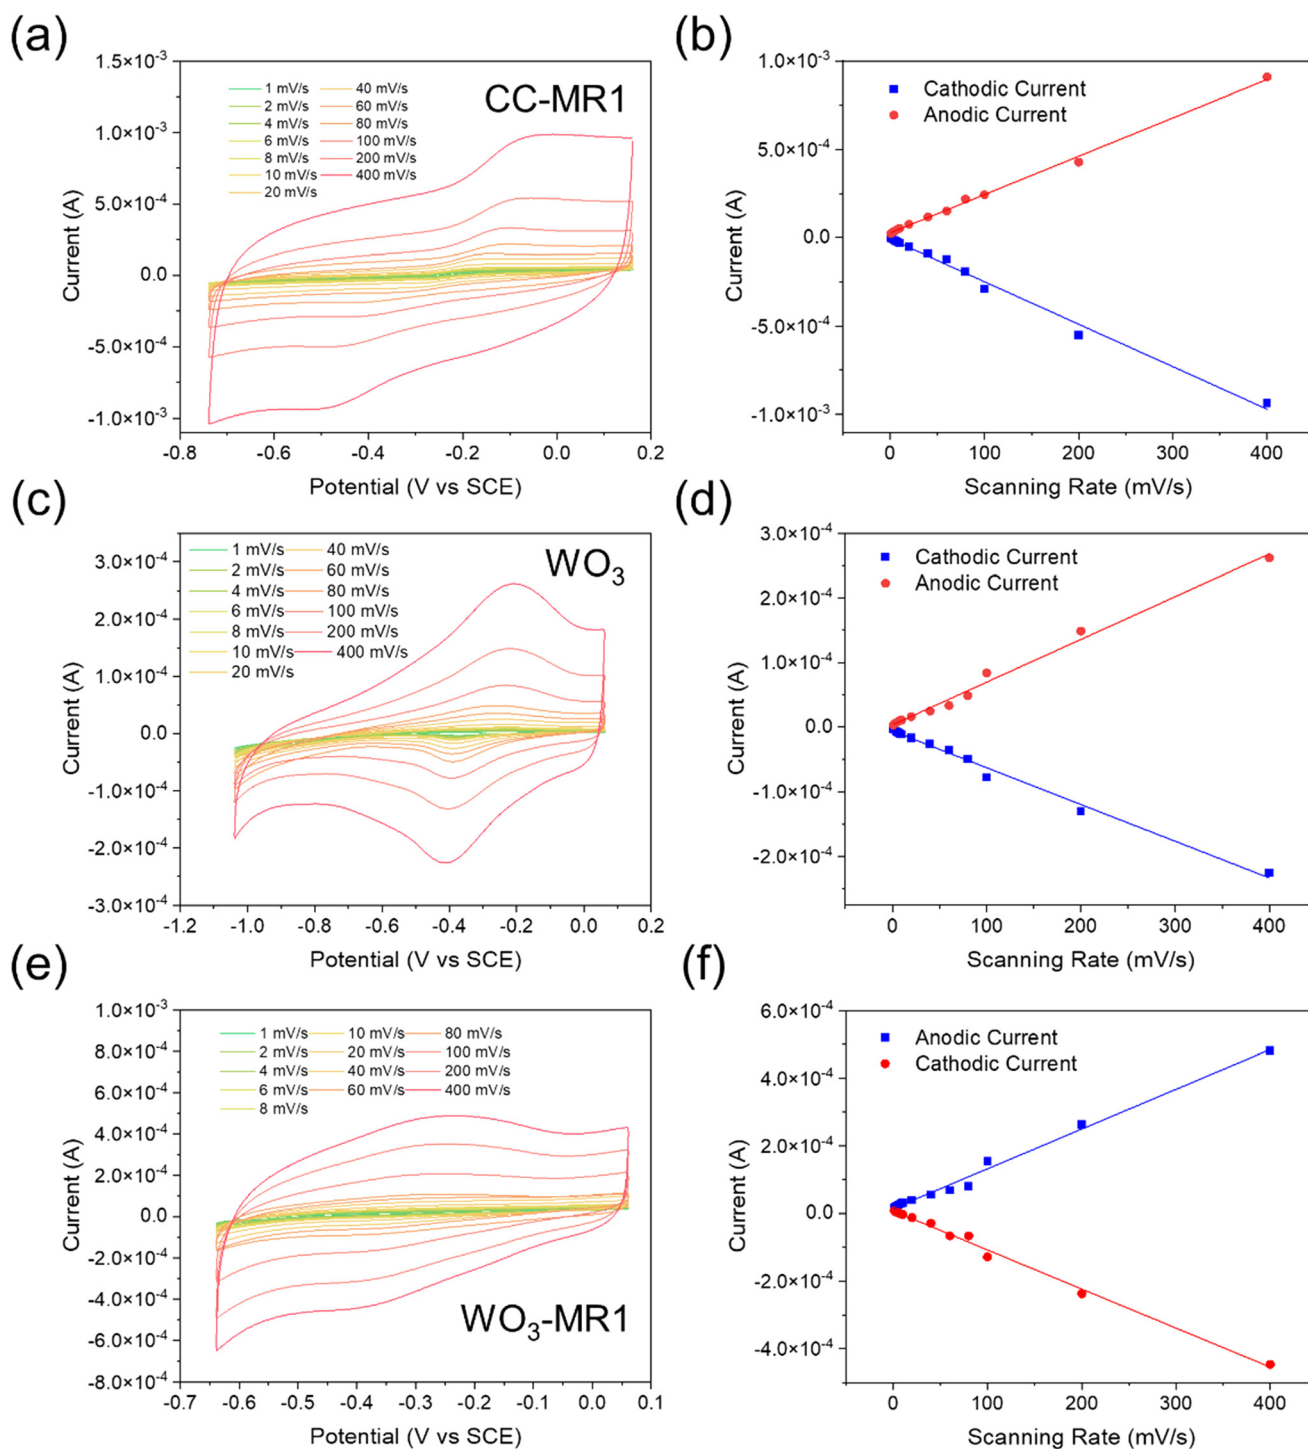


Fig. 3 CV at different scan rates from 1 mV s^{-1} to 40 mV s^{-1} of (a) CC-MR-1, (c) WO_3 , and (e) WO_3 -MR-1; peak current vs. scan rate plot of (b) CC-MR-1, (d) WO_3 and (f) WO_3 -MR-1.



separation were observed in the CV profiles, indicating the redox processes associated with the immobilized flavin.^{46,47} Additionally, a peak shift of approximately 0.1 V vs. SCE was noted, which is attributed to the internal resistance of the semiconductor electrode, specifically WO₃ in this case. The relationship between peak current densities and different scanning rates was analyzed to further elucidate the redox species' nature within the MR-1 biofilm. As shown in Fig. 3b, the peak currents were linearly related to the scanning rates, with a correlation coefficient (R^2) 0.99. This linearity suggests the presence of a diffusion regime oriented perpendicular to the electrode surface. The Randles–Sevcik equation (eqn (1)) can be employed to describe this behavior.

$$I_{\text{rev}} = (2.69 \times 10^5) n^{3/2} ACD^{1/2} v^{1/2} \quad (1)$$

The Tafel plot in Fig. S7† was obtained from the descending parts of the cathodic and ascending parts of anodic peaks of the cyclic voltammogram. We then determined α using the slope of the plot of $\log(i)$ versus potential, as shown in eqn (2).⁴⁸

$$\text{Slope} = \frac{\alpha F}{2.3RT} \text{ or } \frac{-\alpha F}{2.3RT} \quad (2)$$

To quantify the heterogeneous electron-transfer rate constant (k_0), the Gileadi method was employed. This method is instrumental in determining the critical scan rate (V_c) where the electrochemical reaction transitions from reversible to irreversible or from quasi-reversible to irreversible. This transition point is crucial for understanding the electron transfer processes' kinetics and the electrode–electrolyte interface's dynamic behavior.⁴⁹ The V_c was graphically evaluated by plotting E_p against the log of scan rate at low and high scan rates (Fig. S6†). The graphical representation typically results in two distinct linear segments corresponding to the lower and higher scan rate domains. Two different slopes are obtained by fitting lines to these segments, reflecting the different kinetic regimes at varied scan rates. The intersection of the two lines provided the V_c , and k^0 was determined by eqn (3).⁵⁰

$$\log k^0 = -0.48\alpha + 0.52 + \log \left(\frac{nF\alpha V_c D}{2.303RT} \right)^{\frac{1}{2}} \quad (3)$$

As detailed in Table 1, the electrochemical characterization of the WO₃-MR-1 electrode shows diffusion coefficients for the

reduction and oxidation reactions at $1.66 \times 10^{-8} \text{ cm}^2 \text{ s}^{-1}$ and $2.29 \times 10^{-8} \text{ cm}^2 \text{ s}^{-1}$, respectively. These values are accompanied by high electron-transfer rate constants of $8.02 \times 10^{-5} \text{ cm s}^{-1}$ for reduction and $9.02 \times 10^{-5} \text{ cm s}^{-1}$ for oxidation. The diffusion coefficients and rate constants for the CC-MR-1 electrode and the bare WO₃ photoelectrode are also provided for comparative purposes. The WO₃-MR-1 electrode demonstrates a higher diffusion coefficient and faster rate constant than the bare WO₃ photoelectrode. This indicates more efficient electron transfer processes at the solid–liquid interface in the WO₃-MR-1 system. Such superior electrochemical properties underscore the potential of WO₃-MR-1 as a highly promising candidate for biophotocatalytic applications. The enhanced performance of WO₃-MR-1 can be attributed to the synergistic interaction between the microbial biofilm and the semiconductor material, which facilitates a more efficient heterogeneous electron transfer.

3.4. Electrochemical impedance spectroscopy (EIS)

We conducted electrochemical impedance spectroscopy (EIS) to assess the charge transfer resistance within the photoelectrochemical cell. The Nyquist plots derived from EIS for three different electrodes (CC-MR-1, WO₃, and WO₃-MR-1) were analyzed to assess the electrochemical behavior of both control and experimental reactors, as shown in Fig. 4. The high-frequency intercept with the x-axis in these plots indicates the ohmic resistance of the cell, which includes contributions from the inherent resistances of the electrolyte, electrodes, and interface contacts. The Nyquist arc's magnitude reflects the total resistance encompassing these components. An appropriate equivalent circuit model, depicted in Fig. 4a, was employed to interpret the EIS data. This model quantifies various resistance components such as charge transfer resistance, mass transfer resistance, and ohmic resistance within the solar-assisted microbial photoelectrochemical cell (S-MPEC) system.⁵¹ The values for different circuit elements, which were fitted to this model, are provided in Table S3.† From the analysis, the electrolyte resistance (R_s) observed was highest for the carbon cloth electrode at 38.4 Ω . It was lower for the bare WO₃ electrode at 13.72 Ω , and the lowest for the WO₃-MR-1 electrode at 8.637 Ω . This decrease in resistance with the incorporation of MR-1 bacteria into the WO₃ electrode suggests an enhancement in ionic conductivity, likely facilitated by the biological activity of the bacteria. Furthermore, the Nyquist

Table 1 The kinetic parameters of CC-MR-1, WO₃, and WO₃-MR-1, including E^0 , D , k^0 , and α in LB-M9 solution with 10 μM riboflavin at room temperature

	CC-MR-1		WO ₃		WO ₃ -MR-1	
	Reduction	Oxidation	Reduction	Oxidation	Reduction	Oxidation
E^0 (V vs. SCE)	−0.472	−0.375	−0.280	−0.151	−0.259	−0.180
$10^{-8} D$ ($\text{cm}^2 \text{ s}^{-1}$)	2.91	0.356	0.2	0.24	1.66	2.29
α	0.075	0.13	0.111	0.087	0.138	0.112
$10^{-6} k^0$ (cm s^{-1})	78.8	36.5	21.1	29.4	80.2	90.2



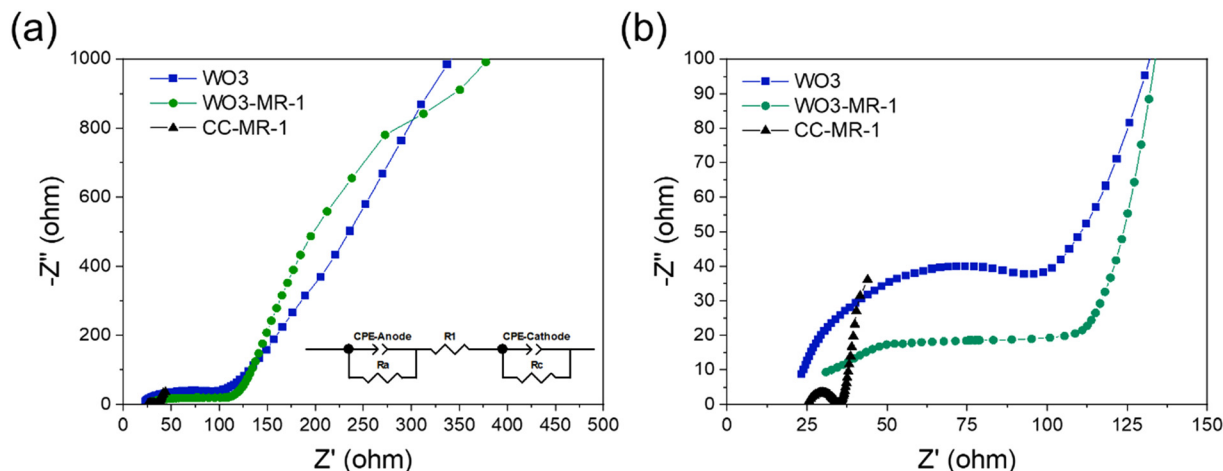


Fig. 4 (a) Electrochemical impedance plots of electrodes of CC-MR-1, WO₃ and WO₃-MR-1 with an equivalent circuit model used to fit experimental data; (b) enlarged electrochemical impedance plots of (a).

plots revealed that the anode resistance was significantly higher for the bare WO₃ (4373 Ω) and even more so for the WO₃-MR-1 (4901 Ω) compared to the carbon cloth (1007 Ω). This increase in anode resistance with the introduction of MR-1 onto the WO₃ electrode points to potential complications in electron transfer efficiency at the anode. Regarding cathodic reactions, the cathodic charge-transfer resistance for the WO₃-MR-1 (39.9 Ω) and CC (5.28 Ω) was found to be lower than that of bare WO₃ (82.1 Ω), highlighting a limitation in the cathodic charge transfer capabilities of the bare WO₃ electrode. This suggests that MR-1 bacteria facilitates a more efficient transfer of H⁺ ions from the oxidation reaction in the anodic chamber, improving overall charge transfer at the cathode.⁵²

3.5. Mechanistic insight into electricity generation in S-MPEC

Based on the findings from this study, we have developed a model to explain the current generation mechanism in the solar-assisted microbial photoelectrochemical cell (S-MPEC) utilizing a WO₃ nanoplate photoelectrode and *S. oneidensis*, as illustrated in Fig. 5. The observation that the system

produces only a minimal current in the absence of light suggests that the polarization resistance at the WO₃ nanoplate electrode may hinder the transfer of bioelectrons. These electrons originate from the exoelectrogens and travel through the conduction band of the WO₃ nanoplate to the FTO substrate, a process that appears to be impeded under dark conditions.^{15,53} Under illuminated conditions, however, the separation of photogenerated electron-hole pairs is significantly enhanced. This improvement is primarily due to the recombination of bioelectrons—derived from lactate/pyruvate (−0.185 V) transferred by the outer membrane c-type cytochromes (OM c-Cyts) of *S. oneidensis* (approximately −0.110 V vs. Ag/AgCl)—with the photoexcited holes (2.86 eV vs. NHE) on the surface of the WO₃ nanoplate photoelectrodes. This recombination process effectively leads to a higher current output.^{54,55}

3.6. PV-S-MPEC system

To enhance the performance of the solar-assisted microbial photoelectrochemical cell (S-MPEC), a commercially available silicon photovoltaic (PV) module delivering 3.5 V was integrated into the system. The performance of this setup is shown in Fig. S5a and b,† where the voltage over time and the associated current and power densities were derived using the eqn (4) and (5):

$$\text{Voltage (V)} = \text{Current (I)} \times \text{Resistance (R)} \quad (4)$$

$$\text{Power (P)} = \text{Current (I)} \times \text{Voltage (V)} \quad (5)$$

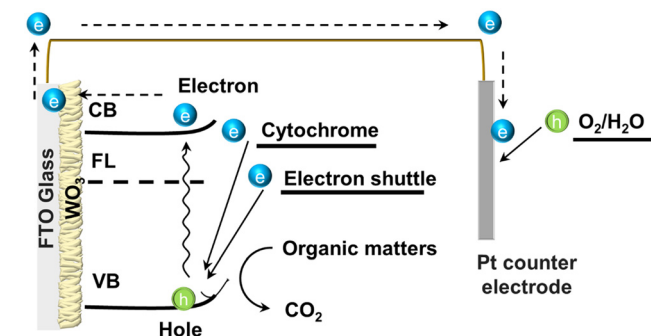


Fig. 5 Schematic diagram of the photocurrent generation by the WO₃ electrode with MR-1 bacteria. FL, CB, and VB represent the fermi level, conduction, and valence bands, respectively.

drop to 3.28 V but achieved a higher current density of 6.70 A m^{-2} and a power density of 21.99 W m^{-2} . The resulting power density of PV-S-MPEC outperforms the reported value of 0.75 W m^{-2} of a microbial fuel cell with polycrystalline silicon solar cell integrated system.¹⁷

Chemical oxygen demand (COD) was also monitored to assess the organic matter reduction efficiency. Initially set at approximately $10\,000 \text{ mg L}^{-1}$, the COD in the PV-S-MPEC using CC-MR-1 bioanode decreased from $10\,090 \text{ mg L}^{-1}$ to 5590 mg L^{-1} over 24 hours, corresponding to a removal rate of 4500 mg L^{-1} per day. The PV-S-MPEC using WO_3 -MR-1 bioanode displayed a more substantial reduction, from $10\,257 \text{ mg L}^{-1}$ to 2090 mg L^{-1} , presenting a removal rate of 8167 mg L^{-1} per day. Based on the calculation (ESI†), the food waste removal rate of PV-S-MPEC using CC-MR-1 bioanode and WO_3 -MR-1 bioanode was estimated to be 83.67 g per day. The PV-S-MPEC system demonstrated a remarkable improvement in output power density and COD removal rate, showing the effectiveness of PV integration in boosting the system's overall efficiency and stability.

4. Conclusion

This study explores the bio-photoelectrochemical interactions between tungsten(vi) oxide and *Shewanella oneidensis* MR-1 within hybrid bio-photoelectrochemical devices. These hybrid systems demonstrate significantly improved photoelectrochemical performance when incorporating live cells. Linear sweep voltammetry reveals that WO_3 photoelectrodes in the solar-assisted microbial photoelectrochemical cell (S-MPEC) exhibits a remarkable 400% increase in current density compared to an abiotic medium under a 0.80 V external bias. Electrochemical impedance spectroscopy (EIS) analysis indicates that the overall resistance of the S-MPEC system using a WO_3 anode is considerably higher than that with a carbon cloth anode. This suggests that the presence of MR-1 bacteria reduces solution resistance and enhances ionic conductivity. Additionally, the cathodic charge-transfer resistance for the WO_3 -MR-1 is lower than that for bare WO_3 , indicating a more efficient electrochemical interaction facilitated by the bacteria. In the PV-S-MPEC system employing WO_3 as the photoanode, the output voltage is measured at 3.28 V, corresponding current density and power density of 6.70 A m^{-2} and 21.99 W m^{-2} , respectively. This study demonstrates that integrating photovoltaic modules with microbial photoelectrochemical cells provides a robust framework that enhances bioelectrochemical performance and waste degradation. Furthermore, the WO_3 -MR-1 system demonstrated the most efficient COD removal rate under irradiation, achieving a rate of 8167 mg L^{-1} per day, compared to 4500 mg L^{-1} per day for the CC-MR-1 system. This efficiency underscores the role of photoexcited holes in driving the oxidation reactions of the MR-1 species, thereby enhancing the bioelectrochemical performance. These findings not only pave the way for new directions in the

development of practical S-MPEC systems but also provide crucial insights into the mechanisms of electron transfer and energy conversion within these systems, as well as the natural synergy between sunlight, semiconductors, and electricigens.

Data availability

Data available on request from the authors.

Conflicts of interest

There are no conflicts to declare.

Note added after first publication

This article replaces the version published on 1st October 2024, which contained errors in the caption for Fig. 1 as well as use of the incorrect valency for compound 'tungsten(iv) oxide' throughout and this has been corrected to 'tungsten(vi) oxide' in this version.

Acknowledgements

The authors acknowledge financial support from the Research Grants Council of Hong Kong (grant no. CityU 21203518 and F-CityU106/18), Innovation and Technology Commission (grant no. MHP/104/21), Shenzhen Science Technology and Innovation Commission (grant no. JCYJ20210324125612035, R-IND12303 and R-IND12304), City University of Hong Kong (grant no. 9229160, 9360140, 7005289, 7005580, 7005720, 9667213, 9667229, 9680331 and 9678291), Australian Research Council (ARC) Discovery Early Career Researcher Award (grant no. DE160100589), National Natural Science Foundation of China (grant no. 21974131), and C. H. Mak thanks for the financial support from the Hong Kong Jockey Club under the research work Hong Kong JC STEM Lab for Circular Bioeconomy (Project No. 2023-0078).

References

- 1 S. Liu, Y. Jin, S. Huang, Q. Zhu, S. Shao and J. C.-H. Lam, One-pot redox cascade paired electrosynthesis of gamma-butyrolactone from furoic acid, *Nat. Commun.*, 2024, **15**(1), 1141.
- 2 C. A. Richard, Z. Pan, H.-Y. Hsu, S. Cekli, K. S. Schanze and J. R. Reynolds, Effect of Isomerism and Chain Length on Electronic Structure, Photophysics, and Sensitizer Efficiency in Quadrupolar (Donor) 2-Acceptor Systems for Application in Dye-Sensitized Solar Cells, *ACS Appl. Mater. Interfaces*, 2014, **6**(7), 5221–5227.
- 3 L. Fu, K. Fu, X. Gao, S. Dong, B. Zhang, S. Fu, H.-Y. Hsu and G. Zou, Enhanced Near-Infrared Electrochemiluminescence from Ternary Ag-In-S to Multinary Ag-Ga-In-S Nanocrystals via Doping-in-Growth and Its Immunosensing Applications, *Anal. Chem.*, 2021, **93**(4), 2160–2165, DOI: [10.1021/acs.analchem.0c03975](https://doi.org/10.1021/acs.analchem.0c03975).



- 4 X. Fu, T. He, S. Zhang, X. Lei, Y. Jiang, D. Wang, P. Sun, D. Zhao, H.-Y. Hsu and X. Li, Halogen-halogen bonds enable improved long-term operational stability of mixed-halide perovskite photovoltaics, *Chem*, 2021, **7**(11), 3131–3143.
- 5 Q. Zhu, B. Gong, S. Huang, Y. Jin, S. Liu, S. Shao, Y. Yang, T. Cataldo, N. M. Bedford and J. C.-H. Lam, Rhombohedral ZnIn₂S₄-catalysed anodic direct electrochemical oxidative cleavage of C–O bond in α -O-4 linkages in ambient conditions, *Green Chem.*, 2024, **26**(7), 4135–4150.
- 6 K. L. Ong, G. Kaur, N. Pensupa, K. Uisan and C. S. K. Lin, Trends in food waste valorization for the production of chemicals, materials and fuels: Case study South and Southeast Asia, *Bioresour. Technol.*, 2018, **248**, 100–112.
- 7 T. N. D. Cao, T. Wang, Y. Peng, H.-Y. Hsu, H. Mukhtar and C.-P. Yu, Photo-assisted microbial fuel cell systems: critical review of scientific rationale and recent advances in system development, *Crit. Rev. Biotechnol.*, 2024, **44**(1), 31–46.
- 8 S. Huang, Y. Jin, M. Zhang, K. Yan, S.-P. Feng and J. C.-H. Lam, MoS₂-catalyzed selective electrocatalytic hydrogenation of aromatic aldehydes in an aqueous environment, *Green Chem.*, 2022, **24**(20), 7974–7987.
- 9 S. Rao, X. Zou, S. Wang, T. Shi, Y. Lu, L. Ji, H.-Y. Hsu, Q. Xu and X. Lu, Electrodeposition of porous Sn-Ni-Cu alloy anode for lithium-ion batteries from nickel matte in deep eutectic solvents, *J. Electrochem. Soc.*, 2019, **166**(10), D427.
- 10 S. Javaid, X. Xu, W. Chen, J. Chen, H.-Y. Hsu, S. Wang, X. Yang, Y. Li, Z. Shao and F. Jones, *et al.* Ni₂/Co₂ doped Au-Fe₇S₈ nanoplatelets with exceptionally high oxygen evolution reaction activity, *Nano Energy*, 2021, **89**, 106463, DOI: [10.1016/j.nanoen.2021.106463](https://doi.org/10.1016/j.nanoen.2021.106463).
- 11 S. P. Santoso, S.-P. Lin, T.-Y. Wang, Y. Ting, C.-W. Hsieh, R.-C. Yu, A. E. Angkawijaya, F. E. Soetaredjo, H.-Y. Hsu and K.-C. Cheng, Atmospheric cold plasma-assisted pineapple peel waste hydrolysate detoxification for the production of bacterial cellulose, *Int. J. Biol. Macromol.*, 2021, **175**, 526–534, DOI: [10.1016/j.ijbiomac.2021.01.169](https://doi.org/10.1016/j.ijbiomac.2021.01.169).
- 12 C. Wang, K. Liu, Y. Jin, S. Huang and J. Chun-Ho Lam, Amorphous RuO₂ Catalyst for Medium Size Carboxylic Acid to Alkane Dimer Selective Kolbe Electrolysis in an Aqueous Environment, *ChemSusChem*, 2023, **16**(16), e202300222.
- 13 F. Qian, H. Wang, Y. Ling, G. Wang, M. P. Thelen and Y. Li, Photoenhanced electrochemical interaction between *Shewanella* and a hematite nanowire photoanode, *Nano Lett.*, 2014, **14**(6), 3688–3693.
- 14 H. Y. Chung, R. J. Wong, R. Amal and Y. H. Ng, Engineering the interfacial contact between Bi₂WO₆ and WO₃ heterojunction photoanode for improved charge transportation, *Energy Fuels*, 2022, **36**(19), 11550–11558.
- 15 J. Cao, Y. Shi, J. Xin, S. Kong and X. Wang, Application of microbial fuel cells with tungsten-based semiconductor modified electrode in the treatment of Cr (VI) pollutions, *Biochem. Eng. J.*, 2023, **198**, 109034.
- 16 H. Ding, Y. Li, A. Lu, X. Wang and C. Wang, Promotion of anodic electron transfer in a microbial fuel cell combined with a silicon solar cell, *J. Power Sources*, 2014, **253**, 177–180.
- 17 Z. Sun, R. Cao, M. Huang, P. Sun, C. Tang and D. Chen, Enhanced electricity generation and pollutant removal in a microbial fuel cell combined with a solar cell, *J. Renewable Sustainable Energy*, 2015, **7**(4), 043109.
- 18 K.-J. Chae, M.-J. Choi, K.-Y. Kim, F. F. Ajayi, I.-S. Chang and I. S. Kim, A solar-powered microbial electrolysis cell with a platinum catalyst-free cathode to produce hydrogen, *Environ. Sci. Technol.*, 2009, **43**(24), 9525–9530.
- 19 C.-N. Wu, L.-C. Sun, Y.-L. Chu, R.-C. Yu, C.-W. Hsieh, H.-Y. Hsu, F.-C. Hsu and K.-C. Cheng, Bioactive compounds with anti-oxidative and anti-inflammatory activities of hop extracts, *Food Chem.*, 2020, **330**, 127244.
- 20 A. Andreas, Z. G. Winata, S. P. Santoso, A. E. Angkawijaya, M. Yuliana, F. E. Soetaredjo, S. Ismadji, H.-Y. Hsu, A. W. Go and Y.-H. Ju, Biocomposite hydrogel beads from glutaraldehyde-crosslinked phytochemicals in alginate for effective removal of methylene blue, *J. Mol. Liq.*, 2021, **329**, 115579, DOI: [10.1016/j.molliq.2021.115579](https://doi.org/10.1016/j.molliq.2021.115579).
- 21 X. Yang, J. Yang, M. I. Ullah, Y. Xia, G. Liang, S. Wang, J. Zhang, H.-Y. Hsu, H. Song and J. Tang, Enhanced Passivation and Carrier Collection in Ink-Processed PbS Quantum Dot Solar Cells via a Supplementary Ligand Strategy, *ACS Appl. Mater. Interfaces*, 2020, **12**(37), 42217–42225, DOI: [10.1021/acsami.0c08135](https://doi.org/10.1021/acsami.0c08135).
- 22 F. F. Ajayi, K.-Y. Kim, K.-J. Chae, M.-J. Choi, S.-Y. Kim, I.-S. Chang and I. S. Kim, Study of hydrogen production in light assisted microbial electrolysis cell operated with dye sensitized solar cell, *Int. J. Hydrogen Energy*, 2009, **34**(23), 9297–9304.
- 23 Q. Zeng, J. Li, J. Bai, X. Li, L. Xia and B. Zhou, Preparation of vertically aligned WO₃ nanoplate array films based on peroxotungstate reduction reaction and their excellent photoelectrocatalytic performance, *Appl. Catal., B*, 2017, **202**, 388–396.
- 24 S. Rao, X. Zou, S. Wang, Y. Lu, T. Shi, H.-Y. Hsu, Q. Xu and X. Lu, Electrodeposition of Ni-Cu alloy films from nickel matte in deep eutectic solvent, *Mater. Chem. Phys.*, 2019, **232**, 6–15.
- 25 C. H. Mak, Y. Peng, M. H. Chong, L. Yu, M. Du, L. Ji, X. Zou, G. Zou, H.-H. Shen and S. P. Santoso, Photoenhanced interfacial electron transfer of a dual functional hematite biophotoelectrode, *J. Mater. Chem. C*, 2023, **11**(33), 11303–11311.
- 26 C.-C. Chang, Y.-C. Chen and C.-P. Yu, Microbial community dynamics in electroactive biofilms across time under different applied anode potentials, *Sustainable Environ. Res.*, 2022, **32**(1), 1–11.
- 27 R. Liu, C. H. Mak, X. Han, Y. Tang, G. Jia, K.-C. Cheng, H. Qi, X. Zou, G. Zou and H.-Y. Hsu, Efficient electronic coupling and heterogeneous charge transport of zero-dimensional Cs₄PbBr₆ perovskite emitters, *J. Mater. Chem. A*, 2020, **8**(45), 23803–23811, DOI: [10.1039/D0TA06076C](https://doi.org/10.1039/D0TA06076C).
- 28 C. H. Mak, R. Liu, X. Han, Y. Tang, X. Zou, H. H. Shen, Y. Meng, G. Zou and H. Y. Hsu, Thermally Activated Delayed Phosphorescence and Interchromophore Exciton Coupling in a Platinum-Based Organometallic Emitter, *Adv. Opt. Mater.*, 2020, **8**(20), 2001023.



- 29 Y. Tang, C. H. Mak, R. Liu, Z. Wang, L. Ji, H. Song, C. Tan, F. Barrière and H. Y. Hsu, In Situ Formation of Bismuth-Based Perovskite Heterostructures for High-Performance Cocatalyst-Free Photocatalytic Hydrogen Evolution, *Adv. Funct. Mater.*, 2020, 2006919.
- 30 Y. Tang, C. H. Mak, J. Zhang, G. Jia, K.-C. Cheng, H. Song, M. Yuan, S. Zhao, J.-J. Kai and J. C. Colmenares, *et al.* Unravelling the Interfacial Dynamics of Bandgap Funneling in Bismuth-Based Halide Perovskites, *Adv. Mater.*, 2023, 35(2), 2207835, DOI: [10.1002/adma.202207835](https://doi.org/10.1002/adma.202207835).
- 31 Y. Tang, C. H. Mak, C. Wang, Y. Fu, F.-F. Li, G. Jia, C.-W. Hsieh, H.-H. Shen, J. C. Colmenares and H. Song, *et al.* Bandgap Funneling in Bismuth-Based Hybrid Perovskite Photocatalyst with Efficient Visible-Light-Driven Hydrogen Evolution, *Small Methods*, 2022, 6(8), 2200326, DOI: [10.1002/smt.202200326](https://doi.org/10.1002/smt.202200326).
- 32 F. Meng, Y. Jia, J. Wang, X. Huang, Z. Gui, L. Huang, R. Li, R. Chen, J. Xu and W. Chen, *et al.* Dopant-Free Hole Transporting Molecules for Highly Efficient Perovskite Photovoltaic with Strong Interfacial Interaction, *Sol. RRL*, 2019, 3(12), 1900319, DOI: [10.1002/solr.201900319](https://doi.org/10.1002/solr.201900319).
- 33 H.-Y. Hsu, H.-H. Hsieh, H.-Y. Tuan and J.-L. Hwang, Oxidized low density polyethylene: A potential cost-effective, stable, and recyclable polymeric encapsulant for photovoltaic modules, *Sol. Energy Mater. Sol. Cells*, 2010, 94(6), 955–959.
- 34 Y. Peng, C. H. Mak, J.-J. Kai, M. Du, L. Ji, M. Yuan, X. Zou, H.-H. Shen, S. P. Santoso and J. C. Colmenares, *et al.* Recent progress on post-synthetic treatments of photoelectrodes for photoelectrochemical water splitting, *J. Mater. Chem. A*, 2021, 9(47), 26628–26649, DOI: [10.1039/D1TA05935A](https://doi.org/10.1039/D1TA05935A).
- 35 Z. Chen, H.-Y. Hsu, M. Arca and K. S. Schanze, Triplet Energy Transport in Platinum-Acetylide Light Harvesting Arrays, *J. Phys. Chem. B*, 2015, 119(24), 7198–7209, DOI: [10.1021/jp509130b](https://doi.org/10.1021/jp509130b).
- 36 H.-Y. Hsu, L. Ji, C. Zhang, C. H. Mak, R. Liu, T. Wang, X. Zou, S.-Y. Leu and E. T. Yu, Ultra-stable 2D layered methylammonium cadmium trihalide perovskite photoelectrodes, *J. Mater. Chem. C*, 2018, 6(43), 11552–11560, DOI: [10.1039/C8TC02153H](https://doi.org/10.1039/C8TC02153H).
- 37 C. H. Mak, X. Huang, R. Liu, Y. Tang, X. Han, L. Ji, X. Zou, G. Zou and H.-Y. Hsu, Recent progress in surface modification and interfacial engineering for high-performance perovskite light-emitting diodes, *Nano Energy*, 2020, 73, 104752, DOI: [10.1016/j.nanoen.2020.104752](https://doi.org/10.1016/j.nanoen.2020.104752).
- 38 H.-Y. Hsu, L. Ji, M. Du, J. Zhao, T. Y. Edward and A. J. Bard, Optimization of Lead-free Organic–inorganic Tin (II) Halide Perovskite Semiconductors by Scanning Electrochemical Microscopy, *Electrochim. Acta*, 2016, 220, 205–210.
- 39 C. H. Mak, X. Han, M. Du, J.-J. Kai, K. F. Tsang, G. Jia, K.-C. Cheng, H.-H. Shen and H.-Y. Hsu, Heterogenization of homogeneous photocatalysts utilizing synthetic and natural support materials, *J. Mater. Chem. A*, 2021, 9(8), 4454–4504, DOI: [10.1039/D0TA08334H](https://doi.org/10.1039/D0TA08334H).
- 40 Y. Tang, C. H. Mak, G. Jia, K.-C. Cheng, J.-J. Kai, C.-W. Hsieh, F. Meng, W. Niu, F.-F. Li and H.-H. Shen, *et al.* Lead-free hybrid perovskite photocatalysts: surface engineering, charge-carrier behaviors, and solar-driven applications, *J. Mater. Chem. A*, 2022, 10(23), 12296–12316, DOI: [10.1039/D2TA01170K](https://doi.org/10.1039/D2TA01170K).
- 41 H. Wu, T. H. Tan, R. Liu, H.-Y. Hsu and Y. H. Ng, Selective Ethanol Oxidation to Acetaldehyde on Nanostructured Zeolitic Imidazolate Framework-8-Wrapped ZnO Photothermocatalyst Thin Films, *Sol. RRL*, 2021, 5(6), 2000423, DOI: [10.1002/solr.202000423](https://doi.org/10.1002/solr.202000423).
- 42 G. Zhu, Y. Yang, J. Liu, F. Liu, A. Lu and W. He, Enhanced photocurrent production by the synergy of hematite nanowire-arrayed photoanode and bioengineered *Shewanella oneidensis* MR-1, *Biosens. Bioelectron.*, 2017, 94, 227–234.
- 43 F. Zhang, S.-J. Yuan, W.-W. Li, J.-J. Chen, C.-C. Ko and H.-Q. Yu, WO₃ nanorods-modified carbon electrode for sustained electron uptake from *Shewanella oneidensis* MR-1 with suppressed biofilm formation, *Electrochim. Acta*, 2015, 152, 1–5.
- 44 E. Marsili, D. B. Baron, I. D. Shikhare, D. Coursolle, J. A. Gralnick and D. R. Bond, *Shewanella* secretes flavins that mediate extracellular electron transfer, *Proc. Natl. Acad. Sci. U. S. A.*, 2008, 105(10), 3968–3973.
- 45 D. Baron, E. LaBelle, D. Coursolle, J. A. Gralnick and D. R. Bond, Electrochemical measurement of electron transfer kinetics by *Shewanella oneidensis* MR-1, *J. Biol. Chem.*, 2009, 284(42), 28865–28873.
- 46 C. N. Durfor, B. A. Yenser and M. L. Bowers, Attachment of riboflavin derivatives to electrode surfaces, *J. Electroanal. Chem. Interfacial Electrochem.*, 1988, 244(1), 287–300, DOI: [10.1016/0022-0728\(88\)80111-6](https://doi.org/10.1016/0022-0728(88)80111-6).
- 47 C. Sumathi, P. Muthukumar, S. Radhakrishnan, G. Ravi and J. Wilson, Riboflavin detection by α -Fe₂O₃/MWCNT/AuNPs-based composite and a study of the interaction of riboflavin with DNA, *RSC Adv.*, 2015, 5(23), 17888–17896, DOI: [10.1039/C4RA14762F](https://doi.org/10.1039/C4RA14762F).
- 48 J. Wang, *Analytical Electrochemistry*, A John Wiley and Sons. Inc., New York, 2000, pp. 81–84.
- 49 N. K. Bhatti, M. S. Subhani, A. Y. Khan, R. Qureshi and A. Rahman, Heterogeneous electron transfer rate constants of viologen at a platinum disk electrode, *Turk. J. Chem.*, 2006, 29(6), 659–668.
- 50 N. K. Bhatti, M. S. Subhani, A. Y. Khan, R. Qureshi and A. Rahman, Heterogeneous electron transfer rate constants of viologen monocations at a platinum disk electrode, *Turk. J. Chem.*, 2006, 30(2), 165–180.
- 51 Z. He and F. Mansfeld, Exploring the use of electrochemical impedance spectroscopy (EIS) in microbial fuel cell studies, *Energy Environ. Sci.*, 2009, 2(2), 215–219, DOI: [10.1039/B814914C](https://doi.org/10.1039/B814914C).
- 52 Z. He, Y. Huang, A. K. Manohar and F. Mansfeld, Effect of electrolyte pH on the rate of the anodic and cathodic reactions in an air-cathode microbial fuel cell, *Bioelectrochemistry*, 2008, 74(1), 78–82, DOI: [10.1016/j.bioelechem.2008.07.007](https://doi.org/10.1016/j.bioelechem.2008.07.007).
- 53 S.-J. Yuan, H. He, G.-P. Sheng, J.-J. Chen, Z.-H. Tong, Y.-Y. Cheng, W.-W. Li, Z.-Q. Lin, F. Zhang and H.-Q. Yu, A photometric high-throughput method for identification of electrochemically active bacteria using a WO₃ nanocluster probe, *Sci. Rep.*, 2013, 3(1), 1315.



- 54 Y.-J. Chen and L.-Y. Chen, The study of carrier transfer mechanism for nanostructural hematite photoanode for solar water splitting, *Appl. Energy*, 2016, **164**, 924–933.
- 55 Y. Wang, B. Li, L. Zeng, D. Cui, X. Xiang and W. Li, Polyaniline/mesoporous tungsten trioxide composite as anode electrocatalyst for high-performance microbial fuel cells, *Biosens. Bioelectron.*, 2013, **41**, 582–588.

