



Cite this: *Nanoscale*, 2025, **17**, 5823

Stepwise kinetics of the early-stage nucleation in chiral perovskites *via ab initio* molecular dynamics and free-energy calculations†

Mariagrazia Fortino,^a Gioacchino Schifino,^a Matteo Salvaglio ^b and
Adriana Pietropaolo *^a

This study provides a comprehensive molecular-level understanding of the early-stage nucleation process in chiral hybrid organic–inorganic perovskites (HOIPs). A combination of *ab initio* molecular dynamics (AIMD) based on density functional theory (DFT) and parallel bias metadynamics simulations was designed to explore a broad spectrum of the nucleation scenarios, disclosing how structural deviations affect the formation of chiral aggregates at the atomic scale. The workflow uses parallel replicas initialized from configurations characterised by different root-mean-square deviations (RMSD) relative to the crystallographic coordinates of the chiral ligands. The free-energy landscape and the kinetic pathways involved in chiral aggregate formation indicate a stepwise mechanism that governs the transition from disordered to chiral states. The computed free-energy barriers and corresponding transition timescales uncover several critical stages in this process, including rapid initial relaxations as well as slower, free-energy-intensive steps, with overall timescales on the order of microseconds as the system approaches its most chiral configuration.

Received 12th November 2024.

Accepted 7th January 2025

DOI: 10.1039/d4nr04735d

rsc.li/nanoscale

Introduction

Hybrid organic–inorganic perovskites (HOIP) have emerged as a rapidly advancing class of materials, attracting significant attention due to their remarkable optoelectronic properties and potential applications in diverse technological areas.^{1–4} These include photovoltaics,^{5–7} light-emitting diodes,^{8–13} photodetectors^{14–19} as well as photonic lasers.^{20–22} One emerging field is the one of chiral hybrid perovskite, featuring the integration of chiral organic molecules into the perovskite framework. Chiral perovskites exhibit unique symmetry-breaking features that introduce peculiar properties with interesting applications in chiroptoelectronics, sensing, as well as quantum computing.^{23–29}

Chiral HOIPs typically adopt low-dimensional layered structures with inherent structural flexibility. Combined with their versatile elemental composition, this can induce chirality when appropriate chiral organic cations are incorporated. The synthesis of chiral perovskites using chiral ligands was first

demonstrated for 1D and 2D single crystals in 2003 and 2006, respectively.^{30,31} Interest in chiral perovskites started in 2017 with the first chiroptical study.³² Since then, numerous contributions have highlighted their distinctive chiral signatures.^{33,34} Despite the growing experimental interest in these materials, their formation mechanisms at the molecular level are still poorly understood. Chiral perovskites can be synthesized through various methods, including solvent-based approaches, melt synthesis, and re-evaporation techniques, each offering unique advantages and challenges.³⁵ Regardless of the synthesis method, the early stages of nucleation are crucial, as they dictate the structural and chiroptical properties of the final material. In this study, we focus specifically on the early-stage nucleation process to unravel the fundamental mechanisms governing the formation of chiral aggregates.^{36,37}

A comprehensive understanding of the chiral nucleation and growth mechanisms, especially in terms of how chirality influences the formation of perovskite aggregates, is crucial for tailoring these materials for specific applications. However, unraveling the complex interplay between chirality, molecular interactions and aggregate formation processes necessitates advanced theoretical approaches.

In this work, we employ a state-of-the-art computational approach combining *ab initio* quantum mechanical methods with parallel bias metadynamics³⁸ simulations to study the early stages of nucleation and chiral aggregate formation in

^aDipartimento di Scienze della Salute, Università "Magna Graecia" di Catanzaro, Catanzaro 88100, Italy. E-mail: apietropaolo@unicz.it

^bThomas Young Centre and Department of Chemical Engineering, University College London, London WC1E 7JE, UK

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d4nr04735d>

All the replicas were initialized from distorted configurations, with different root-mean-square deviation (RMSD) values, from 0 Å to 6 Å, relative to the crystallographic configuration of the chiral ligands. This setup enabled exploring a wide range of possible scenarios where chiral structures emerge from disordered molecular environments, thus elucidating how chiral crystalline arrangements nucleate at the atomic level (Scheme 2). Those simulations reveal crucial

insights into the free energy landscape underpinning the nucleation of chiral environments, offering a detailed view of the transformation pathways and providing information on the associated ordering kinetics. The free-energy profile reconstructed from parallel bias simulations indicates that the transition from disordered to chiral configurations follows a step-wise mechanism, with overall timescales on the order of microseconds. This study provides a fundamental framework for understanding the early-stage formation mechanisms in chiral perovskites and highlights how theoretical methods can tailor experimental analysis.

The computed free-energy profile indicates that the transition from disordered to chiral configurations for the *S*-MBA₂PbI₄ chiral HOIP follows a stepwise mechanism. The discrete stages along the transformation from disorder to chiral order observed in the AIMD simulations emerge as key features of the configurational landscape associated with the ordering process.

Fig. 1a presents the one-dimensional free-energy profile derived from *ab initio* parallel bias metadynamics simulations as a function of RMSD values, capturing deviations in the positions of the four ligands within the unit cell from a perfectly ordered chiral configuration of *S*-MBA₂PbI₄ chiral perovskite (Fig. 1a).


The free-energy surface reveals several local minima, each corresponding to long-lived, metastable ensembles of configurations of MBA_2PbI_4 with progressively higher levels of local chirality. Fig. 1b shows the potential energy surface, calculated by averaging the potential energy across configurations at fixed RMSD values. This potential-energy profile also displays multiple local minima, although the absolute minimum differs between the two profiles.

Fig. 1a shows the transitions between these metastable states as stages 1 to 4, which mark the progression from the most disordered to the most chiral perovskite configurations.


It is worth highlighting that the term ‘most chiral perovskite’ is used to indicate the most ordered configuration, as it reflects the highest degree of structural order and alignment with the chiral reference configuration observed during the nucleation process.

Starting from a disordered arrangement, the first transition corresponding to stage 1 occurs as the RMSD decreases from 3.0 Å to 2.1 Å, overcoming a free-energy barrier of 4.3 kcal mol⁻¹. At stage 2, a 3 kcal mol⁻¹ barrier is encountered, leading to the global free-energy minimum at an RMSD approaching 1.2 Å. Comparison with the potential-energy profile (Fig. 1b) indicates that this absolute minimum represents an entropic minimum since, upon removing the kinetic effects, the minimum shifts towards an RMSD closer to 0 Å.

A 7 kcal mol⁻¹ barrier is then required to further reduce the RMSD to 1.0 Å during stage 3. Finally, the most free-energy-

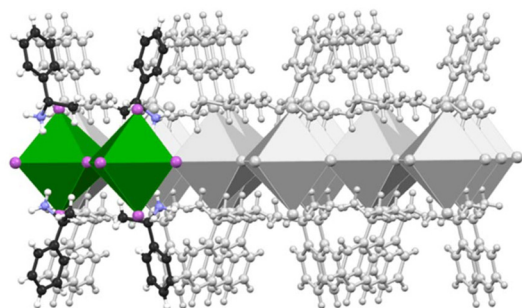

Scheme 1 Schematic representation of the investigated $S\text{-MBA}_2\text{PbI}_4$ structure under periodic boundary conditions. The unit cell used in the simulations comprises two metal–halide octahedra and four organic ligands, shown with coloured ball and stick models and polyhedra. A grey overlay illustrates the periodicity accounted for during the calculations.

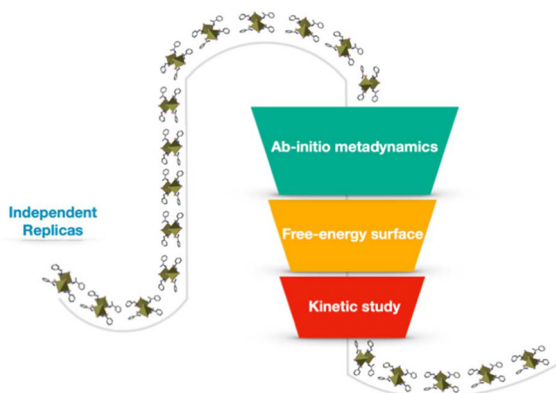

Scheme 2 Schematic representation of the computational workflow used in this study. The workflow includes AIMD simulations combined with parallel bias metadynamics across 10 independent simulation replicas at different RMSD values, followed by the reconstruction of the free-energy surface. A kinetic analysis was conducted based on the identified free-energy barriers.

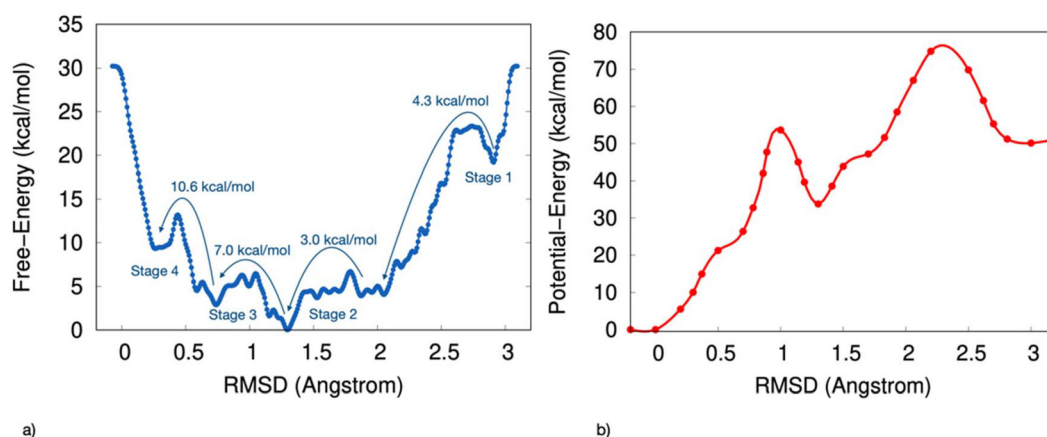


Fig. 1 (a) Mono-dimensional free-energy surface as a function of the RMSD value, which measures the deviation of the two ligand pairs from their positions in the reference structure. (b) The potential energy surface, as a function of the RMSD value, is calculated by averaging the potential energy across configurations at fixed RMSD values.

intensive step occurs from 0.7 Å to 0.3 Å in RMSD, corresponding to stage 4 and requires overcoming a barrier of 10.6 kcal mol⁻¹.

The rate constants were estimated from the calculated free-energy barriers using the procedure outlined in the Methods section and are reported in Table 1. These values provide insights into each stage's relative stability and timescale within the chiral nucleation pathway, identifying the kinetics associated with each transition.

Table 1 Predicted rate constants of the chiral nucleation of S-MBA₂PbI₄ hybrid perovskite

Stage	k (ps ⁻¹)	Time
1 (RMSD 3.0–2.1 Å)	4.4×10^{-3}	227 ps
2 (RMSD 2.1–1.3 Å)	3.9×10^{-2}	26 ps
3 (RMSD 1.3–0.7 Å)	4.6×10^{-5}	21 ns
4 (RMSD 0.7–0.3 Å)	1.1×10^{-7}	9 μs

The first two stages (stage 1 and stage 2) occur on a time-scale of picoseconds. A kinetic constant of 4.4×10^{-3} ps⁻¹ was calculated for stage 1, corresponding to a time of 227 ps, while stage 2 has a kinetic constant of 3.9×10^{-2} ps⁻¹ and a time of 26 ps. As illustrated in Fig. 2, these stages represent a transition from a highly disordered configuration where the ligands are arranged in a disposition with minimal interactions among them to a configuration with a chiral degree (with an RMSD value of 1.2 Å) characterized by a more packed arrangement of the ligands. This chiral ordering is stabilized by salt-bridge interactions between the NH₃⁺ groups of the aromatic ring and the iodide atoms of the inorganic octahedra, with a distance approaching 2.4 Å. Stage 3 occurs on a nano-second timescale, with a computed kinetic constant of 4.6×10^{-5} ps⁻¹ and a time of 21 ns. During this stage, the transition toward the most chiral perovskite configuration involves displacements in the positions of the ligands in a staggered arrangement of the aromatic molecules along the C₂-axis. This also leads to minor adjustments in the inorganic octahedra,

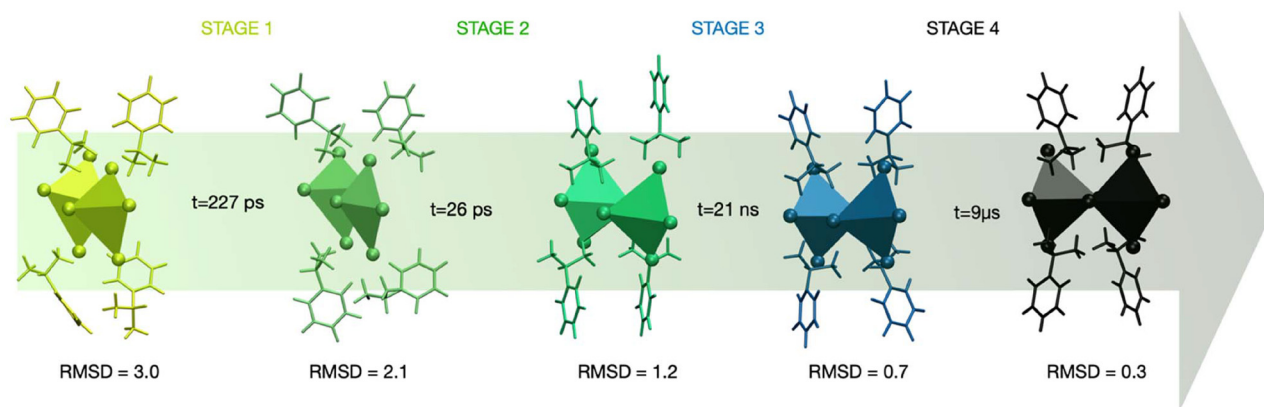


Fig. 2 Schematic illustration of S-MBA₂PbI₄ configurations, highlighting various RMSD values obtained from the predicted free energy minima. The transition from a highly disordered ligands configuration toward the most chiral perovskite-like configuration is represented.

The RMSD relative to the ligand positions in the relaxed structure was used as a collective variable (CV). RMSD values were calculated for the pairs of ligands and represents the average deviation of all four ligand positions from the reference structure. Upper and lower walls have been defined, as implemented in the plumed plugin, to limit the region of the phase space accessible during the simulation, using the following collective variable (σ_d^2):

$$\sigma_d^2 = \frac{1}{(i-1)} \sum (d_i - d_{\text{ref}})^2 \quad (1)$$

where d_{ref} corresponds to the crystallographic coordination distance of 3.2 Å, whereas d_i is the instantaneous coordination of the i th distance.

Methods

Ab initio steered molecular dynamics (SMD) simulations have been conducted to increase the disorder of the spatial organization of the ligands around the inorganic octahedra of the *S*-MBA₂PbI₄ chiral perovskite, thereby generating the initial configurations for the parallel-bias metadynamics replicas. The initial periodic model used for the *ab initio* SMD simulations derives from the crystallographic coordinates of the *S*-MBA₂PbI₄ chiral perovskite reported by Jana *et al.*³⁹ and available in the Cambridge Crystallographic Data Center (CCDC) database with deposition number 2015617. The model includes two inorganic [PbI₆]^{4−} octahedral layers and four chiral MBA chains of the *S*-enantiomeric models to maintain a 2:1 stoichiometric ligand–perovskite ratio consistent with experimental reports.

The coordinates were first optimized using the PBE functional with Quantum Espresso software^{41,42} under periodic

Gaussians with an initial height of 0.4 kcal mol⁻¹ and a width of 0.05 Å were deposited with a stride of 1 fs. The simulations were conducted in the NVT ensemble using a velocity-rescaling thermostat to maintain the temperature. A time step of 1 fs and a temperature of 300 K were employed with a total simulation time of 300 ps.

The transition time from the disordered configuration to the chiral one has been evaluated as the inverse of the kinetics constant, computed as follows:

$$k = \frac{aK_{\text{B}}T}{h} \cdot e^{\frac{-\Delta F^{\ddagger}}{RT}} \quad (2)$$

where a is the transmission coefficient (equal to one in the non-recrossing assumption of transition state theory), K_{B} is Boltzmann's constant, $\Delta F^{\ddagger}$ is the free-energy barrier, and h is Planck's constant.

The potential energy profile was calculated by averaging the potential energy values obtained from the simulated *ab initio* trajectories across configurations extracted from the computed free-energy minima while maintaining fixed RMSD values. To evaluate the reliability of these averaged values, single-point PBE-D3 calculations were performed using Quantum Espresso software on a selection of configurations, each with RMSD values of 0.0, 0.5, 1.0, 1.5, 2.0, 2.5, and 3.0 Å. A comparison between the single-point PBE-D3 potential energy and the averaged potential energy values is presented in the ESI†

Conclusions

Overall, this study presents a detailed molecular-level understanding of the early-stage emergence of chirality during the assembly of the S-MBA₂PbI₄ chiral hybrid perovskite through a combination of *ab initio* molecular dynamics and parallel bias metadynamics simulations. A stepwise mechanism governing the transition from disordered to chiral configurations was disclosed by reconstructing the free-energy landscape and estimating the kinetics along the pathway that emerged from configurational space exploration. The calculated free-energy barriers and corresponding timescales highlight key stages in this process, starting from rapid initial transitions to slower free-energy-intensive stages, as the low-dimensional hybrid perovskite approaches its most ordered chiral state. This latter reaching the C₂ axis, with estimated timescales on the order of microseconds. The ability to map kinetic barriers and timescales offers valuable insights that complement experimental efforts, paving the way for future investigations to optimize the design and functionality of chiral perovskites. Overall, this work provides a fundamental framework for understanding the dynamics of local ordering of chiral perovskites to uncover the mechanisms that drive their chiral nucleation.

Author contributions

MF and GS carried out the simulations, MG, GS, MS, AP planned the simulation workflows, MG, MS, AP wrote the manuscript.

Data availability

The data supporting this article have been included as part of the ESI† and are available on the PLUMED-NEST repository – <https://www.plumednest.org/>.

Conflicts of interest

The authors declare no conflict of interest.

Acknowledgements

The Italian Ministry for University and Research (MUR) and University “Magna Graecia” of Catanzaro are acknowledged for the financial support under PON “RICERCA E INNOVAZIONE” 2014–2020, ASSE IV “ISTRUZIONE E RICERCA PER IL RECUPERO” AZIONE IV.4 “DOTTORATI E CONTRATTI DI RICERCA SU TEMATICHE DELL’INNOVAZIONE” D. M. 1062/2021 program and under the research program PRIN20228PH3JX. We acknowledge the CINECA award under the ISCRA initiative, for the availability of high-performance computing resources and support. MS acknowledges funding from the ht-MATTER UKRI Frontier Research Guarantee Grant (EP/X033139/1).

References

- 1 A. Kojima, K. Teshima, Y. Shirai and T. Miyasaka, *J. Am. Chem. Soc.*, 2009, **131**, 6050.
- 2 M. M. Lee, J. Teuscher, T. Miyasaka, T. N. Murakami and H. J. Snaith, *Science*, 2012, **338**, 643.
- 3 Z. Li, T. R. Klein, D. H. Kim, M. Yang, J. J. Berry, M. F. A. M. van Hest and K. Zhu, *Nat. Rev. Mater.*, 2018, **3**, 18017.
- 4 Y. Fu, H. Zhu, J. Chen, M. P. Hautzinger, Y. X. Zhu and S. Jin, *Nat. Rev. Mater.*, 2019, **4**, 169.
- 5 D. H. Cao, C. C. Stoumpos, O. K. Farha, J. T. Hupp and M. G. Kanatzidis, *J. Am. Chem. Soc.*, 2015, **137**, 7843.
- 6 N. J. Jeon, H. Na, E. H. Jung, T. Y. Yang, Y. G. Lee, G. Kim, H. W. Shin, S. I. Seok, J. Lee and J. Seo, *Nat. Energy*, 2015, **3**, 682.
- 7 A. Filippetti, A. Kahmann, C. Caddeo, A. Mattoni, M. Saba, A. Bosin and M. A. Loi, *J. Mater. Chem. A*, 2021, **9**, 11812.
- 8 N. Wang, L. Cheng, R. Ge, S. Zhang, Y. Miao, W. Zou, C. Yi, Y. Sun, Y. Cao, R. Yang, Y. Wei, Q. Guo, Y. Ke, M. Yu, Y. Jin, Q. Ding, D. Di, L. Yang, G. Xing, H. Tian, C. Jin and F. Gao, *Nat. Photonics*, 2016, **10**, 699.
- 9 X. Yang, X. Zhang, J. Deng, Z. Chu, Q. Jiang, J. Meng, P. Wang, L. Zhang, Z. Yin and J. You, *Nat. Commun.*, 2018, **9**, 570.
- 10 Y. Zou, Q. Huang, Y. Yang, M. Ban, S. Li, Y. Han, T. Wu, Y. Tan, X. Gao, T. Song and B. Sun, *Adv. Mater. Interfaces*, 2018, **5**, 1801030.



- 11 J. Byun, H. Cho, C. Wolf, M. Jang, A. Sadhanala, R. H. Friend, H. Yang and T. W. Lee, *Adv. Mater.*, 2016, **28**, 7515.
- 12 J. Xing, Y. Zhao, M. Askerka, L. N. Quan, X. Gong, W. Zhao, J. Zhao, H. Tan, G. Long, L. Gao, Z. Yang, O. Voznyy, J. Tang, Z.-H. Lu, Q. Xiong and E. H. Sargent, *Nat. Commun.*, 2018, **9**, 3541.
- 13 W. Su and Y. Fanglong, *Trends Chem.*, 2022, **4**, 965.
- 14 J. Li, J. Wang, Y. Zhang, H. Wang, G. Lin, X. Xiong, W. Zhou, H. Luo and D. Li, *2D Mater.*, 2018, **5**, 021001.
- 15 Y. Chen, Y. Sun, J. Peng, J. Tang, K. Zheng and Z. Liang, *Adv. Mater.*, 2018, **30**, 1703487.
- 16 L. Ji, H. Y. Hsu, J. C. Lee, A. J. Bard and E. T. Yu, *Nano Lett.*, 2018, **18**, 994.
- 17 L. Dou, Y. M. Yang, J. You, Z. Hong, W. H. Chang, G. Li and Y. Yang, *Nat. Commun.*, 2014, **5**, 5404.
- 18 K. Leng, I. Abdelwahab, I. Verzhbitskiy, M. Telychko, L. Chu, W. Fu, X. Chi, N. Guo, Z. Chen, C. Zhang, Q. H. Xu, J. Lu, M. Chhowalla, G. Eda and K. P. Loh, *Nat. Mater.*, 2018, **17**, 908.
- 19 J. Li, J. Wang, J. Ma, H. Shen, L. Li, X. Duan and D. Li, *Nat. Commun.*, 2019, **10**, 806.
- 20 B. R. Sutherland and E. H. Sargent, *Nat. Photonics*, 2016, **10**, 295.
- 21 H. Zhu, Y. Fu, F. Meng, X. Wu, Z. Gong, Q. Ding, M. V. Gustafsson, M. T. Trinh, S. Jin and X. Y. Zhu, *Nat. Mater.*, 2015, **14**, 636.
- 22 C. M. Raghavan, T. P. Chen, S. S. Li, W. L. Chen, C. Y. Lo, Y. M. Liao, G. Haider, C. C. Lin, C. C. Chen, R. Sankar, Y. M. Chang, F. C. Chou and C. W. Chen, *Nano Lett.*, 2018, **18**, 3221.
- 23 Y. Shi, P. Duan, S. Huo, Y. Li and M. Liu, *Adv. Mater.*, 2018, **30**, 1705011.
- 24 C. Yuan, X. Li, S. Semin, Y. Feng, T. Rasing and J. Xu, *Nano Lett.*, 2018, **18**, 5411.
- 25 G. Long, C. Jiang, R. Sabatini, Z. Yang, M. Wei, L. N. Quan, Q. Liang, A. Rasmita, M. Askerka, G. Walters, X. Gong, J. Xing, X. Wen, R. Quintero-Bermudez, H. Yuan, G. Xing, X. Wang, D. Song, O. Voznyy, M. Zhang, S. Hoogland, W. Gao, Q. Xiong and E. H. Sargent, *Nat. Photonics*, 2018, **12**, 528.
- 26 Y. Yang, R. C. Da Costa, M. J. Fuchter and A. J. Campbell, *Nat. Photonics*, 2013, **7**, 634.
- 27 S. Apergi, G. Brocks and S. Tao, *J. Phys. Chem. Lett.*, 2023, **14**, 11565.
- 28 Y. Zheng, X. Han, P. Cheng, X. Jia, J. Xu and H. Bu, *J. Am. Chem. Soc.*, 2022, **144**, 16471.
- 29 H. Zheng, A. Ghosh, M. J. Swamynadhan, Q. Zhang, W. P. D. Wong, Z. Wu, R. Zhang, J. Chen, F. Cimpoesu, S. Ghosh, B. J. Campbell, K. Wang, A. Stroppa, R. Mahendiran and K. P. Loh, *Nat. Commun.*, 2024, **15**, 5556.
- 30 D. G. Billing and A. Lemmerer, *Acta Crystallogr., Sect. E: Struct. Rep. Online*, 2003, **59**, m381.
- 31 D. G. Billing and A. Lemmerer, *CrystEngComm*, 2006, **8**, 686.
- 32 J. Ahn, E. Lee, J. Tan, W. Yang, B. Kim and J. Moon, *Mater. Horiz.*, 2017, **4**, 851.
- 33 H. Dui and M. A. Loi, *Matter*, 2021, **4**, 3835.
- 34 M. Fortino, A. Mattoni and A. Pietropaolo, *J. Mater. Chem. C*, 2023, **11**, 9135.
- 35 S. Driessen, S. Sarigul-Ozbek, C. M. Sutter-Fella and S. Tao, *J. Phys.: Energy*, 2024, **6**, 042001.
- 36 M. Moroni, C. Coccia and L. Malavasi, *Chem. Commun.*, 2024, **60**, 9310.
- 37 A. Pietropaolo, A. Mattoni, G. Pica, M. Fortino, G. Schifino and G. Grancini, *Chem*, 2022, **8**, 1231.
- 38 J. Pfäendtner and M. Bonomi, *J. Chem. Theory Comput.*, 2015, **11**, 5062.
- 39 M. K. Jana, R. Song, H. Liu, D. R. Khanal, S. M. Janke, R. Zhao, C. Liu, Z. V. Vardeny, V. Blum and D. B. Mitzi, *Nat. Commun.*, 2020, **11**, 4699.
- 40 M. Pols, G. Brocks and S. Tao, *J. Phys. Chem. Lett.*, 2024, **15**(31), 8057.
- 41 P. Giannozzi, S. Baroni, N. Bonini, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, G. L. Chiarotti, M. Cococcioni, I. Dabo, *et al.*, *J. Phys.: Condens. Matter*, 2009, **21**, 395502.
- 42 P. Giannozzi, O. Andreussi, T. Brumme, O. Bunau, M. Buongiorno Nardelli, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, M. Cococcioni, *et al.*, *J. Phys.: Condens. Matter*, 2017, **29**, 465901.
- 43 S. Grimme, A. Hansen, J. G. Brandenburg and C. Bannwarth, *Chem. Rev.*, 2016, **116**(9), 5105.
- 44 The PLUMED consortium, *Nat. Methods*, 2019, **16**, 670.
- 45 G. Bussi, D. Donadio and M. Parrinello, *J. Chem. Phys.*, 2007, **126**, 014101.
- 46 M. Fortino, A. Mattoni and A. Pietropaolo, *J. Phys.: Mater.*, 2024, **7**, 045009.

