


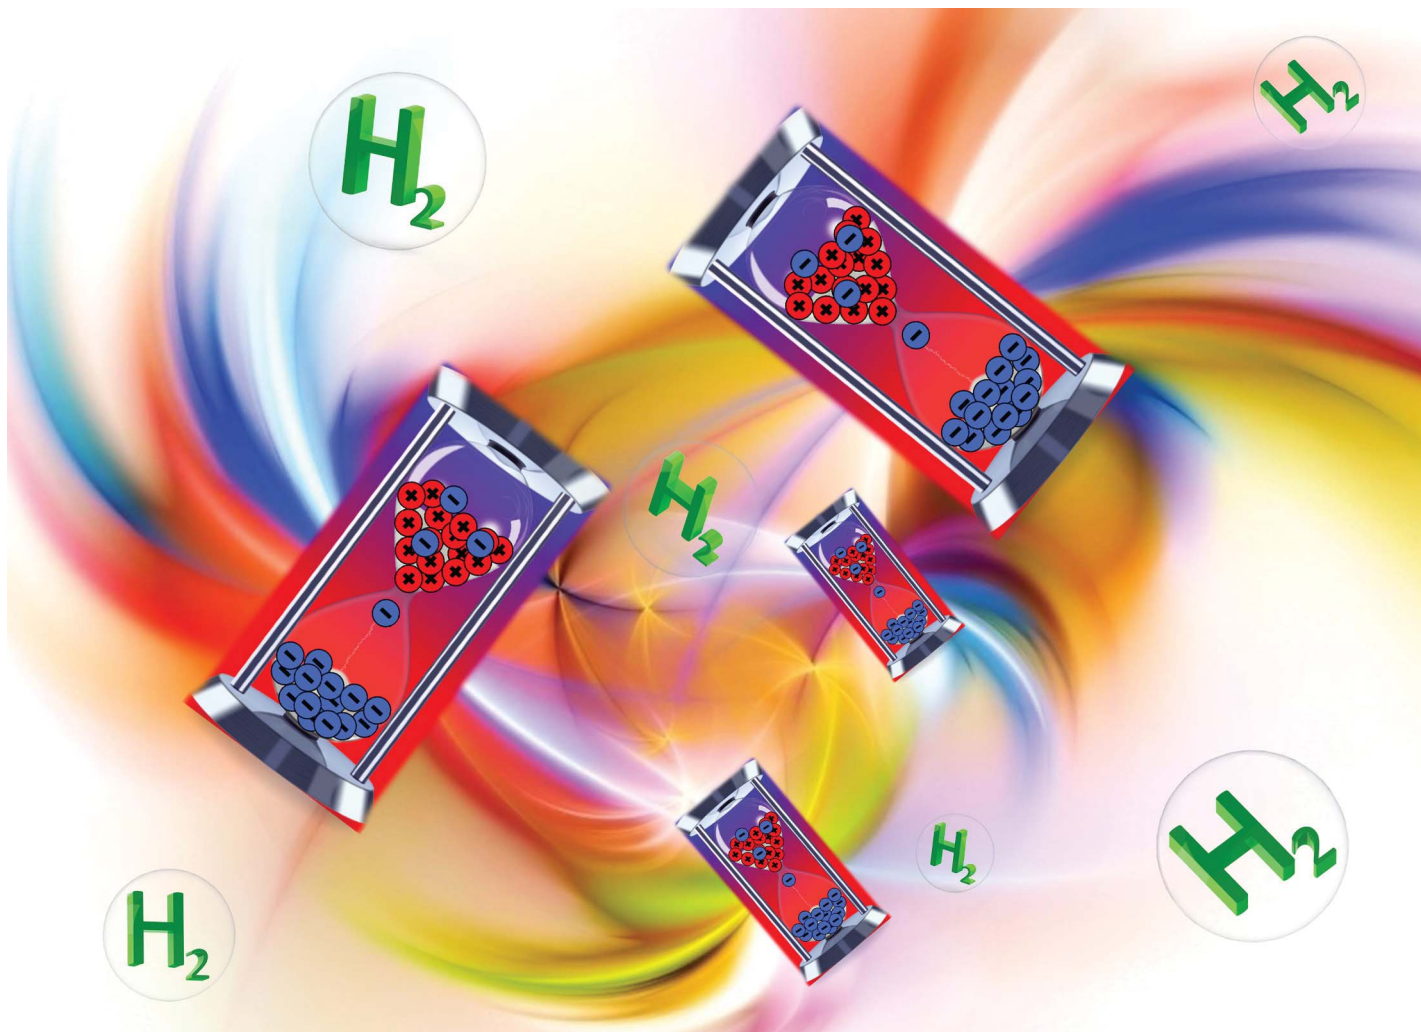

Showcasing research from Jinlong Gong's laboratory, School of Chemical Engineering and Technology, Tianjin University, China.

Gradient doping of phosphorus in Fe_2O_3 nanoarray photoanodes for enhanced charge separation

This paper describes the design and synthesis of a Fe_2O_3 photoanode with gradient incorporation of phosphorus employing a facile dipping and annealing method to improve the charge separation for enhanced photoelectrochemical water oxidation. This gradient P incorporation increases the width of band bending over a large region in Fe_2O_3 , which is crucial for promoting the charge separation efficiency in the bulk.

As featured in:



See Tuo Wang, Jinlong Gong et al., *Chem. Sci.*, 2017, 8, 91.



rsc.li/chemical-science

Registered charity number: 207890

CrossMark
click for updatesCite this: *Chem. Sci.*, 2017, 8, 91

Gradient doping of phosphorus in Fe₂O₃ nanoarray photoanodes for enhanced charge separation†

Zhibin Luo,^{ab} Chengcheng Li,^{ab} Shanshan Liu,^{ab} Tuo Wang^{*ab} and Jinlong Gong^{*ab}

Hematite (α -Fe₂O₃) is a promising candidate for solar-to-hydrogen energy conversion. However, the low carrier mobility and extremely high charge recombination rate limit the practical application of hematite in solar water splitting. This paper describes the fabrication of a Fe₂O₃ photoanode with gradient incorporation of phosphorus (P) employing a facile dipping and annealing method to improve the charge separation for enhanced photoelectrochemical water oxidation. This gradient P incorporation increases the width of band bending over a large region in Fe₂O₃, which is crucial for promoting the charge separation efficiency in the bulk. Although both gradient and homogeneous P-incorporated Fe₂O₃ samples exhibit similar electrical conductivity, the Fe₂O₃ electrode with a gradient P concentration presents an additional charge separation effect. A photocurrent of $\sim 1.48 \text{ mA cm}^{-2}$ is obtained at 1.23 V vs. reversible hydrogen electrode (vs. RHE) under air mass 1.5G illumination. Additionally, the H₂O oxidation kinetics of Fe₂O₃ with gradient P incorporation was further improved upon loading cobalt phosphate as cocatalyst, reaching a photocurrent of $\sim 2.0 \text{ mA cm}^{-2}$ at 1.23 V vs. RHE.

Received 18th August 2016
Accepted 2nd October 2016

DOI: 10.1039/c6sc03707k

www.rsc.org/chemicalscience

Introduction

The rocketing demand for energy supplies has depleted fossil fuels and has caused global environmental problems.^{1,2} Since the initial work on light-driven water splitting over TiO₂, photoelectrochemical (PEC) water splitting harvesting sunlight has been widely accepted as one of the most promising routes for hydrogen production.^{3,4} Hematite (α -Fe₂O₃) is a nontoxic and photostable n-type semiconductor with an indirect bandgap of about 2.1 eV,⁵ which can theoretically allow the utilization of approximately 40% of the solar spectrum. However, relatively poor conductivity, rapid electron-hole recombination rates, short hole diffusion length (2–4 nm) and sluggish oxygen-evolution kinetics are intrinsic limitations of hematite for effective solar water splitting.⁶ Various strategies have been proposed to address these obstacles, including element doping, nanostructure engineering, and surface modifications (such as depositing passivation layers and oxygen-evolution cocatalysts).⁷

Recently, progress has been achieved to address the limitations of hematite through improving solar conversion efficiency via several strategies. Grätzel and co-workers fabricated Si-doped dendritic hematite films with an outstanding PEC

performance.⁵ Sn-doped hematite nanowires synthesized by Li and co-workers also showed a remarkable photocurrent density.⁸ Sivula *et al.* demonstrated that mesoporous hematite yielded impressive water-oxidation photocurrents.⁹ Phosphorus (P) doped hematite reported by Chen and co-workers exhibited an extraordinary PEC performance owing to the enhanced electron mobility.¹⁰ Wang and colleagues attained a recorded turn-on voltage of 0.45 V *versus* reversible hydrogen electrode (vs. RHE) with NiFeO_x cocatalyst.¹¹ Lee and co-workers prepared a unique single-crystalline “wormlike” morphological hematite photoanode modified by platinum incorporation and achieved a stable, record-breaking performance.¹²

According to the aforementioned achievements, well-aligned one-dimensional (1-D) nanostructures can offer short diffusion distances for minority carrier transport, large surface area for interfacial charge collection, as well as a long optical path for light harvesting. Meanwhile, reactive ballistic deposition (RBD) technique is a versatile method to fabricate highly-oriented and well-defined 1-D nanostructures without introducing undesired impurities. The morphology, surface area and well-aligned nanobundle structure of hematite films can be tailored by the RBD technique.

Introduction of metallic¹³ or nonmetallic¹⁰ dopants is a promising strategy to increase the electron mobility of hematite for improved photocatalytic efficiency. P stands out as a promising candidate for hematite doping, which substitutes Fe atoms as an n-type dopant. As an electron donor, nonmetallic P possesses more valence electrons than Si, Ti, Co and many other doping elements. Additionally, P–O bonds in hematite exhibit

^aKey Laboratory for Green Chemical Technology of Ministry of Education, School of Chemical Engineering and Technology, Tianjin University, Tianjin 300350, China. E-mail: jlgong@tju.edu.cn; wangtuo@tju.edu.cn

^bCollaborative Innovation Center of Chemical Science and Engineering, Tianjin 300350, China

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c6sc03707k

a more covalent nature than other dopant-O bonds, which can effectively avoid the formation of deep electron trapping sites in hematite.¹⁰ Although P incorporation in hematite has been well recognized to improve the conductivity for better charge transportation, the charge recombination in hematite remains a problem. Thus, an element incorporation strategy that improves the charge separation efficiency in bulk hematite is urgently needed.

This paper describes the design and fabrication of highly oriented hematite nanobundle array with gradient P incorporation using RBD followed by a facile dipping and annealing method. The gradient distributed P concentration in the hematite can increase its conductivity, as well as induce a more upward band bending within a widened region, facilitating charge separation across the radial direction of hematite nanobundle. Further introducing a thin layer of cobalt phosphate (Co-Pi) as cocatalyst can improve the PEC performance of hematite by accelerating the oxygen evolution reaction (OER) kinetics.

Results and discussion

The fabrication process of the Fe_2O_3 photoanode is illustrated in Scheme 1. Highly oriented Fe_2O_3 nanobundle arrays (Fig. 1a) were grown on fluorine-doped tin oxide (FTO) glass substrate employing a homemade RBD system by evaporating metallic Fe metal in a high vacuum chamber with oxygen as the reactive gas (Scheme 1a). The prepared 1-D Fe_2O_3 nanobundle arrays are expected to be efficient in charge transportation by shortening the pathway the minority carriers have to travel. The minority carriers could flow through a direct radial pathway of the nanobundle. The P precursor was then introduced to establish a gradient incorporation concentration in Fe_2O_3 nanobundles (denoted as grad-P: Fe_2O_3), which was achieved *via* a facile solution immersion combined with a short-time thermal treatment (750 °C for 10 min, details in the Experimental section) (Scheme 1b). Subsequently, a thin layer of Co-Pi cocatalyst was deposited to accelerate the water-oxidation reaction on the surface of Fe_2O_3 (grad-P: Fe_2O_3 /Co-Pi) (Scheme 1c). The use of element doping/incorporation to enhance the


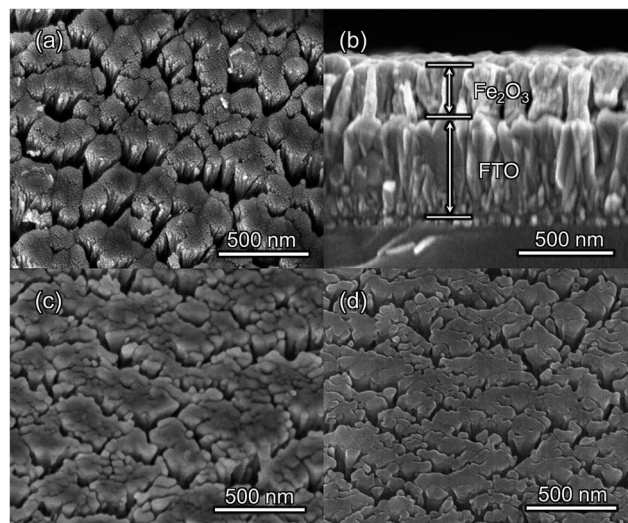


Fig. 1 SEM images of (a) top-view and (b) side-view of bare Fe_2O_3 (500 °C for 2 h); top-view of (c) bare Fe_2O_3 (750 °C for 10 min after 500 °C for 2 h) and (d) grad-P: Fe_2O_3 (750 °C for 10 min after 500 °C for 2 h).

conductivity is a well-established concept in semiconductor physics.¹⁴ Although the promoted charge conductivity of Fe_2O_3 has been well recognized by element doping/incorporation, the high charge recombination rate in bulk Fe_2O_3 still remains a challenge. Hence we propose to carefully control the P doping concentration with a gradient profile in Fe_2O_3 to widen the band bending region, thus promoting the charge separation efficiency in the bulk.

In our study, short-time thermal treatment (750 °C for 10 min) can induce gradient P incorporation, where the P concentration decreases gradually from the surface to the core of the Fe_2O_3 nanobundles. As will be discussed later, the gradient change of P concentration in the Fe_2O_3 nanobundle can widen the band bending region, which improves the separation of charge carriers, for enhanced PEC performance.¹⁵ On the other hand, a relatively long-time thermal treatment (750 °C for 30 min, details in the Experimental section) attains a homogeneous P-incorporated Fe_2O_3 photoanode (denoted as homo-P: Fe_2O_3).¹⁶

The morphologies of the as-prepared bare Fe_2O_3 and grad-P: Fe_2O_3 nanobundle array thin films were examined by scanning electron microscopy (SEM) (Fig. 1). Tilted Fe_2O_3 nanobundle arrays are found to be well-aligned on the FTO substrate (Fig. 1a). The thickness of these thin films is 200 ± 10 nm according to the side-view SEM (Fig. 1b). Comparing the morphology of the Fe_2O_3 thin films with and without P incorporation, slight aggregation and shrinkage occur upon the thermal treatment (750 °C for 10 min) (Fig. 1c and d). This rapid thermal treatment induces gradient concentration of P in Fe_2O_3 as well as increasing the crystallinity of Fe_2O_3 . The improved crystallinity of Fe_2O_3 upon annealing at 750 °C has been confirmed by high-resolution transmission electron microscopy (HRTEM) (ESI, Fig. S1†). The visual color of both bare Fe_2O_3 and grad-P: Fe_2O_3 nanobundle array thin films are reddish (ESI, Fig. S2†), and there is no remarkable color change on Fe_2O_3 thin

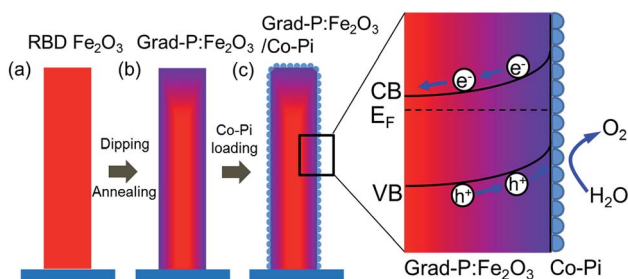

Scheme 1 Schematic illustration of the synthetic procedure of a grad-P: Fe_2O_3 /Co-Pi photoanode. (a) Oriented Fe_2O_3 nanobundle arrays grown on FTO substrate using RBD; (b) the prepared Fe_2O_3 nanobundle arrays were incorporated with gradient P concentrations (the color gradient as an indicator of P content); (c) a thin Co-Pi layer was loaded on grad-P: Fe_2O_3 photoanode.

films upon P incorporation. These thin films also show similar crystal structure (ESI, Fig. S3a†) and optical properties (ESI, Fig. S3b†). The absorption edges are at about 610 nm, corresponding to the bandgap energy of Fe_2O_3 . Therefore, morphology and absorption property changes of the grad-P: Fe_2O_3 photoanode can be ruled out for improved PEC performance. The TEM images reveal that no apparent lattice distortion of grad-P: Fe_2O_3 is observed compared with that of bare Fe_2O_3 (ESI, Fig. S4†). The well-aligned diffraction patterns recorded by the corresponding selected area electron diffraction (SAED) (inset, Fig. 2a) indicate the high crystallinity of grad-P: Fe_2O_3 . The HRTEM image also shows a fine crystalline character without any grain boundaries (Fig. 2a). In addition, the Fe_2O_3 displays a lattice spacing of 0.250 nm, corresponding to the (110) plane. This observation confirms that thermal treatment is of great importance to improve the crystallinity of Fe_2O_3 .

In order to confirm that P element has been incorporated in hematite, Raman analysis was performed. The Raman peaks around 660 cm^{-1} in homo- and grad-P: Fe_2O_3 could be ascribed to the disorder phase induced by P incorporation,¹⁷ whereas this peak is absent in bare Fe_2O_3 (ESI, Fig. S5†). A complete elemental energy-dispersive X-ray spectroscopy (EDX) mapping over a grad-P: Fe_2O_3 nanobundle was conducted (ESI, Fig. S6b–d†) to illustrate that the Fe_2O_3 nanobundle can be fully incorporated by P dopant from the top to the bottom. Both Raman and overview EDX mapping indicate the presence of P element in hematite.

The detailed P element distribution in the Fe_2O_3 nanobundle (Fig. 2b) was examined by the compositional line-profile scan of EDX (Fig. 2c). It is obvious that the P concentration exhibits a gradient decline from the surface towards the core of Fe_2O_3 nanobundle along the radial direction. A series of spots across the bundle by EDX analysis also reveal the concentration profile of P across the Fe_2O_3 nanobundle along the radial direction (Fig. 2d). To further verify the P element distribution in the grad-P: Fe_2O_3 , X-ray photoelectron spectroscopy (XPS) depth analysis was performed by employing argon-ion sputtering. Before argon-ion sputtering, the atomic concentration of P was about 5.1% at the surface of the as prepared grad-P: Fe_2O_3 . Upon the argon-ion sputtering of 2 and 4 minutes (the sputtering depths are approximately 10 and 20 nm, details in Experimental

section), the atomic concentration of P decreased to 4.1 and 2.4%, respectively (inset, Fig. 3b). Based on the above analysis, it is clear that the P concentration presents a gradient profile in the grad-P: Fe_2O_3 sample.

XPS also reveals the chemical states of the grad-P: Fe_2O_3 . Upon P doping, the Fe 2p binding energy shifts to 709.78 eV (Fig. 3a), while P 2p exhibits a binding energy of 132.68 eV (Fig. 3b). The Fe 2p and P 2p signals of grad-P: Fe_2O_3 are close to that of FePO_4 ,¹⁸ which indicates a strong interaction between the Fe and P in P: Fe_2O_3 . According to the crystal structure (ESI, Fig. S3a†) and optical properties (ESI, Fig. S3b†), as well as the chemical states of the grad-P: Fe_2O_3 compared with FePO_4 , it is clear that P was well incorporated in the grad-P: Fe_2O_3 thin film.

PEC water oxidation performance of bare Fe_2O_3 , homo-P: Fe_2O_3 and grad-P: Fe_2O_3 photoanodes were evaluated by measuring photocurrent density–potential (I – V) characteristics using a standard three-electrode configuration under air mass (AM) 1.5G illumination (100 mW cm^{-2}) (Fig. 4). The bare Fe_2O_3 photoanode was prepared *via* identical treatment conditions as that of grad-P: Fe_2O_3 photoanode without P incorporation. The photocurrent density of the bare Fe_2O_3 photoanode is 0.58 mA cm^{-2} at 1.23 V (vs. RHE), which is comparable to reported values in the literature.¹⁹

It is found that the photocurrent density of P-incorporated Fe_2O_3 nanobundle arrays is closely related to the P content (ESI, Fig. S7†; P content in our study was determined by the EDX analysis). The photocurrent density of homo-P: Fe_2O_3 nanobundle arrays is enhanced as the P atomic concentration is increased from 0 to 2%, and then decreases with further increase of P atomic ratio. The homo-P: Fe_2O_3 (2%) exhibits a photocurrent density of 1.10 mA cm^{-2} at 1.23 V (vs. RHE), which is doubled compared to the bare Fe_2O_3 nanobundle. It is noteworthy that the grad-P: Fe_2O_3 photoanode shows a higher photocurrent density of 1.48 mA cm^{-2} at 1.23 V (vs. RHE), which is superior to that of the homo-P: Fe_2O_3 photoanode. In order to rule out that the lower PEC performance of homo-P: Fe_2O_3 is due to the damage of the conductive FTO layer upon longer thermal treatment (30 min vs. 10 min), we have carefully examined the resistivity of the FTO glass upon various annealing conditions using a four-point probe. The resistivity for all these FTO samples are on the same order of $10^{-4}\text{ }\Omega\text{ cm}$ (ESI, Table S1†),

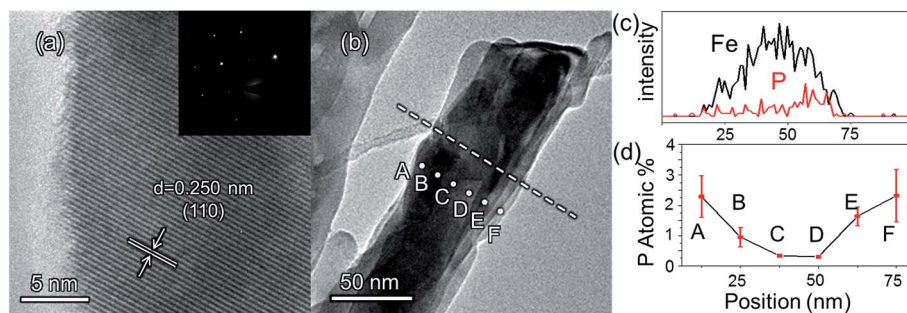


Fig. 2 (a) HRTEM image of a selected area of grad-P: Fe_2O_3 ; inset of (a) is the SAED pattern; (b) TEM image of a single grad-P: Fe_2O_3 bundle; (c) the P element distribution in a Fe_2O_3 nanobundle (line in image b); (d) the P element concentration along the radial direction (dots in image b) (the error bar represents the standard deviation).



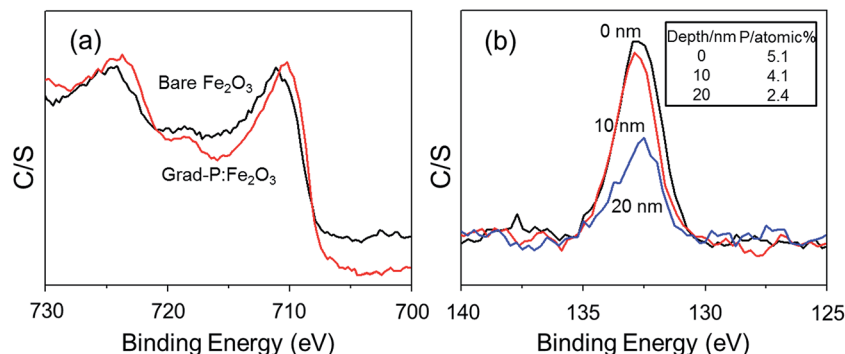


Fig. 3 (a) XPS spectra of the Fe 2p signal in bare Fe_2O_3 and grad-P: Fe_2O_3 photoanodes; (b) XPS depth profile signal of P 2p in grad-P: Fe_2O_3 , where the P concentration decreases with increasing sputtering time (inset shows the P atomic concentration values at different depth).

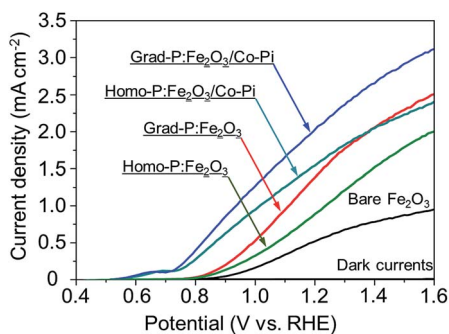


Fig. 4 I - V characteristics of bare Fe_2O_3 , homo-P: Fe_2O_3 , grad-P: Fe_2O_3 , homo-P: $\text{Fe}_2\text{O}_3/\text{Co-Pi}$ and grad-P: $\text{Fe}_2\text{O}_3/\text{Co-Pi}$ photoanodes measured in 1 M KOH solution under AM 1.5G illumination (100 mW cm^{-2}). The dark currents are negligible for all samples.

indicating that the conductivity of FTO could be well preserved in the thermal treatment in this study. Specifically, the resistivity of FTO which is subjected to the annealing condition for grad- and homo-P: Fe_2O_3 , is very similar (~ 8.7 and $9.2 \times 10^{-4} \Omega \text{ cm}$, respectively), suggesting the lower PEC performance of homo-P: Fe_2O_3 is not due to the FTO substrate. The I - V characteristics for these photoanodes were measured with 10 repeated samples to demonstrate the sample-to-sample variation. The photocurrent values at 1.23 V (vs. RHE) were compared, with standard deviations marked as error bars, to verify the reliability of photocurrent improvement upon P-doping (ESI, Fig. S8†).

The increase of carrier density can increase the band bending at the semiconductor/electrolyte interface, which could facilitate the charge transfer.²⁰ When the P content is low, the band bending is small. Therefore, the excited electron/hole cannot be separated effectively in the Fe_2O_3 (Fig. 5a). As the P content is increased, the band bending will also increase, which improves the separation of electron/hole pairs (Fig. 5b). Meanwhile, the width of depletion layer will decrease with increasing P content. Thus, with too much P content, the depletion region will become too narrow for effective charge separation (Fig. 5c). In addition, the high concentration of dopant may lead to the segregation of dopant phase, which will

serve as recombination centers trapping carriers.²¹ Consequently, further increase of P content will hinder the photocatalytic efficiency. Therefore, the photocurrent will increase with the increased P content in the hematite until it reaches a maximum value with a moderate P content in hematite, and then the photocurrent will begin to decline due to the side effects with excessive P content.

In the grad-P: Fe_2O_3 nanobundle, the P concentration exhibits a gradient decline from the surface towards the core of Fe_2O_3 nanobundle along the radial direction. As illustrated in the band bending schematic (Fig. 5c), the gradient profile of P content will lead to increasing band bending from the Fe_2O_3 core towards the surface, hence widening the total band bending region. Therefore, a more upward band bending from the bulk to the surface over a large region is formed.^{20,22} The degree of band bending at the surface region of grad-P: Fe_2O_3 is more significant compared with moderately doped homo-P: Fe_2O_3 (Fig. 5d vs. b), and comparable with heavily doped homo-P: Fe_2O_3 (Fig. 5d vs. c). Meanwhile, the width of band bending region of the grad-P: Fe_2O_3 is prolonged compared with heavily doped homo-P: Fe_2O_3 (Fig. 5d vs. c). Previous studies have revealed that the electric field in the band bending region of gradient doped GaN would be remarkably enhanced,²² and the hole diffusion length is also increased in the electric field induced by GaAs with gradient doping.²³ Thus, charge separation is expected to be greatly enhanced in the grad-P: Fe_2O_3 electrode with a gradient P concentration.

Based on the analysis above, it is speculated that the incorporation of P plays two important roles in this work. On the one hand, P doping substantially increases the electron density of Fe_2O_3 and greatly boosts its conductivity, which is the case for both homo- and grad-P: Fe_2O_3 samples. On the other hand, the gradient distribution of P induces a more upward band bending within a widened region, improving the charge separation efficiency in bulk Fe_2O_3 . Therefore, the PEC performance of grad-P: Fe_2O_3 exceeds that of homo-P: Fe_2O_3 with an additional charge separation effect in bulk Fe_2O_3 .

In order to clarify the enhanced charge transportation upon P incorporation in homo- and grad-P: Fe_2O_3 , Mott-Schottky analysis was conducted. The slopes of the Mott-Schottky plot of P: Fe_2O_3 photoanodes are substantially smaller than that of bare



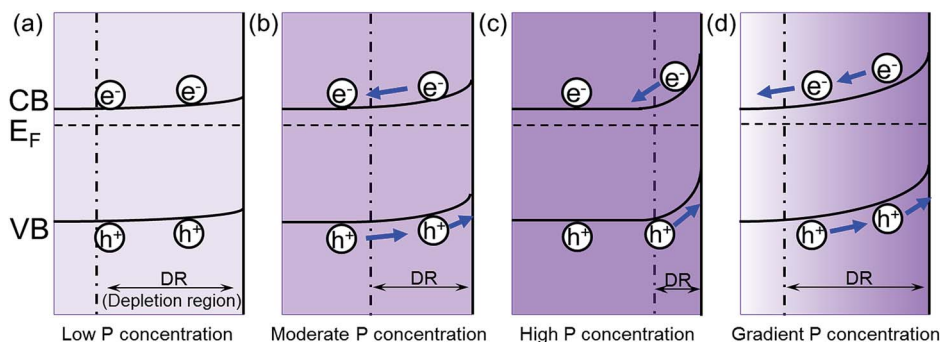


Fig. 5 The effect of P concentration on the band bending in hematite. The band bending of (a) low P concentration; (b) moderate P concentration; (c) high P concentration; (d) gradient P concentration. E_F is the Fermi level relative to the estimated conduction band (CB) and valence band (CB) edges as previously reported,^{22,23} and the boundary for the depletion region is marked by the dashed line.

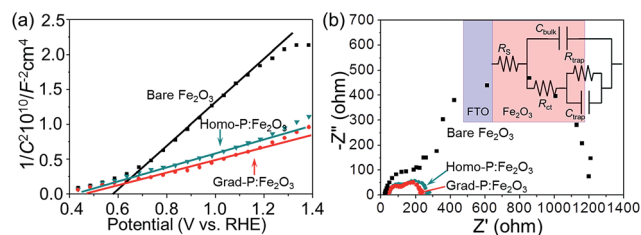


Fig. 6 (a) Mott-Schottky plots and (b) EIS Nyquist plots of bare Fe_2O_3 , homo-P: Fe_2O_3 and grad-P: Fe_2O_3 photoanodes (inset: equivalent circuit of the photoanode).

Fe_2O_3 (Fig. 6a), and the positive slopes suggest that P atoms act as n-type dopants in hematite. Although the Mott-Schottky analysis is derived from a planar electrode model, it is still reasonable to calculate the carrier density for comparison purposes.²⁴ The carrier densities calculated from the slopes of the Mott-Schottky plots for bare Fe_2O_3 , homo- and grad-P: Fe_2O_3 photoanodes are $1.9 \times 10^{20} \text{ cm}^{-3}$, $5.4 \times 10^{20} \text{ cm}^{-3}$ and $5.8 \times 10^{20} \text{ cm}^{-3}$, respectively. Although a more noticeable increase of carrier density is theoretically expected for a P atomic concentration larger than 1%, the three-fold increase in this study is likely due to the non-single crystalline nature of Fe_2O_3 , as well as the incomplete activation of incorporated P dopants. Nevertheless, the higher and comparable carrier densities of homo- and grad-P: Fe_2O_3 compared with bare Fe_2O_3 clearly indicate that P incorporation is effective to improve the electrical conductivity of Fe_2O_3 and the charge transportation is similar in grad-P: Fe_2O_3 and homo-P: Fe_2O_3 .

To further verify the similar charge transport property between grad-P: Fe_2O_3 and homo-P: Fe_2O_3 , Nyquist plots of electrochemical impedance spectroscopy (EIS) were attained under AM 1.5G illumination (100 mW cm^{-2}), with a bias of 1.23 V (vs. RHE) (Fig. 6b). An equivalent circuit model was built to fit the EIS data (inset, Fig. 6b), where R_s represents all the series resistances in the electrochemical cell, R_{ct} represents the resistance in the Fe_2O_3 , R_{trap} represents the charge resistance across the semiconductor/electrolyte interface, C_{bulk} represents the capacitance in the depletion layer of the semiconductor, and C_{trap} represents the capacitance at the surface of the

semiconductor. In this case, a smaller R_{ct} indicates a lower charge-transfer resistance in the Fe_2O_3 . The fitting results show that both grad-P: Fe_2O_3 ($105.3 \pm 2.3 \Omega$) and homo-P: Fe_2O_3 ($111.2 \pm 2.2 \Omega$) show comparable improved conductivity compared with bare Fe_2O_3 ($213.1 \pm 7.3 \Omega$) owing to the P incorporation (ESI, Table S2†). In another attempt to verify the effectiveness of resistivity reduction upon P incorporation, electrode assemblies (FTO/ Fe_2O_3 /Al, details in Experimental section) with planar homo- and grad-P: Fe_2O_3 films were fabricated for solid-state I - V characterization (ESI, Fig. S9†). The similar slope increase in solid-state I - V curves for homo- and grad-P: Fe_2O_3 indicate a significant conductivity improvement compared with bare Fe_2O_3 , and our homogenous and gradient doping approach will not result in noticeable conductivity difference. Based on the Mott-Schottky and EIS analysis, as well as the solid-state I - V characterization, it can be confirmed that P doping equally boosts the conductivity of grad- and homo-P: Fe_2O_3 .

To confirm the existence of an additional charge separation effect caused by gradient P incorporation, as indicated by the band diagram analysis (Fig. 5), 0.5 M H_2O_2 was added into the electrolyte as a hole scavenger for I - V measurement under AM 1.5G (Fig. 7).²⁵ The reaction kinetics in the presence of H_2O_2 hole scavenger is equally fast for all samples. In

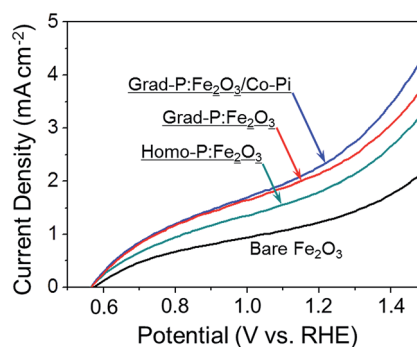


Fig. 7 I - V characteristics of bare Fe_2O_3 , homo-P: Fe_2O_3 , grad-P: Fe_2O_3 and grad-P: Fe_2O_3 /Co-Pi photoanodes measured for H_2O_2 oxidation under AM 1.5G illumination. The dark currents were negligible for all samples.



this circumstance, the photocurrent of grad-P:Fe₂O₃ is remarkable higher than that of homo-P:Fe₂O₃, even though these two samples exhibit similar conductivity. This result suggests that the improved photocurrent is very likely attributed to an extra charge separation effect caused by the gradient P incorporation in Fe₂O₃.

To further confirm the additional charge separation effect caused by gradient P incorporation, the efficiency of charge transport in the bulk (η_{bulk} , relating to bulk charge separation) was calculated (Fig. 8a, details in Experimental section). The η_{bulk} of bare Fe₂O₃ photoanode is $\sim 11\%$ at 1.23 V (vs. RHE), which is comparable to the previously reported value ($\sim 13\%$).²⁶ Upon P doping, the η_{bulk} of grad-P:Fe₂O₃ reaches $\sim 22\%$ at 1.23 V (vs. RHE), which is doubled compared to that of bare Fe₂O₃. The η_{bulk} of grad-P:Fe₂O₃ is also higher than that of homo-P:Fe₂O₃ ($\sim 16\%$) at 1.23 V vs. RHE, which could be attributed to the improved charge separation efficiency in the bulk of grad-P:Fe₂O₃. Considering the similar conductivity between grad-P:Fe₂O₃ and homo-P:Fe₂O₃, it could be inferred that gradient P incorporation results in an extra promotive effect for Fe₂O₃ that facilitates charge separation.

To further improve the PEC performance of the grad-P:Fe₂O₃ photoanode, we adopted Co-Pi as an OER cocatalyst to accelerate water oxidation on the surface.²⁷ The Co-Pi cocatalyst thin layer is nearly optically transparent on the Fe₂O₃, which is confirmed by the optical image (ESI, Fig. S2†) and UV-vis spectra (ESI, Fig. S3b†). As a result, the grad-P:Fe₂O₃/Co-Pi photoanode could reach a photocurrent density of 2.0 mA cm⁻² at 1.23 V (vs. RHE). A remarkable cathodic shift in the onset potential from 0.85 V (vs. RHE) for bare Fe₂O₃ and grad-P:Fe₂O₃ photoanodes to 0.58 V (vs. RHE) for this grad-P:Fe₂O₃/Co-Pi photoanode is attained.

To quantify the contributions of gradient P incorporation and the OER cocatalyst (Co-Pi) to the promotion of surface reaction kinetics, the efficiency of surface charge transfer (η_{surface} , relating to surface charge separation, *i.e.*, surface reaction kinetics) was calculated as well (Fig. 8b, details in Experimental section). The η_{surface} for grad-P:Fe₂O₃ ($\sim 57\%$ at 1.23 V vs. RHE) and homo-P:Fe₂O₃ ($\sim 57\%$ at 1.23 V vs. RHE) are almost identical, which is higher than that of bare Fe₂O₃ ($\sim 40\%$ at 1.23 V vs. RHE), illustrating that the severe surface recombination and sluggish surface reaction for Fe₂O₃ are partially

alleviated upon P incorporation. It is worth noting that the similar η_{surface} for grad- and homo-P:Fe₂O₃ indicates that their surface activity is almost the same. This result is consistent with the phenomenon that the onset potential of homo-P:Fe₂O₃ is identical to that of grad-P:Fe₂O₃ (Fig. 4). Upon the loading Co-Pi cocatalyst, η_{surface} of the grad-P:Fe₂O₃/Co-Pi sample is greatly enhanced in the whole potential range (0.6–1.4 V vs. RHE) and achieves $\sim 88\%$ at 1.23 V (vs. RHE). This significant η_{surface} improvement indicates the reduced surface recombination losses upon Co-Pi loading, which may result either from faster water oxidation or slower recombination.

To quantitatively evaluate the efficiency of PEC water splitting of these photoanodes, the photoconversion efficiency is calculated (Fig. 9a). A maximum photoconversion efficiency of 0.32% is observed for the grad-P:Fe₂O₃/Co-Pi photoanode at 0.92 V (vs. RHE) while the efficiencies for bare Fe₂O₃, homo- and grad-P:Fe₂O₃ photoanodes are 0.05, 0.09 and 0.12% at 1.05 V (vs. RHE), respectively. Furthermore, incident photon-to-electron conversion efficiency (IPCE) was also obtained to assess the contribution of monochromatic light to the current density at wavelengths ranging from 350 to 650 nm at a potential of 1.23 V (vs. RHE) in 1 M KOH solution (Fig. 9b). The grad-P:Fe₂O₃ photoanode exhibits significantly enhanced IPCE in comparison with bare Fe₂O₃ photoanode in the absorption region of Fe₂O₃, suggesting that the absorbed photons can be utilized more efficiently, due to the improved electrical conductivity and charge separation of the grad-P:Fe₂O₃.

A 5 h stability test of these photoanodes was performed at 1.23 V (vs. RHE) under AM 1.5G illumination (Fig. 10). The result shows that all these photoanodes retained acceptable stability during 5 h. In the given 5 h experimental time duration, the photocurrent density of the bare Fe₂O₃ photoanode shows a slight decrease from 0.58 to 0.53 mA cm⁻². However, the grad-P:Fe₂O₃ photoanode shows an impressive stability during the testing time, keeping a steady photocurrent density of 1.48 mA cm⁻² (the steady photocurrent density of the homo-P:Fe₂O₃ photoanode is 1.10 mA cm⁻²). The photocurrent density of the grad-P:Fe₂O₃/Co-Pi photoanode shows an apparent decrease from 2.0 to 1.78 mA cm⁻². The decline of this grad-P:Fe₂O₃/Co-Pi photoanode is most likely due to the decomposition of the Co-Pi water-oxidation cocatalyst.

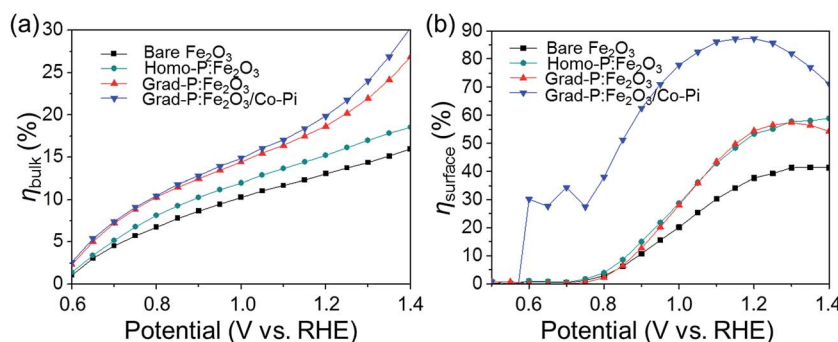


Fig. 8 Charge separation efficiency (a) in the bulk (η_{bulk}) and (b) on the surface (η_{surface}) of photoanodes.



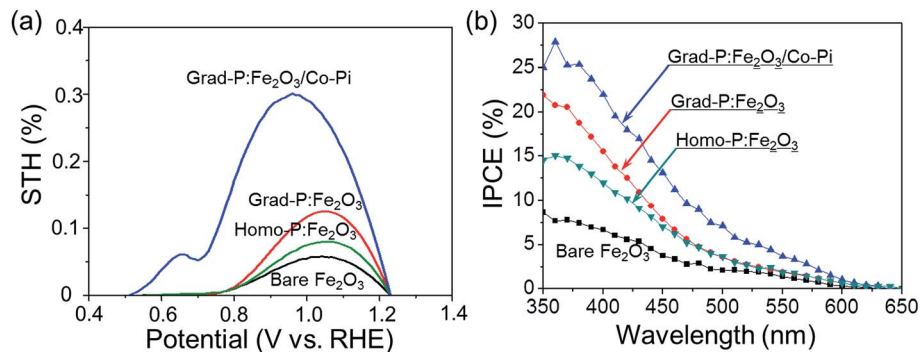


Fig. 9 (a) Photoconversion efficiency as a function of applied potential; (b) IPCE in the region 350–650 nm at a bias of 1.23 V (vs. RHE) for bare Fe₂O₃, homo-P:Fe₂O₃, grad-P:Fe₂O₃ and grad-P:Fe₂O₃/Co-Pi photoanodes.

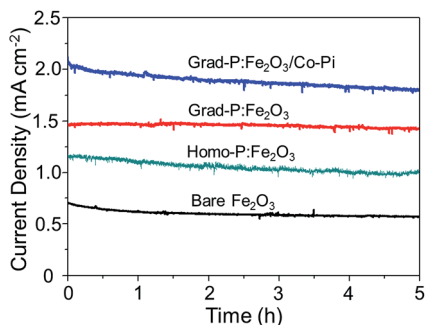


Fig. 10 Stability test of bare Fe₂O₃, homo-P:Fe₂O₃, grad-P:Fe₂O₃ and grad-P:Fe₂O₃/Co-Pi photoanodes for 5 h at 1.23 V (vs. RHE) under AM 1.5G illumination.

Conclusions

We have demonstrated the design and fabrication of effective, stable and well-defined 1-D hematite nanoarray thin films with gradient P incorporation in the radial direction, using a RBD technique followed by a facile dipping and annealing method. An AM 1.5G photocurrent of 2.0 mA cm⁻² at 1.23 V (vs. RHE) for water oxidation was achieved. EDX quantitative analysis and XPS depth profile verify that the P element indeed has a gradient concentration profile in the radial direction. The Mott–Schottky, EIS analysis and the solid-state *I*–*V* characterization, as well as the *I*–*V* characteristics with H₂O₂ as the hole scavenger clearly show that the improved PEC performance can be ascribed to the enhanced charge separation of the gradient P incorporation in the Fe₂O₃, which increases the band bending over a large region. Higher water-oxidation efficiency and lower onset potential can be achieved by loading appropriately designed Co-Pi OER cocatalysts. We believe that this gradient doping strategy can be applied to other semiconductor photoelectrodes for improved performance of solar water splitting.

Experimental section

Reactive ballistic deposition of porous hematite films

A homemade RBD system was used to prepare the porous hematite thin films. The base pressure of the high vacuum chamber of RBD system is around 5×10^{-8} mbar. Oxygen as

reactive gas was introduced to backfill the vacuum chamber to about 1×10^{-6} mbar using a leak valve. A homemade e-beam evaporator was used to evaporate an iron rod (minimum purity of 99.95%) with the iron rod mounted on the top of the e-beam evaporator directly near the tungsten filament. The Fe evaporation was conducted in the O₂ ambient at about 1×10^{-6} mbar. FTO coated glasses were used as the substrates. The sample holder could rotate by a full 360 degrees, making it possible to have arbitrary deposition angles. The distance between the evaporation source and the substrate was approximately 4 inches. A quartz crystal microbalance was used to monitor the deposition rates to estimate the thickness of the deposited films. In our preparation, we fixed a deposition rate of about 2 nm min⁻¹, and the deposition time was set at 100 min to attain a thickness of 200 nm.

The gradient P-incorporated porous Fe₂O₃ thin films were prepared by a dipping and annealing treatment. Before the treatment, the porous Fe₂O₃ thin films were annealed in air at 500 °C for 2 h. The rate of heating was 5 °C min⁻¹ and then the samples were allowed to cool to room temperature naturally. First, the annealed Fe₂O₃ thin films were soaked in 0.2 M Na₃PO₄ solution for 10 min, and then the wet films were dried in a drying oven at 100 °C for more than 1 h. After the pre-treatment, these samples were further annealed in 750 °C for 10 min to induce a gradient P incorporation in Fe₂O₃. Finally, these samples were washed thoroughly with deionized water to remove any residual impurities.

Co-Pi OER cocatalyst was loaded on the samples by a photo-assisted electrodeposition method. The Fe₂O₃ thin film was immersed in 0.5 mM Co(NO₃)₂ in 0.1 M K₂HPO₄ buffer at pH 7, which was purged for more than 1 h by nitrogen. A 300 W xenon lamp (Beijing Perfectlight Technology Co. Ltd; LS-SXE300CUV) equipped with an AM 1.5G filter was used as the light source to obtain simulated sunlight. The power intensity of the simulated sunlight was calibrated to 100 mW cm⁻². The photo-assisted electrodeposition was conducted at a bias of 0.4 V vs. Ag/AgCl electrode (1.0 V vs. RHE) for 2 min.

TEM sample preparation

The Fe₂O₃ nanobundle arrays on the FTO substrate were scraped off carefully in a 20 ml beaker with a sharp blade, and then 1.5 ml isopropanol was added as solvent to obtain a suspension.



This journal is © The Royal Society of Chemistry 2017

The donor concentration was calculated with the following equation:³⁰

$$N_d = (2/e\epsilon\epsilon_0)[d(1/C^2)/dV^{-1}] \quad (7)$$

where $e = 1.60 \times 10^{-19}$ C is the electron charge, $\epsilon = 80$ is the dielectric constant of hematite, $\epsilon_0 = 8.85 \times 10^{-14}$ F cm⁻¹ is the vacuum permittivity, C is the capacitance of the space charge region, V is the electrode applied potential, and N_d is the donor concentration.

Impedance measurements were measured in a 1.0 M KOH aqueous solution under simulated sunlight illumination over a frequency range from 10^5 to 10^{-1} Hz. Data were fitted using Zview software (Scribner Associates).

Stability of PEC performance of bare Fe₂O₃, homo-P:Fe₂O₃, grad-P:Fe₂O₃ and grad-P:Fe₂O₃/Co-Pi photoanodes was measured at a constant potential of 1.23 V (vs. RHE) under AM 1.5G illumination for 5 h.

Acknowledgements

We acknowledge the National Key Research and Development Program of China (2016YFB0600901), the National Science Foundation of China (21525626, 51302185, U1463205), Specialized Research Fund for the Doctoral Program of Higher Education (20120032110024, 20130032120018), and the Program of Introducing Talents of Discipline to Universities (B06006), and the Natural Science Foundation of Tianjin City (13JCYBJC37000) for financial support.

References

- 1 N. S. Lewis and D. G. Nocera, Powering the Planet: Chemical Challenges in Solar Energy Utilization, *Proc. Natl. Acad. Sci. U. S. A.*, 2006, **103**, 15729–15735.
- 2 M. G. Walter, E. L. Warren, J. R. McKone, S. W. Boettcher, Q. Mi, E. A. Santori and N. S. Lewis, Solar Water Splitting Cells, *Chem. Rev.*, 2010, **110**, 6446–6473.
- 3 A. Fujishima and K. Honda, Electrochemical Photolysis of Water at a Semiconductor Electrode, *Nature*, 1972, **238**, 37–38.
- 4 P. Zhang, J. Zhang and J. Gong, Tantalum-based Semiconductors for Solar Water Splitting, *Chem. Soc. Rev.*, 2014, **43**, 4395–4422.
- 5 A. Kay, I. Cesar and M. Grätzel, New Benchmark for Water Photooxidation by Nanostructured α -Fe₂O₃ Films, *J. Am. Chem. Soc.*, 2006, **128**, 15714–15721.
- 6 F. Le Formal, E. Pastor, S. D. Tilley, C. A. Mesa, S. R. Pendlebury, M. Grätzel and J. R. Durrant, Rate Law Analysis of Water Oxidation on a Hematite Surface, *J. Am. Chem. Soc.*, 2015, **137**, 6629–6637.
- 7 K. Sivula, F. Le Formal and M. Grätzel, Solar Water Splitting: Progress Using Hematite (α -Fe₂O₃) Photoelectrodes, *ChemSusChem*, 2011, **4**, 432–449.
- 8 Y. Ling, G. Wang, D. A. Wheeler, J. Z. Zhang and Y. Li, Sn-Doped Hematite Nanostructures for Photoelectrochemical Water Splitting, *Nano Lett.*, 2011, **11**, 2119–2125.
- 9 K. Sivula, R. Zboril, F. Le Formal, R. Robert, A. Weidenkaff, J. Tucek, J. Frydrych and M. Grätzel, Photoelectrochemical Water Splitting with Mesoporous Hematite Prepared by a Solution-Based Colloidal Approach, *J. Am. Chem. Soc.*, 2010, **132**, 7436–7444.
- 10 Y. Zhang, S. Jiang, W. Song, P. Zhou, H. Ji, W. Ma, W. Hao, C. Chen and J. Zhao, Nonmetal P-doped Hematite Photoanode with Enhanced Electron Mobility and High Water Oxidation Activity, *Energy Environ. Sci.*, 2015, **8**, 1231–1236.
- 11 J. Jang, C. Du, Y. Ye, Y. Lin, X. Yao, J. Thorne, E. Liu, G. McMahon, J. Zhu, A. Javey, J. Guo and D. Wang, Enabling Unassisted Solar Water Splitting by Iron Oxide and Silicon, *Nat. Commun.*, 2015, **6**, 7447.
- 12 J. Y. Kim, G. Magesh, D. H. Youn, J. W. Jang, J. Kubota, K. Domen and J. S. Lee, Single-crystalline, Wormlike Hematite Photoanodes for Efficient Solar Water Splitting, *Sci. Rep.*, 2013, **3**, 2681.
- 13 D.-D. Qin, Y.-L. Li, T. Wang, Y. Li, X.-Q. Lu, J. Gu, Y.-X. Zhao, Y.-M. Song and C.-L. Tao, Sn-doped Hematite Films as Photoanodes for Efficient Photoelectrochemical Water Oxidation, *J. Mater. Chem. A*, 2015, **3**, 6751–6755.
- 14 P. Liao, J. A. Keith and E. A. Carter, Water Oxidation on Pure and Doped Hematite (0001) Surfaces: Prediction of Co and Ni as Effective Dopants for Electrocatalysis, *J. Am. Chem. Soc.*, 2012, **134**, 13296–13309.
- 15 F. F. Abdi, L. Han, A. H. M. Smets, M. Zeman, B. Dam and R. V. D. Krol, Efficient Solar Water Splitting by Enhanced Charge Separation in a Bismuth Vanadate-Silicon Tandem Photoelectrode, *Nat. Commun.*, 2013, **4**, 2195.
- 16 I. S. Cho, C. H. Lee, Y. Feng, M. Logar, P. M. Rao, L. Cai, D. R. Kim, R. Sinclair and X. Zheng, Codoping Titanium Dioxide Nanowires with Tungsten and Carbon for Enhanced Photoelectrochemical Performance, *Nat. Commun.*, 2013, **4**, 1723.
- 17 Z. Fu, T. Jiang, L. Zhang, B. Liu, D. Wang, L. Wang and T. Xie, Surface Treatment with Al³⁺ on a Ti-doped α -Fe₂O₃ Nanorod Array Photoanode for Efficient Photoelectrochemical Water Splitting, *J. Mater. Chem. A*, 2014, **2**, 13705–13712.
- 18 L. Castro, R. Dedryvere, M. El Khalifi, P.-E. Lippens, J. Breger, C. Tessier and D. Gonbeau, The Spin-polarized Electronic Structure of LiFePO₄ and FePO₄ Evidenced by in-Lab XPS, *J. Phys. Chem. C*, 2010, **114**, 17995–18000.
- 19 A. G. Tamirat, W.-N. Su, A. A. Dubale, H.-M. Chen and B.-J. Hwang, Photoelectrochemical Water Splitting at Low Applied Potential Using a NiOOH Coated Codoped (Sn,Zr) α -Fe₂O₃ Photoanode, *J. Mater. Chem. A*, 2015, **3**, 5949–5961.
- 20 G. Wang, Y. Ling, H. Wang, L. Xihong and Y. Li, Chemically Modified Nanostructures for Photoelectrochemical Water Splitting, *J. Photochem. Photobiol., C*, 2014, **19**, 35–51.
- 21 X. Zhang, H. Li, S. Wang, F.-R. F. Fan and A. J. Bard, Improvement of Hematite as Photocatalyst by Doping with Tantalum, *J. Phys. Chem. C*, 2014, **118**, 16842–16850.
- 22 X. Guo, X. Wang, B. Chang, Y. Zhang and P. Gao, High Quantum Efficiency of Depth Grade Doping Negative-



- Electron-Affinity GaN Photocathode, *Appl. Phys. Lett.*, 2010, **97**, 063104.
- 23 J. Zou, Z. Yang, J. Qiao, P. Gao and B. Chang, Activation Experiments and Quantum Efficiency Theory on Gradient-Doping NEA GaAs Photocathodes, *Proc. SPIE-Int. Soc. Opt. Eng.*, 2007, **6782**, 67822R.
- 24 F. Cardon and W. P. Gomes, On the Determination of the Flat-Band Potential of a Semiconductor in Contact with a Metal or an Electrolyte from the Mott-Schottky Plot, *J. Phys. D: Appl. Phys.*, 1978, **11**, L63–L67.
- 25 O. Zandi and T. W. Hamann, Enhanced Water Splitting Efficiency Through Selective Surface State Removal, *J. Phys. Chem. Lett.*, 2014, **5**, 1522–1526.
- 26 O. Zandi and T. W. Hamann, The Potential versus Current State of Water Splitting with Hematite, *Phys. Chem. Chem. Phys.*, 2015, **17**, 22485–22503.
- 27 X. Chang, T. Wang, P. Zhang, J. Zhang, A. Li and J. Gong, Enhanced Surface Reaction Kinetics and Charge Separation of p–n Heterojunction $\text{Co}_3\text{O}_4/\text{BiVO}_4$ Photoanodes, *J. Am. Chem. Soc.*, 2015, **137**, 8356–8359.
- 28 J. Seo, T. Takata, M. Nakabayashi, T. Hisatomi, N. Shibata, T. Minegishi and K. Domen, Mg-Zr Cosubstituted Ta_3N_5 Photoanode for Lower-Onset-Potential Solar-Driven Photoelectrochemical Water Splitting, *J. Am. Chem. Soc.*, 2015, **137**, 12780–12783.
- 29 S. Hoang, S. Guo, N. T. Hahn, A. J. Bard and C. B. Mullins, Visible Light Driven Photoelectrochemical Water Oxidation on Nitrogen-Modified TiO_2 Nanowires, *Nano Lett.*, 2012, **12**, 26–32.
- 30 N. Mirbagheri, D. Wang, C. Peng, J. Wang, Q. Huang, C. Fan and E. E. Ferapontova, Visible Light Driven Photoelectrochemical Water Oxidation by Zn- and Ti-Doped Hematite Nanostructures, *ACS Catal.*, 2014, **4**, 2006–2015.

