

Showcasing research from Professor Tatjana N. Parac-Vogt's laboratory, Department of Chemistry, KU Leuven, Belgium.

Versatile post-functionalisation strategy for the formation of modular organo-inorganic polyoxometalate hybrids

A novel and general strategy for combining multiple types of metal-oxo clusters in a single hybrid molecule has been developed by Prof. Parac-Vogt's group at KU Leuven, Belgium. A versatile modular approach allows the incorporation of different metal-oxo nanoclusters with characteristic structures into a single hybrid molecule by covalently linking them with polyol ligands. The one-pot synthesis of these novel compounds was achieved in high yields under simple reaction conditions and could be translated to create other hybrid materials based on a variety of metal-oxo cluster building-blocks.

As featured in:



See Tatjana N. Parac-Vogt *et al.*, *Chem. Sci.*, 2022, **13**, 2891.

Cite this: *Chem. Sci.*, 2022, 13, 2891

All publication charges for this article have been paid for by the Royal Society of Chemistry

Versatile post-functionalisation strategy for the formation of modular organic–inorganic polyoxometalate hybrids†

David E. Salazar Marcano,^a Mhamad Aly Moussawi,^a Alexander V. Anyushin,^a Sarah Lentink,^a Luc Van Meervelt,^b Ivana Ivanović-Burmazović^c and Tatjana N. Parac-Vogt^{d,*a}

Hybrid structures incorporating different organic and inorganic constituents are emerging as a very promising class of materials since they synergistically combine the complementary and diverse properties of the individual components. Hybrid materials based on polyoxometalate clusters (POMs) are particularly interesting due to their versatile catalytic, redox, electronic, and magnetic properties, yet the controlled incorporation of different clusters into a hybrid structure is challenging and has been scarcely reported. Herein we propose a novel and general strategy for combining multiple types of metal-oxo clusters in a single hybrid molecule. Two novel hybrid POM structures (HPOMs) bis-functionalised with dipentaerythritol (R–POM₁–R; R = (OCH₂)₃CCH₂OCH₂C(CH₂OH)) were synthesised as building-blocks for the formation of heterometallic hybrid triads (POM₂–R–POM₁–R–POM₂). Such a modular approach resulted in the formation of four novel heterometallic hybrids combining the Lindqvist (V₆), Anderson–Evans (XMo₆) (X = Cr or Al) and trisubstituted Wells–Dawson (P₂V₃W₁₅) POM structures. Their formation was confirmed by multinuclear Nuclear Magnetic Resonance (NMR), infrared (IR) and UV-Vis spectroscopy, as well as Mass Spectrometry, Diffusion Ordered Spectroscopy (DOSY) and elemental analysis. The thermal stability of the hybrids was also examined by Thermogravimetric Analysis (TGA), which showed that the HPOM triads exhibit higher thermal stability than comparable hybrid structures containing only one type of POM. The one-pot synthesis of these novel compounds was achieved in high yields in aqueous and organic media under simple reflux conditions, without the need of any additives, and could be translated to create other hybrid materials based on a variety of metal-oxo cluster building-blocks.

Received 14th November 2021

Accepted 7th February 2022

DOI: 10.1039/d1sc06326j

rsc.li/chemical-science

Introduction

The synthesis of intricate hybrid organic–inorganic structures for the formation of new functional materials remains a major challenge. This problem can be addressed by exploiting well-known building blocks with established catalytic, electronic, conductive, optical or biological properties, and combining them to form hybrid materials that will benefit from the synergy of their combined properties.^{1,2} Polyoxometalates (POMs), which are discrete anionic metal–oxygen nanoclusters of group 5 and 6 transition metals in their highest oxidation states, are

promising inorganic building-blocks for the formation of such hybrid materials.³ This family of compounds includes a wide variety of structures such as (1) the Lindqvist structure with general formula [M₆O₁₉]^{n−}, (2) the Anderson–Evans structure with general formula [(Xⁿ⁺)M₆O₂₄]^{(6−n)−}, and (3) the Wells–Dawson structure with general formula [X₂M₁₈O₆₂]^{n−} (M is typically Mo⁶⁺, W⁶⁺ or V⁵⁺ depending on the structure; X is a heteroatom such as P, Cr, Al, etc.). POMs have many interesting physical and chemical properties due to their tuneable size, charge density, acidity, and redox potential. As a result, they have been extensively investigated for applications in many fields such as catalysis, materials science, energy storage, supramolecular chemistry and medicine.^{4–9} Moreover, some archetypal POM structures can be functionalised with organic ligands to form organic–inorganic hybrid polyoxometalates (HPOMs), further expanding their physical and chemical properties.^{10–12}

POMs covalently functionalised with triols ((HOCH₂)₃C–R), in which three of the bridging oxo ligands are replaced by the triol, are one of the most important classes of HPOMs.^{12,13}

^aLaboratory of Bioinorganic Chemistry, KU Leuven Department of Chemistry, Celestijnenlaan 200F, 3001 Leuven, Belgium. E-mail: tatjana.vogt@kuleuven.be

^bBiomolecular Architecture, KU Leuven Department of Chemistry, Celestijnenlaan 200F, 3001 Leuven, Belgium

^cDepartment of Chemistry, Ludwig-Maximilians-University, Butenandtstr. 5–13, Haus D, 81377 Munich, Germany

† Electronic supplementary information (ESI) available. CCDC 2114104 and 2114105. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/d1sc06326j



It should be noted that **C**, with two dP ligands attached to either side of the POM core (R–POM–R), represents a new member of a family of related compounds based on the Anderson–Evans structure functionalised with dP that were recently reported by Wei *et al.* and, therefore, it further demonstrates the versatility of this POM scaffold.³⁴ The formation of a dumbbell-like structure (POM–R–POM) was reported to be obtained when the ratio of CrMo₆ and dP was set to 2 : 1 while changing the ratio to 1 : 1.4 gave rise to the mono-functionalised CrMo₆ (POM–R). However, isolation of the symmetrical bis-functionalised CrMo₆ HPOM was not reported by Wei *et al.* Nevertheless, through the procedure reported herein, using a higher temperature and a 1 : 4 ratio of CrMo₆ to dP, it was possible to synthesize **C** without any side products, showing that controlling the ratio of starting materials and the temperature allows for the formation of different functionalised structures.

Synthesis & characterisation of D-terminal POM–POM hybrids

The POM–POM hybrids formed *via* post-functionalisation of **L** or **C** with **D** were obtained by refluxing the POM linker with TBA₅H₄[P₂V₃W₁₅O₆₂] for one week in dry acetonitrile under an inert argon atmosphere while the reaction mixture was kept in the dark to prevent photo-induced side reactions. In this way, TBA_{11.4}H_{2.6}[V₆O₁₃{(OCH₂)₃CCH₂OCH₂C(CH₂O)₃(P₂V₃W₁₅O₅₉)}₂] (**DLD**) and TBA_{12.4}H_{2.6}[CrMo₆O₁₈{(OCH₂)₃CCH₂OCH₂C(CH₂O)₃(P₂V₃W₁₅O₅₉)}₂] (**DCD**) were obtained in high yields from **L** and **C** respectively. The reactions were left running for a week to ensure the POM linker fully reacted, but evidence of the formed POM–POM hybrid with only trace amounts of the starting materials was observed by multinuclear NMR after refluxing for just over an hour, which suggests that a shorter reaction time is possible.

As shown in Fig. 4, evidence for the attachment of the free triol group of **L** to **D** could be clearly seen from changes in the chemical shift of the peaks in the ¹H, ¹³C, ⁵¹V and ³¹P NMR spectra of **DLD** (Fig. S16–S18†) with respect to the starting

materials. By ¹H NMR a significant downfield shift from 3.46 ppm to 5.45 ppm was observed for the –CH₂–O– protons of the triol group, corresponding to binding of the tripodal anchor to the V₃ cap of **D**. To a lesser extent, a shift was also observed for the peaks of the adjoining ethyl protons in the bridging –CH₂–O–CH₂– ether group. Similar changes were also observed in the ¹³C NMR spectrum of **DLD** with respect to **L**. In addition, ⁵¹V NMR showed a major downfield shift from –585 ppm to –538 ppm for the peak belonging to the V₃ cap of **D**, as a result of functionalisation, while the peak of the V₆ core remained relatively unchanged at –497 ppm. The integration of both peaks in the ⁵¹V NMR spectrum was approximately the same, which is indicative of the formation of a symmetrical POM–POM hybrid with two V₃ caps attached to either side of the V₆ core. Moreover, ³¹P NMR showed only two peaks at –7.51 ppm and –13.55 ppm, which were observed to shift slightly from the typical chemical shifts of **D**, further confirming functionalisation and the structural integrity of the Wells–Dawson POM structure. The integrity of the POM cores was also confirmed by IR spectroscopy (Fig. S15†) from the peak at 1084 cm^{–1} due to the {PO₄} template of the Wells–Dawson structure and the peaks in the range 400–1000 cm^{–1} due to ν M=O and ν M–O–M vibrations (M = V or W).^{47,53,54} In addition, the UV-Vis absorbance spectrum of **DLD** (Fig. S19†) showed a significantly higher absorbance compared to the 1 : 2 mixture of **L** and **D** with the same total concentration. However, after normalisation with respect to the maximum absorbance, the spectra matched very well, further confirming that **DLD** is indeed a 1 : 2 combination of **L** and **D**. Hence, distinct spectroscopic changes evidence the formation of a novel POM–POM hybrid *via* the covalent attachment of the Lindqvist and Wells–Dawson POM structures, thereby combining their characteristic properties in a single discrete hybrid structure.^{16,30,36,55}

The formation of **DCD** was also observed by multinuclear NMR and the integrity of the POM cores was confirmed by IR spectroscopy. IR showed peaks in the range 400–1000 cm^{–1} due to ν M=O and ν M–O–M vibrations (M = Mo, V or W) which are clearly due to both the Anderson–Evans and Wells–Dawson POM cores (Fig. S21†). Furthermore, as observed with **DLD**, the UV-Vis absorbance spectrum of **DCD** (Fig. S24†) was dominated by the O → W⁶⁺ and O → V⁵⁺ LMCT bands of **D**.³² Similarly, **DCD** also displayed a higher absorbance than a 1 : 2 mixture of **C** and **D** with the same total concentration, but the normalised spectra gave an excellent match, indicating that **DCD** is indeed a result of a 1 : 2 combination of **C** and **D**. Additionally, a major shift in the peak corresponding to the V₃ cap from –585 ppm to –539 ppm was also observed by ⁵¹V NMR as a result of functionalisation (Fig. 5; S23†). Likewise, ³¹P NMR gave only two peaks at –7.58 ppm and –13.51 ppm corresponding to the functionalised Wells–Dawson structure (Fig. 5; S22†). Moreover, the peak at –7.58 ppm, which is due to the ³¹P environment closest to the V₃ cap, had a half-width (Δν_{1/2}) of 11.1 Hz, which was significantly broader than the second ³¹P peak at –13.51 ppm, and was also much broader than the peaks in the ³¹P NMR spectra of **DLD** and **D**, which had a Δν_{1/2} of around 4–7 Hz. This broadening of the most deshielded peak is caused by the paramagnetic Cr³⁺ centre of the Anderson–Evans structure

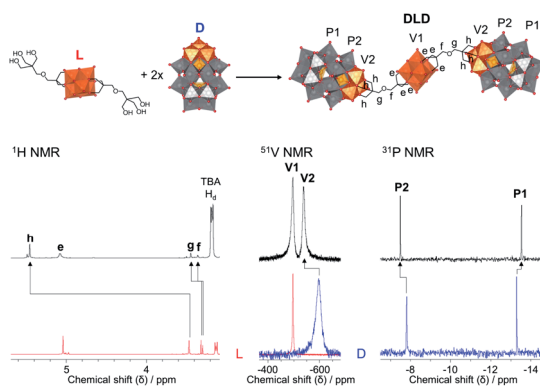


Fig. 4 Synthesis of **DLD** from **L** and **D** (top) and the corresponding ¹H, ⁵¹V and ³¹P NMR spectra (bottom; ordered from left to right) of the POM–POM hybrid (black) and the starting materials (red for **L** and blue for **D**) illustrating the changes in the chemical shifts due to POM post-functionalisation of **L**.

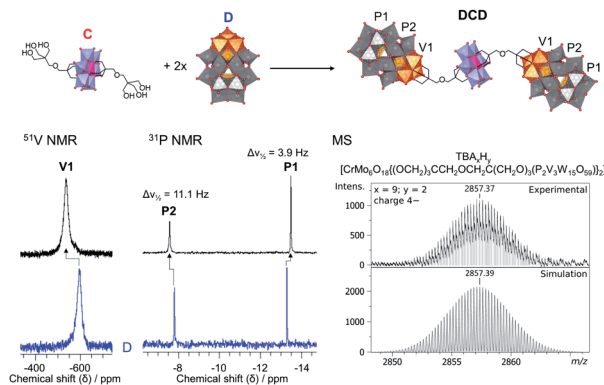


Fig. 5 Synthesis of DCD from C and D (top) together with the corresponding ^{51}V and ^{31}P NMR spectra (bottom left) of the POM–POM hybrid (black) and of D (blue) as well as the experimental and simulated cryo-MS spectra for DCD (bottom right).

and clearly indicates the proximity of the POMs through their covalent attachment. Moreover, this suggests that the combination of C and D could potentially be exploited to probe biomolecules, such as proteins, due to ^1H paramagnetic relaxation enhancement resulting from C and the favourable interactions which can take place between proteins and the Wells–Dawson structure.^{56,57}

The successful formation of both DLD and DCD was also confirmed by Ultra High Resolution cryo-mass spectrometry (UHR cryo-MS), which gave several peaks corresponding to the intact POM–POM hybrid structures with different numbers of protons and TBA as counter-cations (Fig. 5; Tables S2–S3; Fig. S14 & S20†). Their composition was also further confirmed by elemental analysis. Crystallisation of these novel POM–POM hybrids was also attempted in various solvents and solvent mixtures, but unfortunately crystals of suitable quality for X-ray diffraction could not be obtained due to the flexibility of the dP linker, as has been previously reported for other POM–POM hybrids.³⁰ To the extent of our knowledge, these novel heterometallic POM–POM hybrids represent the first examples of the covalent attachment of other POM structures onto Wells–Dawson type POMs, and DCD in particular demonstrates the high number of different metal centres that can be combined in this way.

Synthesis & characterisation of A-terminal POM–POM hybrids

Similar to the formation of DLD and DCD, the synthesis of POM–POM hybrids with Anderson–Evans terminal groups was performed by refluxing the dP-functionalised POM linker and A. In this way, an additional two new POM–POM hybrids were obtained:

$\text{TBA}_8[\text{V}_6\text{O}_{13}\{(\text{OCH}_2)_3\text{CCH}_2\text{OCH}_2\text{C}(\text{CH}_2\text{O})_3(\text{Al}(\text{OH})_3\text{Mo}_6\text{O}_{18})\}_2]$ (ALA) and $\text{TBA}_9[\text{CrMo}_6\text{O}_{18}\{(\text{OCH}_2)_3\text{CCH}_2\text{OCH}_2\text{C}(\text{CH}_2\text{O})_3(\text{Al}(\text{OH})_3\text{Mo}_6\text{O}_{18})\}_2]$ (ACA). However, the syntheses were performed in water due to the higher reported reactivity of the labile OH groups of A towards substitution in aqueous media with respect to that in organic solvents.³⁵ Hence, taking into account the insolubility of the TBA salts of C and L in water, an

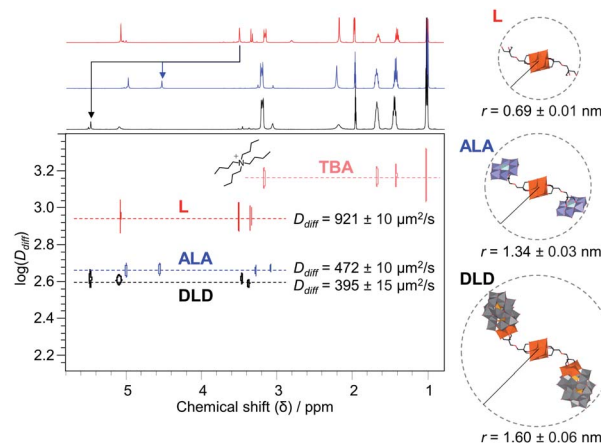


Fig. 6 Overlaid ^1H 2D DOSY NMR spectra of L, ALA and DLD labelled with the translational diffusion coefficient (D_{diff}) used to determine the hydrodynamic radius (r) for each structure, as shown on the right, and the corresponding ^1H 1D NMR spectra shown at the top.

ion metathesis procedure – involving precipitation of the Na-salt by addition of NaClO_4 to the TBA-salts in acetonitrile – was employed to obtain the water-soluble sodium salts of these compounds, which were characterised by multinuclear NMR, UV-Vis and/or IR spectroscopy (Fig. S10–S13†).⁵⁸

The synthesis of ALA was confirmed by multinuclear NMR, MS, UV-Vis, IR, and elemental analysis. Functionalisation of L was observed by ^1H NMR, which showed a downfield shift of the $-\text{OCH}_2-$ protons from around 3.46 ppm for L to 4.50 ppm for ALA (Fig. 6; S28†). Similar changes were also observed from the ^{13}C NMR spectra, which showed a downfield shift in the corresponding carbon environment from 63.70 ppm for L to 76.89 ppm for ALA (Fig. S29†). In addition, the peaks in negative mode ESI-MS of ALA in acetonitrile could be assigned to ALA with different numbers of protons and TBA as counter-cations giving rise to species with charges of 2- or 3- (Fig. S25; Table S4†). However, the spectra obtained by cryo-MS suggest that ALA does not ionise well or is not particularly stable under the measurement conditions used since only one profile centred at m/z 3383.87 (Fig. S26†) could be tentatively assigned to the mono-anionic species with 2 TBA and 5 protons as counter ions ($[\text{TBA}_2\text{H}_5\text{ALA}]^-$; calcd. $m/z = 3384.05$). The difference between the calculated and observed m/z is also significantly larger than expected for ultra-high resolution measurements preventing a confident assignment of the cryo-MS spectra. Nevertheless, similar to DLD and DCD, the UV-Vis absorbance spectrum of ALA (Fig. S32†) displayed a higher absorbance than a 1 : 2 mixture of L and A with the same total concentration while the normalised spectra matched fairly well, with the exception of an additional peak at 218 nm. This extra peak at 218 nm is due to the functionalisation of A, which causes a hypochromic shift in the absorbance peak originating from the $\text{O} \rightarrow \text{Mo}^{6+}$ LMCT that was also observed for the functionalisation of CrMo_6 to form C. This further confirms that ALA is composed of a 1 : 2 combination of L and A *via* covalent attachment. The peaks at 1132 and 1035 cm^{-1} in the IR spectrum (Fig. S27†) due to C–O stretching vibrations are also indicative of functionalisation,



and the peaks in the region 400–1000 cm^{-1} originating from ν $\text{M}=\text{O}$ and ν $\text{M}-\text{O}-\text{M}$ vibrations ($\text{M} = \text{V}$ or Mo) confirm the presence of both POM cores. The integrity of the V_6 and AlMo_6 POM cores after post-functionalisation were also evidenced from single sharp peaks at -497 ppm and 15.69 ppm in the ^{51}V NMR and ^{27}Al NMR spectra, respectively (Fig. S30–S31†). Moreover, the attachment of **A** to **L** resulted in a decrease in the translational diffusion coefficient (D_{diff}) from $921 \mu\text{m}^2 \text{s}^{-1}$ (**L**) to $472 \mu\text{m}^2 \text{s}^{-1}$ (**ALA**) as determined from all peaks corresponding to the POM–POM hybrid by ^1H 2D Diffusion Ordered NMR spectroscopy (DOSY), which shows that all peaks correspond to the same species and that **ALA** is significantly larger than **L** (Fig. 6). It is worth noting that a similar decrease in D_{diff} compared to **L** was also observed for **DLD**, but **DLD** gave an even lower D_{diff} due to the larger size of **D** with respect to **A**. In fact, the hydrodynamic radius (r) determined from the observed D_{diff} using the Stokes–Einstein equation showed the expected increase in size from 0.69 ± 0.01 nm for **L** to 1.34 ± 0.03 nm for **ALA** and 1.60 ± 0.06 nm for **DLD**. These values also match fairly well with the crystal structure of **L** and the simulated structures of **ALA** and **DLD**, which were based on a combination of the structure of **L** with the crystal structures of **A** (ICSD 415139) or **D** (CCDC 675452), from which r was estimated to be 0.96, 1.19, and 1.99 nm respectively.^{55,59}

Based on the successful isolation of **DCD** and following a similar procedure used for the synthesis of **ALA**, the synthesis of a triple Anderson–Evans POM–POM hybrid structure based on **C** with terminal **A** was also attempted. Negative mode ESI-MS (Fig. S33†) of the isolated product gave a peak centred around m/z 1931.61 which can be attributed to the di-anionic POM with 2 TBA and 5 protons as counter ions ($[\text{TBA}_2\text{H}_5\text{ACA} + (\text{ACN}) + 2(\text{H}_2\text{O})]^{2-}$; calcd $m/z = 1931.40$) confirming the successful synthesis of **ACA**. However, **ACA** exhibited a similar behaviour to that observed for **ALA** under the cryo-MS measurement conditions since only one profile centred at m/z 4027.85 (Fig. S34†) could correspond to the mono-anionic species with 3 TBA and 5 protons as counter ions ($[\text{TBA}_3\text{H}_5\text{ACA}]^-$; calcd $m/z = 4028.03$) but, like with **ALA**, the difference between the calculated and observed m/z is significantly larger than expected for ultra-high resolution measurements and, therefore, this profile could not be unambiguously assigned. Furthermore, due to the paramagnetic nature of the Cr^{3+} centre, NMR analysis was limited to ^{13}C and ^{27}Al NMR (Fig. S36–S37†). ^{13}C NMR of **ACA** showed that grafting of the free triol group of **C** onto **A** resulted in the disappearance of the peak at 64.21 ppm, which is due to the $-\text{CH}_2\text{OH}$ groups of **C**, and the appearance of a peak at 77.31 ppm corresponding to the formation of $-\text{CH}_2\text{O}-\text{Al}$, as seen for **ALA**. However, only one additional peak due to **ACA** at 42.06 ppm, corresponding to the quaternary carbon furthest from the CrMo_6 core, could be observed since the other carbon environments are too close to the Cr^{3+} centre and, therefore, did not give rise to noticeable peaks. Nevertheless, ^{27}Al NMR gave a single peak at 15.64 ppm due to the functionalised AlMo_6 POM core, which also closely matches with the ^{27}Al NMR spectrum of **ALA**. Additionally, the characteristic peaks of the Anderson–Evans structure in the IR spectrum at 937 (ν $\text{Mo}=\text{O}$, s), 916 (ν $\text{Mo}=\text{O}$, s), 899 (ν $\text{Mo}=\text{O}$, s) and 650 (ν $\text{Mo}-\text{O}-\text{Mo}$,

vs.) cm^{-1} confirm the integrity of the POM structures (Fig. S35†). Moreover, the UV-Vis absorbance spectrum (Fig. S38†) shows that **ACA** consists of a 1 : 2 combination of **C** and **A** via covalent attachment since it displayed a higher absorbance than a 1 : 2 mixture of **C** and **A** with the same total concentration while the normalised spectra matched fairly well, with only slight differences due to the functionalisation of **A**. Furthermore, similar to **DLD** and **DCD**, single crystals suitable for X-ray diffraction could not be obtained for **ALA** or **ACA**, in accordance with previous reports,³⁵ yet the elemental composition of the isolated compounds displayed the expected stoichiometry as shown in the ESI.†

Thermal stability

The thermal stability of all new HPOMs reported in this work was evaluated by Thermogravimetric Analysis (TGA) under an N_2 atmosphere between 30 °C and 630 °C. All HPOMs were observed to remain stable below 180 °C, which is comparable to the previously reported stability of similar structures.^{34,35,60} Between 180 and 500 °C a weight loss was observed in the TGA profiles of the HPOMs, indicating their decomposition due to loss of the organic components (Fig. 7). **L** was the least stable as it began to significantly decompose just above 180 °C while, in contrast, **C** was much more stable and only started decomposing above 250 °C. Furthermore, bis-functionalisation to form **C** results in a higher thermal stability compared to the corresponding mono-functionalised form and having Cr^{3+} as the heteroatom improves the stability with respect to the equivalent bis-functionalised structure with Mn^{3+} .³⁴ The higher thermal stability of the Anderson–Evans building block was also reflected in the higher stability of **ACA** compared to **ALA**, each of which had similar stabilities compared to their respective building-blocks. However, the highest stability was observed for the **DLD** and **DCD**, which only decomposed above 250 °C. As previously observed for the other HPOMs based on CrMo_6 , **DCD** was also slightly more stable than **DLD** with no major decomposition until 265 °C. In addition, **DCD** demonstrated a higher thermal stability than the homogenous “dumbbell” and “triangular” POM–POM hybrids based on $\text{P}_2\text{V}_3\text{W}_{15}$ POMs covalently linked with purely organic linkers, which showed

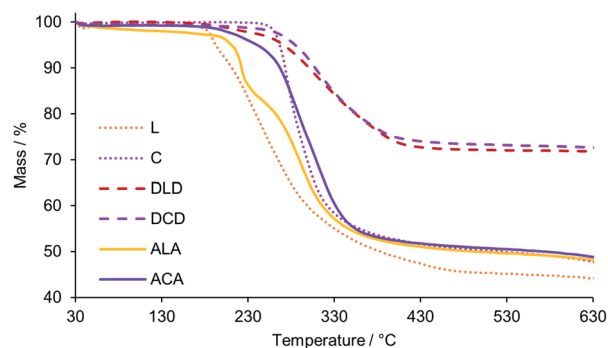


Fig. 7 TGA profiles (top) showing the weight loss with increasing temperature for the building blocks, **L** and **C**, and their corresponding POM–POM hybrids: **DLD**, **DCD**, **ALA**, and **ACA**.



Table 1 Residual mass of the POM–POM hybrids at around 630 °C

HPOM	Calcd res. mass/%	Observed res. mass/%
DLD	71.89	71.85
DCD	71.39	72.63
ALA	49.59	48.01
ACA	51.1	48.63

significant decomposition just above 200 °C.^{30,33} Moreover, for all POM–POM hybrids the residual weight at 630 °C after complete loss of the organic part was in good agreement with the calculated values for the loss of all TBA counter ions and the dP linker as shown in Table 1, further confirming their structures. Hence, the number of counter-cations for all compounds was determined based on a multi-technique approach combining NMR, elemental analysis and TGA.

Conclusions

In summary, a set of novel metal-oxo cluster building-blocks were synthesised for the formation of a wide variety of hybrid structures combining different inorganic cluster types. The first examples of POM–POM hybrid structures combining the Wells–Dawson POM structure with Lindqvist and Anderson–Evans POMs were successfully obtained as confirmed by multinuclear NMR, IR, UV-Vis, MS and elemental analysis. Furthermore, it was also shown that this method can be used to link together Anderson–Evans and Lindqvist POMs, as well as Anderson–Evans structures with different heteroatoms. All POM triads were thermally stable until 180 °C, and showed in general higher thermal stability compared to the HPOM structures linked by only organic ligands. Moreover, the proposed post-functionalisation strategy for the formation of these heterometallic hybrid structures composed of multiple inorganic components is relatively simple and results in high yields without the need of additional reagents. The same strategy could be applied to an even wider range of metal oxo-clusters and, in principle, it could also be employed to produce more complex structures such as polymers containing different POMs linked together, as well as asymmetric POM–POM hybrids containing two or more different types of POM structures (POM₁–POM₂–POM₃–POM_n) allowing for the controlled design of compounds with the desired composition. For example, the Anderson–Evans structure can accommodate a large variety of different central heteroatoms, including most first-row transition metals and even some p-block elements (*e.g.*, X = Mn, Fe, Co, Ni, Cu, Zn, Ga, Al, Te, *etc.*), resulting in the formation of either bis- or mono-functionalised structures that can be combined to tune the properties of the material based on the choice of the metal centre.¹⁵ The Lindqvist structure also offers additional structural variability since it can be mono-, bis-, tri- or tetra- functionalised, depending on the oxidation state and composition of the metal centres ([V₃Mo₃O₁₆{(OCH₂)₃C-R}]; [V₆O_{19-3x-y}(OH)_y{(OCH₂)₃C-R}_x] where *x* = 2, 3, and 4).^{14,17,61} Furthermore, the vanadium and nickel substituted Keggin

structures ([XM₁₂O₄₀]ⁿ⁻) can also be functionalised with polyols in the same way as for the Wells–Dawson structure.^{62,63} In addition, tailoring of the structures formed *via* this strategy is not limited to the inorganic components, since employing different polyols with other functional groups as organic linkers could also be used for added functionality. Therefore, the novel strategy proposed here based on metal-oxo clusters functionalised with polyols could be used as a platform for the combination of a wide variety of other metal-oxo structures *via* covalent attachment. Ideally, this strategy could also be extended to functional surfaces or nanoparticles and even to the non-covalent self-assembly of species *via* the free triol groups.^{21–26,64,65}

Data availability

Crystallographic data for compounds C and L has been deposited at the CCDC and allocated the deposition numbers CCDC-2114104 and 2114105, respectively. All other data supporting the results discussed in this work is available within the paper and its ESI.†

Author contributions

D. E. S. M., M. A. M., A. V. A., and S. L. performed the synthesis and characterisation of the novel compounds. The cryo-MS measurements were performed and interpreted with the assistance of I. I. B. The crystal structures were solved by L. V. M. T. N. P. V. helped with the design and interpretation of the experiments. The manuscript was written through contributions of D. E. S. M., M. A. M., A. V. A., S. L. and T. N. P. V. All authors have given approval to the final version of the manuscript.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

We thank KU Leuven (grant C14/19/076) and the Research Foundation Flanders (FWO) for funding. D. E. S. M. (83523/1183021N) and M. A. M. (203282/1279721N) thank the FWO for fellowships. L. V. M. thanks the Hercules Foundation for supporting the purchase of the diffractometer through project AKUL/09/0035.

Notes and references

- 1 L. Rozes and C. Sanchez, *Chem. Soc. Rev.*, 2011, **40**, 1006–1030.
- 2 C. Sanchez, P. Belleville, M. Popall and L. Nicole, *Chem. Soc. Rev.*, 2011, **40**, 696–753.
- 3 M. Hutin, M. H. Rosnes, D.-L. Long and L. Cronin, in *Comprehensive Inorganic Chemistry II*, Elsevier, 2013, vol. 2, pp. 241–269.
- 4 S.-S. Wang and G.-Y. Yang, *Chem. Rev.*, 2015, **115**, 4893–4962.



- 5 Y.-F. Song, *Polyoxometalate-Based Assemblies and Functional Materials*, Springer International Publishing, Cham, 2018, vol. 176.
- 6 J. T. Rhule, C. L. Hill, D. A. Judd and R. F. Schinazi, *Chem. Rev.*, 1998, **98**, 327–358.
- 7 D.-L. Long, E. Burkholder and L. Cronin, *Chem. Soc. Rev.*, 2007, **36**, 105–121.
- 8 M. Stuckart and K. Y. Monakhov, *Chem. Sci.*, 2019, **10**, 4364–4376.
- 9 Y. Ji, L. Huang, J. Hu, C. Streb and Y.-F. Song, *Energy Environ. Sci.*, 2015, **8**, 776–789.
- 10 A. Proust, B. Matt, R. Villanneau, G. Guillemot, P. Gouzerh and G. Izzet, *Chem. Soc. Rev.*, 2012, **41**, 7605–7622.
- 11 A. Proust, R. Thouvenot and P. Gouzerh, *Chem. Commun.*, 2008, 1837–1852.
- 12 J. Zhang, Y. Huang, G. Li and Y. Wei, *Coord. Chem. Rev.*, 2019, **378**, 395–414.
- 13 A. Dolbecq, E. Dumas, C. R. Mayer and P. Mialane, *Chem. Rev.*, 2010, **110**, 6009–6048.
- 14 O. Linnenberg, A. Kondinski and K. Y. Monakhov, in *Supramolecular Systems: Chemistry, Types and Applications*, 2017, pp. 39–66.
- 15 A. Blazevic and A. Rompel, *Coord. Chem. Rev.*, 2016, **307**, 42–64.
- 16 Y. Hou and C. L. Hill, *J. Am. Chem. Soc.*, 1993, **115**, 11823–11830.
- 17 A. V Anyushin, A. Kondinski and T. N. Parac-Vogt, *Chem. Soc. Rev.*, 2020, **49**, 382–432.
- 18 S. Vanhaecht, T. Quanten and T. N. Parac-Vogt, *Inorg. Chem.*, 2017, **56**, 3095–3101.
- 19 S. Vanhaecht, T. Quanten and T. N. Parac-Vogt, *Dalton Trans.*, 2017, **46**, 10215–10219.
- 20 S. Vanhaecht, J. Jacobs, L. Van Meervelt and T. N. Parac-Vogt, *Dalton Trans.*, 2015, **44**, 19059–19062.
- 21 R. J. Errington, S. S. Petkar, B. R. Horrocks, A. Houlton, L. H. Lie and S. N. Patole, *Angew. Chem., Int. Ed.*, 2005, **44**, 1254–1257.
- 22 B. J. S. Johnson and A. Stein, *Inorg. Chem.*, 2001, **40**, 801–808.
- 23 A. W. H. Lee and B. D. Gates, *Langmuir*, 2016, **32**, 7284–7293.
- 24 A. W. H. Lee and B. D. Gates, *Langmuir*, 2017, **33**, 8707–8715.
- 25 Y. Wang and I. A. Weinstock, *Chem. Soc. Rev.*, 2012, **41**, 7479–7496.
- 26 H. J. H. Kang, R. F. Ali, M. T. Y. Paul, M. J. Radford, I. Andreu, A. W. H. Lee and B. D. Gates, *Chem. Commun.*, 2019, **55**, 10452–10455.
- 27 M.-P. Santoni, A. K. Pal, G. S. Hanan, M.-C. Tang, K. Venne, A. Furtos, P. Ménard-Tremblay, C. Malveau and B. Hasenknopf, *Chem. Commun.*, 2012, **48**, 200–202.
- 28 M. S. Centellas, M. Piot, R. Salles, A. Proust, L. Tortech, D. Brouri, S. Hupin, B. Abécassis, D. Landy, C. Bo and G. Izzet, *Chem. Sci.*, 2020, **11**, 11072–11080.
- 29 H. Zeng, G. R. Newkome and C. L. Hill, *Angew. Chem.*, 2000, **112**, 1841–1844.
- 30 C. P. Pradeep, M. F. Misdrahi, F.-Y. Li, J. Zhang, L. Xu, D.-L. Long, T. Liu and L. Cronin, *Angew. Chem.*, 2009, **121**, 8459–8463.
- 31 P. Yin, T. Li, R. S. Forgan, C. Lydon, X. Zuo, Z. N. Zheng, B. Lee, D. Long, L. Cronin and T. Liu, *J. Am. Chem. Soc.*, 2013, **135**, 13425–13432.
- 32 T. Auvray, M.-P. Santoni, B. Hasenknopf and G. S. Hanan, *Dalton Trans.*, 2017, **46**, 10029–10036.
- 33 C. P. Pradeep, F.-Y. Li, C. Lydon, H. N. Miras, D.-L. Long, L. Xu and L. Cronin, *Chem.–Eur. J.*, 2011, **17**, 7472–7479.
- 34 Q. Xu, S. Yuan, L. Zhu, J. Hao and Y. Wei, *Chem. Commun.*, 2017, **53**, 5283–5286.
- 35 H. Ai, Y. Wang, B. Li and L. Wu, *Eur. J. Inorg. Chem.*, 2014, **2014**, 2766–2772.
- 36 K. P. Sullivan, W. A. Neiwert, H. Zeng, A. K. Mehta, Q. Yin, D. A. Hillesheim, S. Vivek, P. Yin, D. L. Collins-Wildman, E. R. Weeks, T. Liu and C. L. Hill, *Chem. Commun.*, 2017, **53**, 11480–11483.
- 37 M. Lu, Y. Wei, B. Xu, C. F.-C. Cheung, Z. Peng and D. R. Powell, *Angew. Chem., Int. Ed.*, 2002, **41**, 1566–1568.
- 38 J. L. Stark, A. L. Rheingold and E. A. Maatta, *J. Chem. Soc., Chem. Commun.*, 1995, 1165–1166.
- 39 J. Zhang, J. Hao, Y. Wei, F. Xiao, P. Yin and L. Wang, *J. Am. Chem. Soc.*, 2010, **132**, 14–15.
- 40 J. Zhang, P. Yin, J. Hao, F. Xiao, L. Chen and Y. Wei, *Chem.–Eur. J.*, 2012, **18**, 13596–13599.
- 41 A. Bayaguud, J. Zhang, R. N. N. Khan, J. Hao and Y. Wei, *Chem. Commun.*, 2014, **50**, 13150–13152.
- 42 J. Zhang, F. Xiao, J. Hao and Y. Wei, *Dalton Trans.*, 2012, **41**, 3599–3615.
- 43 H. An, J. Zhang, S. Chang, Y. Hou and Q. Zhu, *Inorg. Chem.*, 2020, **59**, 10578–10590.
- 44 A. Bayaguud, K. Chen and Y. Wei, *CrystEngComm*, 2016, **18**, 4042–4045.
- 45 I. Fa Bamba, C. Falaise, G. K. Gbassi, P. Atheba, M. Haouas and E. Cadot, *J. Coord. Chem.*, 2020, **73**, 2567–2578.
- 46 C. Qin and J. Zubieta, *Inorg. Chim. Acta*, 1992, **198–200**, 95–110.
- 47 P. Wu, J. Chen, P. Yin, Z. Xiao, J. Zhang, A. Bayaguud and Y. Wei, *Polyhedron*, 2013, **52**, 1344–1348.
- 48 P. R. Marcoux, B. Hasenknopf, J. Vaissermann and P. Gouzerh, *Eur. J. Inorg. Chem.*, 2003, **2003**, 2406–2412.
- 49 B. Hasenknopf, R. Delmont, P. Herson and P. Gouzerh, *Eur. J. Inorg. Chem.*, 2002, **2002**, 1081–1087.
- 50 C. G. Lin, W. Chen, D. L. Long, L. Cronin and Y. F. Song, *Dalton Trans.*, 2014, **43**, 8587–8590.
- 51 J. Zhang, Y. Huang, J. Zhang, S. She, J. Hao and Y. Wei, *Dalton Trans.*, 2014, **43**, 2722–2725.
- 52 J. Zhang, Z. Zhao, J. Zhang, S. She, Y. Huang and Y. Wei, *Dalton Trans.*, 2014, **43**, 17296–17302.
- 53 Q. Chen, D. P. Goshorn, C. P. Scholes, X. L. Tan and J. Zubieta, *J. Am. Chem. Soc.*, 1992, **114**, 4667–4681.
- 54 L. E. Briand, H. J. Thomas and G. T. Baronetti, *Appl. Catal., A*, 2000, **201**, 191–202.
- 55 C. P. Pradeep, D.-L. Long, G. N. Newton, Y.-F. Song and L. Cronin, *Angew. Chem., Int. Ed.*, 2008, **47**, 4388–4391.
- 56 J. Iwahara, C. D. Schwieters and G. M. Clore, *J. Am. Chem. Soc.*, 2004, **126**, 12800–12808.



- 57 L. Vandebroek, Y. Mampaey, S. Antonyuk, L. Van Meervelt and T. N. Parac-Vogt, *Eur. J. Inorg. Chem.*, 2019, **2019**, 506–511.
- 58 D. E. Salazar Marcano, S. Lentink, M. A. Moussawi and T. N. Parac-Vogt, *Inorg. Chem.*, 2021, **60**, 10215–10226.
- 59 V. Shivaiah and S. K. Das, *J. Chem. Sci.*, 2005, **117**, 227–233.
- 60 H. Jia, Q. Li, A. Bayaguud, S. She, Y. Huang, K. Chen and Y. Wei, *Sci. Rep.*, 2017, **7**, 12523.
- 61 S. Spillane, R. Sharma, A. Zavras, R. Mulder, C. A. Ohlin, L. Goerigk, R. A. J. O'Hair and C. Ritchie, *Angew. Chem., Int. Ed.*, 2017, **56**, 8568–8572.
- 62 D. Karimian, B. Yadollahi and V. Mirkhani, *Microporous Mesoporous Mater.*, 2017, **247**, 23–30.
- 63 X.-X. Li, S.-T. Zheng, W.-H. Fang and G.-Y. Yang, *Inorg. Chem. Commun.*, 2011, **14**, 1541–1545.
- 64 C. Sperandio, J. Rodriguez and A. Quintard, *Chem. Sci.*, 2020, **11**, 1629–1635.
- 65 J. Teichert and M. Ruck, *Eur. J. Inorg. Chem.*, 2019, **2019**, 2267–2276.

