

Cite this: *Mater. Adv.*, 2023,
4, 4333

Connecting metal–organic cages (MOCs) for CO₂ remediation

Javier Martí-Rujas 

In this Perspective article, recent developments in the self-assembly of supramolecular porous materials made of zero-dimensional (0D) porous metal organic cages (**MOCs**), connected by different approaches, and their application in CO₂ remediation are reviewed. The connection of **MOCs** carried out by coordination-bond driven linking, covalent bond linking and mechanical bond formation, leads to the formation of novel smart materials ranging from *solid* to *gel* states of matter, and in some cases, porous materials with hierarchical porosity stemming from the intrinsic **MOC** porosity and the voids generated among the connected **MOCs**. Both porosities can be tuned depending on the **MOC** sizes and on the way the cages are connected (*i.e.*, coordination-driven and covalent bond linking). In general, the supramolecular, often networked, materials arising from the connection of **MOCs** tend to show *diffuse scattering*, denoting only short-range order, making their structural elucidation very challenging or simply not possible. Thus, the bulk structure of materials formed by connected **MOCs** is often deduced from information obtained through other techniques like powder XRD, pair distribution function (PDF) analysis, solid-state NMR, dynamic light scattering (DLS), and positron annihilation lifetime spectroscopy (PALS). Materials obtained upon the connection of **MOCs** are usually in the form of amorphous solids, gels, xerogels and porous liquids (PLs) but have shown to outperform the CO₂ capacity and improved mechanical properties when compared to the single **MOCs**. The preparation of materials at the interface between solids and liquids is important to create functional materials displaying unique properties such as porosity in liquids and gels arising from the **MOCs** and their networked assembly, hence allowing CO₂ gas diffusion into the cage's voids where CO₂ can be trapped or catalytically transformed into other molecules (*i.e.*, formic acid (HCOOH)). Thus, materials containing connected **MOCs** can be exploited where **MOFs** cannot be used due to their brittle nature, typical of solid crystalline materials, for instance in applications where the porous material has to fit to different shapes for example those required to fit in tubes or shapes that usually crystalline solids cannot adapt easily, thus expanding the applications of connected **MOC** materials in areas involving fluids.

Received 28th July 2023,
Accepted 31st August 2023

DOI: 10.1039/d3ma00477e

rsc.li/materials-advances

1. Introduction

Combustion of fossil fuels, such as natural gas, petroleum, and coal in order to meet the energy demands of our past and recent societies, has contributed to an atmospheric rise in carbon dioxide (CO₂), and hence the Earth's temperature increases due to the greenhouse effect.¹ The rise of atmospheric CO₂ is threatening the Earth equilibrium including the natural environment and the human society. Therefore, technologies on carbon capture and conversion approaches are being proposed to decrease the CO₂ atmospheric emission.^{2,3}

Metal organic frameworks (MOFs) as post zeolitic materials are highly crystalline materials obtained by self-assembling

organic ligands and metal ions or clusters of metals (called secondary building units or SBUs) “stuck” together by coordination bonds.^{4–8} MOFs are also regarded as coordination polymers or coordination networks. The possibility of synthesizing porous MOFs and fine-tuning their porosity has given the chance to exploit such materials for gas adsorption, and in particular MOFs and MOF-based materials have emerged as good candidates to capture CO₂⁹ and are also suitable for CO₂ transformation into other molecules that are not harmful to the environment.²

MOF's structural properties including porosity, designability, crystallinity, flexibility and well-defined structures obtained from single crystal X-ray diffraction data (SC-XRD)¹⁰ and powder X-ray diffraction data (powder XRD)¹¹ have contributed to the rapid advancement of MOFs as functional materials for CO₂ remediation.⁹ The atomic resolution 3D crystal structure allows not only the direct visualization of the

Dipartimento di Chimica Materiali e Ingegneria Chimica. “Giulio Natta”,
Politecnico di Milano, Via L. Mancinelli 7, 20131 Milan, Italy.
E-mail: javier.marti@polimi.it



giving them a periodic nature. Thus, it can be envisaged that their inherent porosity might be maintained if monomeric **MOCs** are linked together through organic ligands in a supramolecular structure. However, the probability to obtain the linked **MOCs** in a crystalline and ordered state is difficult. On the other hand, it is also important to design strategies leading to porous materials that behave more like soft matter rather than crystalline (*i.e.*, rigid structure), because soft matter materials can be used in applications in the liquid or gel states. Therefore, not only to increase the **MOCs**' stability and flexibility, but to explore the formation of new and large supramolecular entities, strategies such as linking **MOCs** *via* coordination of bridging ligands to unsaturated metal sites; connecting the 0D cages upon *covalent bond* formation; or by interlocking **MOCs** using *mechanical bonds*, have been recently developed (Fig. 1).

Two **MOCs** can be connected in different manners. In the next examples the synthetic approaches shown in Fig. 1 have been applied to crosslink **MOCs**. In this way, polymeric structures made of discrete **MOCs** are produced. This strategy uses **MOCs** for obtaining supramolecular polymers with different types of porosities (*i.e.*, hierarchical porosity) generated from *intrinsic microporosity* inside the cage cavity and *mesoporosity* between the cages generated after the linkage of the **MOCs** (Fig. 1).

Crucially, the mesoporosity will depend also on the length, the flexibility and shape of the linker molecule connecting the **MOCs**. The bulk porous nature of the material can be used for trapping CO₂ or for transforming CO₂ into non-harmful substances. The

new supramolecular materials formed by connected **MOCs** showed that CO₂ can be adsorbed outperforming the CO₂ adsorption capacity and catalytic activity of non-connected **MOCs**. Moreover, the overall stability and flexibility of the linked **MOCs** is also enhanced with respect to the original molecular **MOCs**.

2.2. The low crystallinity of solid materials formed of connected **MOCs** and their structural characterization

The preparation of large supramolecular entities, such as those arising from the connection of **MOCs**, often in between the solid and liquid states (*i.e.*, soft matter), yields solids that are poorly crystalline, with only short-range order, or just amorphous, in which the absence of Bragg diffraction does not allow full structure determination using single crystal X-ray diffraction (SC-XRD)¹⁰ or powder XRD structure solution.¹¹ The entrapment of crystallization solvent inside the **MOCs** or in the spaces generated between the connected cages, tend to form amorphous materials. It is important to mention that in some cases, depending on the way the self-assembly takes place such as when fast crystallization processes are required to control the crystallization product (*i.e.*, crystallization under *kinetic control*), often result as microcrystals or amorphous phases which complicates the structure elucidation by SC-XRD (*vide ante*).

The impossibility in the understanding of the 3D atomic arrangement in the self-assembled material does not allow us to make efficient progress in the design and fine tuning for improving the properties of materials made of connected **MOCs**. Thus, understanding their functional properties without detailed structural characterization is often very challenging. However, techniques such as X-ray diffraction (SAXS), pair distribution function (PDF) analysis, combined with solution and solid-state NMR, dynamic light scattering (DLS), and positron annihilation lifetime spectroscopy (PALS) can be used to gain information on the supramolecular superstructure formed upon linking **MOCs**.

Despite the difficulties in the structural characterization of some of the supramolecular materials obtained by connecting monomeric **MOCs**, a myriad of new properties were discovered, such as softness and processability of porous materials, making the effort of studying new avenues of assembling individual **MOCs** into polymeric materials worth exploring. As most porous materials are used in the solid-state, they cannot be used in common flow processes. Supramolecular **MOC** polymers displaying characteristic features of liquid or liquid-like materials such as gels²⁷ are clearly interesting with huge potential in industrial applications.

3. Polymeric structures generated by linking **MOCs** with ligands *via* coordination bonds

3.1. Formation of a supramolecular solid polymer connecting **MOCs** *via* coordination bonds with hierarchical porosity

An example showing how **MOCs** can be connected through covalent bonds using bidentate ligands was reported in 2011 by

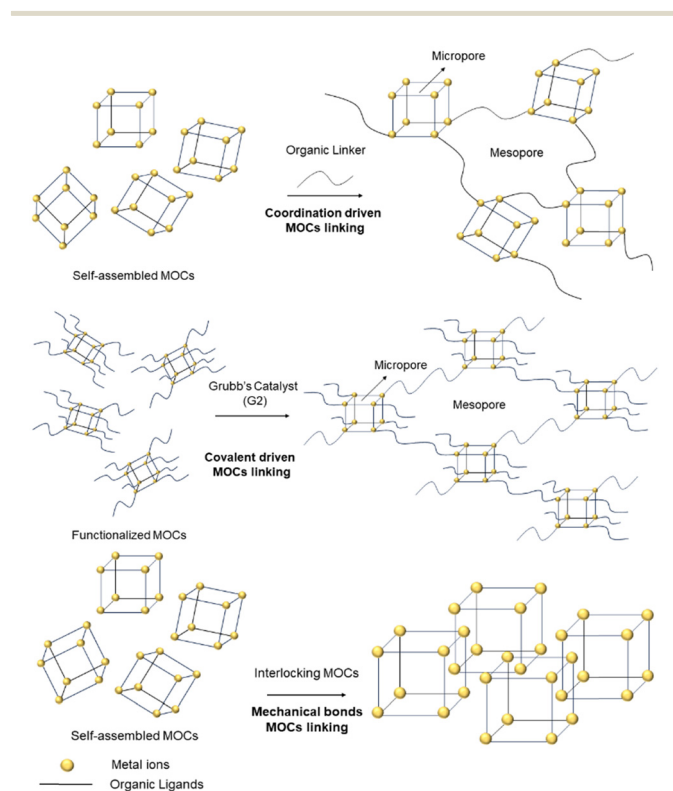


Fig. 1 Cartoon showing the stepwise synthesis of connected **MOCs** *via* ligand coordination (top), covalent bond formation from functionalized **MOCs** (middle) and interlocking of **MOCs** *via* mechanical bonds (bottom).



Chun and Moon in which 2,7-naphthalenedicarboxylate and Cu^{2+} were self-assembled into a large **MOC** with 12 Cu–Cu paddlewheel units, $[\text{Cu}_{24}(2,7\text{-ndc})_{24}(\text{DMF})_{10}(\text{H}_2\text{O})_{14}]$ (**MOC-1**).³⁷ The SC-XRD structure was determined by synchrotron radiation and the self-assembled material is a 3.3 nm cuboctahedron (Archimedean solid) as shown in Fig. 2. In the crystalline state, the cuboctahedrons are in close contact with adjacent ones *via* the triangular windows packing in a body-centered cubic structure (*Im* $\bar{3}$ *m* space group). The **MOC** is very large with its 68% of space occupied by solvent molecules, which is 22 147 Å³ of its total unit cell volume. The cuboctahedron can be considered nearly spherical with an internal diameter of an imaginary sphere of 1.8 nm (Fig. 2a) falling in the microporous regime. The as synthesized **MOC-1** is crystalline but becomes amorphous in the activation process, upon evacuation of guests, because they act as templating agents. However, the amorphous phase of **MOC-1** shows an *amorphous-to-crystalline* (AC) transformation once it traps guest molecules. **MOC-1** can trap CO_2 which shows reversible type I isotherms without significant hysteresis because only the internal voids of amorphous **MOC-1** (microporous regime) are available for gas inclusion.³⁷ One approach to see if there is an increase in CO_2 adsorption, with respect to isolated **MOC-1**, can be carried out by synthesizing a polymeric structure of connected **MOC-1**, but the intrinsic porosity of individual **MOCs** must be maintained.

The linkers used to connect the **MOC-1** were diamine spacers with different lengths and flexibility such as ethylenediamine (**en**), xylenediamine (**xn**) and diaminoheptane (**hn**) (Fig. 2b). Crosslinking such ligands with **MOC-1**, results in a porous material that has two pore regimes: the intrinsic **MOC** belonging to the microporous regime and the one created among the linked cages, the mesoporous regime. The supramolecular material with ethylenediamine linker shows some crystallinity while the solid materials including xylenediamine and diaminoheptane are amorphous phases. This is probably due to the higher flexibility of **xn** and **hn**.

Interestingly, CO_2 sorption experiments at 195 K and 1 bar are systematically lowered in going from purely microporous **MOC-1** to mesoporous materials **MOC-1(en)**, **MOC-1(xn)** and **MOC-1(hn)**. This behavior is explained as the adsorption of small gases is favoured in micropores showing strong fluid wall interactions. Although the mesoporous materials did not perform better than **MOC-1** for CO_2 adsorption, this example demonstrates the potential to prepare bimodal porous

materials (hierarchical porosity) whose porosities can be tuned by selecting different cages and linkers. In this way, the preparation of supramolecular hybrid metal organic materials that are more in the regime of soft-matter (*i.e.*, supramolecular polymers with intrinsic (micro)porosity) than conventional solid **MOFs** or **MOCs** can be synthesized.

3.2. Synthesis of a supramolecular porous aerogel (SAG) for CO_2 adsorption connecting **MOCs** through coordination bonds

When thinking about materials used as adsorbents, what comes to mind are solid crystalline materials which are brittle, such as **MOFs**. Porous materials displaying properties like processability and softness are important as they can be used in applications where crystalline, rigid, and porous **MOFs** cannot be exploited. Furukawa and co-workers using derivatives of the highly stable cuboctahedral **MOC** $[\text{Rh}_2(\text{bdc})_2]_{12}$ (**MOC-2**)³⁸ (where H_2bdc – benzene-1,3-dicarboxylic acid) self-assembled using a dirhodium paddlewheel motif and a dicarboxylic acid (Fig. 3a) could synthesize amorphous soft porous materials.³⁹ Because of the different lability among equatorial (poorly labile) and apical (highly labile) dirhodium paddlewheel atoms in the **MOC-2**, the cages can be linked *via* coordination bonds using appropriate ligands (*vide ante*). The icosahedral **MOC-2** has high structural stability upon desolvation and guest removal due to the Rh–Rh single bond and strong Rh–carboxylate coordination bond.

The authors demonstrated how a supramolecular **MOC** polymer obtained by linking a derivative dirhodium **MOC-3**, in which H_2bdc ligand is substituted by 5-dodecoxybenzene-1,3-dicarboxylic acid = $\text{H}_2\text{bdc-C}_{12}$ to increase its solubility, using linkers with two imidazole functionalities (Fig. 4).⁴⁰ To polymerize the $\text{C}_{12}\text{RhMOP}$ monomers (**MOC-3**), the imidazole linker 1,4-bis(imidazole-1-ylmethyl)benzene (**bix**) was used. The addition (stepwise) of **bix** into a DMF solution of **MOC-3** was monitored by dynamic light scattering (DLS) giving a maximum of particle sizes of 78 nm that were revealed to be spherical as shown by field emission scanning electron microscopy (FESEM). Larger particles can be obtained adding less molecular equivalents of **bix**. Powder XRD experiments show that the spherical particles are amorphous as no Bragg diffraction is observed.

Kinetic control in the synthesis of porous extended **MOF** structures^{41–43} and **MOCs**^{44,45} has been proved to be a good strategy to selectively obtain the desired products. In this vein, applying kinetic control by excess of **bix** molecules to a **MOC-3** solution and cooling from 80 °C to room temperature, it was possible to isolate a **MOC** monomer with the $(\text{C}_{12}\text{RhMOC})(\text{bix})_{12}$ composition of 5.2 ± 1.2 nm size. After 1d, no aggregation was observed by keeping the suspension at room temperature. Because all the coordination sites are occupied by **bix** ligand, the only way to link the cages is by heating the solution containing the isolated **MOCs** (fully coordinated with **bix**) in order to release **bix** ligands and thus trigger the polymerization of $(\text{C}_{12}\text{RhMOC})(\text{bix})_{12}$ into larger particles of 22 ± 7 nm. The supramolecular colloidal gel (**SCG**) was obtained upon incubation (Fig. 3b). The macromolecular polymeric structure of

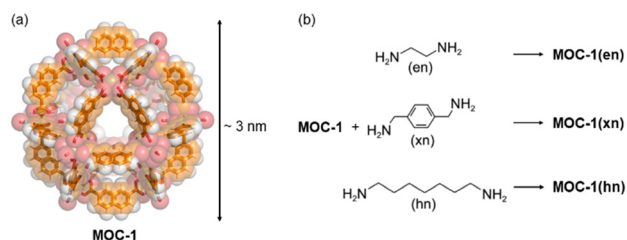


Fig. 2 (a) Single crystal XRD structure of the cuboctahedral **MOC-1**.³⁷ (b) Chemical reaction of **MOC-1** with the diamine spacers used to form the supramolecular material made of connected **MOC-1**.³⁷



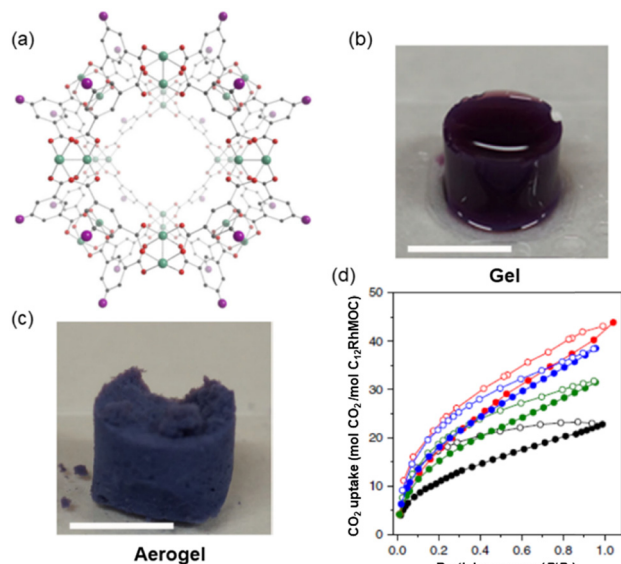


Fig. 3 (a) Structure of the $C_{12}RhMOF$ porous monomer (**MOC-3**) obtained from the related $[Rh_2(bdc)_2]_{12}$ crystal structure formed by rhodium ions (green) coordinated to the oxygen atoms (red) of H_2bdc-C_{12} ligand in gray, with the appended aliphatic chain simplified as a purple sphere. (b) Gel and (c) aerogel obtained from the connection of monomeric **MOC-3**. (d) CO_2 adsorption isotherm at 195 K of **SAG-1** (red), supramolecular **MOC** polymer (blue), supramolecular **MOC** polymer of bigger dimensions (green) and $C_{12}RhMOP$ (black). Adsorption and desorption experiments are represented with filled and empty symbols respectively. Reproduced from ref. 40.

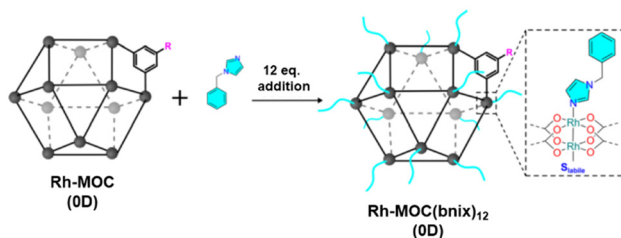


Fig. 4 Cartoon showing the functionalization of Rh-MOC (0D) with **bnix** ligand to mimic the external surface of supramolecular colloid $C_{12}Rh-CPP$ and gel $C_{12}Rh-SAG$. Reproduced from ref. 47 with permission from ACS, copyright 2022.

linked **MOCs** did not form sufficient electrostatic interactions to pack the building components in an ordered manner, resulting in an amorphous phase as shown by powder XRD.

The porosity of the supramolecular polymer was evidenced by CO_2 gas adsorption by transforming first the **SCG** to the aerogel (treated with supercritical CO_2 and then heating in the vacuum) **SAG-1** (where **SAG** = supramolecular aerogel). **SAG-1** was composed of a hierarchical microporous structure of fused particles of 38 ± 11 nm in size (Fig. 3c).

The supramolecular material contains a robust RhMOC backbone with permanent microporosity in an amorphous state. The intrinsic porosity of **MOC-3** is preserved after polymerization as shown by the type I isotherm at 195 K (Fig. 3d).

Crucially, the uptake at $P/P_0 = 0.95$ of **SAG-1** is superior to that observed for the porous monomer with $68.64 \text{ cm}^3 \text{ g}^{-1}$ and $40.23 \text{ mol } CO_2/\text{mol } C_{12}RhMOC$ vs. $46.01 \text{ cm}^3 \text{ g}^{-1}$ and $22.20 \text{ mol } CO_2/\text{mol } C_{12}RhMOC$ respectively. Thus, using *kinetic control*, it is possible to prepare a supramolecular material with two different macroscopic morphologies including spherical **MOCs** particles and 3D interconnected colloidal gels.

3.3. Synthesis of a supramolecular porous aerogel (SAG) for photocatalytic reduction of CO_2 into formic acid

As mentioned, one efficient method to reduce the amount of CO_2 gas is by transforming it into molecules that can be used in other applications.⁴⁶ The versatility of **SAG-1** has also been exploited as a heterogeneous catalyst in the photocatalytic reduction of carbon dioxide into formic acid ($HCOOH$).⁴⁷ Crucially, the catalytic activity was better than the single **MOCs** paddlewheel complexes and other heterogeneous photocatalysts.

For the catalytic study, the authors exploited both **MOCs**, **MOC-2** and **MOC-3**, using isophthalic acid and 5-dodecoxybenzene-1,3-dicarboxylic acid respectively, and by using **bnix** the **MOCs** were self-assembled into supramolecular polymers in the form of colloids or gels depending on the quantity of **bnix** used. Unfortunately, the supramolecular polymers are amorphous showing only short-range order.

Interestingly, both the colloidal and the gel evidenced catalytic activity for the transformation of CO_2 into formic acid as the only product. Both $C_{12}Rh-CPP$ (colloid) and $C_{12}Rh-SAG$ show the same catalytic activity ($TOF = 59 \text{ h}^{-1}$) despite having different morphology. Importantly, the catalytic activity is a bit higher than the molecular building block $C_{12}RhMOC$ ($TOF = 52 \text{ h}^{-1}$). To understand the catalytic behavior, pristine $C_{12}RhMOC$ was functionalized with monodentate 1-benzylimidazole (**bnix**) to yield $[Rh_2(C_{12}-bdc)_2]_{12}(bnix)_{12}$ ($C_{12}RhMOCbnix$) to mimic the external surface of the **MOCs** in $C_{12}Rh-CPP$ and $C_{12}Rh-SAG$ (Fig. 4). Interestingly, the catalytic activity is increased with values very similar to those observed in the supramolecular structures with linked **MOCs**. From those results, first, the authors concluded that the catalytic activity is not limited to surface effects in the heterogeneous polymers and, second, that the internal part of the cages is accessible to the reactants. The presence of the coordinated **bnix** and **bnix** ligands slightly increases the electron density around the Rh centers, resulting in an increase in the catalytic activity.

The self-assembled supramolecular catalysts have demonstrated high TOF up to 60 h^{-1} outperforming by 30% the RhMOC and other state-of-the-art heterogeneous photocatalyst systems including Rh-MOFs by at least a factor of 12. The optimal catalytic activity has been rationalized because of the high number of Rh atoms per gram of the catalyst but also favoured by the accessibility inside the supramolecular cage. Structural aspects focussing on the inter-atomic distances between atoms were determined using PDF analysis, regarding the stability of the **MOCs** linked by **bnix** ligands. Both samples, pristine and spent samples show that the $G(r)$ curves demonstrate that at the molecular level, there is no distortion or



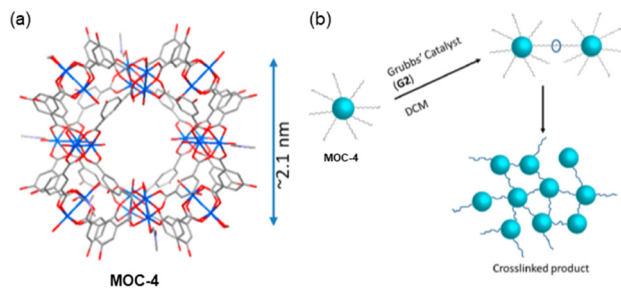


Fig. 6 (a) Synchrotron single crystal X-ray structure of **MOC-4** displaying the core **MOC** as the disordered alkyl chains could not be resolved crystallographically. (b) Cartoon depicting the cross-linking process *via* G2 Grubbs' catalyst in DCM. Reproduced from ref. 52 with permission from ACS, copyright 2019.

cages with long alkyl chains having terminal alkenes (**MOC-4**) (Fig. 6a).⁵² Using olefin metathesis reactions, the functionalized **MOC-4** were then connected. In the new synthesized system, the **MOCs** are bridged by $-\text{OC}_{18}\text{H}_{34}\text{O}-$ units among the isophthalate ligands (Fig. 6b). Synchrotron single crystal X-ray crystallography revealed the structure which shows that the Cu_{24} metals linked by the organic ligand yield a cuboctahedral of *ca.* 2 nm packing in the *Pnmm* space group.

The **MOC** structure remains stable when dissolved in organic solvents but not in water. The functionalized **MOC** were linked *via* olefin metathesis using Grubbs' second-generation catalyst (G2) by solubilizing the cage in DCM under atmosphere conditions. In this work, three **MOC-4** cross-linked versions with $\approx 20\%$, $\approx 40\%$ and $\approx 80\%$ degrees of cross-linking were studied. The three products referred to as **MOC-4** \times 20, **MOC-4** \times 40 and **MOC-4** \times 80 were indicated by solution ^1H NMR. Upon crosslinking, the solid (**MOC-4** \times 40) and (**MOC-4** \times 80) appeared from the solutions in common organic solvents (*i.e.*, DCM, chloroform, ethyl acetate, THF and DMF) as microcrystalline samples (Fig. 7a). The partial solubility of **MOC-4** \times 20 suggested that the cross-linking reaction did not proceed sufficiently due to inhomogeneous local cross-linking.

The most homogeneously cross-linked **MOC-4** solid (**MOC-4** \times 40) was used for CO_2 gas adsorption experiments at 195 K/1.2 bar, and adsorbed 2.18 mmol g^{-1} of CO_2 while monomeric **MOC-4** adsorbed 1.16 mmol g^{-1} . Thus, the

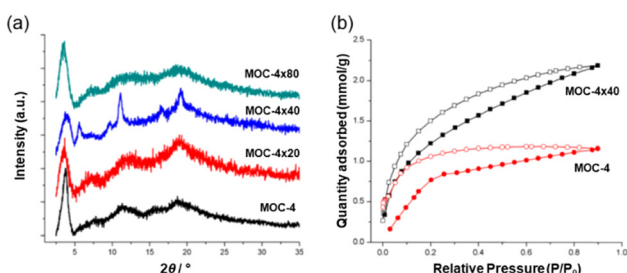


Fig. 7 (a) Powder XRD patterns of the **MOC-4** and the supramolecular cross-linked products. (b) CO_2 adsorption experiments carried out at 195 K and 1.2 bar. Reproduced from ref. 52 with permission from ACS, copyright 2019.

presence of additional voids is a result of the cross-linking process, and this allows for a higher CO_2 adsorption in the solid with “connected” **MOCs** than the single **MOC-4**. Interestingly, CO_2 adsorption at 298 K shows the same trend as seen for the 195 K experiments only with a slight decrease in the uptake of CO_2 of 2.3 mmol g^{-1} for **MOC** \times 40 and 1.3 mmol g^{-1} for **MOC-4** (Fig. 7b).

5. From MOCs to polycatenanes or [n]-catenane networks

5.1. Linking MOCs *via* mechanical bonds to form polycatenanes made of cages

The last approach to connecting **MOCs** in a polymeric manner outlined in this Perspective is by linking them not by coordination bonds, or by covalent bonds as recently seen, but by *mechanical bonds*.^{53–56} Although studies of CO_2 adsorption in poly-catenanes formed of interlocked **MOCs** are very few,⁵⁷ clearly the intriguing structural properties of cage-catenanes make such materials potential candidates for exploitation in CO_2 remediation. Polycatenanes made of rings (*i.e.*, not by **MOCs**) can be defined as mechanically linked polymers derived from catenane subunits. The mechanical properties of catenanes are important because the individual ring components in the catenane can have rotations, twisting and elongation movements giving the mechanical molecule important functional properties.⁵⁶ In order to separate two rings in a catenane it is necessary to break chemical bonds even though they are not connected *via* chemical bonds. If instead of using rings for the formation of the catenane chains, **MOCs** are used, then cage-catenanes or cage-polycatenanes can be generated.^{58,59} However, the synthesis of the cage-catenanes is challenging because several aspects must be considered for appropriate cage interlocking.

First, the size and number of windows and the size of the cavity should be large enough to allow the formation of the mechanical bond.⁵⁹ Second, suitable metal atoms with a certain lability are needed for the error checking in the reversible coordination bond formation involving intermediate structures. Third, the presence of guest molecules that act as templating agents are needed to obtain crystalline structures.⁵⁹ Fourth, depending if the catenation is forming 1D-chains, 2D layers or 3D cage catenation, the electrostatic forces keeping the chains or layers will influence their crystallinity, their dynamic behavior upon external stimuli, and hence the gas adsorption properties. Thus, catenanes formed of interlocked **MOCs** is another degree of structural complexity.

5.1. Mechanically interlocked tetrahedral M_6L_4 MOCs yielding 3D cage polycatenanes

The example of Lu and co-workers reported a polycatenane self-assembly of tetrahedral **MOCs** prepared using six $[\text{NiL}]^{2+}$ cations (where L = 1,4,8,11-tetraazaundecane) and four tri(4-carboxy-benzyl)amine ligand (H_3tcb) (Fig. 8a and b).⁵⁷ The crystal structure was determined using an initial model



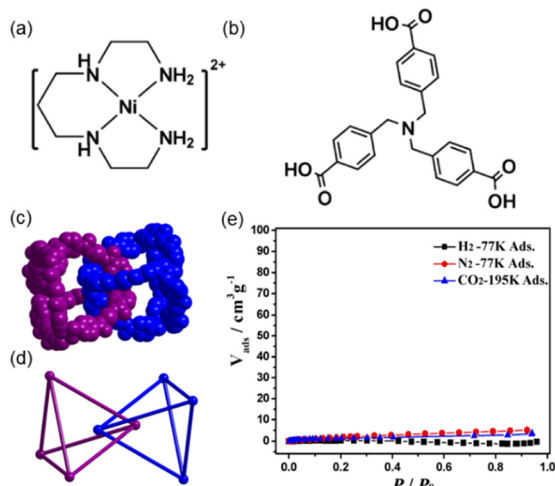


Fig. 8 (a) Structure of cation $[\text{NiL}]^{2+}$ and (b) ligand H_3tcba used for self-assembling **MOC-5**. (c) Space-filling and (d) ball-and-stick representations of two interlocked **MOC-5** nanocages, showing the interlocked corners in face-to-face stacking fashion with a distance of 6.219 Å between two nitrogen atoms of two tcba^{3-} . A single cage is interlocked by other four cages (not shown). (e) Sorption isotherms of N_2 , H_2 and CO_2 for dehydrated mechanically interlocked **MOC-5**. Reproduced from ref. 57.

obtained from SC-XRD but refined using powder XRD data by Rietveld refinement as suitable crystals for SC-XRD were not available. Four tcba^{3-} anions link six $[\text{NiL}]^{2+}$ cations *via* its three carboxy-benzyl groups leading to tetrahedral cages with the formula $[\text{NiL}]_6(\text{tcba})_4$ (**MOC-5**). In **MOC-5**, each $\text{Ni}(\text{II})$ is six-coordinated to four N atoms from L and two carboxylate O atoms from two individual tcba^{3-} anions, and each tcba^{3-} connects three $[\text{NiL}]^{2+}$. The **MOC** is formed of four tcba^{3-} anions located at the vertexes of the cage and six $\text{Ni}(\text{II})$ metals situated at the edges of the cage resulting in a **M6L4** nanocage (Fig. 8c and 8d). The size of the cage considering the distances among edges is 16.64 Å. In the center of the cage there is a ClO_4^- anion. The solvent accessible volume is *ca.* 10% of the total unit cell volume. The large openings of the **M6L4 MOC-5** nanocages allows a quadruple catenation in which one cage is mechanically interlocked with another four through all its four vertices (Fig. 8d). The overall structure is a 3D extended polycatenane remaining one of the few of such structures reported.⁶⁰

Gas adsorption experiments show that the polycatenane formed of interlocked tetrahedral cages is nonporous for CO_2 at 195 K (Fig. 8e), because it becomes amorphous upon guest water release (activation process). However, it shows that for small alcohols such as methanol, ethanol *i*-propanol and *i*-butanol it is porous. The sorption isotherms show that the smaller the alcohol the better the adsorption capacity per cage. Thus, after interlocking of the tetrahedral **MOCs** there is enough space for adsorbing gas molecules (*i.e.*, alcohols).

5.2. Mechanically interlocked icosahedral M_{12}L_8 MOCs yielding 1D cage polycatenanes

Another type of poly- $[n]$ -catenane structure that can be a potential candidate for CO_2 adsorption is the 1D chain

structure of interlocked icosahedral M_{12}L_8 nanocages which have huge internal voids of *ca.* 2700 Å³. So far, the work done on such materials has been using the tridentate and rigid ligands 2,4,6-tris-(4-pyridyl)pyridine (**TPP**),^{61,62} (**MOC-6**) and 2,4,6-tris-(4-pyridyl)benzene (**TPB**),^{44,45,63–65} (**MOC-7**) in which one single icosahedral M_{12}L_8 nanocage is interlocked by two adjacent cages forming 1D chains along the *c*-crystallographic direction (Fig. 9a). Single crystals of the M_{12}L_8 poly- $[n]$ -catenanes are stable at room temperature and have shown to behave dynamically upon external stimuli. In particular, the heterogeneous gas–solid adsorption of aromatic molecules *via* molecular recognition, has been demonstrated by multiple single-crystal-to-single-crystal reactions.⁶⁶ However, CO_2 adsorption has not yet been tested for such materials involving **MOC-7**. The mechanically interlocked material shown in Fig. 9b might show CO_2 uptake.

So far, such **MOC-7** within the polymeric structures can be suitable for gas adsorption because they are interlocked in the absence of solvent molecules. It has been demonstrated that the amorphous phase of the M_{12}L_8 poly- $[n]$ -catenane can adsorb, from the gas phase, aromatic molecules as evidenced by powder XRD analysis, thus indicating a significant dynamic behavior of the non-ordered phase containing the interlocked M_{12}L_8 nanocages.⁶³ It has also been demonstrated that in a heterogeneous solid–liquid phase process, methanol can be trapped in the amorphous nanocages producing a swelling effect on the material.⁶³ Thus, CO_2 could also be entrapped in the interlocked **MOC-7** cages.

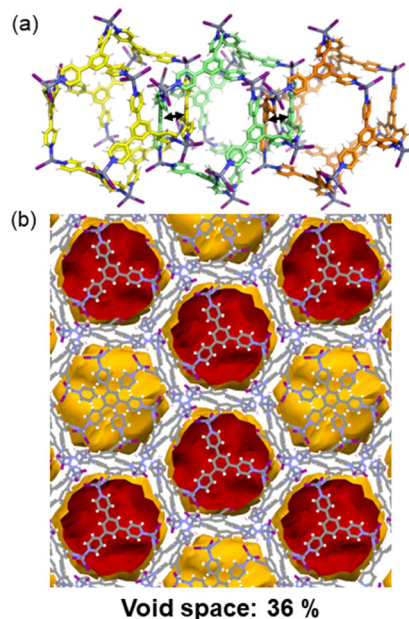


Fig. 9 (a) Interlocking of three M_{12}L_8 nanocages expanding along the *c*-axis. To differentiate the individual M_{12}L_8 cages the carbon atoms are green, yellow and orange. (b) View of the isolated voids in the M_{12}L_8 MOCs after manually removing the solvent molecules. Reproduced from ref. 45.



6. Benefits of linking MOCs for CO₂ remediation

The beneficial aspects of synthesizing new materials by connecting **MOCs** for CO₂ remediation are numerous and important ranging from structural to functional aspects. The most salient features described in this article are highlighted below.

First, the crosslinking of **MOCs** gives the possibility of synthesizing porous materials with hierarchical porosity including microporosity and mesoporosity with applications in CO₂ remediation that can outperform those of isolated **MOCs**.

Second, the formation of supramolecular metal–organic architectures upon connecting **MOCs** yields materials that are soft-matter-like materials such as supramolecular porous gels and aerogels which find applications in areas involving fluids.

Third, as shown, the CO₂ uptake performance of **MOC-3** is preserved after cross-linking (*i.e.*, the original porous properties of **MOC-3** are maintained) and in **SAG-1** the CO₂ uptake at $P/P_0 = 0.95$ is higher compared to that of the isolated **MOC-3** (40.23 mol CO₂/mol C₁₂RhMOC (**SAG-1**) vs. 22.20 mol CO₂/mol C₁₂RhMOC (**MOC-3**)) showing the benefit of connecting isolated **MOC-3**.

Fourth, improved photocatalytic reduction of CO₂ into formic acid using the supramolecular aerogel **SAG-1** is significantly improved, outperforming by 30% that of single **MOCs** paddlewheel complexes and other heterogeneous photocatalysts.

Fifth, novel materials that are between porous solids and porous liquids can be synthesized (by connecting **MOC-2** with the introduction of IL in the mesopores), showing about double CO₂ sorption capacity at *ca.* 100 KPa when compared to the IL. This is explained due to the accessible porosity in the soft material of connected **MOCs**.

Sixth, using a different cross-linking mechanism by covalent bond formation, and not by means of coordination bonds as in the previous cases, linked **MOC-4** (at 192 K/1.2 bar) shows improved gas uptake of 2.18 mmol g⁻¹ of CO₂, while monomeric **MOC-4** adsorbed 1.16 mmol g⁻¹.

Mechanically interlocked **MOCs** are far less explored for CO₂ adsorption, but the dynamic behavior and the internal voids left after the **MOCs**' interlocking show potential in CO₂ remediation applications.

7. Conclusions

Crystal engineering and soft matter engineering strategies aimed to synthesize new materials embedding **MOCs** linked through coordination driven and covalent cross-linking, have shown promising structural and functional properties. Materials formed of connected **MOCs** have been exploited for the specific application of CO₂ adsorption and its catalytic transformation into organic compounds. In this Perspective, it has been shown that for the few examples of **MOCs** linked by coordination bonds or covalent bonds, in most of the cases,

the CO₂ adsorbed is superior when the cages are connected compared to the monomer **MOCs** not forming part of the supramolecular polymer. Photocatalytic CO₂ reduction to formic acid has been shown to work well in a supramolecular aerogel of connected **MOCs**. Gel-like materials prepared by connecting **MOCs** can be exploited in applications where **MOFs** cannot be used due to their brittle nature, typical of solid crystalline materials. Semi-solid materials like gels containing strongly connected **MOCs** are processable, soft, and can be shaped and used for instance in application shapes that usually crystalline solids cannot adapt easily, thus expanding the applications of connected **MOCs** materials in areas involving fluids. Mechanically interlocked tetrahedral **MOCs** have been tested also for CO₂ adsorption. Despite not showing CO₂ uptake they can take up other small molecules like alcohols. Larger interlocked cages such as **M₁₂L₈**, due to their dynamic behaviour upon external stimuli, are potential candidates which are worth trying in applications of CO₂ remediation. The potential of linking different types of **MOCs** using coordination driven, covalent linking or mechanical bonds, into supramolecular porous materials, really shows how versatile this research area is. Supramolecular materials including linked **MOCs**, like the ones reviewed in this Perspective, will soon produce novel materials with unexplored functional properties not only in CO₂ remediation but in many other applications from regenerative medicine to soft robotics.

Author contributions

J. M.-R. conceived and wrote the article.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

J. M.-R. thanks Politecnico di Milano for funding (Fondo Chiamata Diretta Internazionalizzazione. Prg. Id. 61566).

Notes and references

- 1 E. S. Sanz-Pérez, C. R. Murdock, S. A. Didas and C. W. Jones, *Chem. Rev.*, 2016, **116**, 11840–11876.
- 2 L. Zhang, Z.-J. Zhao and J. Gong, *Angew. Chem., Int. Ed.*, 2017, **56**, 11326–11353.
- 3 M. Ding, R. W. Flaig, H.-L. Jiang and O. M. Yaghi, *Chem. Soc. Rev.*, 2019, **48**, 2783–2828.
- 4 B. F. Hoskins and R. Robson, *J. Am. Chem. Soc.*, 1990, **112**, 1546–1554.
- 5 M. Fujita, Y. J. Kwon, S. Wahsizu and K. Ogura, *J. Am. Chem. Soc.*, 1994, **115**, 1151.
- 6 O. M. Yaghi and H. Li, *J. Am. Chem. Soc.*, 1995, **117**, 10401.
- 7 M. Kondo, T. Yoshitomi, K. Seki, H. Matsuzaka and S. Kitagawa, *Angew. Chem., Int. Ed. Engl.*, 1997, **36**, 1725.



- 57 L. Jiang, P. Ju, X.-R. Meng, X.-J. Kuang and T.-B. Lu, *Sci. Rep.*, 2012, **2**, 668–672.
- 58 Y. Yamauchi, M. Yoshizawa and M. Fujita, *J. Am. Chem. Soc.*, 2008, **130**, 5832–5833.
- 59 L. Chen, Q. Chen, M. Wu, F. Jiang and M. Hong, *Acc. Chem. Res.*, 2015, **48**, 201–210.
- 60 X. Kuang, X. Wu, R. Yu, J. P. Donahue, J. Huang and C.-Z. Lu, *Nat. Chem.*, 2010, **2**, 461.
- 61 J. Heine, J. Schmedt auf der Gunne and S. Dehnen, *J. Am. Chem. Soc.*, 2011, **133**, 10018.
- 62 E. C. Constable, G. Zhang, C. E. Housecroft and J. Zampese, *CrystEngComm*, 2011, **13**, 6864.
- 63 J. Martí-Rujas, S. Elli, A. Sacchetti and F. Castiglione, *Dalton Trans.*, 2022, **51**, 53–58.
- 64 J. Martí-Rujas and A. Famulari, *Cryst. Growth Des.*, 2022, **22**, 4494–4502.
- 65 J. Martí-Rujas, S. Ma and A. Famulari, *Inorg. Chem.*, 2022, **61**, 10863–10871.
- 66 J. Martí-Rujas, S. Elli, A. Zanotti, A. Famulari and F. Castiglione, *Chem. – Eur. J.*, DOI: [10.1002/chem.202302025](https://doi.org/10.1002/chem.202302025).

