



Cite this: *RSC Appl. Interfaces*, 2024, **1**, 779

Efficient peroxymonosulfate activation by Fe–BiOCl hollow microspheres for carbamazepine removal†

Liyong Ding,^{‡*a} Xuejuan Huang,^{‡b} Yuqin Liu,^b
Qingqing Jiang ^b and Juncheng Hu ^{*b}

The preparation of highly effective and stable photocatalysts for visible-light-driven activation of peroxymonosulfate (PMS) to remove refractory organic contaminants is an attractive study. Herein, a series of Fe–BiOCl photocatalysts with a hollow structure were prepared through a regular one-step solvothermal approach and applied to activate PMS for carbamazepine (CBZ) degradation. Benefiting from the synergistic effect of photocatalysis and PMS activation, the 3% Fe–BiOCl/PMS system exhibits a higher CBZ removal ability under visible irradiation, with the corresponding apparent rate constant ($k = 0.0449 \text{ min}^{-1}$) being 12 times higher than that of individual BiOCl ($k = 0.0037 \text{ min}^{-1}$). Further experiments verify that the doping of Fe and the construction of the hollow structure of BiOCl can improve light absorption and utilization efficiency. More importantly, the introduced Fe^{3+} can facilitate the fast separation of photogenerated carriers and the activation of PMS. Capture experiments and EPR tests demonstrate that multiple active species ($\text{OH}^\cdot$, $\text{SO}_4^{\cdot-}$, $^1\text{O}_2$ and $\text{O}_2^{\cdot-}$) participate in the PMS activation for the CBZ degradation process, with $\text{SO}_4^{\cdot-}$ being the primary active species. Furthermore, the effects of photocatalyst amount, PMS concentration, initial solution pH, and co-existing anions on CBZ removal were explored. A possible mechanism for the photocatalytic removal of CBZ is also proposed. In addition, the 3% Fe–BOC displays outstanding photocatalytic activity over four consecutive cycles, indicating that it could be a reliable PMS activator for CBZ elimination in practical application. This work provides new ideas for constructing efficient and stable BiOCl-based catalytic systems for visible-light-driven removal of emerging contaminants.

Received 17th February 2024,
Accepted 5th April 2024

DOI: 10.1039/d4lf00051j

rsc.li/RSCApplInter

1. Introduction

Recently, the continuous detection of pharmaceuticals and personal care products (PPCPs) in aquatic ecosystems and their possible hazards have aroused widespread attention.^{1–4} Carbamazepine (CBZ), a commonly used psychotherapeutic drug, is considered one of the most detected representative PPCPs in natural water due to its negligible biodegradation or photodegradation in the environment.^{5–7} To date, several strategies for removing CBZ from wastewater have been established, including adsorption, biodegradation, pyrolysis, photolysis, advanced oxidation processes, *etc.*^{8–11} Because of

its environmentally friendly nature and high removal efficiency, photocatalytic oxidation is regarded as a promising method.¹²

As a significant bismuth-based semiconductor, BiOCl possesses advantages such as an adjustable bandgap, photochemical stability, non-toxicity, *etc.* However, due to the rapid recombination of photogenerated carriers and a limited light response range, its widespread application is severely restricted.^{13,14} Some attempts have been undertaken to address these shortcomings, including ion doping, precious metal deposition, defect engineering, *etc.* Of particular note is the interfacial modulation method involving the doping of transition metals (such as Cu, Fe, *etc.*) to enhance light absorption and facilitate the efficient separation of photoinduced charge carriers, thereby improving photocatalytic properties.^{15–22} For instance, the introduction of Fe dopants can modify the electronic structure of the photocatalyst, narrowing the bandgap or shifting the position of energy levels. These alterations can affect the absorption of light and the redox properties of the photocatalyst.²³ Generally, the modification of transition metals on the

^a College of Chemical and Material Engineering, Quzhou University, Quzhou 324000, China. E-mail: liyongding1988@163.com


^b Hubei Key Laboratory of Catalysis and Materials Science, School of Chemistry and Materials Science, South-Central Minzu University, Wuhan 430074, China. E-mail: jchu@mail.scuec.edu.cn

† Electronic supplementary information (ESI) available: ESI data include the detailed description of the photocatalytic activity data, SEM images and XRD patterns. See DOI: <https://doi.org/10.1039/d4lf00051j>

‡ These authors contributed equally to this work.

As we know, PMS can usually be activated by metal or non-metallic catalysts, ultraviolet, microwave, ultrasonic, and photocatalysis.⁴¹ Among them, Fe is favored by researchers due to its redox properties and low cost, making it a commonly used and effective activator for PMS.^{42–44} As an illustration, Sun *et al.*³⁵ prepared a Co₂FeAl-LDO catalyst with multiple metal modification for carbamazepine removal through catalytic activation of PMS. The synergistic effect between Fe, Co and Al on PMS activation enabled higher CBZ elimination efficiency. Tian *et al.*⁴⁵ found that the effectively separated photogenerated electrons in the IO WO₃ catalyst can accelerate the circulation of Fe³⁺/Fe²⁺ in Fe/PMS and Fe/PDS systems, leading to an enhanced norfloxacin removal rate. Furthermore, the construction of hollow structures is not only conducive to increasing the specific surface area of the photocatalyst and adding more active sites, but also enhances light absorption through light scattering and reflection, thereby improving light utilization.⁴⁶ Therefore, by properly combining PMS activation and photocatalysis, along with the construction of Fe–BiOCl hollow microspheres, they are expected to exhibit synergistically enhanced CBZ removal performance, but few examples are available.

Fig. 1 depicts the X-ray diffraction (XRD) patterns of the samples with different Fe doping amounts. All characteristic diffraction peaks are easily ascribed to the tetragonal phase of BiOCl, indicating that the crystal structure of BiOCl remains unchanged by doping modification.^{47–49} On account of the low loading and large dispersion of Fe, no diffraction peaks of Fe₂O₃ or FeOOH are detected. The diffraction peak intensity decreases with the increase of Fe doping indicating the change in crystallinity, which will affect the adsorption

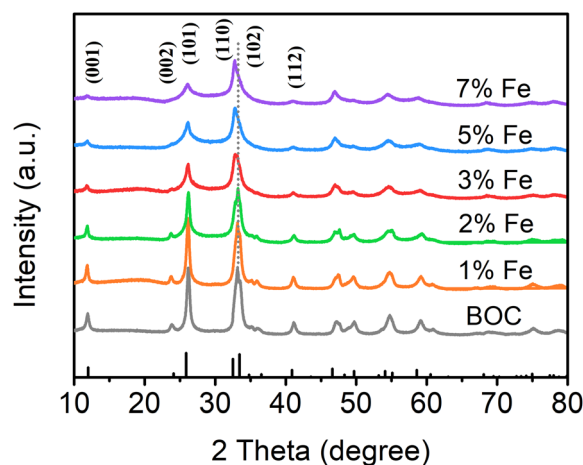

© 2024 The Author(s). Published by the Royal Society of Chemistry

Raman spectra were used to evaluate the crystal structure alterations before (BOC) and after the doping treatment (3% Fe-BOC). As seen in Fig. 4f, the peak at 142.9 cm^{-1} is ascribed to the A_{1g} stretching mode, whereas the peaks at 65.8 and 191.2 cm^{-1} are ascribed to the external A_{1g} and inherent E_g stretching modes of Bi-Cl, correspondingly.⁶⁰ In addition, the weak peak at 393.6 cm^{-1} is related to B_{1g} and E_g bands caused by the motion of O atoms.^{60,61} There is no change in the peak position after Fe doping, while the peak at 393.6 cm^{-1} almost disappears, which may be caused by the





performed to assess the photocatalytic activity of the materials. As shown in Fig. 5a, several rounds of comparative studies were performed to assess the photocatalytic activity of the materials with different doping amounts. In the individual PMS system, the removal rate does not change significantly after illumination, showing that visible light irradiation is insufficient to activate PMS in the absence of the catalyst. The slight elimination of CBZ is attributed to

3.2.1. Effects of doping amounts. Degradation studies under visible light with CBZ as the target contaminant were



Fig. 5 Effects of (a) Fe doping amount, (b) catalyst dosage, (c) PMS concentrations, (d) initial pH values, (e) co-existing inorganic anions on the removal of CBZ and (f) cycling tests of 3% Fe-BOC (experimental conditions: (a) 30 mg catalyst, 0.5 mM PMS, pH = 6.7; (b) 3% Fe-BOC, 0.7 mM PMS, pH = 6.7; (c) 30 mg 3% Fe-BOC, pH = 6.7; (d) 30 mg 3% Fe-BOC, 0.7 mM PMS; (e) and (f) 30 mg 3% Fe-BOC, 0.7 mM PMS, pH = 6.7).

adsorption. Therefore, the self-photolysis process of CBZ is negligible. In addition, 19.6% of CBZ is degraded under visible light within 60 min in PMS–BiOCl systems due to the UV light response properties of BiOCl. Additionally, it is important to note that Fe doping significantly improved PMS activation and CBZ degradation efficiency; the CBZ removal rates of different photocatalysts under visible irradiation are 76.2% (1% Fe-BOC), 70.9% (2% Fe-BOC), 79.7% (3% Fe-BOC), 76.1% (5% Fe-BOC) and 77.5% (7% Fe-BOC), respectively. As described in Fig. S2a and Table S1,[†] the apparent rate constants are 2.80×10^{-2} , 3.06×10^{-2} , 4.49×10^{-2} , 4.33×10^{-2} , and $4.62 \times 10^{-2} \text{ min}^{-1}$, respectively. Among them, 3% Fe-BOC exhibits relatively better degradation activity.

3.2.2. Effects of the catalyst dosage. As shown in Fig. 5b, 3% Fe-BOC was chosen to investigate the impact of different dosages on CBZ removal. When the catalyst dosage is in the range of 10–30 mg, the amount of dark adsorption changes with the increase of catalyst addition, and the CBZ removal rates of BOC and 3% Fe-BOC are 34.4% and 83.9%, respectively (Fig. S2b[†]). This is generally ascribed to the huge

quantity of catalysts providing more active sites, thus enhancing the oxidation of CBZ. This also indicates that the surface reaction is the main rate-limiting step. When the catalyst dosage is increased to 50 mg, 80% of CBZ can be removed in 20 min, but the CBZ elimination rate is not enhanced. This is probably due to the scavenging of $\text{SO}_4^{\cdot-}$ by the excess catalyst.^{35,44} Therefore, a 30 mg catalyst is chosen as the optimal dosage for the next trials.

3.2.3. Effects of the PMS concentration. Fig. 5c and S2c[†] reveal the influence of the PMS concentration on the degradation performance. The response rate constant of CBZ removal rises as the PMS concentration rises, demonstrating that the PMS concentration is the most important factor influencing the removal efficiency. Under low PMS concentration conditions ($\leq 0.3 \text{ mM}$), the unsatisfactory catalytic performance may be caused by insufficient oxidizing active substances in the reaction. On the other hand, as the concentration of PMS continued to increase, the reaction rate constant of CBZ removal still increased, but the trend slowed down noticeably, which may be ascribed to the



of Cl^- and the removal rate reaches 85.8%. On the one hand, this phenomenon is caused by CBZ reacting with high concentrations of Cl^- to produce a series of chlorine-containing organic by-products.⁴² On the other hand, the reaction between PMS and Cl^- will produce various secondary reactive radicals, which can directly oxidize CBZ.^{33,69} Consequently, the CBZ concentration decreases significantly during dark adsorption.

$$\text{OH}^\bullet/\text{SO}_4^{\bullet-} + \text{HSO}_5^- \rightarrow \text{SO}_5^{\bullet-} + \text{HSO}_4^-/\text{H}_2\text{O} \quad (1)$$

$$\text{SO}_4^{\bullet-} + \text{OH}^\bullet \rightarrow \text{HSO}_5^- \quad (2)$$

$$\text{SO}_4^{\bullet-} + \text{SO}_4^{\bullet-} \rightarrow \text{S}_2\text{O}_8^{2-} \quad (3)$$

$$\text{NO}_3^- + \text{SO}_4^{\bullet -}/\text{OH}^{\bullet} \rightarrow \text{NO}_3^{\bullet} + \text{SO}_4^{2-}/\text{OH}^- \quad (4)$$

$$\begin{aligned} &\text{HCO}_3^- + \text{SO}_4^{\cdot-}/\text{OH}^{\cdot}/(\text{O}_2^{\cdot-} + \text{H}^+) \\ &\rightarrow \text{CO}_3^{\cdot-} + (\text{SO}_4^{2-} + \text{H}^+)/\text{H}_2\text{O}/2\text{OH}^{\cdot} \end{aligned} \quad (5)$$

$$\text{Cl}^- + \text{SO}_4^{\bullet-} \rightarrow \text{Cl}^\bullet + \text{SO}_4^{2-} \quad (6)$$

$$\text{Cl}^- + \text{OH}^\cdot \rightarrow \text{HOCl}^{\cdot-} \quad (7)$$

$$\text{Cl}^- + \text{HSO}_5^- \rightarrow \text{HOCl} + \text{SO}_4^{2-} \quad (8)$$

3.2.4. Effects of initial pH. The initial pH of the solution also acts as an important determinant in catalytic efficiency. We studied the photocatalytic removal of CBZ at pH = 3, 5, 6.7 (original solution), 9 and 11 to reveal the effect of pH on the Fe-BOC/PMS system, respectively. As shown in Fig. S2d,[†] the reaction rate constant of CBZ removal increases with the increase of the initial pH of the solution in the pH range from 3.0 to 6.7, and the removal rate of CBZ is beyond 82%. But when the pH increases from 6.7 to 11, the reaction rate constant decreases. This phenomenon may be clarified *via* the two aspects listed below: firstly, the pK_a value of PMS ($pK_a = 9.4$) determines that it exists in the form of HSO_5^- in a solution environment of $0 < pH < 9$.⁶⁵ It is reported that the main decomposition product of HSO_5^- in acidic solutions is $SO_4^{\cdot -}$ and $OH^{\cdot}$ predominates in the alkaline solutions,⁴³ while $SO_4^{\cdot -}$ usually exhibits a stronger oxidation capacity and longer lifetime than $OH^{\cdot}$. Besides, acidic conditions promote the formation and reaction of Fe^{2+} , thereby promoting the activation of PMS.⁴⁴ Under strong alkaline conditions, PMS will self-decompose in a non-radical way and the formation of active free radicals will be inhibited.^{65,66} Meanwhile, Fe ions easily form hydroxides or metal-complexes, which hinder the contact and reaction with PMS.⁶⁷ These two factors work together to reduce the degradation efficiency of CBZ in an alkaline environment. Thus, higher CBZ removal rates and degradation efficiencies can be achieved in neutral and acidic solutions.

3.2.5. Effects of co-existing anions. We also investigated the effects of several common inorganic anions (Cl^- , SO_4^{2-} , HCO_3^- and NO_3^-) on the catalytic degradation capacity of the 3% Fe-BOC/PMS system. The existence of SO_4^{2-} has no impact on the degradation efficiency of CBZ in the system (Fig. 5e and S2e†). The elimination rates of CBZ are 79.9% and 80.6% after the introduction of HCO_3^- and NO_3^- , respectively, and the corresponding reaction rate constant also decreased slightly. This can be attributed to the partial consumption of active radicals by HCO_3^- and NO_3^- in solution. Furthermore, the weakly alkaline environment formed by the hydrolysis of HCO_3^- also inhibits the degradation process.^{64,68} It is important to point out that the adsorption ability of CBZ is greatly increased in the presence

Recycling studies for CBZ photodegradation were conducted to establish the stability of the 3% Fe-BOC/PMS system. The results are shown in Fig. 5f. After four degradation cycles, the loss of catalytic activity is negligible, demonstrating that the sample is stable and reusable. To further investigate the structural stability of the photocatalyst, the SEM and XRD images of pristine and used 3% Fe-BOC were obtained. As shown in Fig. S3,† there is no obvious difference in the morphology of 3% Fe-BOC before and after the CBZ degradation process. The XRD pattern also shows no obvious change in the crystal phase structure (Fig. S4†). These results reveal that the 3% Fe-BOC hollow microsphere possesses excellent stability and recyclability, which is especially important for CBZ removal by PMS activation under visible light.

UV-vis diffuse reflectance spectra were utilized to analyze the optical absorption capabilities of different samples. As shown in Fig. 6a, the absorption edge of the individual BiOCl sample lies around 380 nm, which is consistent with the values reported in the literature.⁷⁰ The composite's absorption edge progressively redshifts with the increase of Fe doping, and the light response range expands to the visible light region, which is possibly explained by the formation of impurity energy levels after Fe incorporation.⁷¹ The bandgap energies of BOC, 1% Fe-BOC, 3% Fe-BOC, and 5% Fe-BOC are determined to be 3.52, 2.90, 2.75, and 2.66 eV, correspondingly (Fig. 6a, inset). These results show that the introduction of Fe extends the optical response range of BiOCl, thereby effectively improving the light absorption ability.

Moreover, PL spectroscopy was employed to evaluate the separation performance of photogenerated $e^{-}h^{+}$ pairs. Fig. 6b shows that the fluorescence emission peak intensity of all composites is weaker than that of pure BiOCl, indicating that Fe-modified BiOCl successfully inhibits the photogenerated $e^{-}h^{+}$ pair recombination. Photoelectrochemical studies were conducted to better

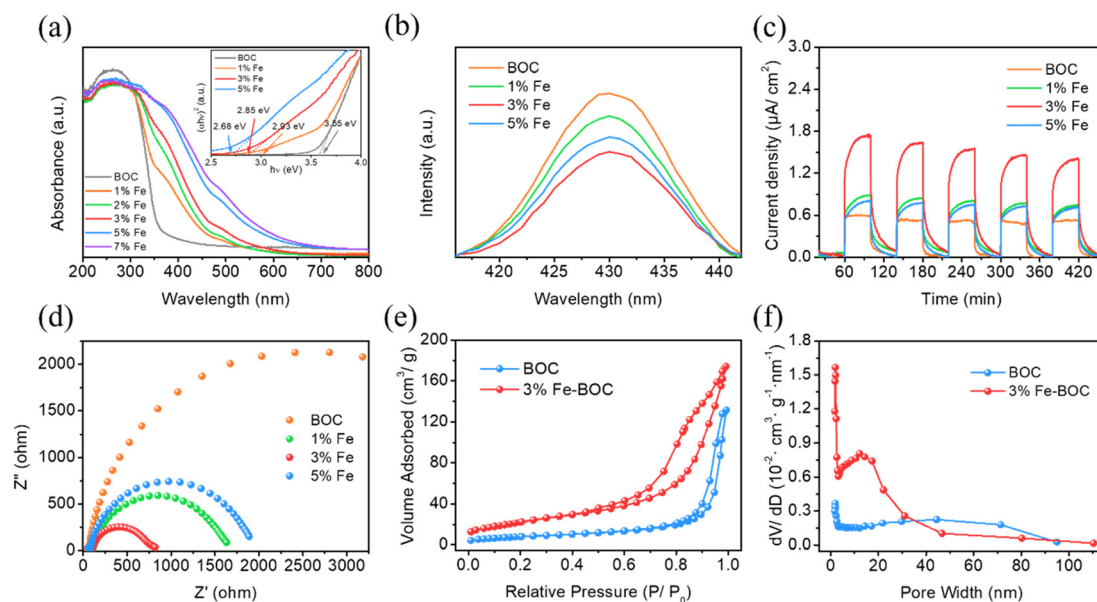


Fig. 6 (a) UV-vis diffuse reflectance spectra and the calculated bandgap spectra (inset), (b) photoluminescence spectra, (c) transient photocurrent response, (d) Nyquist plots, (e) N_2 adsorption-desorption isotherms and (f) pore diameter distribution curves of different samples.

investigate the separation and migration performance of photogenerated carriers. Fig. 6c displays that the 3% Fe-BOC sample has the strongest photocurrent response, which confirms the effective separation and migration of photogenerated electrons and holes. Fig. 6d shows that 3% Fe-BOC has the smallest Nyquist radius, which convincingly demonstrates that it has a smaller charge transfer resistance and facilitates fast migration of photogenerated carriers. Based on the results of the aforementioned investigation, it is possible to deduce that Fe doping enhances the light absorption ability of BiOCl and promotes the effective separation and transfer of photogenerated carriers, thereby achieving an enormous boost in the catalytic degradation ability under visible irradiation.

N_2 adsorption-desorption tests were performed to investigate the specific surface areas and porous structures of BOC and 3% Fe-BOC, and the related data are summarized in Table S2.† Pure BiOCl and 3% Fe-BOC have specific surface areas of 28.7 and 82.5 $m^2 g^{-1}$, respectively. Both have similar pore volumes, while pure BiOCl exhibits a relatively large average pore size. In general, the increase of the specific surface area promotes the exposure of more reactive sites on the catalyst's surface, which is a significant component in improving photocatalytic performance. As shown in Fig. 6e, both BOC and 3% Fe-BOC display type IV isotherms and H3-type hysteresis loops in the relative pressure ranges of $P/P_0 = 0.8-1.0$ (BOC) and $P/P_0 = 0.5-1.0$ (3% Fe-BOC), which are characteristic of slit-like mesopores produced by lamellar aggregation.⁷² In 3% Fe-BOC, the shape of the desorption branch isotherm and hysteresis loop suggests the existence of interstitial pores formed by spherical particle accumulation, implying that the sample has a uniform pore structure.^{73,74} Furthermore, the pore size distribution of the

samples (Fig. 6f) show that the pore diameter of 3% Fe-BOC is concentrated in the 10–20 nm range, while BOC has a wider mesopore size distribution. Therefore, we can conclude that the significantly increased specific surface area and abundant pore structure of 3% Fe-BOC effectively promote the exposure of the reaction site and the adsorption of pollutant components, which is conducive to the occurrence of surface catalytic reactions.

3.3. Photocatalytic mechanism of the catalyst-PMS system

In the photocatalyst-PMS system, a variety of reactive species including $OH^\cdot$, $SO_4^{\cdot-}$, 1O_2 and $O_2^{\cdot-}$ are likely to participate in CBZ degradation. To explore the corresponding photocatalytic reaction mechanism on the Fe-BOC/PMS system, we first studied the involvement of various active substances in the reaction through capture experiments. Methanol (MeOH), *tert*-butanol (TBA), *p*-benzoquinone (BQ), L-histidine (HD) and ethylenediaminetetraacetic acid disodium salt (EDTA-2Na) are used as scavengers to quench $SO_4^{\cdot-}$, $OH^\cdot$, $O_2^{\cdot-}$, 1O_2 and h^+ , correspondingly.⁷⁵ As demonstrated in Fig. 7a, 34.7% and 71% of CBZ are removed after adding MeOH and TBA, suggesting that $SO_4^{\cdot-}$ exhibits an essential function in the degradation process. The addition of BQ and HD also significantly inhibits the degradation efficiency; the removal rates of CBZ are 19.4% and 23.1%, respectively. Thus, it is reasonable to believe that $O_2^{\cdot-}$ and 1O_2 also participate in the CBZ degradation process.

To acquire more insight into the reactive oxygen species, EPR spin-trap spectra were detected. In the absence of illumination, no EPR signal is recorded in either BOC or Fe-BOC samples (Fig. 7b). After 5 min of visible illumination, a number of peaks with strength ratios of 1:2:2:1 and 1:1:





Fig. 7 Scavenging experiment of the active species (a), ESR spin-trapping spectra for the detection of (b) $\text{OH}^{\bullet}$ and $\text{SO}_4^{\bullet-}$, (c) $\text{O}_2^{\bullet-}$ and (d) $^1\text{O}_2$, and Mott-Schottky plots of (e) BOC and (f) 3% Fe-BOC.

1:1:1:1 become apparent, corresponding to the distinctive signal peaks of $\text{OH}^{\bullet}$ and $\text{SO}_4^{\bullet-}$, respectively.^{32,45,76} The intensity of the signal peak increases when the illumination time extends to 10 min, indicating that 3% Fe-BOC could enhance PMS activation and the breaking of O–O bonds to form $\text{OH}^{\bullet}$ and $\text{SO}_4^{\bullet-}$. Similarly, the presence of $\text{O}_2^{\bullet-}$ and $^1\text{O}_2$ is confirmed in Fig. 7c and d. Adsorbed O_2 and photogenerated electrons can react to form $\text{O}_2^{\bullet-}$. $^1\text{O}_2$ is mainly derived from the free radical reaction after PMS is added. Additionally, as seen in Fig. 7a, h^+ is also involved in the oxidative reactions. Capture experiments and EPR tests demonstrate that multiple active species are involved in the photocatalytic removal process.

The band structures of BOC and 3% Fe-BOC were further studied by the Mott-Schottky test. Fig. 7e and f reveal that



the flat band potentials of BOC and 3% Fe-BOC are -0.60 V and -0.44 V (vs. Hg/HgO), respectively. The positive slope indicates that both of them are n-type semiconductors. The potential relative to the standard reversible hydrogen electrode can be converted using the formula $E_{\text{RHE}} = E_{\text{Hg}/\text{HgO}} + 0.059 \times \text{pH} - 0.098$, by which the CB potentials of BOC and 3% Fe-BOC are -0.35 and -0.19 eV (vs. RHE), respectively. The VB positions of BOC and 3% Fe-BOC can be determined using UV-vis DRS and Mott-Schottky plots and are found to be 3.17 and 2.53 eV, respectively.

We propose the possible charge transfer paths and reaction mechanisms in the catalytic degradation of CBZ by 3% Fe-BOC based on the above discussion (Fig. 8). First, the e^- in the valence band is easily stimulated by visible light and transitions into the impurity energy level, where the



Fig. 8 Possible mechanism for the visible-light-driven CBZ degradation in the 3% Fe-BOC/PMS system.

conversion of Fe^{3+} to Fe^{2+} will consume some e^- , thereby limiting the photogenerated carrier recombination (eqns (9) and (10)). The e^- of the doped energy level is subsequently injected into the conduction band, leaving an extensive amount of h^+ in the valence band. The great number of e^- and h^+ can directly participate in the reaction to yield $\text{O}_2^{\cdot-}$ and $\text{OH}^{\cdot}$ ($\text{e}^- + \text{O}_2 \rightarrow \text{O}_2^{\cdot-}$, $\text{h}^+ + \text{H}_2\text{O} \rightarrow \text{OH}^{\cdot}$), or be captured by PMS/adsorbed oxygen for further reactions to produce $\text{O}_2^{\cdot-}$, $^1\text{O}_2$, $\text{SO}_4^{\cdot-}$ and other kinds of active substances (eqns (11)–(14)), which will participate in the catalytic oxidation process of CBZ. Furthermore, Fe^{2+} can serve as active sites to destroy the O–O bonds of PMS and accelerate the formation of oxidative active radicals, while Fe^{3+} can also be converted to Fe^{2+} by HSO_5^- in the solution. The conversion of Fe^{3+} and Fe^{2+} ensures the continuous catalytic process (eqns (15) and (16)). As a result, the catalytic removal of CBZ is carried out by the combined action of h^+ , $\text{O}_2^{\cdot-}$, $^1\text{O}_2$ and $\text{SO}_4^{\cdot-}$ (eqn (17); the related reactions are simply summarized as follows:



4. Conclusions

In summary, we used a straightforward one-step solvothermal approach to prepare several kinds of Fe-doped BiOCl hollow microspheres. These hollow microspheres, with a thickness of approximately 300 nm, self-assembled from nanosheets. The resulting hollow structure enhances light absorption by inducing light scattering and reflection, thereby improving light utilization. Our results demonstrate that the incorporation of Fe substantially boosts the photocatalytic performance of BiOCl hollow microspheres. Among these, 3% Fe-BOC exhibits the highest degradation efficiency for CBZ, achieving an elimination rate of 84.6% within 30 min under visible light irradiation. The apparent rate constant is 12 times that of pure phase BiOCl. The increased photocatalytic efficiency can be attributed to the reduction of the bandgap energy of BiOCl by doped Fe, expanding the range of light response into the visible spectrum. Additionally, the incorporated Fe^{3+} acts as an e^- acceptor, facilitating the

separation of photogenerated carriers and activating PMS to produce reactive oxidizing substances, thus efficiently degrading CBZ. Capture experiments and EPR analysis confirm the participation of $\text{OH}^{\cdot}$, $\text{SO}_4^{\cdot-}$, $^1\text{O}_2$ and $\text{O}_2^{\cdot-}$ in CBZ removal, with $\text{SO}_4^{\cdot-}$ identified as the primary active species. Furthermore, 3% Fe-BOC shows outstanding photocatalytic activity over four consecutive cycles, indicating that it should be a reliable PMS activator for CBZ elimination in practical application. In the presence of PMS, a plausible mechanism for the photocatalytic removal of CBZ was also proposed. This work shows the application of visible-light-driven Fe-BiOCl hollow microspheres in the degradation of pollutants and introduces an innovative approach for the rational design and modification of BiOX-based photocatalysts.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was supported by the National Natural Science Foundation of China (No. 22272207, 22106087), the Fundamental Research Funds for the Central Universities, South-Central MinZu University (No. CZ223008), and the Joint Funds of the Zhejiang Provincial Natural Science Foundation of China (No. LZ22B070001).

References

- 1 M. Qiao, G. G. Ying, A. C. Singer and Y. G. Zhu, *Environ. Int.*, 2018, **110**, 160–172.
- 2 A. M. Ali, H. T. Ronning, L. K. Sydnese, W. M. Alarif, R. Kallenborn and S. S. Al-Lihaibi, *Sci. Total Environ.*, 2018, **621**, 654–662.
- 3 Y. Yang, Y. S. Ok, K. H. Kim, E. E. Kwon and Y. F. Tsang, *Sci. Total Environ.*, 2017, **596–597**, 303–320.
- 4 N. Liu, X. Jin, C. Feng, Z. Wang, F. Wu, A. C. Johnson, H. Xiao, H. Hollert and J. P. Giesy, *Environ. Int.*, 2020, **136**, 105454.
- 5 P. Rodrigues, L. Guimaraes, A. P. Carvalho and L. Oliveira, *J. Hazard. Mater.*, 2023, **448**, 130909.
- 6 Z. Ren, S. Chen, S.-F. Jiang, W.-F. Hu and H. Jiang, *Ind. Eng. Chem. Res.*, 2021, **60**, 2112–2122.
- 7 S. Li, Z. Wang, X. Zhao, X. Yang, G. Liang and X. Xie, *Chem. Eng. J.*, 2019, **360**, 600–611.
- 8 M. Patel, R. Kumar, K. Kishor, T. Mlsna, C. U. Pittman, Jr. and D. Mohan, *Chem. Rev.*, 2019, **119**, 3510–3673.
- 9 S. Feijoo, M. Kamali and R. Dewil, *Chem. Eng. J.*, 2023, **455**, 140589.
- 10 X. Yang, J. Yang, X. Liu, Q. Wang, D. Liu and D. Wang, *Chem. Eng. J.*, 2023, **460**, 141831.
- 11 M. B. Ahmed, J. L. Zhou, H. H. Ngo, W. Guo, N. S. Thomaidis and J. Xu, *J. Hazard. Mater.*, 2017, **323**, 274–298.
- 12 S. Li, Q. Ma, L. Chen, Z. Yang, M. Aqeel Kamran and B. Chen, *Chem. Eng. J.*, 2022, **433**, 134492.
- 13 L. Zhang, Y. Li, Q. Li, J. Fan, S. A. C. Carabineiro and K. Lv, *Chem. Eng. J.*, 2021, **419**, 129484.



- 14 M. Xu, J. Yang, C. Sun, L. Liu, Y. Cui and B. Liang, *Chem. Eng. J.*, 2020, **389**, 124402.
- 15 T. Xia, M. Ju, H. Qian, X. Bai, R. Lai, C. Xie, G. Yu, Y. Tang, C. Wang and Q. Hou, *J. Catal.*, 2024, **429**, 115257.
- 16 Y. Xing, X. Jiang, L. Han, X. Jin, G. Ni, Y. Peng, X. Yong and X. Wang, *J. Cleaner Prod.*, 2023, **400**, 136631.
- 17 V. Dutta, S. Sonu, P. Raizada, V. K. Thakur, T. Ahamad, S. Thakur, P. Kumar Verma, H. H. P. Quang, V. H. Nguyen and P. Singh, *Environ. Sci. Pollut. Res.*, 2023, **30**, 124530–124545.
- 18 M. Malhotra, A. Sudhaik, Sonu, P. Raizada, T. Ahamad, V.-H. Nguyen, Q. Van Le, R. Selvasembian, A. K. Mishra and P. Singh, *Ind. Crops Prod.*, 2023, **202**, 117000.
- 19 K. Sharma, A. Kumar, T. Ahamad, Q. V. Le, P. Raizada, A. Singh, L. H. Nguyen, S. Thakur, V.-H. Nguyen and P. Singh, *J. Mater. Sci. Technol.*, 2023, **152**, 50–64.
- 20 F. Tian, T. Tang, X. Di, X. Guo, D. Liu, Y. Shi, Z. Shen, X. Yu and X. Shao, *Catal. Sci. Technol.*, 2024, **14**, 62–65.
- 21 S. Wang, L. Wang and W. Huang, *J. Mater. Chem. A*, 2020, **8**, 24307–24352.
- 22 M. Z. Shahid, R. Mehmood, M. Athar, J. Hussain, Y. Wei and A. Khaliq, *ACS Appl. Nano Mater.*, 2020, **4**, 746–758.
- 23 K. Kalidasan, S. Mallapur, K. Munirathnam, H. Nagarajaiah, M. B. M. Reddy, R. R. Kakarla and A. V. Raghu, *Chemosphere*, 2024, **352**, 141354.
- 24 X. Wei, M. U. Akbar, A. Raza and G. Li, *Nanoscale Adv.*, 2021, **3**, 3353–3372.
- 25 S. Bai, N. Zhang, C. Gao and Y. Xiong, *Nano Energy*, 2018, **53**, 296–336.
- 26 J. Di, J. Xia, H. Li, S. Guo and S. Dai, *Nano Energy*, 2017, **41**, 172–192.
- 27 X. Gao, C. Gong, X. Wang, W. Zhu and Y. Luo, *J. Solid State Chem.*, 2021, **298**, 122131.
- 28 J. Cui, S. Tao, X. Yang, X. Yu, S. Sun, Q. Yang, W. Wei and S. Liang, *Mater. Res. Bull.*, 2021, **138**, 111208.
- 29 Y. Wang, C. Ban, J. Meng, J. Ma, H. Zou, Y. Feng, J. Ding, Y. Duan, L. Gan and X. Zhou, *Sep. Purif. Technol.*, 2023, **312**, 123379.
- 30 Z. He, H. Fareed, H. Yang, Y. Xia, J. Su, L. Wang, L. Kang, M. Wu and Z. Huang, *J. Colloid Interface Sci.*, 2023, **629**, 355–367.
- 31 C. Guan, T. Hou, W. Nie, Q. Zhang, L. Duan and X. Zhao, *Appl. Surf. Sci.*, 2022, **604**, 154498.
- 32 R. Li, M. Cai, Z. Xie, Q. Zhang, Y. Zeng, H. Liu, G. Liu and W. Lv, *Appl. Catal., B*, 2019, **244**, 974–982.
- 33 S. Giannakis, K.-Y. A. Lin and F. Ghanbari, *Chem. Eng. J.*, 2021, **406**, 127083.
- 34 Z. Zheng and I. M. C. Lo, *Appl. Catal., B*, 2021, **299**, 120636.
- 35 Q.-T. Sun, B.-D. Xu, J. Yang, T.-T. Qian and H. Jiang, *Chem. Eng. J.*, 2020, **400**, 125899.
- 36 C. Dong, Z. Wang, Z. Ye, J. He, Z. Zheng, X. Gong, J. Zhang and I. M. C. Lo, *Appl. Catal., B*, 2021, **296**, 120223.
- 37 Z. Lian, T. Wu, X. Zhang, S. Cai, Y. Xiong and R. Yang, *Chem. Eng. J.*, 2023, **469**, 143774.
- 38 A. A. P. Khan, Sonu, A. Sudhaik, P. Raizada, A. Khan, M. A. Rub, N. Azum, M. M. Alotaibi, P. Singh and A. M. Asiri, *Catal. Commun.*, 2023, **179**, 106685.
- 39 K. Sharma, V. Hasija, M. Malhotra, P. K. Verma, A. A. Parwaz Khan, S. Thakur, Q. Van Le, H. H. Phan Quang, V.-H. Nguyen, P. Singh and P. Raizada, *Int. J. Hydrogen Energy*, 2024, **52**, 804–818.
- 40 S. Sharma, V. Dutta, P. Raizada, V. Kumar Thakur, A. K. Saini, D. Mittal, V.-H. Nguyen, T. Ahamad, C. Chien Nguyen, S. Young Kim, Q. V. Le and P. Singh, *Mater. Lett.*, 2022, **313**, 131716.
- 41 W.-D. Oh, Z. Dong and T.-T. Lim, *Appl. Catal., B*, 2016, **194**, 169–201.
- 42 M.-P. Zhu, J.-C. E. Yang, D. Delai Sun, B. Yuan and M.-L. Fu, *Chem. Eng. J.*, 2022, **436**, 135201.
- 43 Y. F. Rao, L. Qu, H. Yang and W. Chu, *J. Hazard. Mater.*, 2014, **268**, 23–32.
- 44 S. Xiao, M. Cheng, H. Zhong, Z. Liu, Y. Liu, X. Yang and Q. Liang, *Chem. Eng. J.*, 2020, **384**, 123265.
- 45 Y. Tian, N. Jia, L. Zhou, J. Lei, L. Wang, J. Zhang and Y. Liu, *Chemosphere*, 2022, **288**, 132627.
- 46 X. Huang, P. Wang, Q. Jiang and J. Hu, *Mater. Today Commun.*, 2023, **35**, 105766.
- 47 T.-t. Cao, H. Cui, Q.-w. Zhang and C.-w. Cui, *Appl. Surf. Sci.*, 2021, **559**, 149938.
- 48 L. Ding, R. Wei, H. Chen, J. Hu and J. Li, *Appl. Catal., B*, 2015, **172–173**, 91–99.
- 49 L. Ding, C. Zhang, Q. Jiang, H. Chen, W. Sun and J. Hu, *Mater. Lett.*, 2015, **158**, 229–232.
- 50 H. Yu, D. Ge, Y. Wang, S. Zhu, X. Wang, M. Huo and Y. Lu, *J. Alloys Compd.*, 2019, **786**, 155–162.
- 51 C. Huang, S. Zou, Y. Liu, S. Zhang, Q. Jiang, T. Zhou, S. Xin and J. Hu, *ACS Appl. Mater. Interfaces*, 2021, **13**, 5088–5098.
- 52 W. Wang, Q. Zhu, F. Qin, Q. Dai and X. Wang, *Chem. Eng. J.*, 2018, **333**, 226–239.
- 53 J. Sun, X. Li, Q. Zhao and B. Liu, *Appl. Catal., B*, 2021, **281**, 119478.
- 54 Z. Long, H. Wang, K. Huang, G. Zhang and H. Xie, *J. Hazard. Mater.*, 2022, **424**, 127554.
- 55 Y. Mi, L. Wen, Z. Wang, D. Cao, R. Xu, Y. Fang, Y. Zhou and Y. Lei, *Nano Energy*, 2016, **30**, 109–117.
- 56 Z. Shen, F. Li, J. Lu, Z. Wang, R. Li, X. Zhang, C. Zhang, Y. Wang, Y. Wang, Z. Lv, J. Liu and C. Fan, *J. Colloid Interface Sci.*, 2021, **584**, 174–181.
- 57 C. Huang, J. Hu, S. Cong, Z. Zhao and X. Qiu, *Appl. Catal., B*, 2015, **174–175**, 105–112.
- 58 T. Zhang, L. Chen, T. Jiang, J. Hou, G. Zhang and A. Hussain, *Mater. Today Commun.*, 2021, **26**, 102145.
- 59 L. Wu, G. Jiang, X. Wang, Y. Wang, Y. Zhou and Z. Wu, *J. Colloid Interface Sci.*, 2022, **622**, 62–74.
- 60 J. Cao, W. Cen, Y. Jing, Z. Du, W. Chu and J. Li, *Chem. Eng. J.*, 2022, **435**, 134683.
- 61 H. Huang, C. Ma, Z. Zhu, X. Yao, Y. Liu, Z. Liu, C. Li and Y. Yan, *Chem. Eng. J.*, 2018, **338**, 218–229.
- 62 C.-Y. Wang, Y.-J. Zhang, W.-K. Wang, D.-N. Pei, G.-X. Huang, J.-J. Chen, X. Zhang and H.-Q. Yu, *Appl. Catal., B*, 2018, **221**, 320–328.
- 63 Z. Wu, Y. Wang, Z. Xiong, Z. Ao, S. Pu, G. Yao and B. Lai, *Appl. Catal., B*, 2020, **277**, 119136.



- 64 S. Fan, J. Shang, S. Kulan, X. He, X. Wang, B. Nasen, J. Nie, D. Feng and X. Cheng, *Chem. Eng. J.*, 2022, **450**, 138190.
- 65 Y. Gao, Z. Zhao, L. Song, D. Cao, S. Zhou, T. Gao, J. Shang and X. Cheng, *Chem. Eng. J.*, 2023, **454**, 140282.
- 66 L. Liang, S. Gao, J. Zhu, L. Wang, Y. Xiong, X. Xia and L. Yang, *Chem. Eng. J.*, 2020, **391**, 123599.
- 67 L. Ling, D. Zhang, C. Fan and C. Shang, *Water Res.*, 2017, **124**, 446–453.
- 68 S. Xiang, H. Dong, Y. Li, J. Xiao, Q. Dong, X. Hou and D. Chu, *Sep. Purif. Technol.*, 2023, **305**, 122487.
- 69 A. Wang, Z. Hua, C. Chen, W. Wei, B. Huang, S. Hou, X. Li and J. Fang, *Chem. Eng. J.*, 2021, **426**, 131276.
- 70 S. Zhong, X. Wang, Y. Wang, F. Zhou, J. Li, S. Liang and C. Li, *J. Alloys Compd.*, 2020, **843**, 155598.
- 71 Z. Mou, H. Zhang, Z. Liu, J. Sun and M. Zhu, *Appl. Surf. Sci.*, 2019, **496**, 143655.
- 72 L. Ding, H. Chen, Q. Wang, T. Zhou, Q. Jiang, Y. Yuan, J. Li and J. Hu, *Chem. Commun.*, 2016, **52**, 994–997.
- 73 Y.-H. Lee, Y.-M. Dai, J.-Y. Fu and C.-C. Chen, *Mol. Catal.*, 2017, **432**, 196–209.
- 74 C. Chen, T. Jiang, J. Hou, T. Zhang, G. Zhang, Y. Zhang and X. Wang, *J. Mater. Sci. Technol.*, 2022, **114**, 240–248.
- 75 L. Wang, X. Lan, W. Peng and Z. Wang, *J. Hazard. Mater.*, 2021, **408**, 124436.
- 76 L. Ding, M. Li, Y. Zhao, H. Zhang, J. Shang, J. Zhong, H. Sheng, C. Chen and J. Zhao, *Appl. Catal., B*, 2020, **266**, 118634.

