

CrossMark
click for updatesCite this: *Chem. Sci.*, 2015, 6, 2050

A noble metal-free proton-exchange membrane fuel cell based on bio-inspired molecular catalysts†

P. D. Tran,^{‡a} A. Morozan,^{‡b} S. Archambault,^{‡c} J. Heidkamp,^{‡d} P. Chenevier,^e H. Dau,^d M. Fontecave,^{af} A. Martinet,^{*c} B. Jusselme^{*b} and V. Artero^{*a}

Hydrogen is a promising energy vector for storing renewable energies: obtained from water-splitting, in electrolyzers or photoelectrochemical cells, it can be turned back to electricity on demand in fuel cells (FCs). Proton exchange membrane (PEM) devices with low internal resistance, high compactness and stability are an attractive technology optimized over decades, affording fast start-up times and low operating temperatures. However, they rely on the powerful catalytic properties of noble metals such as platinum, while lower cost, more abundant materials would be needed for economic viability. Replacing these noble metals at both electrodes has long proven to be a difficult task, so far incompatible with PEM technologies. Here we take advantage of newly developed bio-inspired molecular H₂ oxidation catalysts and noble metal-free O₂-reducing materials, to fabricate a noble metal-free PEMFC, with an 0.74 V open circuit voltage and a 23 μW cm⁻² output power under technologically relevant conditions. X-ray absorption spectroscopy measurements confirm that the catalysts are stable and retain their structure during turnover.

Received 6th December 2014
Accepted 5th January 2015

DOI: 10.1039/c4sc03774j

www.rsc.org/chemicalscience

Proton exchange membrane (PEM) technology currently stands as the most promising fuel cell variety for both portable and automotive applications. PEMFCs have low internal resistance, high compactness and stability. Having been optimized over decades, they display high efficiency, start rapidly and operate at low temperature. However, they require platinum to catalyse both the H₂ oxidation reaction (HOR) and the O₂ reduction reaction (ORR) which hampers their economic viability and sustainability. Substituting earth-abundant catalysts for noble metals is thus critical. Significant progress has been achieved regarding the development of ORR catalysts^{1–7} but no PEMFC using earth-abundant catalysts at both electrodes has been reported so far.

We recently reported on noble metal-free catalysts for the HOR^{8,9} working under highly acidic conditions compatible with PEM technology. Hydrogenases^{10,11} are unique metalloproteins that catalyse HOR as efficiently as platinum nanoparticles do and in particular with remarkably high reaction rates (1500–

9000 s⁻¹ at pH 7 and 37 °C in water).¹² Their active sites (Fig. 1) have inspired the design of new synthetic HOR catalysts, the most efficient ones being bisdiphosphine nickel complexes¹³ exquisitely combining a nickel centre in an electron-rich environment as found in NiFe hydrogenases with proton relays provided by a pendant base mimicking the aza-propane-dithiolato cofactor of FeFe hydrogenases.¹⁴ In both classes of hydrogenases,¹⁵ the presence of basic residues at the vicinity of the catalytic metal centre indeed facilitates the activation and heterolytic cleavage of H₂. Immobilization of such synthetic catalysts, either covalently or through π–π stacking

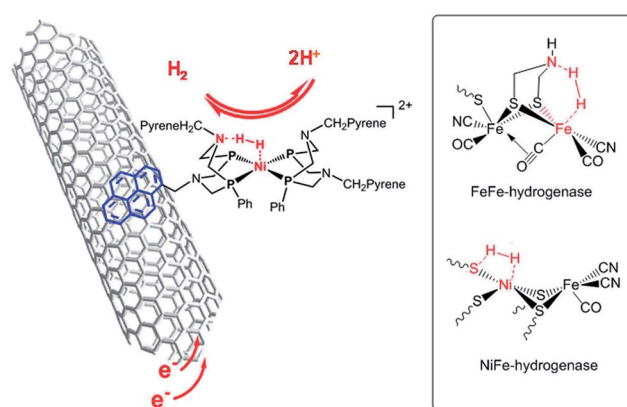


Fig. 1 Structure of the Ni–CNT HOR catalyst based on a synthetic nickel bisdiphosphine complex inspired by the structures of the active sites of FeFe and NiFe hydrogenases shown in the inset.

^aLaboratoire de Chimie et Biologie des Métaux, Université Grenoble Alpes, CNRS, CEA, 17 rue des Martyrs, 38054 Grenoble Cedex 09, France. E-mail: vincent.artero@cea.fr

^bCEA Saclay, IRAMIS, NIMBE/UMR 3685, Laboratory of Innovation in Surface Chemistry and Nanosciences (LICSEN), Gif sur Yvette F-91191, France

^cInstitut LITEN CEA LITEN/DTNM/LCSN, Grenoble, France

^dFB Physik, Free University Berlin, Berlin, Germany

^eUniversité Grenoble Alpes, CNRS, CEA, INAC-SPRAM, F-38000 Grenoble, France

^fCollège de France, 11 Place Marcelin Berthelot, 75005 Paris, France

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c4sc03774j

‡ These authors equally contributed to the work.



interactions, on multiwall carbon nanotubes (CNTs) yielded Ni-CNT HOR catalytic nanomaterials.^{8,9} When interfaced with a Nafion membrane, these nanomaterials show catalytic activity for hydrogen evolution/uptake at the thermodynamic equilibrium, prolonged stability under turnover conditions and resistance to CO poisoning. It was thus tempting to implement these original materials as anode PEMFC catalysts. Here we report the first functional PEMFC based on earth-abundant materials at both anode and cathode.

Deposition of one of these Ni-CNT HOR materials on a Nafion membrane was first achieved through spray coating.¹⁶ The preparation of a catalytic ink with suitable rheological properties required partial substitution of CNTs with carbon black nanoparticles with lower form factor. The anode Ni-CNT ink was then composed of a $[\text{Ni}(\text{P}_2^{\text{Ph}}\text{N}_2^{\text{CH}_2\text{pyrene}})_2](\text{BF}_4)_2/\text{CNTs}$ (Ni-CNT, 30 wt% dry mass) material (Fig. 1),⁹ Vulcan XC-72 (40–50 wt%) and Nafion (20–30 wt%) in a water/isopropanol mixture (80/20 wt%). The use of a 5 : 1 Vulcan XC-72 : CNTs mass ratio led to particles in the 10–100 μm range as measured by dynamic light scattering.

A novel Co-N-C ORR catalyst with suitable rheological properties was obtained through adaptation of a previous procedure developed by some of us.^{3,16} Pyrolysis of a mixture of a N-heterocyclic organic compound (triazolopyridine) and Vulcan XC-72 in the presence of $\text{Co}(\text{NO}_3)_2$ (ref. 3 and 17) at 700 °C gave a fine dispersion of 0.1–100 μm particles in Nafion (20–30 wt%) and water/isopropanol as a proper ink for spray coating. By analogy with the previously described material, the ORR activity is assigned to pyridinic-N functional groups located at the surface of the carbon matrix and binding cobalt ions as well as metallic cobalt nanoparticles.³ This material displays an overpotential for the ORR ~ 300 mV higher than Pt/C in a half cell configuration and good stability for more than 15 h during chrono-amperometry measurements. A detailed structural and catalytic study is provided in the ESI.†

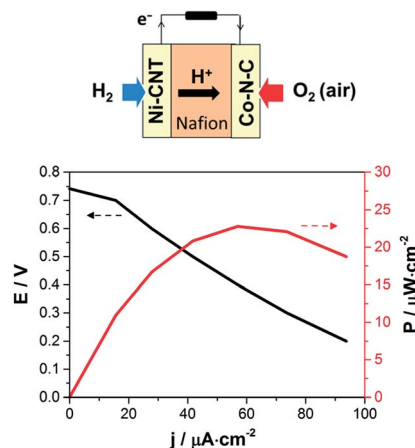


Fig. 2 Left: schematic description of the PEMFC assembly; right: polarization and power density curves of the Ni-CNT/Co-N-C PEMFC recorded at 60 °C with a supply of partially humidified H_2 (20 mL min^{-1}) at the anode and passive air convection at the cathode.

After spray coating of the catalytic inks (0.44 to 0.64 mg cm^{-2} , corresponding to about $10 \mu\text{m}$ thickness) on both sides of a NRE-212 Nafion membrane (5.76 cm^2) at 60–80 °C, the assembly was hot-pressed ($50 \text{ }^\circ\text{C}$, $2 \times 10^5 \text{ Pa}$, 3 min) to improve catalyst-electrolyte contact and metal collectors were deposited on each side by evaporation of a gold layer, thin enough to allow for gas permeation. The resulting membrane-electrode assembly (MEA, Fig. 2) was assessed at 60 °C in air under natural convection and ambient humidity in a dedicated micro fuel cell test-rig. Partially humidified hydrogen (20 mL min^{-1} bubbling in water) was supplied to the anode, and air was passively supplied to the cathode.

The polarization and power density curves for the resulting Ni-CNT/Co-N-C PEMFC are shown in Fig. 2. Table 1 compares the performances of this noble metal-free PEMFC with other cells in which one electrode has been replaced by a standard Pt-based electrode similarly prepared from 40% Pt/C catalytic material. The noble metal-free PEMFC proved functional with an open-circuit voltage (OCV) of 0.74 V, to be compared with the 1.0 V OCV value measured for a Pt/Pt PEMFC under the same conditions. The Ni-CNT/Pt and the Pt/Co-N-C control PEMFCs provided OCV values only 150 and 210 mV lower, respectively, than a standard Pt/Pt PEMFC, showing that each noble metal-free catalyst operates at reasonable overvoltages. The maximum power density of the noble metal-free PEMFC was $23 \mu\text{W cm}^{-2}$ under dynamic conditions and it stabilized at $20 \mu\text{W cm}^{-2}$ under stationary conditions. From Table 1, it can be concluded that the ORR catalyst, tested against Pt in a full PEMFC device, shows a higher current density (13 mA cm^{-2}) than in half-cell configuration ($1\text{--}3 \text{ mA cm}^{-2}$, Fig. S4 and S5†) but the reverse is observed for the HOR catalyst (0.224 mA cm^{-2} in a PEMFC versus 1 mA cm^{-2} in half-cell configuration, Fig. S6†). The limitation in terms of current density and output power thus comes here from the bio-inspired anode material and its interface with the membrane rather than from the cathode catalyst, indicating a direction for further improvement of performances. Finally, the operation of Pt/Co-N-C and Ni-CNT/Pt PEMFCs at temperatures increasing from 25 °C to 60 °C showed a low increase in current density by a factor of ≤ 1.5 , corresponding to an activation energy below 10 kJ mol^{-1} and 20 kJ mol^{-1} , respectively. These low activation energy values show that the current is likely limited by the gas transport processes in the bulk of the electrode materials.

Table 1 Open circuit voltage (OCV), current density and maximum power density generated by various PEMFCs based on Ni-CNT, Co-N-C or Pt catalysts; PEMFCs were measured at 60 °C with a supply of partially humidified H_2 (20 mL min^{-1}) at the anode and passive air convection at the cathode

Anode	Cathode	OCV/V	$I@0.2 \text{ V}/\mu\text{A cm}^{-2}$	$P_{\text{max}}/\mu\text{W cm}^{-2}$
Pt	Co-N-C	0.79	1.3×10^4	2600
Ni-CNT	Pt	0.85	224	70
Ni-CNT	Co-N-C	0.74	94	23
Pt	Pt	1.00	1.75×10^5	1.05×10^3



and the FCH Joint Undertaking (Nano-Cat project, grant no. 325239). The XAS measurements were carried out at beamline KMC-1 of the BESSY synchrotron operated by the Helmholtz Zentrum Berlin (HZB); we thank M. Mertin and Dr F. Schäfers (both HZB) for their technical support and the Berlin cluster of excellence on Unifying Concepts in Catalysis (UniCat) for the financial support.

References

- M. Lefevre, E. Proietti, F. Jaouen and J. P. Dodelet, *Science*, 2009, **324**, 71–74.
- R. Bashyam and P. Zelenay, *Nature*, 2006, **443**, 63–66.
- A. Morozan, P. Jegou, B. Josselme and S. Palacin, *Phys. Chem. Chem. Phys.*, 2011, **13**, 21600–21607.
- K. P. Gong, F. Du, Z. H. Xia, M. Durstock and L. M. Dai, *Science*, 2009, **323**, 760–764.
- R. Liu, D. Wu, X. Feng and K. Müllen, *Angew. Chem., Int. Ed.*, 2010, **49**, 2565–2569.
- A. Morozan, B. Josselme and S. Palacin, *Energy Environ. Sci.*, 2011, **4**, 1238–1254.
- S. Pylypenko, S. Mukherjee, T. S. Olson and P. Atanassov, *Electrochim. Acta*, 2008, **53**, 7875–7883.
- A. Le Goff, V. Artero, B. Josselme, P. D. Tran, N. Guillet, R. Metaye, A. Fihri, S. Palacin and M. Fontecave, *Science*, 2009, **326**, 1384–1387.
- P. D. Tran, A. Le Goff, J. Heidkamp, B. Josselme, N. Guillet, S. Palacin, H. Dau, M. Fontecave and V. Artero, *Angew. Chem., Int. Ed.*, 2011, **50**, 1371–1374.
- W. Lubitz, H. Ogata, O. Rüdiger and E. Reijerse, *Chem. Rev.*, 2014, **114**, 4081–4148.
- P. Chenevier, L. Mugherli, S. Darbe, L. Darchy, S. DiManno, P. D. Tran, F. Valentino, M. Iannello, A. Volbeda, C. Cavazza and V. Artero, *C. R. Chim.*, 2013, **16**, 491–516.
- A. K. Jones, E. Sillery, S. P. J. Albracht and F. A. Armstrong, *Chem. Commun.*, 2002, 866–867.
- T. Ueno, M. Ohashi, M. Kono, K. Kondo, A. Suzuki, T. Yamane and Y. Watanabe, *Inorg. Chem.*, 2004, **43**, 2852–2858.
- G. Berggren, A. Adamska, C. Lambert, T. R. Simmons, J. Esselborn, M. Atta, S. Gambarelli, J. M. Mouesca, E. Reijerse, W. Lubitz, T. Happe, V. Artero and M. Fontecave, *Nature*, 2013, **499**, 66–69.
- T. R. Simmons, G. Berggren, M. Bacchi, M. Fontecave and V. Artero, *Coord. Chem. Rev.*, 2014, **270–271**, 127–150.
- Y. Matsubara, E. Fujita, M. D. Doherty, J. T. Muckerman and C. Creutz, *J. Am. Chem. Soc.*, 2012, **134**, 15743–15757.
- A. Morozan, P. Jegou, M. Pinault, S. Campidelli, B. Josselme and S. Palacin, *Chemsuschem*, 2012, **5**, 647–651.
- The same behavior is observed if the material is simply equilibrated with the aqueous electrolyte during the measure of a few cyclic voltammograms (Fig. S10†) or if the experiment is carried out during 1 h under H₂ evolution conditions (Fig. S11 and Table S2†). If the same measurement is carried out on the Ni–CNT material coated with a Nafion membrane, the XANES signal is unmodified even after 1 hour of operation for H₂ evolution at –0.3 V vs. RHE (Fig. S11 and Table S2†).
- K. A. Vincent, J. A. Cracknell, O. Lenz, I. Zebger, B. Friedrich and F. A. Armstrong, *Proc. Natl. Acad. Sci. U. S. A.*, 2005, **102**, 16951–16954.
- K. A. Vincent, J. A. Cracknell, J. R. Clark, M. Ludwig, O. Lenz, B. Friedrich and F. A. Armstrong, *Chem. Commun.*, 2006, 5033–5035.
- A. F. Wait, A. Parkin, G. M. Morley, L. dos Santos and F. A. Armstrong, *J. Phys. Chem. C*, 2010, **114**, 12003–12009.
- L. Xu and F. A. Armstrong, *Energy Environ. Sci.*, 2013, **6**, 2166–2171.
- S. Krishnan and F. A. Armstrong, *Chem. Sci.*, 2012, **3**, 1015–1023.
- A. Ciaccavava, A. De Poulpique, V. Techer, M. T. Giudici-Ortoni, S. Tingry, C. Innocent and E. Lojou, *Electrochem. Commun.*, 2012, **23**, 25–28.
- A. de Poulpique, H. Marques-Knopf, V. Wernert, M. T. Giudici-Ortoni, R. Gadiou and E. Lojou, *Phys. Chem. Chem. Phys.*, 2014, **16**, 1366–1378.
- A. Zebda, C. Gondran, A. Le Goff, M. Holzinger, P. Cinquin and S. Cosnier, *Nat. Commun.*, 2011, **2**, 370.

