

(2.7 eV), exceptional thermodynamic and chemical stability has attracted recent research attention.^{9,12–14} However, like other metal oxide semiconductor based photocatalysts, it also suffers from limitations such as a high rate of recombination of photo induced charge carriers and low absorbance above 460 nm, which limit its practical applications in the field of visible light photocatalysis.^{15–17} In order to overcome these limitations various structural and surface modification strategies have been adopted in recent years such as doping with non-metals or metals,^{18,19} developing different g-C₃N₄ nanostructures with different morphologies and porosity, creating hetero-junctions with other semiconducting materials, deposition of noble metals,^{20–23} and coupling with carbonaceous^{12,24} materials.

Among the various structural modification methods, doping with metals (*e.g.*, Fe, Co, K, and Cu)^{25–28} or non-metals (*e.g.*, B, C, S, P and Br)^{29–33} can not only alter the electronic structure of g-C₃N₄ but also increase the defect structures as well as the surface active sites and hence improves the catalytic activity dramatically. In particular, it is reported that when g-C₃N₄ is doped with S, a new electron occupied energy level is formed slightly above the VB of pristine g-C₃N₄ due to the interaction of 3P states of S and 2P states of N which results in narrowing of the band gap and hence an increase in its visible light absorption capacity.^{34,35} For example, Gang *et al.* in 2010 have reported the synthesis of S-doped g-C₃N₄ by heating pure g-C₃N₄ in the presence of a gaseous H₂S atmosphere at 450 °C. The obtained S-doped g-C₃N₄ photocatalyst was found to exhibit improved H₂ evolution capacity under visible light.³⁴ The synthetic method used produced a large amount of poisonous gases and hence was not considered as an environmentally friendly method. Recently, an eco-friendly approach for the synthesis of S doped g-C₃N₄ has been reported by using thiourea as the precursor which showed enhanced photocatalytic properties under visible light irradiation.³⁶

Apart from the doping strategy, constructing a hetero-junction with other semiconductor nanomaterials, such as TiO₂,¹³ Ag₂O,⁹ CdS,³⁷ Ag₃PO₄,³⁸ and Fe₂O₃,⁵ facilitates separation of electron–hole charge carriers and increases the light harvesting capacity of the resultant composites. Among different types of metal oxides, Bi₂O₃ is the most frequently studied metal oxide visible light responsive photocatalyst because it has a band gap of 2.8 eV which falls in the visible region of the light spectrum and it can also be prepared easily from low cost materials. But the main problem of α -Bi₂O₃ is that its valence band potential (VB) is sufficiently positive but its conduction band potential (CB) is not negative enough to reduce the surface O₂ to O₂[−] ions through a rapid single electron reduction process and as a result photo-induced electron hole pairs recombine quickly and hence its photocatalytic activity decreases.^{39–41}

On the other hand, noble metals such as Ag nanoparticles have attracted remarkable research interest because these metal nanoparticles exhibit the surface plasmon resonance (SPR) effect due to which they can strongly absorb visible light and can also improve the separation of electron and hole pairs on the semiconductor surface.^{2,16,20,42–44} Furthermore, Ag based

photocatalysts are economically more viable due to their relatively low price compared to other noble metals. Thus constructing a hetero-junction that contains S doped g-C₃N₄, Bi₂O₃ and Ag can generate a system that will not only increase interfacial boundary formation which is beneficial for the efficient separation of photo-generated electron hole pairs but can also extend the range of optical absorption in the visible region.

In the present study we have synthesized binary Bi₂O₃/Ag nanocomposites mounted on an S doped g-C₃N₄ 2D nanosheet surface by using a simple chemical precipitation method followed by calcination at 330 °C. The prepared ternary Sg-C₃N₄/Bi₂O₃/Ag nanocomposites were characterized by XRD, FTIR, FESSM, TEM, XPS, PL, UV-vis DRS, and electrochemical study. The photocatalytic properties of the prepared ternary nanocomposites were investigated by catalytic degradation of rhodamine B (RhB) and tetracycline hydrochloride (TCH) under natural sunlight. The obtained results demonstrate that upon introduction of Ag into Sg-C₃N₄/Bi₂O₃ the photocatalytic activity of the resultant composite increases significantly. Furthermore, the mechanism of the degradation process has been studied in detail. The mechanistic pathway is well explained by means of scavenger studies and the reactive species involved in the degradation process is established from the respective confirmatory tests.

2. Materials and methods

2.1. Reagents used

Analytical grade thiourea, bismuth nitrate pentahydrate (Bi(NO₃)₃·5H₂O), silver nitrate (AgNO₃), sodium hydroxide (NaOH), nitric acid (HNO₃), rhodamine B, tetracycline hydrochloride (TCH), benzoquinone, DMSO, EDTA, *tert*-butyl alcohol, terephthalic acid (TA), dichloro methane (DCM), and nitroblue tetrazolium chloride were purchased from Merck India and Himedia Lab. Pvt. Ltd. and were used without any purification. Deionised water was used throughout the experiments.

2.2. Preparation of photocatalysts

S doped g-C₃N₄ was prepared by heating thiourea in air at 500 °C with the help of an alumina crucible covered with a lid for 2 h. After synthesizing S doped g-C₃N₄, the ternary Sg-C₃N₄/Bi₂O₃/Ag nanocomposites were prepared by using the following procedure: typically 0.075 g of Bi(NO₃)₃·5H₂O was added to 30 ml of 1.5 M aqueous solution of nitric acid for preventing hydrolysis of Bi³⁺ ions. Then 0.5 g of Sg-C₃N₄ was added to it with magnetic stirring for 2 h so that all the Bi³⁺ ions will be completely adsorbed on the surface of Sg-C₃N₄. After that different amounts of AgNO₃ solution were added dropwise to the above suspension and the mixture was stirred for 30 min in the dark. Then KOH solution (50% w/v) was added gradually to it followed by continuous stirring until the solution pH reached 13 at which a yellow colour precipitate was formed. Then the resulting suspension was heated at 80 °C for 2 h. The obtained product was washed with ethanol and deionised water repeatedly several times. Finally, the solid product obtained was dried in an air oven, and then calcined at 330 °C for 2 h to get the



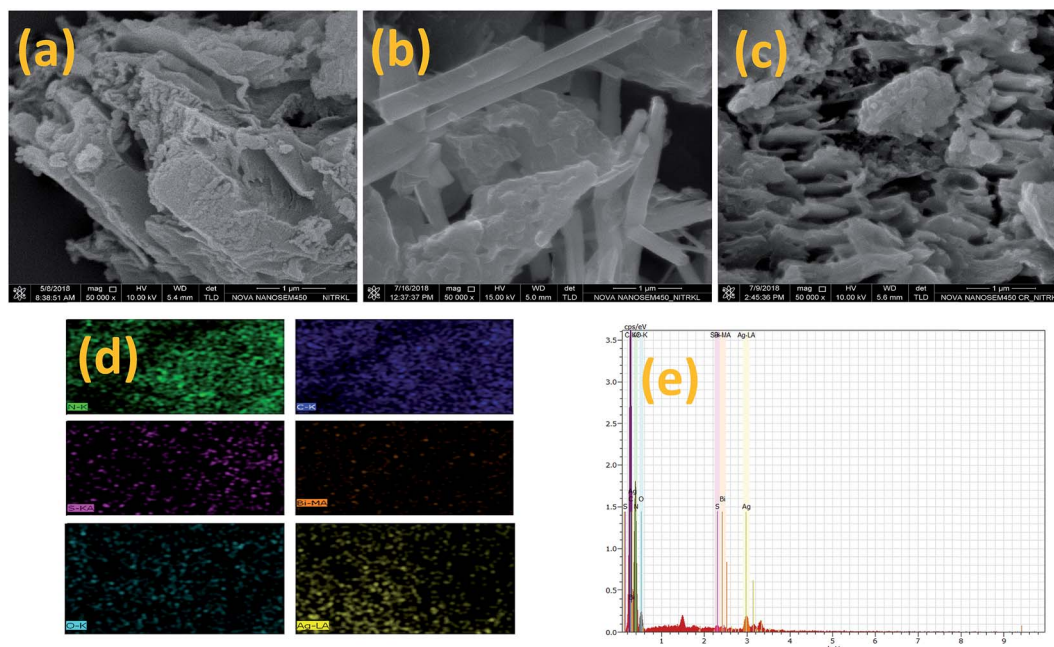


Fig. 5 FESEM images of (a) Sg-C₃N₄, (b) Sg-C₃N₄/Bi₂O₃, and (c) Sg-C₃N₄/Bi₂O₃/Ag (15%); (d) elemental mapping of Sg-C₃N₄/Bi₂O₃/Ag (15%); (e) FESEM EDX spectra of Sg-C₃N₄/Bi₂O₃/Ag (15%).

surface of Sg-C₃N₄, it is interesting to note that the morphology of Bi₂O₃ changed from a rod shape to an irregular shape which may be due to the size depression effect of Ag, Bi₂O₃ and Sg-C₃N₄ as reported in the previous literature.^{40,49–51} Further the elemental content of the ternary composite is characterised *via* EDX (Fig. 5d and e), which reveals that it is composed of S, C, N, Bi and O elements and is free from other foreign elements. The obtained results show good correlation with XPS data, discussed in the respective section.

3.4.2. TEM analysis. For further investigation of the particle size distribution, morphology, and crystalline properties of Ag and Bi₂O₃ particles formed on the surface of the 2D layered structure of Sg-C₃N₄ and also for confirmation of the heterojunction, we carried out TEM and HRTEM analysis. Fig. 6 shows the TEM images of Sg-C₃N₄/Bi₂O₃/Ag (15%) ternary nanocomposites. It is observed from the TEM image (Fig. 6a) that spherical Ag nanoparticles and irregular shaped Bi₂O₃ particles are decorated on the Sg-C₃N₄ 2D nanosheet surface. The size of the Ag nanoparticles is found to be in the range of 5–10 nm and that of irregular shaped Bi₂O₃ particles is within 80–120 nm, and the particles are well distributed on the surface of 2D sheets of Sg-C₃N₄. Further, from the HRTEM images (Fig. 6d–f) the measured lattice spacings of 0.23 nm and 0.325 nm correspond to the (111) plane of Ag (JCPDS 40783) and the (–120) plane of Bi₂O₃ (JCPDS 14-0699), respectively. However, no crystal plane corresponding to Sg-C₃N₄ is observed, which is due to its organic nature which causes quick weakening of the developing crystal fringes under electron beam irradiation.⁵² The TEM elemental analysis further confirms the existence of Ag, Bi, S, C, and N elements. This result suggests the formation of the heterostructure ternary Sg-C₃N₄/Bi₂O₃/Ag nanocomposite.

3.5. XPS analysis

In order to determine the surface composition and chemical states of various elements present in the ternary nanocomposite Sg-C₃N₄/Bi₂O₃/Ag (15%), we performed XPS analysis and the result obtained is depicted in Fig. 7. Fig. 7a shows the high-resolution spectra of C 1s with two peaks at 283.9 and 287 eV, where the former corresponds to the sp² hybridised C in the N-heterocyclic aromatic ring (N–C=N) of Sg-C₃N₄ (ref. 35) and the latter is assigned to the adventitious carbon on the sample surface⁵³. The peak de-convolution of the N 1s spectrum generates three different peaks (Fig. 7b). The peak at 397.8 eV is ascribed to the carbon atoms bonded to sp² hybridised aromatic N atoms (C–N=C),⁵⁴ while the component at 398.9 eV usually relates to the bonding of tertiary N atoms to the adjacent carbon atoms in the form of N–(C)₃. The weak peaks at 400.5 eV correspond to the bonding of sp² nitrogen atoms to three carbon atoms in aromatic rings.⁵⁵ In the O 1s spectrum (Fig. 7c), the peak located at 530.8 eV is assigned to the HO–C=O bond and the peak at 529.12 eV is attributed to the Bi–O–Bi bond present in the ternary nanocomposite.⁴⁰ Again S 2p is fitted into two peaks (Fig. 7d). The peaks at 163.5 and 166.5 eV indicate the formation of C–S and N–S bonds by substitution of sulphur with nitrogen and carbon of the g-C₃N₄ lattice.⁵⁶ In Fig. 7e, two peaks for trivalent Bi (Bi³⁺) positioned at 157.9 and 163.0 eV are observed, which are assigned to Bi 4f_{5/2} and Bi 4f_{7/2}, respectively.⁴⁰ In the Ag 3d XPS spectra shown in Fig. 7f two peaks centred at 367.8 and 373.51 eV are observed. These peaks indicate the binding energy value of Ag 3d_{5/2} and Ag 3d_{3/2}, respectively. This suggests that the Ag is present in its zero oxidation state in the synthesised ternary nanocomposite.⁵⁷



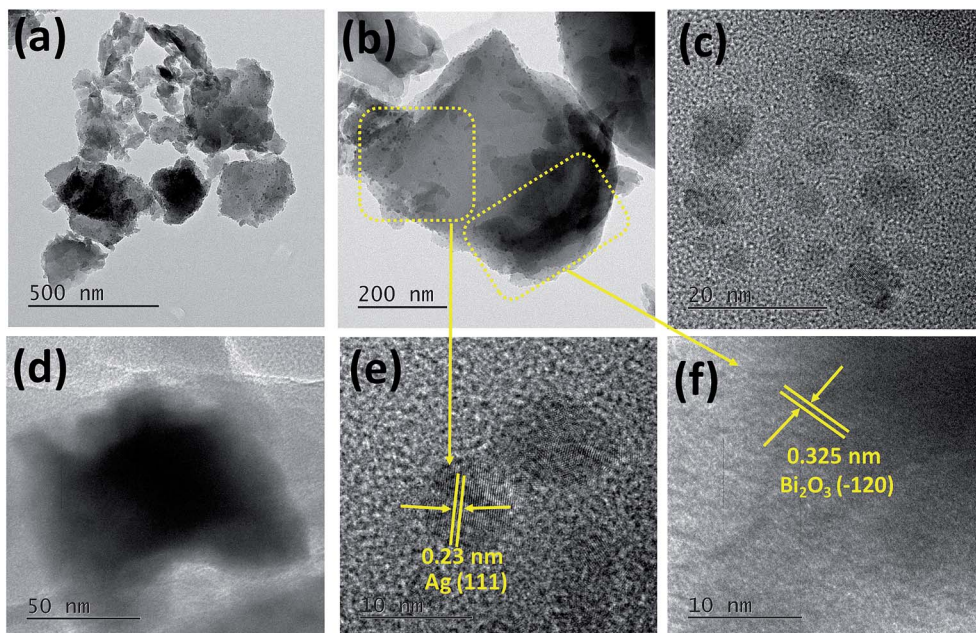


Fig. 6 (a) TEM image of Sg-C₃N₄/Bi₂O₃/Ag (15%). (b) High-resolution TEM image of a selected area of Sg-C₃N₄ in the composite. (c and d) Distribution of Ag nanoparticles and irregular shaped Bi₂O₃ particles on the surface of Sg-C₃N₄. (e and f) Lattice fringes of Ag and Bi₂O₃.

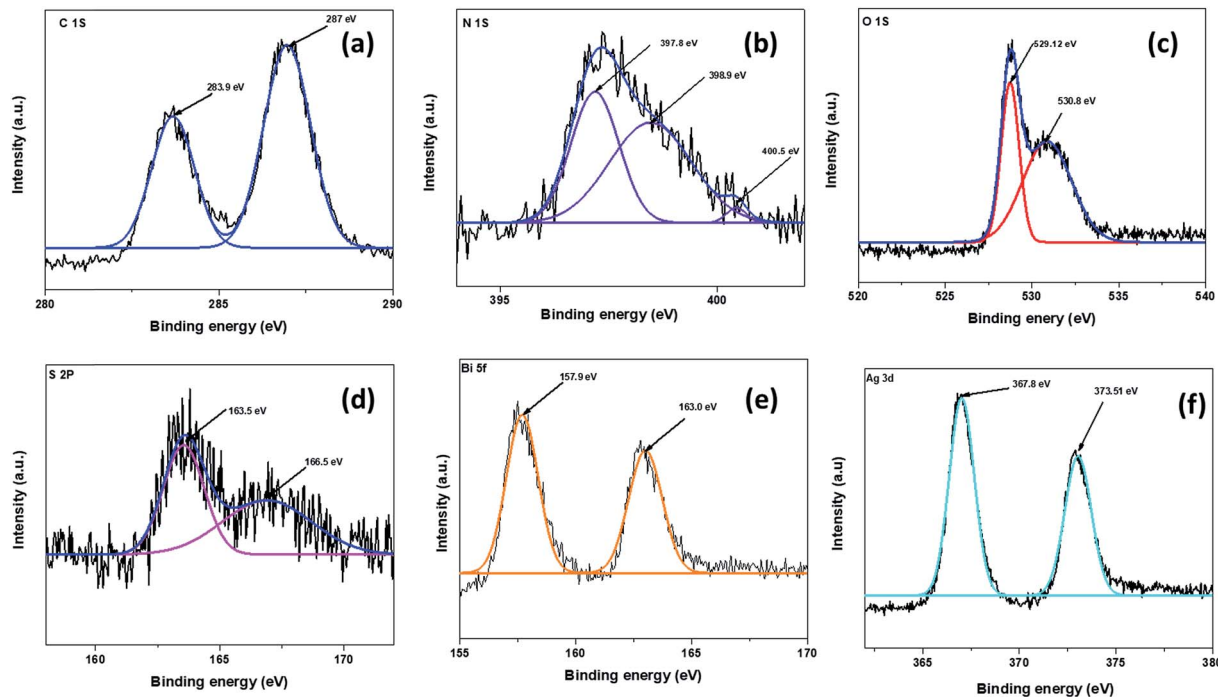


Fig. 7 XPS spectra for Sg-C₃N₄/Bi₂O₃/Ag (15%) in the regions of (a) C 1s, (b) N 1s, (c) O 1s, (d) S 2p, (e) Bi 4f, and (f) Ag 3d.

3.6. Impedance study

Furthermore, to obtain more information regarding the photo-generated electron hole pair separation and charge transfer across the electrode–electrolyte interface of the fabricated ternary photocatalysts we carried out electrochemical impedance (EIS) measurements. Fig. 8 shows the typical Nyquist plots

of Sg-C₃N₄, Sg-C₃N₄/Bi₂O₃ and Sg-C₃N₄/Bi₂O₃/Ag (15%) measured in the dark at zero applied bias between 105 and 102 Hz. The semi-circular part in the higher frequency zone indicates the interfacial charge transfer resistance *i.e.* a larger Nyquist arc radius means higher resistance at the interface, and hence lower conductance and *vice versa*. A smaller semicircle in



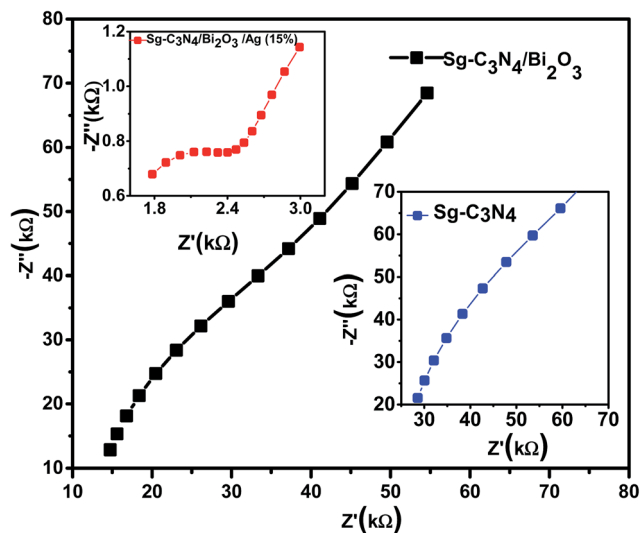


Fig. 8 EIS Nyquist plots of Sg-C₃N₄, Sg-C₃N₄/Bi₂O₃, and Sg-C₃N₄/Bi₂O₃/Ag (15%).

the high frequency zone of the Nyquist plot suggests higher separation efficiency of the photogenerated charge carriers. From the EIS study it is clearly observed that the Sg-C₃N₄/Bi₂O₃/Ag (15%) nanocomposite photocatalyst displays better photogenerated charge carrier separation and transfer efficiency compared to Sg-C₃N₄ and Sg-C₃N₄/Bi₂O₃ photocatalysts. From the above experimental observation it is well understood that the Sg-C₃N₄/Bi₂O₃/Ag (15%) ternary nanocomposite can be effectively used as a photocatalyst with improved photocatalytic degradation activity for organic pollutants.

3.7. Photocatalytic activity

In order to examine the photocatalytic behaviour of the synthesized ternary nanocomposite materials, we used rhodamine B (RhB) dye as a model pollutant and its photocatalytic degradation study was performed under natural solar light. Photocatalytic experiments were carried out by using 60 mg of photocatalyst in 70 ml of 15 ppm RhB solution. Since RhB is a coloured compound and can undergo photolysis under solar light irradiation, we performed blank experiments without using the photocatalyst. A very negligible decolourisation effect was observed in this case which clearly indicates that the deterioration of RhB is only due to the photocatalytic properties of the synthesized photocatalysts. Fig. 9a–c show the photocatalytic decolourization of RhB dye in the presence of the prepared photocatalysts. It was observed that for all the samples the rate of decolourisation increases with time. In order to further examine the effect of adsorption on the decolourisation process, we also performed an adsorption experiment in the dark with a contact time of 90 min keeping all parameters and adsorbent dose constant. It was found that only 3% of the RhB solution gets adsorbed onto the catalyst surface. The results for the decolourisation of RhB by various prepared photocatalysts are presented in Fig. 9a. It is observed from the figure that the photocatalytic efficiency of the Sg-C₃N₄/Bi₂O₃ nanocomposite in

RhB decolourisation is only about 10.25%. So in order to further improve the photocatalytic properties we tried to modify Sg-C₃N₄/Bi₂O₃ nanocomposites by decorating them with various amounts of Ag nanoparticles. It is found that with an increase in Ag content from 5 wt% to 15 wt% the photocatalytic performance of the resultant ternary nanocomposite increases gradually and then decreases slightly for 20 wt% Ag. Among all the prepared nanocomposites Sg-C₃N₄/Bi₂O₃/Ag (15%) shows 95% degradation ability which is significantly higher than that of other prepared nanocomposites. The order of decolourisation efficiency of the prepared nanocomposites is found to be Sg-C₃N₄/Bi₂O₃/Ag (15%) > Sg-C₃N₄/Bi₂O₃/Ag (20%) > Sg-C₃N₄/Bi₂O₃/Ag (10%) > Sg-C₃N₄/Bi₂O₃/Ag (5%) > Sg-C₃N₄/Bi₂O₃. The decrease in photocatalytic ability with an increase in wt% of Ag from 15% to 20% might be due to the agglomeration of Ag nanoparticles in the presence of higher Ag content. These agglomerated nanoparticles block the active sites of the composites and decrease the electron–hole pair separation efficiency. Thus the content of Ag in the ternary nanocomposite plays a very important role in determining the photocatalytic ability. Moreover, we also studied the kinetics of the degradation of RhB dye by the prepared ternary nanocomposites and the experimental data obtained are found to be best fitted to the kinetic model of a pseudo-first order reaction (Fig. 9b). The pseudo-first order kinetic equation is presented below

$$\ln(C/C_0) = kt \quad (1)$$

where C is the final concentration at time t and C_0 is the initial concentration, and the slope of the plot of $\ln(C/C_0)$ vs. the irradiation time (t) gives the value of k or k_{app} which is called the pseudo first order rate constant or apparent rate constant. The k values for different samples are shown in Fig. 9c and also in Table S1.† It is found from Table S1† that the Sg-C₃N₄/Bi₂O₃/Ag (15%) ternary nanocomposite photocatalyst shows much higher photocatalytic efficiency than other prepared nanocomposites which can be ascribed to the best synergistic interaction between the ternary phases, better visible light absorption capability, and higher photogenerated electron–hole charge separation ability compared to other synthesized nanocomposites.

Furthermore, it is known that coloured dye solution affects the photocatalytic properties of catalysts to a great extent through the photosensitization effect. Therefore, in order to examine the intrinsic photocatalytic efficiency of all the synthesized ternary nanocomposites for broader application, we also tested their photocatalytic performance towards the degradation of 10 ppm TCH solution under natural sunlight. The procedure for TCH degradation and experimental conditions were maintained identical to those of RhB. Fig. 9d presents the rate of degradation of TCH as a function of time. Fig. 9e and f present the TCH degradation kinetics and the value of rate constant (k_{app}) for different photocatalysts during the first cycle of the experiment. It is clearly seen that Sg-C₃N₄/Bi₂O₃ degrades only 47.8% of TCH under 60 min illumination of sunlight. While with respect to Sg-C₃N₄/Bi₂O₃/Ag (5%), Sg-C₃N₄/Bi₂O₃/Ag (10%), Sg-C₃N₄/Bi₂O₃/Ag (15%) and Sg-C₃N₄/Bi₂O₃/Ag (20%), the



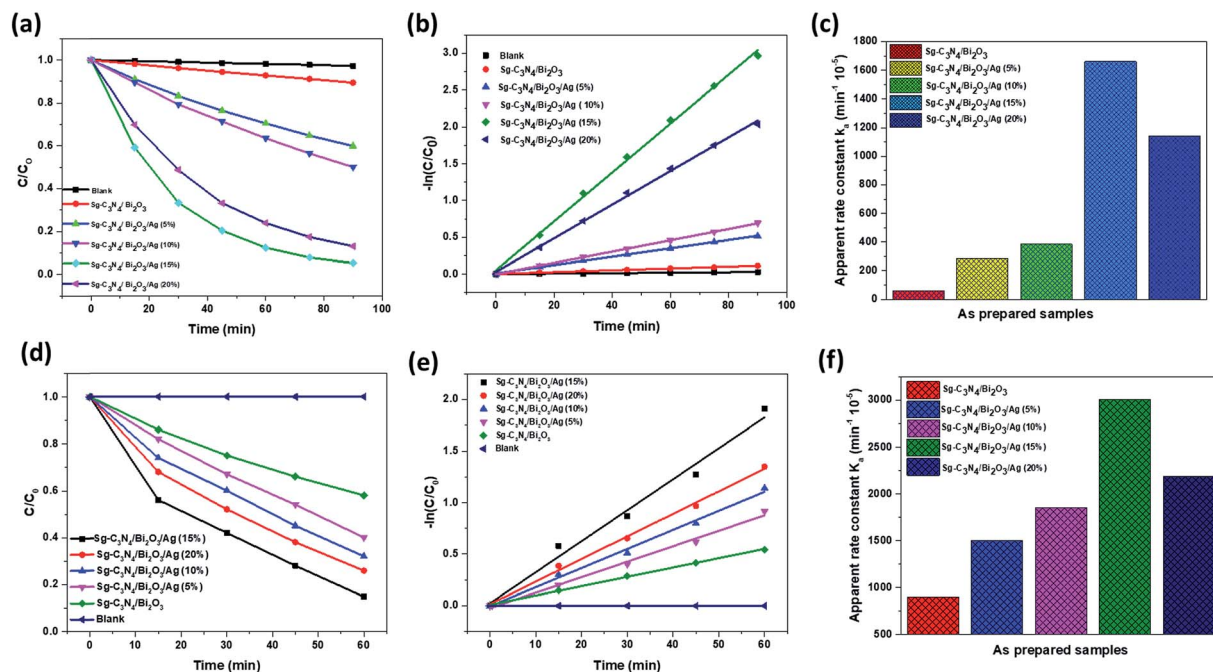


Fig. 9 (a) Photocatalytic decolorisation plots of RhB under natural sunlight, (b) first order kinetic study of RhB degradation, (c) apparent rate constant of the materials for RhB degradation, (d) photocatalytic degradation plots of TCH under natural sunlight, (e) first order kinetic study of TCH degradation, and (f) apparent rate constant of the materials for TCH degradation.

degradation percentages of TCH are 60%, 68%, 85.18% and 74.08%, respectively, under the same reaction conditions. From this result (Table S1[†]), it can be concluded that in comparison to other prepared ternary nanocomposites, Sg-C₃N₄/Bi₂O₃/Ag (15%) shows better photocatalytic ability towards the degradation of TCH under solar light. This study provides conclusive proof that the catalytic behaviour is only due to the photocatalytic ability of the ternary nanocomposites, even though some minimal sensitization effect is observed as in the case of RhB, but that can be ignored.

3.8. Determination of reactive species involved in the decolorisation process

In the semiconductor based photocatalysis process electrons (e⁻), holes (h⁺), hydroxyl radicals ([•]OH), superoxide radicals ([•]O₂⁻) etc. are the main reactive species that are basically generated and are involved in the degradation of harmful organic pollutants. So for examining the main reactive species involved in the decolorisation process, we performed decolorization of RhB dye in the presence of different scavenger solutions (1 mM). The result of the scavenger study obtained with the Sg-C₃N₄/Bi₂O₃/Ag (15%) nanocomposite photocatalyst is presented in Fig. 10a. From this figure it is seen that when *para*-benzoquinone is used as the scavenger, 36.48% decolorisation of RhB is observed which signifies that superoxide radicals play a role in the degradation process. However, when *tert*-butyl alcohol and EDTA are used, which are generally used to trap hydroxyl radicals and holes, the decolorization rate decreases significantly. This result suggests that both hydroxyl radicals and holes play a major role in the decolorisation

process. Again, when DMSO is used as a scavenger for electrons the result shows that 34.37% of RhB solution is decolorised which suggests that electrons are also important reactive species involved in the process of degradation (Table S2[†]). Therefore, from the above experimental findings it is concluded that the roles of various reactive species in the RhB decolorisation process are in the following order: h⁺ > [•]OH > e⁻ > [•]O₂⁻.

In order to further support the scavenger study, we also carried out a confirmatory test for the formation of hydroxyl and superoxide radicals during the photocatalytic reaction process. For hydroxyl radicals, a terephthalic acid (TA) assisted PL spectroscopy technique was used in which TA solution was used to trap the photogenerated [•]OH radicals which form highly fluorescent 2-hydroxyterephthalic acid (TAOH). Thus the fluorescence intensity of 2-hydroxyterephthalic acid can be correlated with the concentration of [•]OH generated during the reaction process. From Fig. 10b and c, it is clear that for Sg-C₃N₄, Sg-C₃N₄/Bi₂O₃ and Sg-C₃N₄/Bi₂O₃/Ag (15%) the fluorescence intensity of TAOH gradually increases, suggesting that for all three samples the generation of [•]OH increases with an increase in illumination time. As the VB (valence band) potential for Sg-C₃N₄ is +1.23 eV (*vs.* NHE) and the CB potential is -1.27 eV (*vs.* NHE), the holes present in the VB of Sg-C₃N₄ cannot oxidise directly OH⁻ to [•]OH ([•]OH/OH⁻ = +1.99 eV *vs.* NHE). Hence the [•]OH must be produced in an indirect manner, by the reaction of protons with [•]O₂⁻. Again as the CB potential of Sg-C₃N₄ is more negative than the O₂/[•]O₂⁻ (-0.33 eV *vs.* NHE) reduction potential these [•]O₂⁻ radical species were produced by means of single electron reduction of surface adsorbed O₂ molecules. However, in the case of the Sg-C₃N₄/Bi₂O₃



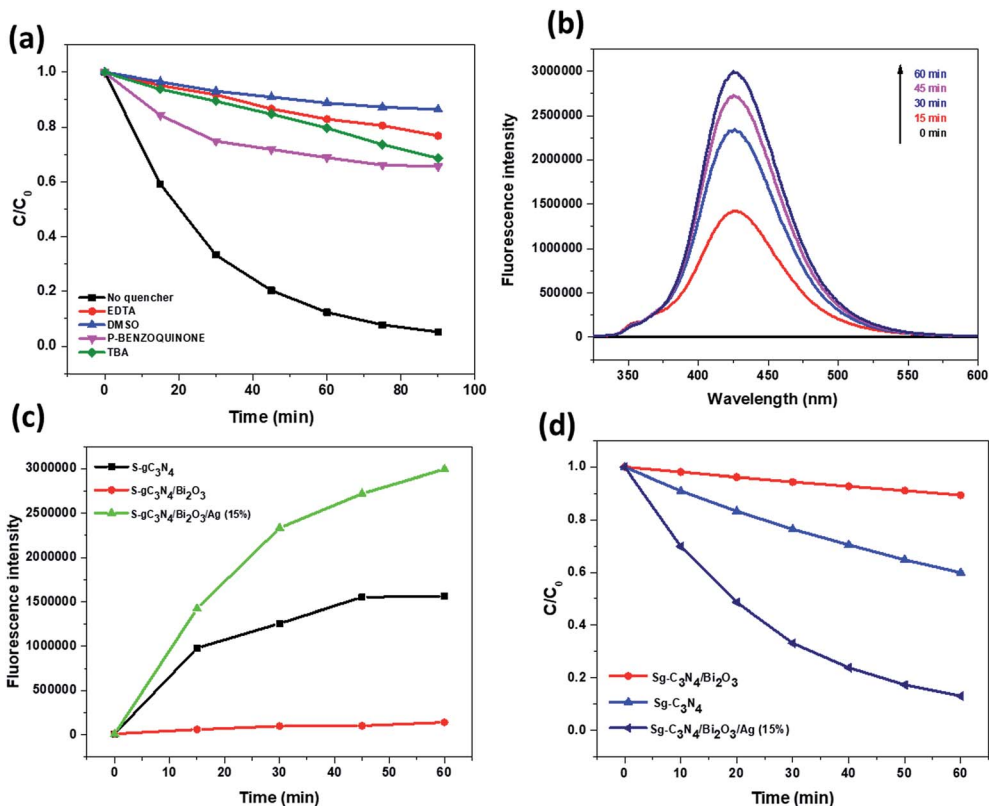


Fig. 10 (a) Photodecolorization of RhB by the SgC₃N₄/Bi₂O₃/Ag (15%) composite in the presence of different scavengers, (b) fluorescence spectra of 3-hydroxyterephthalic acid formed at different irradiation times in aqueous suspension of the SgC₃N₄/Bi₂O₃/Ag (15%) catalyst, (c) comparison of the PL intensity with time for Sg-C₃N₄, SgC₃N₄/Bi₂O₃ and SgC₃N₄/Bi₂O₃/Ag (15%) materials, and (d) rate of reduction of NBT with time by Sg-C₃N₄, SgC₃N₄/Bi₂O₃ and SgC₃N₄/Bi₂O₃/Ag (15%).

nanocomposite, as the VB potential of Bi₂O₃ is more positive than that of Sg-C₃N₄ the photogenerated holes on the surface of Bi₂O₃ will be transferred to Sg-C₃N₄. Meanwhile, the electrons generated on the surface of Sg-C₃N₄ will be transferred to Bi₂O₃, because the CB potential of Bi₂O₃ is less negative than that of Sg-C₃N₄. But as the CB potential of Bi₂O₃ is +0.40 eV (*vs.* NHE), which is too low to reduce O₂ to [•]O₂⁻, the formation of [•]O₂⁻ radical species by the reduction of surface adsorbed O₂ molecules is restricted. This suggests that the formation of [•]OH in the case of Sg-C₃N₄/Bi₂O₃ in both a direct and indirect manner is quite low which is clear from the experimental results. Furthermore, in the case of the Sg-C₃N₄/Bi₂O₃/Ag (15%) ternary nanocomposite, owing to the incorporation of Ag into the Sg-C₃N₄/Bi₂O₃ nanocomposite system, the amount of [•]OH produced is the most significant. This is because the metallic Ag⁰ sites which act as an electron pool transfer the photo-excited electrons from Sg-C₃N₄ and reduce the O₂ to [•]O₂⁻ which again combines with protons and subsequently forms [•]OH radicals.

Again, in order to obtain conclusive evidence of the formation of [•]O₂⁻ species in the reaction system, we performed an NBT test under visible light illumination conditions for 1 h. In the NBT test, the reagent nitroblue tetrazolium chloride (NBT) was used as a molecular probe for the detection of superoxide radical ([•]O₂⁻) species. It is well known that NBT gets reduced


selectively by superoxide radicals ([•]O₂⁻) and forms formazan, which can be detected from the decrease in NBT absorption intensity with the progress of illumination time. The obtained result is presented in Fig. 10d. It is found that the formation of [•]O₂⁻ species is the highest for the Sg-C₃N₄/Bi₂O₃/Ag (15%) ternary nanocomposite among other prepared photocatalysts. Again from the result of the terephthalic acid test and NBT test it can be concluded that the extent of [•]OH formation depends upon the amount of [•]O₂⁻ species produced during the reaction process, and thus the [•]OH species in the reaction system are produced indirectly from [•]O₂⁻.

3.9. Possible mechanism for photodegradation activity of the Sg-C₃N₄/Bi₂O₃/Ag nanocomposite

From the obtained experimental results, we have proposed a mechanistic pathway for the photocatalytic activity of the synthesized ternary nanocomposite (Scheme 2). From the UV-Vis DRS study the band gap for Sg-C₃N₄ and Bi₂O₃ is estimated to be 2.50 eV and 2.65 eV, respectively. This reflects that both Sg-C₃N₄ and Bi₂O₃ components of the composite can absorb visible light. The VB and CB potentials for Sg-C₃N₄ and Bi₂O₃ are calculated by using the following equations:

$$E_{\text{VB}} = X - E_{\text{c}} + 0.5E_{\text{g}} \quad (2)$$











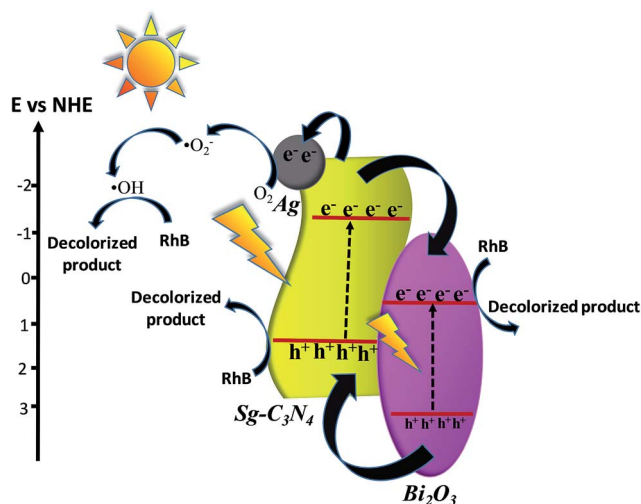


Scheme 2 Proposed mechanism for RhB decolorization by the Sg-C₃N₄/Bi₂O₃/Ag ternary photocatalyst.

$$E_{CB} = E_{VB} - E_g \quad (3)$$

where E_g represents the band gap energy, and E_{VB} and E_{CB} are the valence band and conduction band edge potentials (vs. NHE). E_e represents the free electron energy on the hydrogen scale (4.5 eV) and X is the absolute electronegativity of the respective semiconductor material. The X values for Sg-C₃N₄ and Bi₂O₃ are 4.48 and 6.23 eV, respectively. On the basis of the above formulae the positions of the conduction band and valence band for Sg-C₃N₄ and Bi₂O₃ are depicted in Scheme 2. According to the band gap alignment, since the conduction band potential of Sg-C₃N₄ (-1.27 eV vs. NHE) was more negative than that of Bi₂O₃ (+0.4 eV vs. NHE), the photogenerated electrons will migrate from the CB of Sg-C₃N₄ to the CB of Bi₂O₃. As the O₂/[•]O₂⁻ reduction potential is -0.33 eV vs. NHE, the electrons accumulated on the CB band of Bi₂O₃ cannot reduce surface adsorbed O₂ to [•]O₂⁻ and hence these electrons directly participate in the reduction of RhB. But in the case of Sg-C₃N₄/Bi₂O₃/Ag (15%), some of the electrons which are present in the CB of Sg-C₃N₄, due to photo-excitation of its valence band electrons, get transferred to the O₂ molecules *via* the attached Ag⁰ sites to produce [•]O₂⁻ radical species. But from the scavenger study it is confirmed that in comparison to [•]O₂⁻, [•]OH plays a major role in the decolorisation process. This suggests that these [•]O₂⁻ species formed yet again react with protons to produce H₂O₂ which is further transformed to [•]OH. Moreover, it is worth noting that the VB of Sg-C₃N₄ (+1.23 eV vs. NHE) is located above the valence band of Bi₂O₃ (+3.05 eV vs. NHE) which forms a unique band arrangement that efficiently facilitates the gradual and smooth transfer of photo-induced holes from Bi₂O₃ to Sg-C₃N₄ *via* the intermediate hetero-junction created between them. The redox potential of OH⁻/[•]OH (1.99 eV vs. NHE) is more positive with respect to the redox potential of the VB holes of Sg-C₃N₄, which indicates that the holes on the valence band of Sg-C₃N₄ would react with RhB directly. Therefore, it is observed that all the active species generated in the

reaction system play a significant role in the decolorisation of RhB. The possible reactions that are involved in the photo-decolourisation process are listed below.



3.10. Evaluation of toxicity of TCH

It is well known that TCH has a strong bacteriostatic effect.⁶⁰ So in order to measure the residual toxicity of TCH after photo-degradation, *E. coli* was chosen as the model microorganism. Fig. S1† shows the antibacterial activity of TCH after photocatalytic degradation reaction for 0 min, 30 min, and 60 min of light illumination. From the figure it is clearly observed that before light illumination no bacterial colonies are observed which is due to the strong antibacterial activity of TCH molecules. But after photocatalytic reaction for 30 min a few bacterial colonies are observed, which indicates that the toxicity of TCH is decreased compared to pure TCH. At the end of 1 h treatment, the number of bacterial colonies increased further and their size became bigger, suggesting that the toxicity of TCH is eliminated efficiently by using the synthesized ternary nanocomposite photocatalyst.

3.11. Analysis of degradation products of TCH

In order to investigate the photocatalytic degradation products of TCH molecules, we carried out GC-MS analysis of the aliquots taken out at different time intervals (0 min, 30 min, and 60 min) during the photocatalytic reaction. From GC-MS analysis it was observed that the photocatalytic degradation process of TCH molecules proceeds through a complex mechanism and as a result of which various degraded intermediate molecules were formed.⁵⁸ During the photocatalytic degradation of TCH, the intermediate molecules formed were due to ring opening, oxidation, and reduction reactions, and as a result of which the formation of numerous polar and nonpolar intermediates with different m/z values ranging from 73 to 490 was observed. Some of the intermediate compounds identified from the mass spectra, their retention times and possible chemical structures are listed in Table S3.† This experimental study proves that TCH



is degraded to smaller organic molecules/intermediates, which may eventually turn into CO₂ and H₂O and other smaller products.⁵⁹

3.12. Reusability of the photocatalyst

For the practical application of the photocatalyst, reusability is a very important factor that must be considered. So in order to determine the stability and reusability of the photocatalyst, recycling experiments for RhB degradation by Sg-C₃N₄/Bi₂O₃/Ag (15%) were performed. The results reveal that there is not much decrease in the catalytic activity even after four successive cycles (Fig. S2†). Moreover, the XRD analyses of used samples were also performed to compare the stability of fresh and used samples. It is found that almost no discrepancy in the phase and structure of the recycled photocatalyst was observed. This illustrates that the prepared photocatalyst presents excellent stability and efficiency.

4. Conclusion

In summary, we have successfully synthesized solar light driven visible light responsive S doped g-C₃N₄/Bi₂O₃/Ag plasmonic photocatalysts, by using facile chemical precipitation followed by a heat treatment process. Among all the synthesized ternary nanocomposites Sg-C₃N₄/Bi₂O₃/Ag (15%) showed enhanced photocatalytic activity towards the decolourisation of RhB dye and degradation of TCH under natural solar light. This result might be due to the better visible light absorption, efficient electron-hole pair separation, and formation of a hetero-junction and synergetic interaction between the nano-sized Ag, irregular shaped Bi₂O₃ and 2D sheets of Sg-C₃N₄ of the ternary nanocomposite. The mechanistic pathway for the degradation of RhB dye was thoroughly investigated by means of scavenger experimental studies and it is found that the effects of various reactive species on the degradation process are in the following order: h⁺ > ·OH > e⁻ > ·O₂⁻. Moreover, from the reusability study it is observed that the synthesized ternary nanocomposite possesses excellent stability and efficiency. This suggests that the synthesized ternary nanocomposite can be effectively used as a heterogeneous solar light responsive photocatalyst for the decomposition of aqueous organic pollutants.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors would like to acknowledge NIT Rourkela, India (Odisha), for providing the research facility and funding to carry out this work.

References

- M. Mousavi and A. Habibi-Yangjeh, *J. Colloid Interface Sci.*, 2016, **465**, 83–92.
- S. Fu, Y. He, Q. Wu, Y. Wu and T. Wu, *J. Mater. Res.*, 2016, **31**, 2252–2260.
- B. Gupta, A. A. Melvin, T. Matthews, S. Dhara, S. Dash and A. K. Tyagi, *Int. J. Hydrogen Energy*, 2015, **40**, 5815–5823.
- X. Yan, R. Xu, J. Guo, X. Cai, D. Chen, L. Huang, Y. Xiong and S. Tan, *Mater. Res. Bull.*, 2017, **96**, 18–27.
- X. She, J. Wu, H. Xu, J. Zhong, Y. Wang, Y. Song, K. Nie, Y. Liu, Y. Yang, M. T. F. Rodrigues, R. Vajtai, J. Lou, D. Du, H. Li and P. M. Ajayan, *Adv. Energy Mater.*, 2017, **7**, 1–7.
- N. Li, J. Zhang, Y. Tian, J. Zhao, J. Zhang and W. Zuo, *Chem. Eng. J.*, 2017, **308**, 377–385.
- K. Acuña, J. Yáñez, S. Ranganathan, E. Ramírez, J. Pablo Cuevas, H. D. Mansilla and P. Santander, *Sol. Energy*, 2017, **157**, 335–341.
- Z. Khodami and A. Nezamzadeh-Ejhieh, *J. Mol. Catal. A: Chem.*, 2015, **409**, 59–68.
- M. Xu, L. Han and S. Dong, *ACS Appl. Mater. Interfaces*, 2013, **5**, 12533–12540.
- C. Garkoti, J. Shabir and S. Mozumdar, *New J. Chem.*, 2017, **41**, 9291–9298.
- Y. Wang, J. Sun, J. Li and X. Zhao, *Langmuir*, 2017, **33**, 4694–4701.
- X. Cai, H. Liu, L. Zhi, H. Wen, A. Yu, L. Li, F. Chen and B. Wang, *RSC Adv.*, 2017, **7**, 46132–46138.
- O. Elbanna, M. Fujitsuka and T. Majima, *ACS Appl. Mater. Interfaces*, 2017, **9**, 34844–34854.
- L. Sun, T. Du, C. Hu, J. Chen, J. Lu, Z. Lu and H. Han, *ACS Sustainable Chem. Eng.*, 2017, **5**, 8693–8701.
- L. Shi, L. Liang, F. Wang, M. Liu and J. Sun, *Dalton Trans.*, 2016, **45**, 5815–5824.
- S. Zhang, J. Li, X. Wang, Y. Huang, M. Zeng and J. Xu, *ACS Appl. Mater. Interfaces*, 2014, **6**, 22116–22125.
- X. Yang, H. Tang, J. Xu, M. Antonietti and M. Shalom, *ChemSusChem*, 2015, **8**, 1350–1358.
- L. Qu, N. Chen, F. Zhao, C. Hu, Q. Han and Z. Zhang, *J. Mater. Chem. A*, 2015, **3**, 4612–4619.
- Y. Zhou, L. Zhang, J. Liu, X. Fan, B. Wang, M. Wang, W. Ren, J. Wang, M. Li and J. Shi, *J. Mater. Chem. A*, 2015, **3**, 3862–3867.
- T. Liu, Y. Wang, Y. Wei, X. Ma, B. Liu, S. Yin, L. Yang, Y. Jing and H. Li, *RSC Adv.*, 2017, **7**, 8688–8693.
- F. Dong, Z. Zhao, Y. Sun, Y. Zhang, S. Yan and Z. Wu, *Environ. Sci. Technol.*, 2015, **49**, 12432–12440.
- J. Xue, S. Ma, Y. Zhou, Z. Zhang and M. He, *ACS Appl. Mater. Interfaces*, 2015, **7**, 9630–9637.
- V. Sharma, S. Kumar and V. Krishnan, *ChemistrySelect*, 2016, **1**, 2963–2970.
- Y. Li, H. Zhang, P. Liu, D. Wang, Y. Li and H. Zhao, *Small*, 2013, **9**, 3336–3344.
- Y. Xu, F. Ge, Z. Chen, S. Huang, W. Wei, M. Xie and H. Xu, *Appl. Surf. Sci.*, 2019, **469**, 739–746.
- Z. Zhu, X. Tang, T. Wang, W. Fan, Z. Liu and C. Li, *Appl. Catal., B*, 2019, **241**, 319–328.
- M. Zhang, X. Bai, D. Liu, J. Wang and Y. Zhu, *Appl. Catal., B*, 2015, **164**, 77–81.
- Z. Li, C. Kong and G. Lu, *J. Phys. Chem. C*, 2016, **120**, 56–63.



- 29 C. Lu, R. Chen, X. Wu, M. Fan, Y. Liu, Z. Le, S. Jiang and S. Song, *Appl. Surf. Sci.*, 2016, **360**, 1016–1022.
- 30 N. Bao, X. Hu, Q. Zhang, X. Miao, X. Jie and S. Zhou, *Appl. Surf. Sci.*, 2017, **403**, 682–690.
- 31 K. Wang, Q. Li, B. Liu, B. Cheng, W. Ho and J. Yu, *Appl. Catal., B*, 2015, **176–177**, 44–52.
- 32 Y. Zhu, T. Ren and Z. Yuan, *ACS Appl. Mater. Interface*, 2015, **7**, 16850–16856.
- 33 B. Zhu, J. Zhang, C. Jiang, B. Cheng and J. Yu, *Appl. Catal., B*, 2017, **207**, 27–34.
- 34 S. C. Smith, G. Liu, Z. Chen, G. Q. Lu, H.-M. Cheng, P. Niu and C. Sun, *J. Am. Chem. Soc.*, 2010, **132**, 11642–11648.
- 35 L. Jiang, X. Yuan, G. Zeng, X. Chen, Z. Wu, J. Liang, J. Zhang, H. Wang and H. Wang, *ACS Sustainable Chem. Eng.*, 2017, **5**, 5831–5841.
- 36 K. Wang, Q. Li, B. Liu, B. Cheng, W. Ho and J. Yu, *Appl. Catal., B*, 2015, **176–177**, 44–52.
- 37 J. Liu, *J. Phys. Chem. C*, 2015, **119**, 28417–28423.
- 38 W. Cui, Y. Liang, W. An, L. Liu, Y. Qi, J. Lu and S. Lin, *Appl. Catal., B*, 2015, **183**, 133–141.
- 39 R. He, J. Zhou, H. Fu, S. Zhang and C. Jiang, *Appl. Surf. Sci.*, 2018, **430**, 273–282.
- 40 H. Y. Jiang, G. Liu, T. Wang, P. Li, J. Lin and J. Ye, *RSC Adv.*, 2015, **5**, 92963–92969.
- 41 D. He, X. Hou, S. Xue, W. Xie and X. Wei, *Mater. Lett.*, 2015, **161**, 640–643.
- 42 P. Qiu, C. Han, W. Liu, X. Li, L. Ge and S. Fang, *Appl. Catal., B*, 2015, **176–177**, 62–69.
- 43 C. Liu, C. Cao, X. Luo and S. Luo, *J. Hazard. Mater.*, 2015, **285**, 319–324.
- 44 B. Cheng, N. Wu, J. Yu, A. Meng, S. Song and S. Cao, *Appl. Catal., B*, 2015, **181**, 71–78.
- 45 Q. Xu, C. Jiang, B. Zhu, B. Cheng and J. Yu, *Sol. RRL*, 2018, **2**, 1800006.
- 46 J. Zhang, Y. Hu, X. Jiang, S. Chen, S. Meng and X. Fu, *J. Hazard. Mater.*, 2014, **280**, 713–722.
- 47 S. Martha, S. Mansingh, K. M. Parida and A. Thirumurugan, *Mater. Chem. Front.*, 2017, **1**, 1641–1653.
- 48 Z. Zhu, Y. Yu, H. Dong, Z. Liu, C. Li, P. Huo and Y. Yan, *ACS Sustainable Chem. Eng.*, 2017, **5**, 10614–10623.
- 49 J. Li, J. Yan, B. Chai, L. Hu and C. Wang, *Appl. Surf. Sci.*, 2017, **430**, 243–252.
- 50 X. Liu, J. Liu, H. Chu, J. Li, W. Yu, G. Zhu, L. Niu, Z. Sun, L. Pan and C. Q. Sun, *Appl. Surf. Sci.*, 2015, **347**, 269–274.
- 51 H. Y. Jiang, G. Liu, P. Li, D. Hao, X. Meng, T. Wang, J. Lin and J. Ye, *RSC Adv.*, 2014, **4**, 55062–55066.
- 52 S. Sun, M. Sun, Y. Kong, F. Liu, Z. Yu and S. Anandan, *J. Mater. Sci.*, 2017, **52**, 1183–1193.
- 53 H. T. Ren, S. Y. Jia, Y. Wu, S. H. Wu, T. H. Zhang and X. Han, *Ind. Eng. Chem. Res.*, 2014, **53**, 17645–17653.
- 54 T. Liu, Y. Wang, Y. Wei, X. Ma, B. Liu, S. Yin, L. Yang, Y. Jing and H. Li, *RSC Adv.*, 2017, **7**, 8688–8693.
- 55 Z. Wang, Y. Dai, K. Li, B. Huang, J. Lu, S. Gao, Q. Wang and H. Xu, *ACS Appl. Mater. Interfaces*, 2015, **7**, 9023–9030.
- 56 M. Jourshabani, Z. Shariatinia and A. Badiei, *J. Colloid Interface Sci.*, 2017, **507**, 59–73.
- 57 Y. Zhang, J. Wu, Y. Deng, Y. Xin, H. Liu, D. Ma and N. Bao, *Mater. Sci. Eng., B*, 2017, **221**, 1–9.
- 58 A. C. Martins, A. L. Cazetta, O. Pezoti, J. R. B. Souza and T. Zhang, *Ceram. Int.*, 2017, **43**, 4411–4418.
- 59 X. Zhu, Y. Wang, R. Sun and D. Zhou, *Chemosphere*, 2013, **92**, 925–932.
- 60 Y. Xu, J. Liu, M. Xie, L. Jing, J. Yan, J. Deng, H. Xu, H. Li and J. Xie, *Inorg. Chem. Front.*, 2018, **5**, 2818.

