

Cite this: *Chem. Sci.*, 2020, **11**, 6431

All publication charges for this article have been paid for by the Royal Society of Chemistry

## *In situ* Raman study of the photoinduced behavior of dye molecules on TiO<sub>2</sub>(*hkl*) single crystal surfaces†

Sheng-Pei Zhang,<sup>a</sup> Jia-Sheng Lin,<sup>a</sup> Rong-Kun Lin,<sup>a</sup> Petar M. Radjenovic,<sup>a</sup> Wei-Min Yang,<sup>a</sup> Juan Xu,<sup>b</sup> Jin-Chao Dong,<sup>\*a</sup> Zhi-Lin Yang,<sup>ID</sup><sup>a</sup> Wei Hang,<sup>ID</sup><sup>\*a</sup> Zhong-Qun Tian,<sup>ID</sup><sup>\*a</sup> and Jian-Feng Li,<sup>ID</sup><sup>\*a</sup>

In dye-sensitized solar cells (DSSCs), the TiO<sub>2</sub>/dye interface significantly affects photovoltaic performance. However, the adsorption and photoinduced behavior of dye molecules on the TiO<sub>2</sub> substrate remains unclear. Herein, shell-isolated nanoparticle-enhanced Raman spectroscopy (SHINERS) was used to study the adsorption and photoinduced behavior of dye (N719) molecules on different TiO<sub>2</sub>(*hkl*) surfaces. On TiO<sub>2</sub>(001) and TiO<sub>2</sub>(110) surfaces, the *in situ* SHINERS and mass spectrometry results indicate S=C bond cleavage in the anchoring groups of adsorbed N719, whereas negligible bond cleavage occurs on the TiO<sub>2</sub>(111) surface. Furthermore, DFT calculations show the stability of the S=C anchoring group on three TiO<sub>2</sub>(*hkl*) surfaces in the order TiO<sub>2</sub>(001) < TiO<sub>2</sub>(110) < TiO<sub>2</sub>(111), which correlated well with the observed photocatalytic activities. This work reveals the photoactivity of different TiO<sub>2</sub>(*hkl*) surface structures and can help with the rational design of DSSCs. Thus, this strategy can be applied to real-time probing of photoinduced processes on semiconductor single crystal surfaces.

Received 31st January 2020

Accepted 1st April 2020

DOI: 10.1039/d0sc00588f

rsc.li/chemical-science

Dye-sensitized solar cells (DSSCs) have attracted much interest due to their versatility, low cost, and ease of fabrication into flexible devices.<sup>1</sup> However, to date, the highest certified power conversion efficiency (PCE) recorded for a DSSC under simulated sunlight illumination is only 11.9%,<sup>2</sup> while the theoretical maximum PCE is over 30%.<sup>3</sup> Additionally, the long-term stability of DSSCs is very important for practical applications. DSSCs function *via* a charge injection mechanism between closely interacting dye/semiconductor molecules.<sup>4</sup> Studying the adsorption and photoinduced behavior of N719 molecules on TiO<sub>2</sub> surfaces can reveal the fundamental reaction processes and help improve the conversion efficiency and lifetime of DSSCs.<sup>5</sup>

Previously, there have been some research studies on the adsorption configuration and electronic properties of N719 dye molecules at TiO<sub>2</sub> surfaces. Grätzel *et al.* concluded, based on Fourier transform infrared spectroscopy (FTIR), that N719 was anchored on the TiO<sub>2</sub> surface in a bridged configuration *via* two

carboxyl groups.<sup>4a</sup> They further showed with density functional theory (DFT) calculations that deprotonation of the terminal carboxylic groups cause the excitation energy to increase.<sup>6</sup> In addition, Tian *et al.* investigated the Ag@TiO<sub>2</sub>/N719 interface under a series of potential controls using *in situ* Raman spectroscopy and found that the SCN ligand participates in N719 adsorption on the surface of aggregated TiO<sub>2</sub> nanoparticles,<sup>7</sup> while Lund *et al.* employed high-performance liquid chromatography (HPLC) and ultraviolet-visible spectroscopy (UV/Vis) to determine the photoinduced degradation and regeneration rates for N719 at the TiO<sub>2</sub> surface. Depending on the rates achieved by the DSSC, they calculated operating times as high as 20 years or as low as 0.5 years.<sup>5</sup> However, most of these studies only focused on polycrystalline TiO<sub>2</sub> substrate surfaces where it is difficult to study the structure–activity relationship of the substrate. For a better understanding of the reaction processes, investigating atomically flat single crystals with well-defined surface structures as well as electronic and optical properties can act as a bridge between experimental studies and theoretical simulations.

Surface-enhanced Raman spectroscopy (SERS) is a non-destructive and ultrasensitive technique that has become a powerful surface analysis tool.<sup>8</sup> Unfortunately, conventional SERS techniques cannot be applied to single crystal surfaces because they lack sufficient surface plasmon resonance (SPR).<sup>9</sup> In 2010, our group invented the shell-isolated nanoparticle-enhanced Raman spectroscopy (SHINERS)<sup>10</sup> technique for

<sup>a</sup>Department of Physics, State Key Laboratory of Physical Chemistry of Solid Surfaces, iChEM, College of Chemistry and Chemical Engineering, College of Energy, College of Materials, Xiamen University, Xiamen 361005, China. E-mail: Li@xmu.edu.cn; jinchaodong1209@126.com; weihang@xmu.edu.cn; zqtian@xmu.edu.cn

<sup>b</sup>Fujian Province Key Laboratory of Modern Analytical Science and Separation Technology, College of Chemistry, Chemical Engineering and Environment, Minnan Normal University, Zhangzhou 363000, China

† Electronic supplementary information (ESI) available. See DOI: 10.1039/d0sc00588f

obtaining enhanced surface Raman signals, irrespective of the surface and with single crystal surface compatibility. Shell-isolated nanoparticles (SHINs) act as surface Raman signal enhancers without detrimentally affecting the external environment or reaction processes due to their inert silica shell coating.<sup>11</sup> Since then, important catalytic reactions, such as the oxygen reduction reaction (ORR) and oxygen evolution reaction (OER) with their intermediate species, as well as the structure of interfacial water at single-crystal electrode surfaces have been observed using *in situ* SHINERS.<sup>12</sup>

Herein, the adsorption and photoinduced behavior of N719 molecules on three  $\text{TiO}_2(hkl)$  surfaces (rutile  $\text{TiO}_2(001)$ ,  $\text{TiO}_2(110)$ , and  $\text{TiO}_2(111)$ ) under 405 nm laser irradiation were investigated with *in situ* SHINERS. Combined with DFT simulations, the  $\text{TiO}_2(hkl)$  facet effect and the intrinsic photocatalytic mechanism were elucidated and provide a promising method for studying photoinduced surface processes in real-time.

In this system, N719 dye molecules were assembled on rutile  $\text{TiO}_2(hkl)$  surfaces and SHINs were deposited on top and then transferred to a Raman cell filled with acetonitrile (without N719 in solution). During *in situ* Raman measurements, the cell was illuminated with two different wavelength lasers, 638 nm and 405 nm ( $6600 \text{ mW cm}^{-2}$ ), for detecting Raman signals and exciting the photoinduced reactions, respectively (Fig. 1a). Besides, the power density of the 405 nm laser is 66 times higher than one sun condition ( $100 \text{ mW cm}^{-2}$ ), so the photo-induced reaction speed of N719 on the  $\text{TiO}_2$  surface will be much higher due to more photo-generated carriers being produced under 405 nm laser illumination. Therefore, it is more likely for us to obtain the Raman signal in the current research. Fig. 1b shows the TEM image of two adjacent SHINs. The enhancement factor of SHINs on the  $\text{TiO}_2$  surfaces was assessed using three-dimensional finite-difference time-domain (3D-FDTD) simulations (Fig. 1c). Plasmonic coupling dictates the Raman enhancement factor and is shown to be stronger between adjacent SHINs (55 nm dia. Au core @ 2 nm

thick  $\text{SiO}_2$  shell) than between SHINs and the rutile  $\text{TiO}_2(hkl)$  substrate; however N719 molecules were only adsorbed on the  $\text{TiO}_2$  single crystal surface. Therefore, all N719 Raman signals measured herein must originate from the electromagnetic field enhancement between the SHINs and the substrate which had a calculated enhancement factor of about  $10^3$  times (Fig. 1c). Importantly, compared to a strategy with no SHINs (Fig. S1†), this SHINERS strategy provides enough enhancement for detection of surface N719.

In Fig. 2a, three Raman bands are visible on all pristine rutile  $\text{TiO}_2(hkl)$  surfaces at around  $238 \text{ cm}^{-1}$ ,  $448 \text{ cm}^{-1}$  and  $610 \text{ cm}^{-1}$  assigned to the multi-phonon,  $E_g$ , and  $A_{1g}$  modes of the Ti–O–Ti bond vibrations, respectively,<sup>13</sup> and their relative peak intensities ( $I_{238 \text{ cm}^{-1}}$ ,  $I_{448 \text{ cm}^{-1}}$  and  $I_{610 \text{ cm}^{-1}}$ ) are clearly surface facet dependent. For the N719 molecule (see Fig. S2† for the chemical structure), there are two SCN binding groups attached to the Ru atom, both of which share the highest occupied molecular orbital (HOMO) and the 2,2-bipyridyl-4,4-dicarboxylic ligand contains the lowest unoccupied molecular orbital (LUMO) of the molecule. In the UV-vis absorption spectrum of N719 dissolved in ethanol (Fig. S3†), N719 has two clear adsorption peaks. The first peak, located at around 389 nm, is associated with a mixture of ligand-to-ligand charge transfer (LLCT) and metal-to-ligand charge transfer (MLCT) processes, while the second peak at 532 nm is related to low energy MLCT processes within N719 molecules.<sup>14</sup> The  $I_{610 \text{ cm}^{-1}}/I_{448 \text{ cm}^{-1}}$  is the same after adding SHINs on the  $\text{TiO}_2(001)$  surface (Fig. S4†), but interestingly, after N719 is adsorbed at the surface, the  $I_{610 \text{ cm}^{-1}}/I_{448 \text{ cm}^{-1}}$  on all three rutile  $\text{TiO}_2(hkl)$  surfaces changed. In Fig. 2b,  $I_{610 \text{ cm}^{-1}}/I_{448 \text{ cm}^{-1}}$  intensities decreased on  $\text{TiO}_2(111)$  and  $\text{TiO}_2(001)$  surfaces and increased on the  $\text{TiO}_2(110)$  surface. For N719 molecules chemisorbed on rutile  $\text{TiO}_2(hkl)$  surfaces, the different N719 anchoring modes result in different interactions of Ti–O–Ti (Fig. 2b),<sup>15</sup> so the ratios of  $I_{610 \text{ cm}^{-1}}/I_{448 \text{ cm}^{-1}}$  differ between the three  $\text{TiO}_2(hkl)$  surfaces after N719 adsorption, manifesting as a change in Raman peak intensities.<sup>11a</sup>

For N719 adsorbed at different rutile  $\text{TiO}_2(hkl)$  surfaces, both  $1482 \text{ cm}^{-1}$  and  $1610 \text{ cm}^{-1}$  peaks, belonging to the C=N and C=C stretching vibrations of the bipyridyl ring, respectively,<sup>16</sup> are surface facet dependent (Fig. 2b). For  $\text{TiO}_2(110)$ , the  $1482 \text{ cm}^{-1}$  peak intensity ( $I_{1482 \text{ cm}^{-1}}$ ) is obviously stronger than the  $1610 \text{ cm}^{-1}$  peak intensity ( $I_{1610 \text{ cm}^{-1}}$ ), whereas on  $\text{TiO}_2(111)$ , the  $I_{1482 \text{ cm}^{-1}}$  is weaker than  $I_{1610 \text{ cm}^{-1}}$ , and both peak intensities are similar on  $\text{TiO}_2(001)$ . This can be attributed to the different

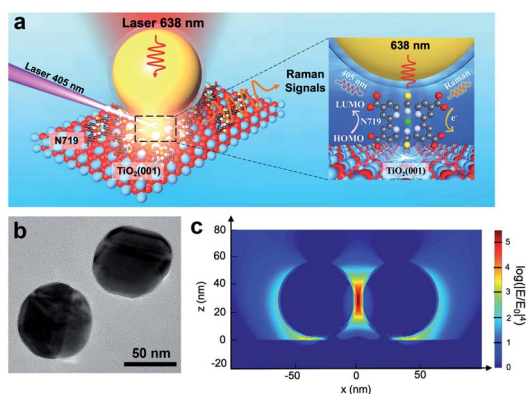


Fig. 1 (a) Schematic diagram of using a SHINERS nanoantenna to study the photoinduced reaction of N719 illuminated with two lasers on  $\text{TiO}_2$ . The inset shows electron transfer from the 405 nm laser excited N719 molecules to the  $\text{TiO}_2$  single crystal surface and the 638 nm laser used to detect the changes in excited the molecules. (b) TEM image of 55 nm Au@2 nm  $\text{SiO}_2$  SHINs. (c) 3D-FDTD simulation of the enhancement hotspot of a SHIN dimer with a nanogap of 2 nm on rutile  $\text{TiO}_2$ .

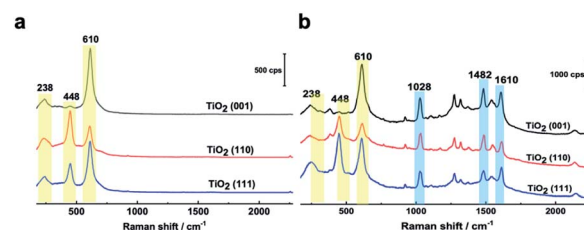


Fig. 2 (a) SHINER spectra of rutile  $\text{TiO}_2(001)$ ,  $\text{TiO}_2(110)$ , and  $\text{TiO}_2(111)$  surfaces in acetonitrile without and (b) with N719 molecules adsorbed.




rutile single crystal surfaces having different N719 adsorption configurations, giving rise to different bond enhancements.<sup>11a,17</sup>

SHINERS was then employed to study, *in situ*, the adsorption and photoinduced behavior of N719 molecules on the  $\text{TiO}_2(001)$  surface under 405 nm laser illumination. Fig. S5† shows Raman spectra of  $\text{TiO}_2(111)$  with and without 405 nm laser illumination and shows no observable interference peaks. This lack of Raman shifts under 405 nm illumination can be further verified using the formula in Fig. S6.† Furthermore, in Fig. S7,† the Raman signals for rutile  $\text{TiO}_2(110)$  without N719 adsorbed in acetonitrile were observed under extended illumination times (50 min). And peaks associated with the rutile  $\text{TiO}_2(110)$  substrate are not changed, indicating that 405 nm laser illumination does not change the  $\text{TiO}_2(hkl)$  substrate spectral peaks. As shown in Fig. 3a and b, as the illumination time increases, the Raman peaks of the adsorbed N719 molecules gradually weaken, while the rutile  $\text{TiO}_2$  peaks increase significantly. Considering these spectral trends over time (Fig. 3b), we tentatively ascribe this trend to desorption of N719 molecules from the  $\text{TiO}_2(001)$  surface as opposed to conformational changes in the N719 adsorption angle. Additionally, the Raman peak of the SCN group at around  $2136\text{ cm}^{-1}$  blue shifts to  $2146\text{ cm}^{-1}$  with increasing illumination time, indicating that as the N719 surface coverage decreases the N719 molecules adsorb on the  $\text{TiO}_2(001)$  surface *via* the S-terminal of the  $\text{N}=\text{C}=\text{S}$  group, corresponding with previous studies.<sup>7,18</sup>

Mass spectrometry was used to examine photoinduced reaction products. In Fig. 3c, the produced ion of  $m/z$  1157 appears after 36 hours under 405 nm laser illumination which corresponds to the loss of an S atom from N719. This confirms bond cleavage of the  $\text{S}=\text{C}$  bond in the SCN group adsorbed on the  $\text{TiO}_2(001)$  surface under 405 nm laser illumination producing


a  $[\text{Ru}^{\text{II}}(\text{H}_2\text{dcbpy})_2(\text{NCS})(\text{CN})]$  species.<sup>19</sup> For comparison, the adsorption behavior of the  $\text{N}=\text{C}=\text{S}$  functional group of a  $\text{Ph}-\text{N}=\text{C}=\text{S}$  species on different rutile  $\text{TiO}_2(hkl)$  surfaces was simulated using DFT. This also allowed for the reaction energy change due to the  $\text{S}=\text{C}$  double bond cleavage to be directly calculated. The calculated structures of the  $\text{Ph}-\text{N}=\text{C}=\text{S}$  group and S atom adsorbed on rutile  $\text{TiO}_2(001)$  are shown in Fig. 3d. The  $\text{S}=\text{C}$  dissociation energy on  $\text{TiO}_2(001)$  was found to be lower than that on  $\text{TiO}_2(111)$  and  $\text{TiO}_2(110)$  surfaces (Fig. S8†). Thus, the  $\text{TiO}_2(001)$  peak intensities ( $238\text{ cm}^{-1}$ ,  $448\text{ cm}^{-1}$ , and  $610\text{ cm}^{-1}$ ) increase as the illumination time increases due to increasing  $\text{S}=\text{C}$  bond cleavage resulting in N719 desorption.<sup>20</sup>

To further determine the facet effect, the adsorption and photoinduced behavior of N719 was also systemically studied on  $\text{TiO}_2(111)$  and  $\text{TiO}_2(110)$  with *in situ* SHINERS. In Fig. 4a, the time-dependent Raman spectra of N719 at the  $\text{TiO}_2(110)$  surface are similar to those at the  $\text{TiO}_2(001)$  surface (Fig. 3a), with N719 Raman intensities decreasing with increasing illumination times; however the trend is less pronounced. Meanwhile, the Raman peak shift of the SCN group around  $2143\text{ cm}^{-1}$  is also small ( $\sim 6\text{ cm}^{-1}$ ). In contrast, in Fig. 4b, the N719 Raman peak intensities gradually increase with time; meanwhile the rutile  $\text{TiO}_2(111)$  peaks around  $236\text{ cm}^{-1}$ ,  $446\text{ cm}^{-1}$  and  $610\text{ cm}^{-1}$  significantly weaken. The resulting decrease in the HOMO-LUMO gap in the adsorption complex produces a species that is more strongly Raman resonant with the 638 nm laser, resulting in the observed higher peak intensities.<sup>21</sup> In addition, The SCN peak is more stable on the  $\text{TiO}_2(111)$  surface during the photoinduced reaction processes and does not shift with time. Furthermore, comparing the mass spectra between surfaces, less of the  $[\text{Ru}^{\text{II}}(\text{H}_2\text{dcbpy})_2(\text{NCS})(\text{CN})]$  photoinduced degradation product is produced on  $\text{TiO}_2(111)$  than on the  $\text{TiO}_2(001)$

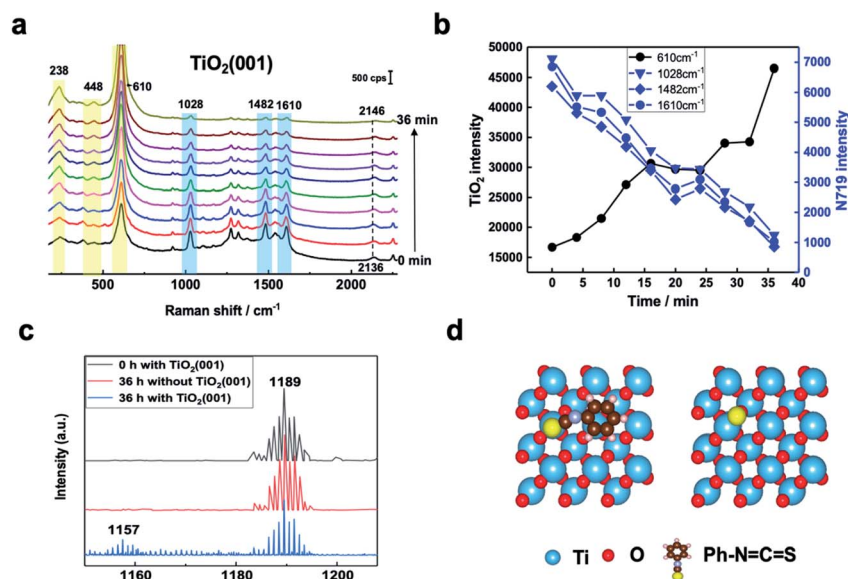

**Fig. 3** (a) SHINER Spectra of N719 adsorbed at  $\text{TiO}_2(001)$  in acetonitrile under 405 nm laser illumination, spectra collected every 4 minutes. (b) Plot of changes in significant N719 (blue lines and points) and  $\text{TiO}_2$  (black line and points) spectral peak intensities with time. (c) Mass spectra of a  $5 \times 10^{-4}\text{ M}$  N719 ethanol solution containing  $\text{TiO}_2(001)$  under 405 nm laser illumination after 0 h and 36 h, and without  $\text{TiO}_2(001)$  after 36 hours. (d) Schematic of the optimized structures of the  $\text{Ph}-\text{N}=\text{C}=\text{S}$  group and S atom adsorbed on rutile  $\text{TiO}_2(001)$ .



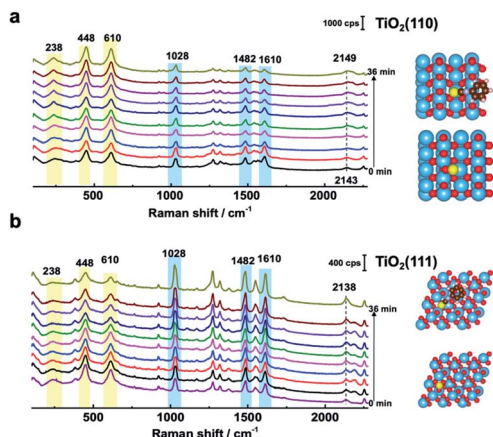

- P. Radjenovic, X. S. Zhou, J. M. Feliu, Z. Q. Tian and J. F. Li, *J. Am. Chem. Soc.*, 2020, **142**, 715; (c) N. Bodappa, M. Su, Y. Zhao, J. B. Le, W. M. Yang, P. Radjenovic, J. C. Dong, J. Cheng, Z. Q. Tian and J. F. Li, *J. Am. Chem. Soc.*, 2019, **141**, 12192; (d) C. Y. Li, J. B. Le, Y. H. Wang, S. Chen, Z. L. Yang, J. F. Li, J. Cheng and Z. Q. Tian, *Nat. Mater.*, 2019, **18**, 697.
- 13 S. K. Parayil, R. J. Psota and R. T. Koodali, *Int. J. Hydrogen Energy*, 2013, **38**, 10215.
- 14 (a) K. E. Lee, M. A. Gomez, T. Regier, Y. Hu and G. P. Demopoulos, *J. Phys. Chem. C*, 2011, **115**, 5692; (b) H. Rensmo, S. Lunell and H. Siegbahn, *J. Photochem. Photobiol. A*, 1998, **114**, 117; (c) A. El-Shafei, M. Hussain, A. Atiq, A. Islam and L. Han, *J. Mater. Chem.*, 2012, **22**, 24048.
- 15 J. G. Ma, C. R. Zhang, J. J. Gong, B. Yang, H. M. Zhang, W. Wang, Y. Z. Wu, Y. H. Chen and H. S. Chen, *J. Chem. Phys.*, 2014, **141**, 234705.
- 16 K. E. Lee, M. A. Gomez, S. Elouatik and G. P. Demopoulos, *Langmuir*, 2010, **26**, 9575.
- 17 (a) A. G. Thomas and K. L. Syres, *Chem. Soc. Rev.*, 2012, **41**, 4207; (b) R. B. Jaculbia, H. Imada, K. Miwa, T. Iwasa, M. Takenaka, B. Yang, E. Kazuma, N. Hayazawa, T. Taketsugu and Y. Kim, *Nat. Nanotechnol.*, 2020, **15**, 105.
- 18 J. Singh, A. Gusain, V. Saxena, A. K. Chauhan, P. Veerender, S. P. Koiry, P. Jha, A. Jain, D. K. Aswal and S. K. Gupta, *J. Phys. Chem. C*, 2013, **117**, 21096.
- 19 P. T. Nguyen, P. E. Hansen and T. Lund, *Sol. Energy*, 2013, **88**, 23.
- 20 C. Pérez León, L. Kador, B. Peng and M. Thelakkat, *J. Phys. Chem. B*, 2006, **110**, 8723.
- 21 S. Ben-Jaber, W. J. Peveler, R. Quesada-Cabrera, E. Cortes, C. Sotelo-Vazquez, N. Abdul-Karim, S. A. Maier and I. P. Parkin, *Nat. Commun.*, 2016, **7**, 12189.

