Journal of Materials Chemistry B



PAPER

View Article Online



Cite this: J. Mater. Chem. B, 2021, 9, 7271

Carambola-like Bi₂Te₃ superstructures with enhanced photoabsorption for highly efficient photothermal therapy in the second near-infrared biowindow*

Ying Zhao, ab Yang Liu, ab Qishun Wang, ob Jianhua Liu, ob Songtao Zhang, a Tiangi Zhang, (D d Daguang Wang, e Yinghui Wang, (D * Longhai Jin (D * d and Hongjie Zhang (1) *abc

Photothermal therapy (PTT) stimulated by light in the second near-infrared (NIR-II) biowindow shows great superiorities in the penetration ability of tissue and maximum permissible exposure (MPE). Exploring new photothermal agents with good optical absorbance in the NIR-II region is highly desirable for efficient cancer therapy. Herein, we successfully prepare carambola-like bismuth telluride (Bi₂Te₃) superstructures modified with PEGylated phospholipid (Bi₂Te₃@PEG) for CT imaging-guided PTT in the NIR-II biowindow. Attributing to their superstructures, Bi₂Te₃@PEG exhibited enhanced photoabsorption with higher photothermal conversion efficiency (55.3% for 1064 nm) compared with that of Bi₂Te₃ nanoparticles. Furthermore, the good X-ray attenuation capacity of Bi endows Bi₂Te₃@PEG with an outstanding performance as computed tomography (CT) contrast agents. Bi₂Te₃@PEG superstructures have been confirmed to effectively eliminate tumor in vitro and in vivo with negligible long-term toxicities, offering them great potential to act as theranostic platforms for cancer diagnosis and treatment

Received 30th March 2021, Accepted 24th May 2021

DOI: 10.1039/d1tb00694k

rsc.li/materials-b

Introduction

Nanomaterials integrated with imaging and treatment into one system have attracted ever-increasing attention in recent years since they are regarded as promising tools for cancer theranostics. Compared with traditional cancer treatments, for instance chemotherapy, radiotherapy, and surgery,² photothermal therapy (PTT) is a promising alternative strategy due to its fascinating advantages, including minimal invasiveness, high spatial controllability and being less harmful to normal tissues.^{3,4} Most of the nanomaterials with good absorbance in the near-infrared (NIR) region have been explored due to their potential applications in PTT, including noble metal materials, 5-7 carbon-based nanomaterials, 8-10 metal chalcogenide

nanomaterials, 11,12 and so on. However, the majority of photo-

To achieve imaging-guided therapy, PTAs are usually combined with nanostructures with imaging functions, for instance, magnetic resonance imaging (MRI), 18,19 photoacoustic imaging (PAI),²⁰ X-ray computed tomography (CT)²¹⁻²³ and so on, which can not only diagnose the tumor location, but also show the accumulation ability of PTAs in the tumor site.24 Among them, CT is a powerful and widely used diagnostic technology with infinite tissue penetration, high spatial resolution and three-dimensional (3D) visualization of the full body. 25 Bismuth-based nanomaterials

thermal agents (PTAs) are triggered by light in the first NIR biowindow (NIR-I, 750-1000 nm) for PTT, which dramatically limits their use in clinical applications due to their low maximum permissible exposure (MPE, 0.33 W cm⁻² for 808 nm). 13,14 By contrast, light in the NIR-II biowindow (1000-1350 nm), with higher MPE (for example, 1.0 W cm⁻² for 1064 nm), deeper tissue penetration ability, and lower light scattering, is more suitable for PTT. 15,16 However, PTAs triggered by light in the NIR-II biowindow for PTT have rarely been reported until recently as a result of their absorption limitations in the NIR-II biowindow. 17 Therefore, it is urgent to design novel PTAs with strong absorption in the NIR-II biowindow and high photothermal conversion efficiencies (PCE, η).

^a State Key Laboratory of Rare Earth Resource Utilization, Changchun Institute of Applied Chemistry (CIAC), Chinese Academy of Sciences, Changchun 130022, China. E-mail: yhwang@ciac.ac.cn, hongjie@ciac.ac.cn


^b University of Science and Technology of China, Hefei 230026, China

^c Department of Chemistry, Tsinghua University, Beijing 100084, China

^d The second hospital of Jilin University, Changchun 130041, China. E-mail: jinlonghai@jlu.edu.cn

^e Department of Gastric and Colorectal Surgery, the First Hospital, Jilin University, Changchun 130021, China

[†] Electronic supplementary information (ESI) available. See DOI: 10.1039/

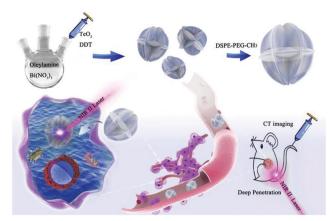

Scheme 1 Preparation of Bi₂Te₃@PEG superstructures for imaging-guided photothermal therapy in the second near-infrared biowindow.

have been exploited as CT contrast agents on account of the high atomic number and X-ray absorption coefficient of Bi, such as in Bi nanodots, ²⁶ Bi-based chalcogenides, ²⁷ BiOCl nanosheets ²⁸ and so on. Additionally, these Bi-based nanomaterials have good absorption in the NIR-I region, indicating that Bi-based nanomaterials could serve as theranostic nanoagents for CT imaging and PTT. 29 However, as far as we know, there have been only a few reports on the development of Bi-based nanomaterials for PTT in the NIR-II biowindow. 30-32

Bi₂Te₃ nanostructures, a kind of Bi-based chalcogenides, have exhibited potential in cancer theranostics, but only Bi₂Te₃ nanosheets prepared by chemical exfoliation have been investigated so far.33 In this work, we synthesized carambola-like Bi₂Te₃ superstructures modified with PEGylated phospholipid (Bi₂Te₃@PEG) as a nanotheranostic agent for CT imagingguided PTT in the NIR-II biowindow (Scheme 1). Benefiting from their carambola-like Bi₂Te₃ superstructure, Bi₂Te₃@PEG showed enhanced photoabsorption in the NIR-II region, resulting in a higher PCE (55.3% for 1064 nm) than that of Bi₂Te₃ nanoparticles. The tumors have been effectively eliminated after 14 d of treatment, demonstrating the good treatment effect of PTT in the NIR-II biowindow. Furthermore, Bi₂Te₃@PEG exhibited higher contrast densities as CT contrast agents than clinical iodine-based contrast agents owing to the high X-ray attenuation coefficient of Bi. These findings validate that Bi₂Te₃@PEG superstructures are a potential nanotheranostic agent for CT imaging-guided PTT in the NIR-II biowindow.

Experimental procedures

Materials

Tellurium dioxide (TeO₂), bismuth(III) nitrate [Bi(NO₃)₃·5H₂O], bismuth(III) chloride (BiCl₃), tellurium (Te), oleylamine (OM), sodium hydroxide (NaOH), and dodecanethiol (DDT) were purchased from Aladdin-Reagent, Shanghai. 1,2-Diastearoyl*sn-glycero-*3-phosphoethanolamine-*N*-[methoxy(polyethylene glycol)] (DSPE-PEG-CH₃) was purchased from TCI (Japan).

Preparation of Bi₂Te₃@PEG

Typically, Bi(NO₃)₃·5H₂O (0.3234 g) and OM (10 mL) were added to a flask and heated to 120 °C under N₂ protection to remove traces water. Afterward, the solution was heated up to 180 °C. At the same time, TeO₂ (0.1596 g) and DDT (2 mL) were heated to 110 °C for 15 minutes under N₂ protection in another flask. Then, the mixture was injected into the first solution quickly. Thereafter, the reaction was terminated using a water bath. Bi₂Te₃ was obtained by centrifugation and washed a few times with chloroform. Then, the obtained product was mixed with DSPE-PEG-CH3 in chloroform and stirred overnight. Finally, the mixture was evaporated and washed a few times with deionized water.

Preparation of Bi₂Te₃ nanoparticles

First, CTAB (0.3 g) was dispersed in a mixture of ethanol and water. Then, 0.15 g of NaOH, 0.946 g of BiCl₃, and 574.2 g of Te were sequentially added into this mixture. After stirring for 15 minutes, 12 mmol NaBH₄ was introduced. Then, the mixture was poured into a 30 mL Teflon-lined autoclave and placed in a 210 °C oven for 24 h. Finally, Bi₂Te₃ nanoparticles were obtained by centrifugation and washed a few times with ethanol and deionized water.

Photothermal properties of Bi₂Te₃@PEG

Bi₂Te₃@PEG solutions (1 mL) with a variety of concentrations (0, 12.5, 25, 50, and 100 ppm) were exposed to a 1064 nm or 808 nm laser (1 W cm⁻²) in the quartz cuvette for 10 min. Meanwhile, an infrared thermal imaging camera was employed to measure the temperature every 30 s and the thermal imaging images were taken every 2 min (FLIR T420, Fluke, USA). Thereafter, the temperature of the solution was cooled down naturally to investigate its PCE (η) . The above experiments were repeated three times.

CT imaging properties

A CT scanner was employed to evaluate the CT imaging properties of Bi₂Te₃@PEG. Typically, different concentrations of iobitridol and Bi₂Te₃@PEG aqueous solutions (0, 0.25, 0.5, 1, and 2 mg mL^{-1}) of I and Bi were used to measure X-ray CT imaging in vitro. Then, Bi_2Te_3 @PEG solution (2 mg mL⁻¹, 200 μ L) was injected intravenously into tumor-bearing Kunming mice for CT imaging in vivo. And, CT images were recorded before and after the injection (3 and 24 h), respectively. Imaging parameters were given as follows: tube voltage, 120 kVp; tube current, 300 mA; thickness, 0.9 mm; field of view, 350 mm; and rotation time, 0.5 s.

Cytotoxicity and photothermal effects of Bi₂Te₃@PEG in vitro

Non-cancerous mouse fibroblast cells (L929) and human cervical cancer cells (HeLa) were inoculated into a 96-well plate. Then, Bi₂Te₃@PEG solutions with different concentrations (0, 12.5, 25, 50, and 100 ppm) were introduced in it and incubated for one day. Thereafter, the cell counting kit 8 (CCK-8) solution was diluted and added into the wells and a plate reader was employed to record the survival rate of the cells. To investigate the photothermal effects of Bi₂Te₃@PEG,

the Bi₂Te₃@PEG solutions with different concentrations (0, 12.5, 25, 50, and 100 ppm) were incubated with HeLa cells. After irradiation (1064 nm, 1 W cm⁻²) for 10 min, the survival rate of the cells was detected by the CCK-8 solution and observed using an inverted fluorescence microscope.

Photothermal effects of Bi₂Te₃(a)PEG in vivo

40 female Kunming mice were selected for the *in vivo* therapy experiment. Typically, they were randomly divided into four groups after planted with U14 tumor cells, including (I) saline, (II) 1064 nm laser, (III) Bi₂Te₃@PEG (nanomaterials group), and (IV) Bi₂Te₃@PEG + 1064 nm (PTT group). Among them, groups III and IV were injected intravenously with Bi₂Te₃@PEG, while groups I and II were injected intravenously with saline every other day. At 24 h post injection, tumors in groups II and IV were exposed to a laser (1064 nm, 1 W cm⁻²). During this time, the weight of the mice and tumor dimension were detected every other day. And, the tumor volume was calculated as follows: $V = (\text{tumor length}) \times (\text{tumor width})^2/2$. After the 2nd day of treatment, the tumor was dissected for pathological analysis. On the 15th day, the Kunming mice were sacrificed and the tumors were dissected to evaluate the therapeutic efficacy.

Long-term toxicology of Bi₂Te₃@PEG in vivo

Bi₂Te₃@PEG was injected intravenously into the Kunming mice. On the 15th day, a few of the mice were sacrificed, and

their main organs were dissected and soaked in formalin solution for histopathological analysis. On the 30th day, the remaining mice were used for blood routine and blood biochemical analyses.

Results and discussion

Synthesis and characterization of Bi₂Te₃@PEG superstructures

Bi₂Te₃ was obtained by the high-temperature method according to a previous study.³⁴ As displayed in the scanning electron microscopy (SEM, Fig. 1A) and transmission electron microscope (TEM) images (Fig. 1B), the prepared Bi₂Te₃ show carambola-like superstructures with an average diameter of \sim 260 nm. Fig. 1C provides the lattice spacing of 0.322 nm, fitting with the (015) plane of Bi₂Te₃. The X-ray diffraction (XRD) pattern shown in Fig. S1 (ESI†) manifests that all characteristic diffractions match well with Bi2Te3 (JCPDS 72-2036). X-ray photoelectron spectroscopy (XPS) was used to determine the composition and surface valence states of Bi₂Te₃ (Fig. 1D). As shown in the high-resolution Bi 4f spectrum (Fig. 1E), the peaks of 162.4 and 157.1 eV are attributed to Bi $4f_{5/2}$ and Bi $4f_{7/2}$ of Bi₂Te₃, respectively, and the peaks at 158.6 and 163.9 eV can be assigned to the oxide surface of Bi₂Te₃. The Te 3d spectrum shown in Fig. 1F contains peaks at 582.2 and 572.0 eV, matching well with Te 3d_{3/2} and Te 3d_{5/2}, respectively. In short, the valence of Bi₂Te₃ shown in XPS is in good compliance with the previous report.³⁵

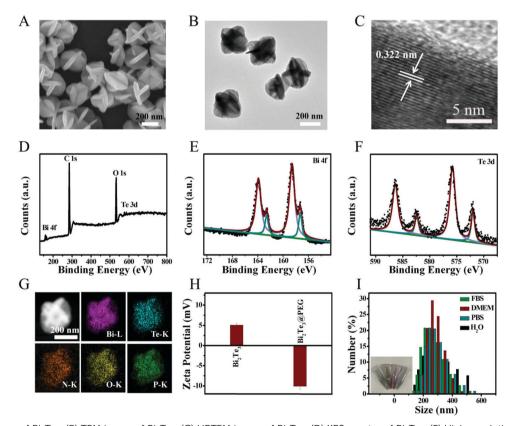


Fig. 1 (A) SEM image of Bi₂Te₃. (B) TEM image of Bi₂Te₃. (C) HRTEM image of Bi₂Te₃. (D) XPS spectra of Bi₂Te₃. (E) High-resolution Bi 4f spectrum of Bi₂Te₃. (F) High-resolution Te 3d spectrum of Bi₂Te₃. (G) STEM image and elemental mapping of Bi, Te, N, O, and P of Bi₂Te₃@PEG. (H) Zeta potential of Bi₂Te₃ and Bi₂Te₃@PEG. (I) Hydrodynamic size of Bi₂Te₃@PEG in H₂O, PBS, FBS, and DMEM.

Then, Bi₂Te₃ was modified with PEGylated phospholipid to improve the biocompatibility. As shown in Fig. S2 (ESI†), the morphology of Bi₂Te₃@PEG is unchanged after modification. Energy-dispersive X-ray (EDX) mapping shows that the Bi, Te, N, O, and P elements are distributed homogeneously in the Bi₂Te₃@PEG superstructures (Fig. 1G), indicating the successful coating of PEGylated phospholipid. As presented in Fig. S3 (ESI†), the characteristic IR bands at 2800-3000, 1715 and 1106 cm⁻¹ assigned to -CH₂, O-P, and C-O-C appear in the Fourier transform infrared (FT-IR) spectrum of Bi₂Te₃@PEG. Moreover, the zeta potential analysis reveals that the potential value ranges from 5.07 mV to -10.11 mV after modification (Fig. 1H). These results further demonstrate the successful modification of PEGylated phospholipid. Furthermore, Bi₂Te₃@ PEG superstructures exhibit good dispersibility in various solutions (Fig. 1I), including water, phosphate-buffered saline (PBS), fetal bovine serum (FBS), and Dulbecco's modified Eagle's medium (DMEM), offering them great potential for bioapplications.

Photothermal properties of Bi₂Te₃@PEG superstructures

Benefiting from the unique carambola-like superstructure, Bi₂Te₃@PEG superstructures have stronger absorption from the UV to the NIR-II region compared with that of Bi₂Te₃ nanoparticles prepared following previous reports (Fig. 2A).³⁶

The carambola-like superstructure make the Bi₂Te₃@PEG superstructures act as good laser cavity mirrors, which could enhance the capacity of photoabsorption and reflection of the laser (Fig. 2B).37 To further demonstrate the effect of the superstructures on the photothermal properties, we compared the temperature changes of Bi₂Te₃@PEG superstructure and Bi₂Te₃ nanoparticle solutions under irradiation (1064 nm, 1 W cm⁻²). Fig. 2C-E and Fig. S4 and S5 (ESI†) indicated that the temperature changes were dependent on both the concentration of the solution and the power density of the 1064 nm laser. In comparison with deionized water, the temperature of Bi₂Te₃@PEG solution (100 ppm) increased to 48.1 °C within 10 min under irradiation, indicating the excellent photothermal performance of Bi₂Te₃@PEG. By contrast, the temperature elevation of Bi₂Te₃ nanoparticles merely reached to 37.8 °C under the same conditions. The PCE (η) of Bi₂Te₃@PEG was calculated as 55.3% according to the fitted cooling curve (Fig. 2F), which was much higher than that of the Bi₂Te₃ nanoparticles (40.88% according to Fig. 2G). And, the good photothermal performance of Bi2Te3@PEG was also obtained by employing an 808 nm laser (1 W cm⁻², Fig. S6, ESI†), further demonstrating the effectiveness of the superstructures for improving the photoabsorption. Furthermore, the photothermal performance of Bi₂Te₃@PEG exhibited no significant difference after a five-cycle process, suggesting their good photothermal

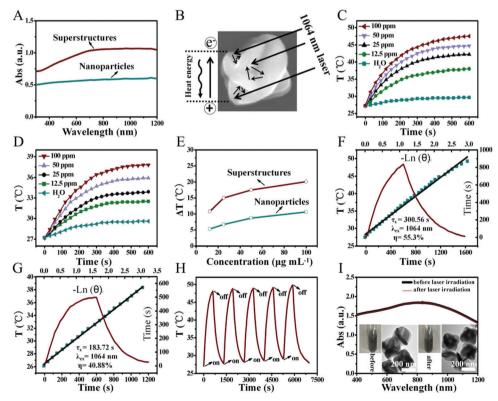


Fig. 2 (A) UV-vis spectra of Bi_2Te_3 @PEG and Bi_2Te_3 nanoparticles. (B) Schematic representation of a carambola-like Bi_2Te_3 @PEG superstructure acting as good laser cavity mirrors. Temperature curves of (C) Bi_2Te_3 appeal and (D) Bi_2Te_3 nanoparticles at various concentrations (0, 12.5, 25, 50, and 100 ppm) under irradiation (1064 nm, 1 W cm $^{-2}$). (E) The ΔT of Bi₂Te₃@PEG and Bi₂Te₃ nanoparticles. Heating and cooling curves of (F) Bi₂Te₃@PEG and (G) Bi₂Te₃ nanoparticles, with a fitted line acquired from the cooling section. (H) Temperature of Bi₂Te₃@PEG over five on/off cycles of the 1064 nm laser. (I) UV-vis spectrum of Bi₂Te₃@PEG before and after irradiation with the 1064 nm laser

stability (Fig. 2H). This result was further confirmed by their unchanged UV/Vis spectrum and morphology after irradiation with the 1064 nm laser (Fig. 2I). All these results validate that Bi₂Te₃@PEG superstructures are potential PTAs for PTT in the NIR-II biowindow.

CT imaging of Bi₂Te₃@PEG in vitro and in vivo

Because of the good X-ray attenuation capacity of Bi, we further evaluated the availability of Bi₂Te₃@PEG to act as a CT contrast agent. Compared with iobitridol (a commercial CT contrast agent), Bi₂Te₃@PEG showed enhanced contrast signals at equivalent concentrations (Fig. 3A and B), which should be attributed to the high K-edge value of Bi. Inspired by the above results, we further investigated their imaging capacity in vivo using the U14 tumor-bearing mice model. After intravenous injection of Bi_2Te_3 @PEG (2 mg mL $^{-1}$, 200 μ L), CT signals of the tumor were detected using a CT scanner. As depicted in Fig. 3C, the tumor area became significantly brighter 24 h after the injection, reflecting the good accumulation ability of Bi₂Te₃(a) PEG in the tumor area. All these findings suggest that Bi₂Te₃@ PEG could act as a promising CT contrast agent for cancer diagnosis.

Cytotoxicity and anticancer effects of Bi₂Te₃@PEG in vitro

Motivated by the excellent photothermal performance of Bi₂Te₃@PEG, we further investigated its potential as a PTA for PTT. First, the cytotoxicity was assessed by incubating different concentrations of Bi₂Te₃@PEG (0, 12.5, 25, 50, and 100 ppm) with L929 or HeLa cells for 24 h. Fig. 4A revealed that the survival rates were still higher than 90% for both L929 and HeLa cells even at the concentration of 100 ppm, demonstrating the good biocompatibility of Bi₂Te₃@PEG. Furthermore, we assessed the anticancer effect of Bi₂Te₃@PEG by the CCK-8 assay. The survival rates of L929 and HeLa cells showed a sharp decline with the increasing of Bi₂Te₃@PEG concentration after irradiation (1064 nm, 1 W cm⁻²) for 10 minutes (Fig. 4B), indicating that hyperthermia produced by Bi₂Te₃@PEG could effectively kill the cancer cells in a few minutes. The results of calcein AM and propidium iodide (PI) staining further demonstrated the good anticancer performance of Bi₂Te₃@PEG.

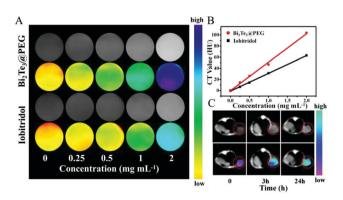


Fig. 3 (A) CT images and (B) CT values (HU) of Bi₂Te₃@PEG and iobitridol at various concentrations of Bi and I in vitro. (C) CT images of Kunming mice bearing a tumor at 0, 3, and 24 h after injection of the Bi₂Te₃@PEG.

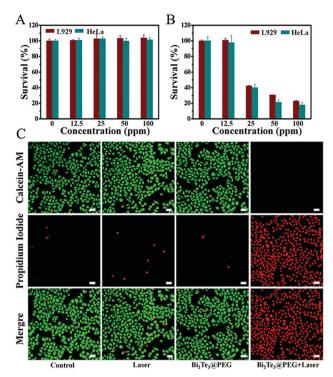


Fig. 4 (A) The survival rates of L929 and HeLa cells treated with a variety of concentrations of Bi_2Te_3 @PEG (0, 12.5, 25, 50, and 100 ppm). (B) L929 and HeLa cell viabilities with the treatment of Bi₂Te₃@PEG + 1064 nm laser (1 W cm⁻²). (C) Fluorescence images of HeLa cells in different groups (scale bars: 50 µm).

As displayed in Fig. 4C and Fig. S7 (ESI†), similar to that in the control and laser groups, both HeLa and L929 cells in the Bi₂Te₃@PEG (100 ppm) group showed strong green fluorescence, which should be attributed to their good biocompatibility. By contrast, cells in the Bi₂Te₃@PEG (100 ppm) + 1064 nm (1 W cm⁻², 10 min) group, as expected, revealed strong red fluorescence and negligible green fluorescence, further demonstrating the remarkable PTT treatment effect in vitro.

Anticancer effects of Bi₂Te₃@PEG in vivo

Inspired by the good anticancer performance of Bi₂Te₃@PEG in vitro, we further evaluated the treatment effects of Bi₂Te₃(a) PEG in vivo using the U14 tumor-bearing Kunming mice model. The photothermal performance of Bi₂Te₃@PEG in vivo was investigated by infrared thermal imaging. Mice bearing tumor were exposed to the laser (1064 nm, 1.0 W cm⁻²) at 24 h post injection of Bi₂Te₃@PEG, and the variation of the temperature in the tumor area was measured using an infrared thermal imaging camera. As depicted in Fig. S8 (ESI†), the temperature of the tumor rapidly increased to 57 °C within 10 min, whereas no significant heating was observed in the laser group, demonstrating that the remarkable photothermal effects of Bi₂Te₃@ PEG offer them great feasibility for local heating of the tumor. Then, the mice were randomly allocated into the following groups: (I) control group, (II) 1064 nm laser group, (III) Bi₂Te₃@PEG group, and (VI) Bi₂Te₃@PEG + laser (1064 nm, 1 W cm⁻²) group. The size of the tumor and the weight of the

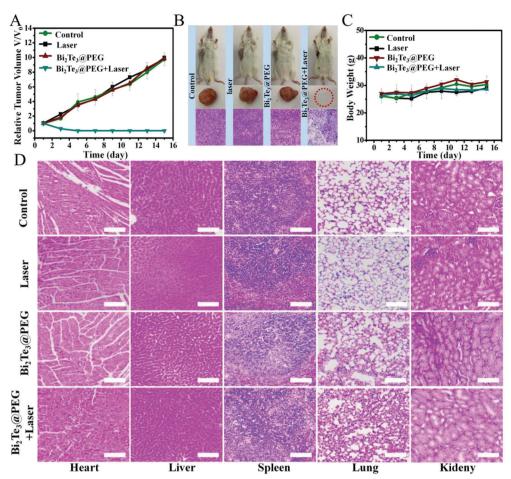


Fig. 5 (A) Volume of tumor in different groups. (B) Pictures of mice, corresponding appearance and H&E staining of tumor tissues after various treatments. (C) Weight of mice in the four groups. (D) H&E staining photographs of essential organs (scale bars: 100 μm).

mice were measured every other day. In contrast with groups I, II, and III, the tumors in treatment group VI were completely eradicated after twice treatments, and no recurrence was observed within 14 days (Fig. 5A), implying the remarkable PTT efficacy of Bi₂Te₃@PEG in the NIR-II biowindow. In addition, the histological assay (haematoxylin-eosin staining (H&E staining)) showed that the tumor tissues suffered severe damage in treatment group VI, whereas no significant necrosis was observed in the other groups, further demonstrating the good treatment effect of Bi₂Te₃@PEG (Fig. 5B). Furthermore, there is a negligible difference in weight of the mice in all groups within 14 days, implying the low acute toxicity of Bi₂Te₃@PEG (Fig. 5C). All these results confirmed that Bi₂Te₃@PEG can serve as a promising PTA for highly effective photothermal therapy in the NIR-II biowindow.

In vivo toxicology of Bi₂Te₃@PEG

The biosafety of nanomaterials is a crucial factor for further biomedical applications. First, the histological assay of the essential organs of mice was investigated after intravenous injection with Bi₂Te₃@PEG for 15 days. Fig. 5D revealed that no obvious damage could be viewed in all groups, indicating that Bi₂Te₃@PEG exhibited low side effects on the major organs in vivo applications. Furthermore, blood routine and blood

biochemical analyses were carried out at 30 d post injection of Bi₂Te₃@PEG. Fig. S9 (ESI†) shows that there was no obvious discrepancy of the blood index between the control and Bi₂Te₃@PEG groups, further demonstrating the negligible long-term toxicity of Bi₂Te₃@PEG.

Conclusions

In summary, carambola-like Bi₂Te₃@PEG superstructures have been successfully synthesized and served as novel nanotheranostic agents for CT imaging-guided PTT in the NIR-II biowindow. Compared with Bi₂Te₃ nanoparticles, Bi₂Te₃@PEG exhibited higher optical absorption in the NIR-II biowindow and higher PCE (55.3% for 1064 nm), which could be attributed to their carambola-like superstructures that can act as good laser cavity mirrors. Besides, because of the good X-ray attenuation capacity of Bi, Bi₂Te₃@PEG could serve as a good contrast agent for CT imaging in vitro and in vivo. Importantly, Bi₂Te₃@PEG could eradicate tumors with the irradiation at 1064 nm using a safe power density of 1 W cm^{-2} , achieving highly effective cancer therapy. This work will provide new insights for designing highly effective PTAs with good photothermal performances through the regulation of the structure.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was supported by the financial aid from the National Natural Science Foundation of China (Grants 52022094, 22020102003, 21521092, 21590794, 51502284, 5207214 and 21673220), the Strategic Priority Research Program of the Chinese Academy of Sciences (Grant XDB20030300), and the Youth Innovation Promotion Association of Chinese Academy of Sciences (Grant 2019232).

Notes and references

- 1 D. Wu, X. Duan, Q. Guan, J. Liu, X. Yang, F. Zhang, P. Huang, J. Shen, X. Shuai and Z. Cao, Adv. Funct. Mater., 2019, 29, 1900095.
- 2 P. Jia, H. Ji, S. Liu, R. Zhang, F. He, L. Zhong and P. Yang, J. Mater. Chem. B, 2021, 9, 101-111.
- 3 M. Ha, S. H. Nam, K. Sim, S. E. Chong, J. Kim, Y. Kim, Y. Lee and J. M. Nam, Nano Lett., 2021, 21, 731-739.
- 4 F. Xu, X. Li, H. Chen, M. Jian, Y. Sun, G. Liu, L. Ma and Z. Wang, J. Mater. Chem. B, 2020, 8, 10136-10145.
- 5 Q. Wang, H. Wang, Y. Yang, L. Jin, Y. Liu, Y. Wang, X. Yan, J. Xu, R. Gao, P. Lei, J. Zhu, Y. Wang, S. Song and H. Zhang, Adv. Mater., 2019, 31, 1904836.
- 6 X. Chen, X. Zhu, T. Xu, M. Xu, Y. Wen, Y. Liu, J. Liu and X. Qin, J. Mater. Chem. B, 2019, 7, 112-122.
- 7 C. Zhan, Y. Huang, G. Lin, S. Huang, F. Zeng and S. Wu, Small, 2019, 15, 1900309.
- 8 F. Zhou, M. Wang, T. Luo, J. Qu and W. R. Chen, Biomaterials, 2021, 265, 120421.
- 9 D. Wang, N. Zhang, X. Jing, Y. Zhang, Y. Xu and L. Meng, J. Mater. Chem. B, 2020, 8, 8271-8281.
- 10 Y. Qiu, D. Ding, W. Sun, Y. Feng, D. Huang, S. Li, S. Meng, Q. Zhao, L. J. Xue and H. Chen, Nanoscale, 2019, 11, 16351-16361.
- 11 L. Dong, K. Li, D. Wen, Y. Lu, K. Du, M. Zhang, X. Gao, J. Feng and H. Zhang, Nanoscale, 2019, 11, 12853-12857.
- 12 Z. Zhou, B. Li, C. Shen, D. Wu, H. Fan, J. Zhao, H. Li, Z. Zeng, Z. Luo, L. Ma and C. Tan, Small, 2020, 16, 2004173.
- 13 Y. Liu, W. Zhen, Y. Wang, J. Liu, L. Jin, T. Zhang, S. Zhang, Y. Zhao, S. Song, C. Li, J. Zhu, Y. Yang and H. Zhang, Angew. Chem., Int. Ed., 2019, 58, 2407-2412.
- 14 Y. Liu, W. Zhen, Y. Wang, J. Liu, L. Jin, T. Zhang, S. Zhang, Y. Zhao, N. Yin, R. Niu, S. Song, L. Zhang and H. Zhang, Nano Lett., 2019, 19, 5093-5101.
- 15 J. Zeng, M. Wu, S. Lan, J. Li, X. Zhang, J. Liu, X. Liu, Z. Wei and Y. Zeng, J. Mater. Chem. B, 2018, 6, 7889-7897.
- 16 Y. Chen, B. Sun, X. Jiang, Z. Yuan, S. Chen, P. Sun, Q. Fan and W. Huang, J. Mater. Chem. B, 2021, 9, 1002-1008.

- 17 W. Zhen, S. An, W. Wang, Y. Liu, X. Jia, C. Wang, M. Zhang and X. Jiang, Nanoscale, 2019, 11, 9906-9911.
- 18 S. Zhang, L. Jin, J. Liu, Y. Liu, T. Zhang, Y. Zhao, N. Yin, R. Niu, X. Li, D. Xue, S. Song, Y. Wang and H. Zhang, Nano-Micro Lett., 2020, 12, 180.
- 19 Y. Liu, J. Wu, Y. Jin, W. Zhen, Y. Wang, J. Liu, L. Jin, S. Zhang, Y. Zhao, S. Song, Y. Yang and H. Zhang, Adv. Funct. Mater., 2019, 29, 1904678.
- 20 W. Hu, X. Miao, H. Tao, A. Baev, C. Ren, Q. Fan, T. He, W. Huang and P. N. Prasad, ACS Nano, 2019, 13, 12006-12014.
- 21 W. Liao, P. Lei, J. Pan, C. Zhang, X. Sun, X. Zhang, C. Yu and S. K. Sun, Biomaterials, 2019, 203, 1-11.
- 22 Y. Fan, W. Tu, M. Shen, X. Chen, Y. Ning, J. Li, T. Chen, H. Wang, F. Yin, Y. Liu and X. Shi, Adv. Funct. Mater., 2020, 30, 1909285.
- 23 J. Xu, P. Yang, M. Sun, H. Bi, B. Liu, D. Yang, S. Gai, F. He and J. Lin, ACS Nano, 2017, 11, 4133-4144.
- 24 F. Li, T. Li, D. Zhi, P. Xu, W. Wang, Y. Hu, Y. Zhang, S. Wang, J. M. Thomas, J. B. Norman, W. Ding, L. Yan and B. Qiu, Biomaterials, 2020, 256, 120219.
- 25 R. Luo, L. Chen, Q. Li, J. Zhou, L. Mei, Z. Ning, Y. Zhao, M. Liu, X. Lai, J. Bi, W. Yin and D. Gao, Inorg. Chem., 2020, 59, 17906-17915.
- 26 P. Lei, R. An, P. Zhang, S. Yao, S. Song, L. Dong, X. Xu, K. Du, J. Feng and H. Zhang, Adv. Funct. Mater., 2017, 27, 1702018.
- 27 Y. Cheng, Y. Chang, Y. Feng, H. Jian, X. Wu, R. Zheng, K. Xu and H. Zhang, Adv. Mater., 2019, 31, 1806808.
- 28 C. Dai, R. Hu, C. Wang, Z. Liu, S. Zhang, L. Yu, Y. Chen and B. Zhang, Nanoscale Horiz., 2020, 5, 857-868.
- 29 P. Lei, R. An, X. Zheng, P. Zhang, K. Du, M. Zhang, L. Dong, X. Gao, J. Feng and H. Zhang, Nanoscale, 2018, 10, 16765-16774.
- 30 S. Dong, Y. Dong, T. Jia, S. Liu, J. Liu, D. Yang, F. He, S. Gai, P. Yang and J. Lin, Adv. Mater., 2020, 32, 2002439.
- 31 J. Li, D. Zhu, W. Ma, Y. Yang, G. Wang, X. Wu, K. Wang, Y. Chen, F. Wang, W. Liu and Y. Yuan, Nanoscale, 2020, 12, 17064-17073.
- 32 A. Li, X. Li, X. Yu, W. Li, R. Zhao, X. An, D. Cui, X. Chen and W. Li, Biomaterials, 2017, 112, 164-175.
- 33 J. Bai, X. Jia, Y. Ruan, C. Wang and X. Jiang, Inorg. Chem., 2018, 57, 10180-10188.
- 34 D. Yao, W. Xin, Z. Liu, Z. Wang, J. Feng, C. Dong, Y. Liu, B. Yang and H. Zhang, ACS Appl. Mater. Interfaces, 2017, 9, 9840-9848.
- 35 Q. Wang, K. Cui, J. Li, Y. Wu, Y. Yang, X. Zhou, G. Ma, Z. Yang, Z. Lei and S. Ren, Nanoscale, 2020, 12, 16208-16214.
- 36 Z. Zhou, W. Zhang, L. Zhang, Y. Cao, Z. Xu, Y. Kang and P. Xue, Biomater. Sci., 2020, 8, 5874-5887.
- 37 Q. Tian, M. Tang, Y. Sun, R. Zou, Z. Chen, M. Zhu, S. Yang, J. Wang, J. Wang and J. Hu, Adv. Mater., 2011, 23, 3542-3547.