

crystal, it is possible to limit cation mixing and hence increase the structural stability during cycling.¹⁴ For example, Zhang *et al.* discovered that Mg doping can increase the crystal lattice space, reduce the extent of cation mixing, and speed the transport of Li^+ , resulting in optimum electrochemical performance for the Mg-doped sample.¹⁵

Targeting the electrode/electrolyte interfacial problem, many efforts have been made in recent years. Surface modification is widely acknowledged as an effective means of stabilizing interfaces by acting like a protective layer between the electrolyte and the electrode, hence improving the cycling performance.^{16–22} For instance, Mo *et al.* investigated the influence of a TiO_2 nanolayer coating in NCM622, and the results indicate that the NCM622 with TiO_2 incorporation can deliver 96% capacity retention after 200 cycles, which is 18% high in comparison to that of the uncoated one. However, due to the ionic insulating properties, the TiO_2 -coated electrode displays a lower first discharge capacity and a first coulombic efficiency.¹⁶ As a result, the optimal surface modification layer must exhibit both a strong resistance to the electrolyte and an excellent lithium-ion conductivity. Li_3PO_4 has been effectively employed for modification of Ni-rich ternary cathode materials with a lithium-ion conductivity of $10^{-8} \text{ S cm}^{-1}$.^{23–26} For example, Li_3PO_4 -coated NCM622 exhibited noticeable improvement in cycling retention at a high cut-off voltage of 4.7 V,²⁴ and Jo *et al.* revealed that the Li_3PO_4 coating layers perform a variety of tasks, including water absorption in the electrolyte, reducing the HF level, facilitating Li^+ transport, and protecting the active material from electrolyte side reactions.²³

The above review implies that the doping element Mg can decrease cation mixing and enhance the structural stability of the host material, and the Li_3PO_4 surface coating layers can

alleviate the electrode/electrolyte interfacial problem. Inspired by this, in this work, we introduced Mg and Li_3PO_4 at the same time, aiming at maximizing their beneficial effects and improving the active material from the inside to the surface, using a simple one-step solid-phase synthesis method.

2. Experimental

2.1 Material synthesis

A hydroxide coprecipitation method was employed to synthesize the spherical precursor powder $\text{Ni}_{0.6}\text{Co}_{0.2}\text{Mn}_{0.2}(\text{OH})_2$ using NaOH and $\text{NH}_3\cdot\text{H}_2\text{O}$ as a precipitant and a chelating agent, respectively. Initially, 2 mol L^{-1} aqueous solutions of $\text{NiSO}_4\cdot 6\text{H}_2\text{O}$, $\text{CoSO}_4\cdot 6\text{H}_2\text{O}$, and $\text{MnSO}_4\cdot 7\text{H}_2\text{O}$ were made by dissolving stoichiometric amounts of each in deionized water. The aforesaid aqueous solutions, 4 mol L^{-1} sodium hydroxide, and the necessary amount of the $\text{NH}_3\cdot\text{H}_2\text{O}$ solution were all concurrently pumped into a tank reactor under a nitrogen atmosphere while being stirred constantly. Throughout the procedure, the temperature was maintained at $55 \text{ }^\circ\text{C}$ and the pH was maintained at approximately 11. Then, the precursor powder $\text{Ni}_{0.6}\text{Co}_{0.2}\text{Mn}_{0.2}(\text{OH})_2$ was collected after filtration, washed, and then dried. The pristine $\text{LiNi}_{0.6}\text{Co}_{0.2}\text{Mn}_{0.2}\text{O}_2$ was obtained by sintering the well-mixed hydroxide precursor powder and $\text{LiOH}\cdot\text{H}_2\text{O}$ powder (at a molar ratio of 1:1.05) at $500 \text{ }^\circ\text{C}$ for 3 h and then at $850 \text{ }^\circ\text{C}$ for 12 h under an oxygen flow.

The modified samples were obtained by thoroughly mixing the $\text{LiNi}_{0.6}\text{Co}_{0.2}\text{Mn}_{0.2}\text{O}_2$ powder with an appropriate amount of MgHPO_4 in mass ratios of 100:1, 100:2, and 100:5 and calcined at $600 \text{ }^\circ\text{C}$ for 5 h in air, and were labeled as LMR@MgHP-1, LMR@MgHP-2 and LMR@MgHP-5, respectively. For comparison,

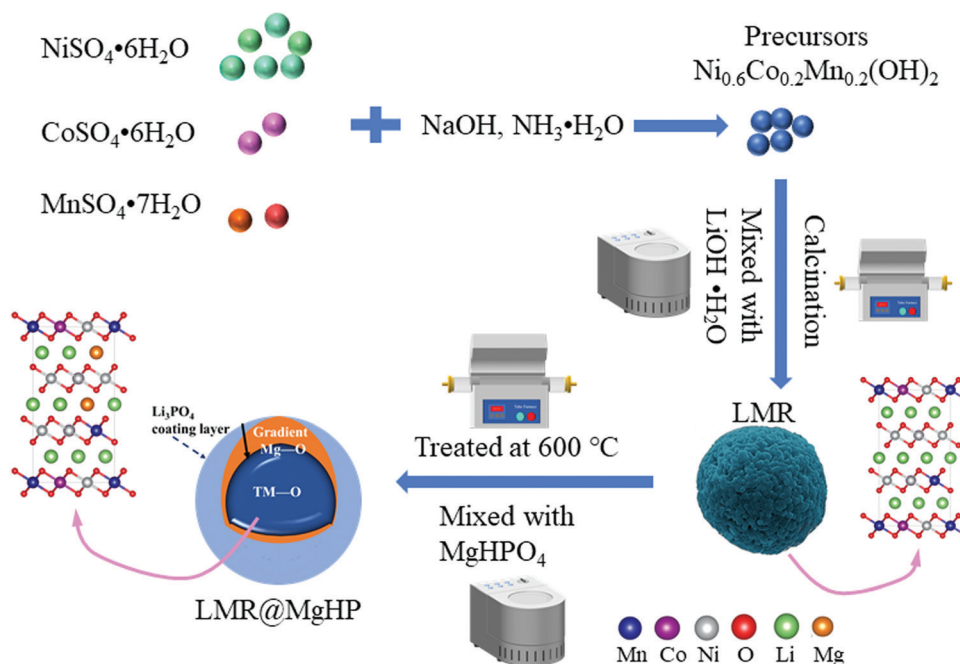


Fig. 1 Scheme of the preparation of LMR@MgHP.



the as-prepared $\text{LiNi}_{0.6}\text{Co}_{0.2}\text{Mn}_{0.2}\text{O}_2$ powder was also treated at $600\text{ }^\circ\text{C}$ for 5 h in the air (recorded as LMR). The schematic process of preparation is shown in Fig. 1.

2.2 Characterization of the material

To characterize the phase of all samples and to establish the lattice parameters of the structure, powder X-ray diffraction (XRD, Bruker D8 AVANCE) with Cu-K α radiation (40 KV, 40 mA) was utilized. The XRD data were obtained at a scanning rate of $0.02\text{ }^\circ\text{ s}^{-1}$ over a two-dimensional range of 10° – 100° and employing a count rate of 2 s. Scanning electron microscopy (SEM, INCA Pen-taFETx3) and transmission electron microscopy (TEM, JEOL JEM-2010F) were used to determine the morphology and size of the particles. The variations in atomic concentration as a function of the depth were detected using focused ion beam scanning electron microscopy (FIB-SEM, ZEISS Crossbeam 540). The surface chemical composition and element distribution of the specimens were ascertained using X-ray photoelectron spectroscopy (XPS, Thermo Scientific K-Alpha).

2.3 Electrochemical measurements

To make a typical positive electrode, a homogenous slurry was made by mixing carbon black, the active material, and a polyvinylidene fluoride binder in a weight ratio of 90:6:4, using the solvating agent *N*-methyl-2-pyrrolidone. After casting the slurry onto an Al foil current collector and drying it for 3 hours at $105\text{ }^\circ\text{C}$ in a vacuum oven, the dried foil was roll pressed. Finally, circular electrodes having a diameter of 12 mm were cut out from the coated Al foil and dried overnight at $105\text{ }^\circ\text{C}$ in a vacuum oven to get rid of oxygen and water, resulting in an active material loading density of approximately 2.1 mg cm^{-2} . To determine the electrochemical performance of the samples, CR2032 coin-type half-cells were constructed in an argon-filled glove box using 1 M LiPF_6 in ethylene carbonate/dimethyl carbonate (EC/DMC) (1:1 vol%). Using a constant-current procedure at $25\text{ }^\circ\text{C}$, the LANHE CT2001A instrument was utilized for characterizing the as-assembled half-cells over potential ranges of 2.8–4.3 V and 2.8–4.5 V. On the PGSTAT302N Electrochemical System, electrochemical impedance spectroscopy (EIS) and cyclic voltammogram (CV) tests were performed. The CV tests were conducted in a voltage window of 2.5–4.5 V vs. Li^+/Li at a scan rate of 0.1 mV s^{-1} , while the EIS programs were completed in the frequency range of 10 mHz–100 kHz.

3. Results and discussion

The XRD patterns of the LMR and MgHPO_4 modified specimens are presented in Fig. 2 and Fig. S1 (ESI †). All of the patterns have a strong correlation to the conventional layered hexagonal α - NaFeO_2 structure with the $R\bar{3}m$ space group (PDF# 85-1969). The creation of a well-ordered layer structure is suggested by the distinct splitting of the (108)/(110) and (006)/(102) peaks of all the samples. However, it should be noted that, for the LMR@MgHP-5 pattern, some mild diffraction peaks at roughly

$2\theta = 20$ – 30° corresponding to the (110) and (101) planes in Li_3PO_4 (PDF# 25-1030) may be detected, which are generated during the calcination reaction between MgHPO_4 and the surficial residual lithium. Meanwhile, no additional diffraction peaks can be observed for LMR@MgHP-1 and LMR@MgHP-2, which is likely due to the amount of Li_3PO_4 being too small to be detected.

The data were refined using the Rietveld method to further study the crystal structures of the samples. To identify the location of Mg ions in the lattice of the LMR@MgHP samples, four different possible structural models, *i.e.*, without Mg occupation, Mg occupying at the Li site, Mg occupying at the TM site, and Mg simultaneously occupying at both Li and TM sites, were considered during the Rietveld refinements of the XRD patterns. The results are listed in Tables S1–S3 (ESI †). It is observed that the *R*-factors reach the lowest value only if the Mg cations occupy the octahedral sites of the Li layer, which indicates that the Li-site doping of Mg is the most reliable model to describe the structure. This result is in line with the results of first-principles calculations for Mg-doped Ni-rich cathode materials.²⁷ The XRD refinement results based on the Li-site model are summarized in Table 1. The computed pattern primarily fell in the $R\bar{3}m$ structural type of α - NaFeO_2 , which has lithium on three ‘a’ sites, transition metal atoms on three ‘b’ sites, and oxygen on six ‘c’ sites. The weight profiled *R* factor, R_{wp} , the confidence factor, and the goodness of fit (GOF) are also summarized. It is worth noting that the reasonably small R_{wp} demonstrates the high accuracy of the proposed structural model. Furthermore, the calculated curves are a good fit for the experimental patterns, which shows that the refinement results are both reliable and acceptable. From the calculated results, it can be observed that the overall structure of the LMR material is influenced by the reaction with MgHPO_4 .

To examine the degree of cation mixing for the specimens, the integrated intensity ratio of $I(003)/I(104)$ is regarded as a sensitive parameter that reveals the most significant changes of the degree of cation mixing.²⁸ As the ionic radius of Ni^{2+} is similar to that of Li^+ , the degree of cation mixing can also be calculated based on the assumption that Ni^{2+} migrates to Li sites.²⁹ From the results, we can conclude that LMR@MgHP-2 displays a superior and more stable structure than LMR. For example, the intensity value of $I(003)/I(104)$ for the LMR@MgHP-2 sample is 1.37 which is higher than that for LMR (1.19), and the value of cation mixing for the LMR@MgHP-2 sample (1.85) is lower than that for LMR (4.04). Besides, the lattice parameter *c* is slightly increased, resulting in a greater *c/a* ratio. We have reason to think that Mg has a greater probability to dope into the bulk $\text{LiNi}_{0.6}\text{Co}_{0.2}\text{Mn}_{0.2}\text{O}_2$ material based on the alterations within the lattice constants before and after MgHPO_4 modification.¹² The enhanced lattice parameters and decreased degree of cation mixing are produced by substituting the Mg^{2+} cation in an attempt to stabilize the framework. Additionally, Liu investigated the effect of TiO_2 coating and Ti doping on the structural characteristics of the material based on



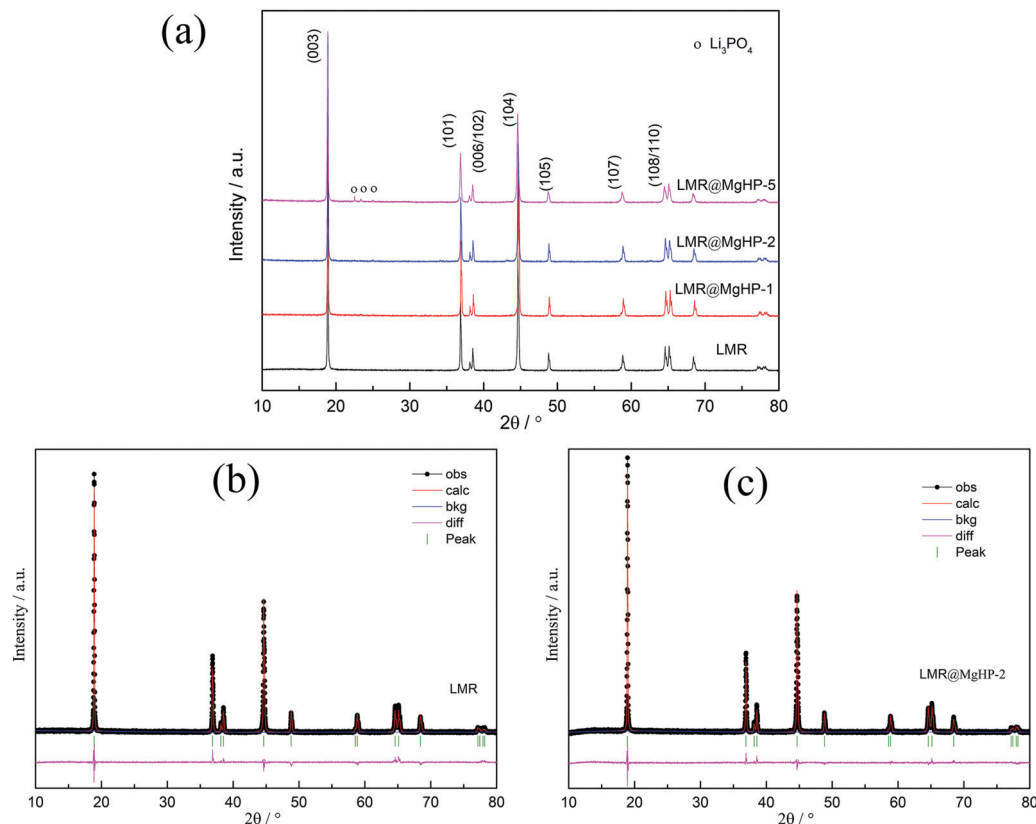


Fig. 2 (a) XRD patterns of all the samples. Rietveld refinements of the XRD patterns of (b) LMR and (c) LMR@MgHP-2.

Table 1 Rietveld analysis results of the specimens

| Sample | Lattice parameters | | $I_{(003)}/I_{(104)}$ | Cation mixing (%) | χ^2 | GOF | R_{wp} (%) |
|------------|--------------------|----------|-----------------------|-------------------|----------|------|--------------|
| | a (Å) | c (Å) | | | | | |
| LMR | 2.86184 | 14.19684 | 1.19 | 4.04 | 1.52 | 1.23 | 8.37 |
| LMR@MgHP-1 | 2.86785 | 14.21004 | 1.21 | 3.04 | 1.36 | 1.16 | 7.87 |
| LMR@MgHP-2 | 2.86842 | 14.21526 | 1.37 | 1.85 | 1.62 | 1.27 | 8.59 |
| LMR@MgHP-5 | 2.86888 | 14.21541 | 1.26 | 1.42 | 1.7 | 1.3 | 8.79 |

$\text{LiNi}_{0.8}\text{Co}_{0.2}\text{O}_2$ and discovered that the coating alone was incapable of modifying the crystal characteristics.³⁰

Fig. 3 illustrates the morphologies of the LMR and LMR@MgHP-2 samples. Both LMR and LMR@MgHP-2 exhibit spherical particles having a diameter of approximately 10 μm aggregated with densely packed primary particles having a diameter of around 500 nm, indicating that the modification procedure does not significantly alter the shape of the pristine material. In terms of the primary particles, the bare LMR exhibits a smooth and clear surface, while the LMR@MgHP-2 sample bears many spots and is slightly rough. As shown in Fig. 3c and f, the surface of the LMR particle does not have any additional layer and the lattice fringes with a crystal plane spacing of 0.246 nm are in accordance with the (101) plane of $\text{LiNi}_{0.6}\text{Co}_{0.2}\text{Mn}_{0.2}\text{O}_2$. In contrast, LMR@MgHP-2 exhibits a homogeneous surface coating layer with a thickness below 10 nm. Some ambiguous lattice fringes of 0.399 nm which

are due to the (110) plane of Li_3PO_4 are detected in the coating layer. This indicates that the coating layer is partially crystallized Li_3PO_4 , which is consistent with the XRD results. Furthermore, EDX elemental mapping of LMR@MgHP-2 (Fig. 3g) verifies that the Ni, Co, Mn, Mg, and P elements are homogeneously distributed on the cathode particle and the atomic contents of all the elements are close to the stoichiometric value (Table. S1, ESI[†]). Additionally, as shown in the linear FIB-SEM scanning result (Fig. S2, ESI[†]), the variations in the atomic concentration of the Mg element as a function of the depth indicate that some Mg element can still be detected at 0.8 μm depth. Thus, combined with the TEM result (Fig. 3f), this implies that the Mg element should be doped into the bulk material.

In an attempt to probe into the Mg and P distributions and the metal ion chemical valence state, X-ray photoelectron spectroscopy (XPS) was carried out, as depicted in Fig. 4 and



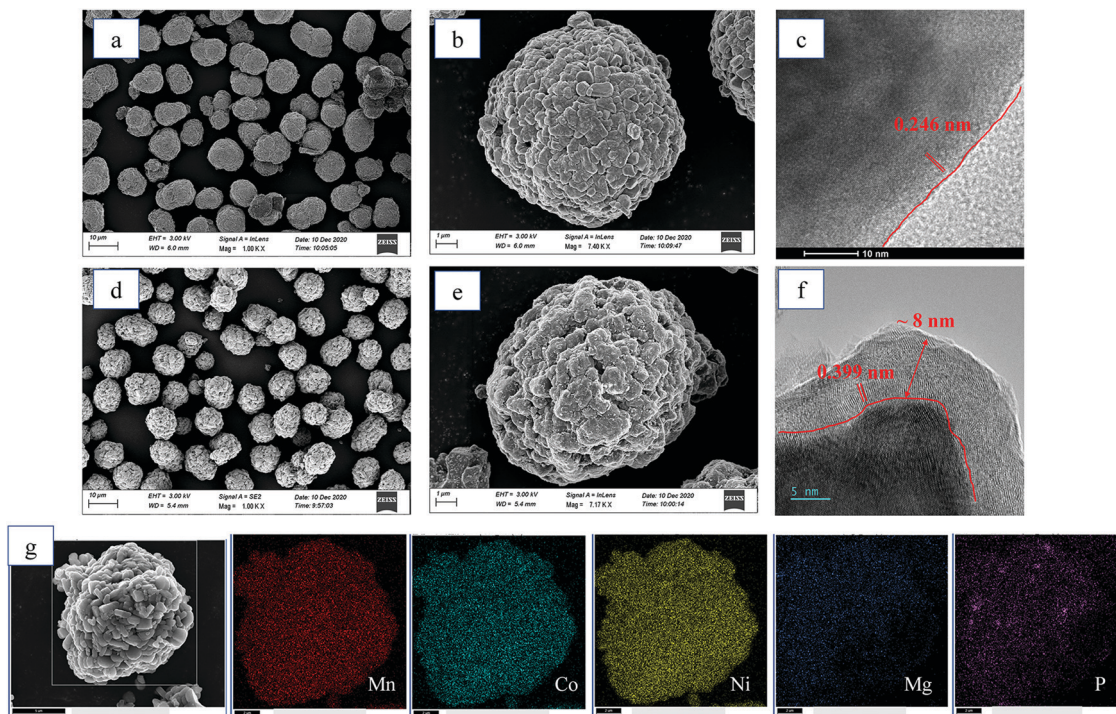


Fig. 3 SEM images of (a and b) LMR and (d and e) LMR@MgHP-2. HRTEM images of (c) LMR and (f) LMR@MgHP-2. (g) EDX elemental mapping of LMR@MgHP-2.

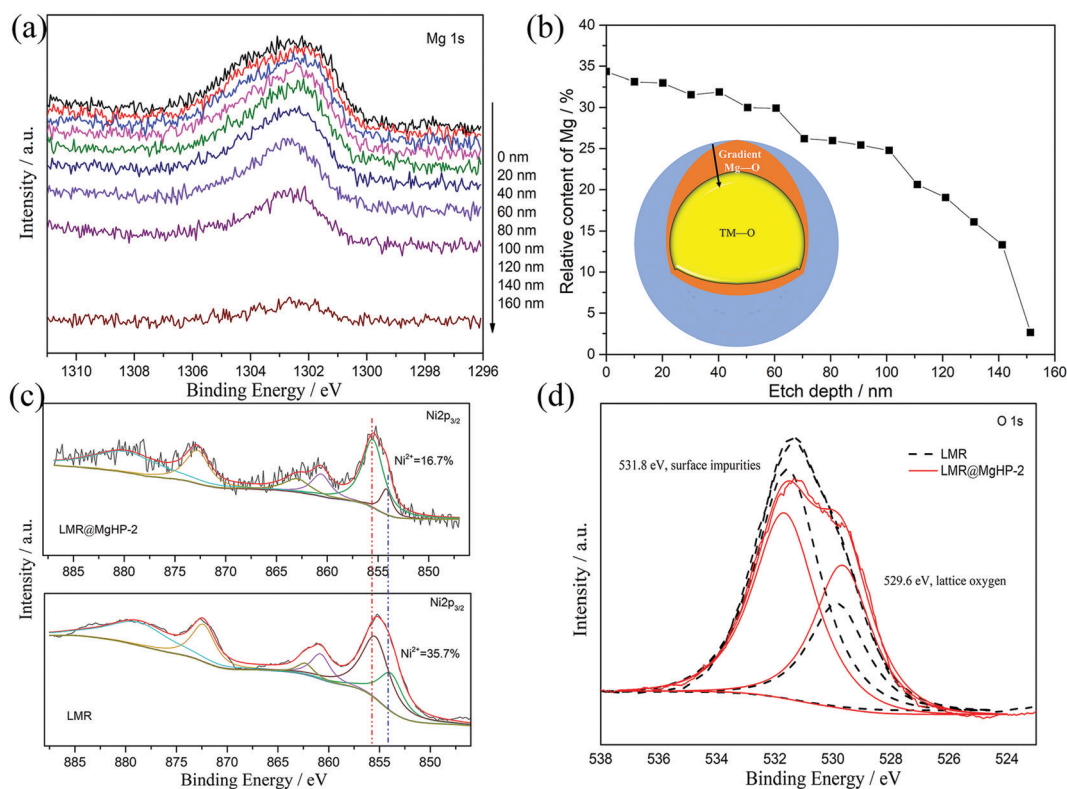


Fig. 4 XPS depth profiles of Mg 1s for LMR@MgHP-2. (b) Relative content percentages of Mg at different etching levels based on (a). (c) Ni 2p and (d) O 1s spectra for the LMR and LMR@MgHP-2 samples.



Fig. S3 (ESI[†]). Fig. 4a displays the XPS depth profiles of Mg for the LMR@MgHP-2 sample. Accordingly, with the increased etching depth, the Mg 1s can still be measured even at 140 nm. The Mg concentration as a function of the etching depth based on Fig. 4a is shown in Fig. 4b. The relative content of Mg reduces steadily from the surface (33.7%) up to 150 nm depth (2.7%), thereby manifesting the distribution gradient of the Mg element. Combining the TEM results (Fig. 3f), the coating layer is only 8 nm, thus demonstrating that Mg²⁺ has been successfully doped into LMR. The XPS spectra at a binding energy of 132.97 eV in P 2p could be summarized as the characteristic of tetrahedral (PO₄)-groups from the Li₃PO₄ coating layer (Fig. S3, ESI[†]). The Ni 2p peaks of LMR and LMR@MgHP-2 on the surface are compared in Fig. 4c. Ni 2p_{3/2} can be identified as a pair of peaks at binding energies of 854.1 eV and 855.4 eV, respectively known as Ni²⁺ and Ni³⁺. Accordingly, the LMR@MgHP-2 sample possesses slightly higher Ni³⁺/Ni²⁺ than LMR. A higher ratio of Ni³⁺/Ni²⁺ means less Ni²⁺ on the surface and consequently reduced Li/Ni cation mixing and decreased activation energy for Li⁺ extraction/insertion.^{31,32} In terms of the Co 2p_{3/2} and Mn 2p_{3/2} peaks, there is no apparent difference observed, illustrating that the chemical environments of Co³⁺ and Mn²⁺ in the structure have not changed. In addition, in the sample LMR@MgHP-2, the XPS peak intensity of metals is lower than that in LMR, which indirectly reflects the existence of a coating layer on the surface of the sample.

Fig. 4d compares the O 1s XPS of the LMR and LMR@MgHP-2 samples. Both samples are segregated into two peaks at bonding energies of 529.6 eV and 531.8 eV, respectively,

corresponding to the lattice oxygen in the crystalline network and the surface oxygen-containing impurities (residual lithium compounds LiOH and Li₂CO₃).^{33,34} Notably, the intensity of the surface oxygen peak of LMR@MgHP-2 is smaller than that of LMR, demonstrating a lower concentration of residual lithium-based molecules on the surface of LMR@MgHP-2. This can be attributed to the consumption of residual lithium during the generation of the Li₃PO₄ coating. The metal–oxygen peak in the LMR@MgHP-2 specimen undergoes a slight increase in terms of its intensity in comparison with that of LMR, which can be explained by the introduction of Mg–O. Thus the XPS results indicate that during the reaction with MgHPO₄ the surface residual lithium compounds could be consumed and converted to Li₃PO₄ as a coating layer and the element Mg could gradually dope into the crystalline network.

The LMR and modified cathode samples were tested for their electrochemical performance between 2.8 and 4.3 V at 25 °C. The initial charge/discharge profiles of all the samples at 0.1C are shown in Fig. S4 (ESI[†]). The identical charge and discharge curves are displayed by all the cathodes and there is no additional plateau present in the modified specimens, thereby indicating the non-involvement of Mg in the electrode reaction. LMR, LMR@MgHP-1, LMR@MgHP-2, and LMR@MgHP-5 samples respectively manifest the initial discharge capacities of 176.9 mA h g⁻¹, 179.3 mA h g⁻¹, 188.5 mA h g⁻¹, and 169.8 mA h g⁻¹ at 0.1C, having initial coulombic efficiencies of 82.1%, 87.0%, 88.3%, and 88.8%. A slightly higher initial coulombic efficiency is observed for all the modified specimens in comparison with the pristine one.

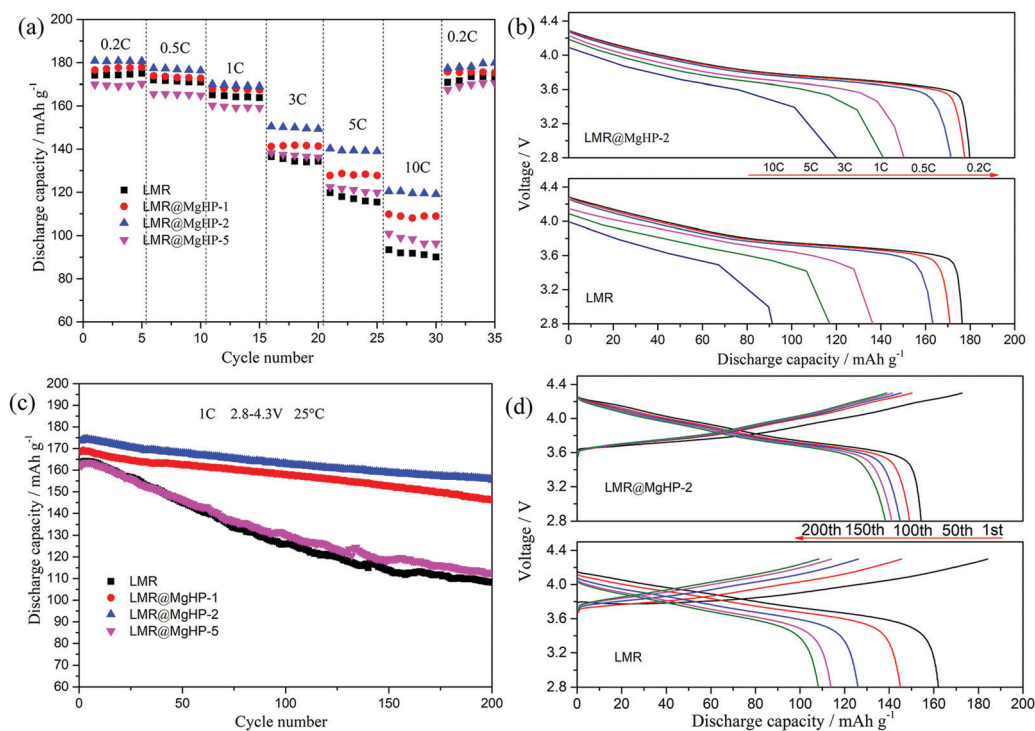


Fig. 5 (a) Rate performance of all the samples between 2.8 and 4.3 V. (b) Initial discharge plots of LMR and LMR@MgHP-2 at various rates. (c) Cycling performance of all the samples at 1C between 2.8 and 4.3 V. (d) Charge–discharge plots of LMR and LMR@MgHP-2 at 1C.



This phenomenon can be attributed to the presence of the gradient doped Mg^{2+} and lithium-ion conductive Li_3PO_4 coating layer which potentially aids in the lithium ion transport at the electrode/electrolyte interface, thereby stabilizing the bulk structure.

The rate performance of all the cathode specimens is depicted in Fig. 5a. As can be shown, as the current density increases from 0.2C to 10C, the discharge capacities of the modified samples LMR@MgHP-1 and LMR@MgHP-2 are larger than those of LMR. For example, the specific capacities for the LMR@MgHP-2 cathode are $140.3 \text{ mA h g}^{-1}$ and $119.4 \text{ mA h g}^{-1}$ at 5C and 10C, while those are $119.8 \text{ mA h g}^{-1}$ and 92.5 mA h g^{-1} for LMR, respectively. Interestingly, the discharge capacity of LMR@MgHP-5 is lower than that of the pristine LMR at a low current rate, which could be ascribed to an excessive introduction of the inactive material MgHPO_4 causing a reduction of the active material; however, with an increase in the current density, LMR@MgHP-5 displays a slightly higher capacity than LMR. This occurrence also shows that the twofold modification of MgHPO_4 can help in improving the rate capability of cathode materials. The charge/discharge curves of LMR and LMR@MgHP-2 at various C-rates are shown in Fig. 5b. The working voltage deterioration and the capacity decay of LMR are much more severe than those of LMR@MgHP-2. These findings suggest that the dual alteration of electrodes with MgHPO_4 could improve the structural stability and rate capability.

Dual modification of LMR by MgHPO_4 could also significantly improve the cyclability of the cathode (Fig. 5c and d). After 200 cycles at 1C, the reversible capacity retention rates of LMR, LMR@MgHP-1, LMR@MgHP-2, and LMR@MgHP-5 are 66.3%, 86.77%, 89.57%, and 69.4%, respectively. The initial discharge capacity and the capacity retention of the LMR@MgHP-2 sample appear to be higher than those of the others, and far superior to any Mg-doped $\text{LiNi}_{0.6}\text{Co}_{0.2}\text{Mn}_{0.2}\text{O}_2$ cathode previously reported.^{12,15,23,24} The charge–discharge curves of different cycles for LMR and LMR@MgHP-2 are shown in Fig. 5d. As a result, the discharge capacity and the average voltage of the pure LMR rapidly decrease (Fig. S5, ESI[†]). The LMR@MgHP-2 sample, on the other hand, shows negligible alterations. These findings show that Mg^{2+} gradient doping and Li_3PO_4 coating generated by the MgHPO_4 reaction can significantly increase the cycling performance and reduce voltage fading for the LMR electrode.

The cyclic voltammetry (CV) of LMR and LMR@MgHP-2 materials was carried out during the first cycle between 2.5 and 4.5 V using a scan rate of 0.1 mV s^{-1} to further study the effects of the MgHPO_4 dual alteration on electrochemical irreversibility. The CV curves of the two samples had only a pair of prominent redox peaks, as shown in Fig. 6a, which correspond to the oxidation–reduction reaction of $\text{Ni}^{2+}/\text{Ni}^{4+}$. During the charging process, the oxidation of Ni^{2+} to Ni^{4+} is followed by the release of Li^+ , resulting in an oxidation peak at around 3.9 V. According to the process of conversion of Ni^{4+} to

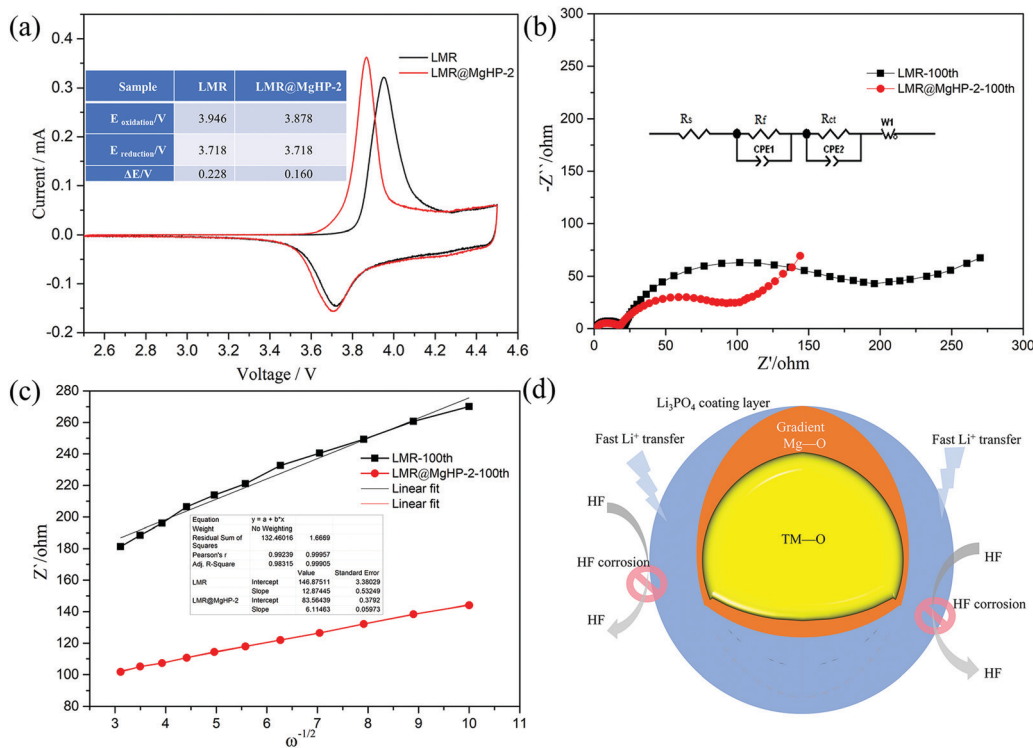


Fig. 6 (a) Cyclic voltammetry of the LMR and LMR@MgHP-2 samples for the first cycle between 2.5 and 4.5 V. (b) Nyquist plots of LMR and LMR@MgHP-2 after 100 cycles at a discharged state of 4.3 V. (c) The relationship between Z' and $\omega^{-1/2}$ based on (b). (d) Scheme of the dual function by MgHPO_4 modification.



Table 2 The values of R_f , R_{ct} and D_{Li^+} for cycled electrodes

| Sample | R_s/Ω | R_{sei}/Ω | R_{ct}/Ω | $\sigma/\Omega\text{ cm}^2\text{ s}^{0.5}$ | $D_{Li^+}/\text{cm}^2\text{ s}^{-1}$ |
|------------|--------------|------------------|-----------------|--|--------------------------------------|
| LMR | 2.15 | 21.39 | 179.06 | 12.87 | 8.36×10^{-11} |
| LMR@MgHP-2 | 2.02 | 18.04 | 90.63 | 6.11 | 1.76×10^{-10} |

Ni^{2+} and Li^+ insertion back into the layered material, the decreased peak comes at around 3.7 V. The electrochemical polarization and cycle reversibility of the electrode materials are generally attributed to the voltage interval between the oxidation and reduction peaks (ΔE).³⁵ For the first cycle, ΔE of LMR@MgHP-2 is 0.160 V, which is slightly lower than that of LMR (0.228 V), showing that LMR@MgHP-2 has less electrochemical polarization, better reversibility, and hence greater electrochemical performance.

Electrochemical impedance spectra (EIS) experiments after 100 cycles at 1C with a charged state of 4.3 V were used to study the internal reaction kinetics of the electrode/electrolyte interface. The Nyquist plots in Fig. 6b reveal two semicircles at a high/medium frequency and an oblique line at a low frequency, corresponding to the impedance of a solid–electrolyte interphase film (R_{sei}), the charge-transfer resistance (R_{ct}), and the Warburg diffusion impedance for lithium ions (Z_w). R_s is related to the solution resistance. The example plots are fitted using the analogous circuit, and the fitted results are presented in Table 2. The R_{sei} value of LMR@MgHP-2 (18.04 Ω) is slightly lower than that of LMR (21.39 Ω), indicating that LMR@MgHP-2 has a relatively stable solid–electrolyte interphase film in the presence of the Li_3PO_4 coating layer. After 100 cycles, the R_{ct} value for the LMR@MgHP-2 sample is 90.63 Ω . The R_{ct} value for

LMR, on the other hand, is 179.06 Ω , which is significantly greater than the value of the modified sample LMR@MgHP-2. In general, the decreased R_{sei} and R_{ct} values for LMR@MgHP-2 indicate enhanced bulk and surface stability following MgHPO_4 dual alteration (Fig. 6d). Furthermore, the diffusion coefficient of lithium ions (D_{Li^+}) is calculated according to the equations.³⁶ As shown in Fig. 6c and Table 2, the LMR@MgHP-2 sample exhibits a lower D_{Li^+} than LMR. Thus, according to the EIS tests, the LMR@MgHP-2 sample could lead to lower R_{sei} and R_{ct} values, and a higher D_{Li^+} , which agrees quite well with the rate performance and CV analysis.

A comparison of the cycling performance of the LMR and LMR@MgHP-2 cathodes at 3C in a high cut-off voltage range of 2.8–4.5 V is further represented in Fig. 7a and b. As a result, as the number of cycles increases, the discharge capacity and initial discharge voltage of the LMR sample suddenly fall. After 100 cycles, the LMR sample delivers a sharp capacity change from 160.5 to 92.5 mA h g^{-1} , with a capacity retention of 57.63%. While the LMR@MgHP-2 sample displays a slow decrease from 172.7 to 136.5 mA h g^{-1} , with a capacity retention of 79.03%. Even though the cut-off voltage is high, it appears that the modified specimen has substantially better cycling performance in comparison to the pristine cathode. Under a high cut-off voltage, there is a high probability that electrolyte decomposition might take place, and the electrolyte is more likely to react with the delithiated metal ions, which is recorded as a side reaction between the electrode/electrolyte interface and is the main cause of the structural damage and capacity decay.^{37–39} According to the results, the cycling performance of the LMR@MgHP-2 sample is still excellent,

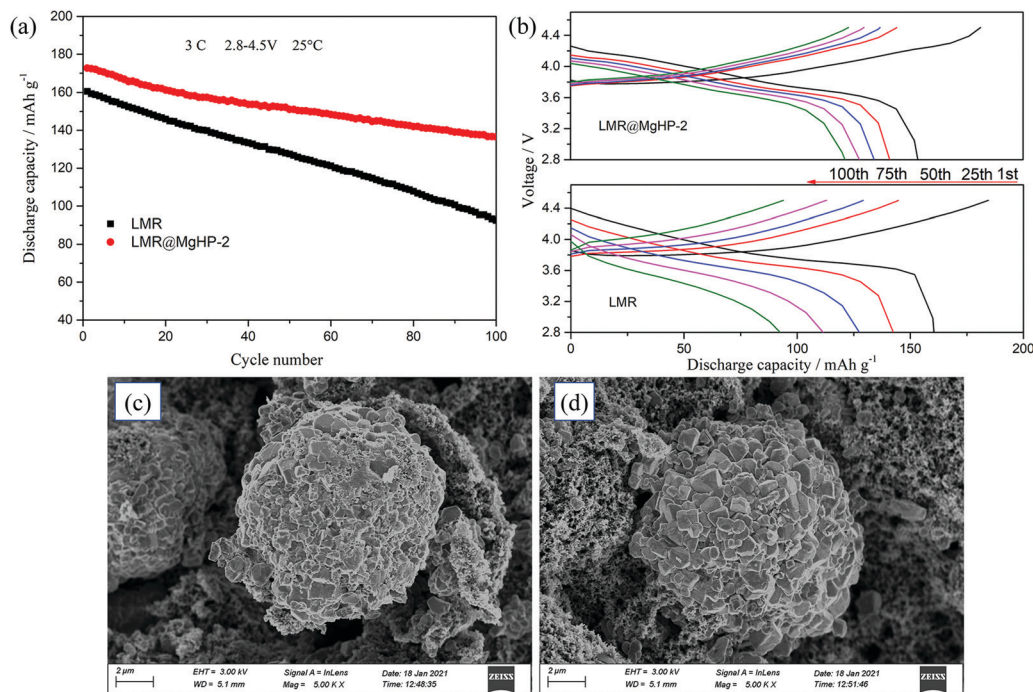


Fig. 7 (a) Cycling performance and (b) the corresponding charge–discharge profiles of LMR and LMR@MgHP-2 at a 3C rate between 2.8 and 4.5 V. The SEM images of (c) the LMR and (d) LMR@MgHP-2 cathodes after 100 cycles.



