



Materials Horizons

Tailoring the Multistability of Origami-Inspired, Buckled Magnetic Structures via Compression and Creasing

Journal:	<i>Materials Horizons</i>
Manuscript ID	MH-COM-07-2021-001152.R1
Article Type:	Communication
Date Submitted by the Author:	23-Aug-2021
Complete List of Authors:	Li, Yi; University of Connecticut, Materials Science and Engineering Avis, Samuel; Durham University, Department of Physics Kusumaatmaja, Halim; Durham University, Department of Physics Zhang, Teng; Syracuse University, Mechanical and Aerospace Engineering Wang, Xueju; University of Connecticut, Materials Science and Engineering

SCHOLARONE™
Manuscripts

An outstanding challenge in the field of origami-inspired multistable structures is to actively control the number of possible stable states and their reconfiguration paths. In this work, we present an integrated experimental and computational study on how they can be systematically tailored and controlled via two effective and easy-to-control parameters, creasing and compressive strains. Computationally, we construct a detailed design phase diagram for a representative ribbon structure showing how the number of stable states can be reversibly varied. Furthermore, we predict the non-linear reconfiguration paths and their corresponding energy barriers to transition between stable states. Experimentally, we realize origami-inspired structures composed of ferromagnetic composite thin films under various creasing and compressive strain conditions, where fast, remote reconfigurations are achieved using a portable magnet. The computational and experimental results are in excellent agreement. We believe the new insights generated from our work are valuable for diverse applications exploiting origami-inspired structures. For instance, here we design and demonstrate programmable structure arrays, biomimetic insect flexion, and an origami robot that can be actuated by remote magnetic forces.

Title: Tailoring the Multistability of Origami-Inspired, Buckled Magnetic Structures via Compression and Creasing

Yi Li¹, Samuel J. Avis¹, Teng Zhang, Halim Kusumaatmaja*, Xueju Wang**

[*] Prof. Xueju Wang, corresponding author
Department of Materials Science and Engineering, Institute of Materials Science,
University of Connecticut,
Storrs, CT 06269, USA
Email: xueju.wang@uconn.edu

[*] Prof. Halim Kusumaatmaja, corresponding author
Department of Physics,
Durham University,
Durham, DH1 3LE, England
Email: halim.kusumaatmaja@durham.ac.uk

[*] Prof. Teng Zhang, corresponding author
Department of Mechanical and Aerospace Engineering, BioInspired Syracuse
Syracuse University,
Syracuse, NY, 13244, USA
Email: tzhang48@syr.edu

Yi Li
Department of Materials Science and Engineering,
University of Connecticut,
Storrs, CT 06269, USA

Samuel J. Avis
Department of Physics,
Durham University,
Durham, DH1 3LE, England

¹These authors contributed equally to this work.

Keywords: Origami-inspired structures, Multistability, Creasing, Magnetic actuation, Energy landscape

Abstract

Origami-inspired multistable structures are gaining increasing interest because of their potential applications in fields ranging from deployable structures to reconfigurable microelectronics. The multistability of such structures is critical for their applications but is challenging to manipulate due to the highly nonlinear deformations and complex configurations of the structures. Here, a comprehensive experimental and computational study is reported to tailor the multistable states of origami-inspired, buckled ferromagnetic structures and their reconfiguration paths. Using ribbon structures as an example, a design phase diagram is constructed as a function of the crease number and compressive strain. As the crease number increases from 0 to 7, the number of distinct stable states first increases and then decreases. The multistability is also shown to be actively tuned by varying the strain from 0% to 40%. Furthermore, analyzing energy barriers for reconfiguration among the stable states reveals dynamic changes in reconfiguration paths with increasing strain. Guided by studies above, diverse examples are designed and demonstrated, from programmable structure arrays to a soft robot. These studies lay out the foundation for the rational design of functional, multistable structures.

1. Introduction

Origami, the ancient art of folding two-dimensional (2D) thin sheets along predefined creases to create three-dimensional (3D) objects,¹⁻³ has inspired the design of many engineering structures for a wide range of applications, including deployable systems,⁴⁻⁶ self-folding machines,⁷ reconfigurable metamaterials,⁸⁻¹⁰ and DNA origami.¹¹ For those applications, a key design feature of the structures is their ability to have multiple stable states as well as the tailoring of those states for tunability and adaptability. Existing works so far have primarily focused on bistable systems for rigid origami patterns (like the Miura folding¹² and its derivatives¹³) and deformable origami (like the twisted square pattern¹⁴). For example, Sadeghi and Li realized rapid and reversible folding by harnessing the asymmetric bistability of designed origami structures¹⁵. Liu et al. demonstrated that a folded hyperorigami, obtained by folding a piece of paper along concentric squares and their diagonals to arrive at a seemingly smooth saddle shape, exhibits bistability between two symmetric configurations.¹⁶ More recently, Melancon et al. realized pressure-deployable origami structures characterized by two stable configurations — one compact and one expanded — at the meter scale.⁵ Furthermore, Fang et al. showed that the potential energy landscapes of stacked Miura-ori and the Kresling-ori structures, and therefore their stability profiles and constitutive force–displacement relations, can be effectively tuned by embedded magnets¹⁷.

In addition to multistability, reconfiguration among the different stable states of origami-inspired structures in a well-controlled manner is demanded in many engineering devices and structures. Theoretical and experimental studies have been performed on reconfiguration paths in origami-inspired structures. For example, Zhai et al. created an origami-inspired mechanical metamaterial that can be deployed and collapsed along different configuration paths.¹⁸ Silverberg et al. showed that hidden degrees of freedom in square twist origami structures give rise to a critical transition from mono- to bi-stability.¹⁴ Moreover, significant advances have been made to improve the tunability and adaptability of origami-inspired structures by

incorporating stimuli-responsive materials, such as shape memory polymers,¹⁹⁻²² hydrogels,^{23,} liquid crystal elastomers,^{25, 26} and magnetic composites,²⁷ into origami-inspired structures to achieve self-folding and on-demand shape morphing under external actuations (i.e., variations in temperature, light, pH, and magnetic fields). Such self-actuating materials have also enabled the assembly of origami structures at the microscale to provide opportunities for micro robotics, biomedical devices, and many others.²⁸⁻³²

Previous studies have laid solid foundations for the design and development of origami-inspired structures with bistability and tunability. One of the remaining challenges in the field of origami-inspired multistable structures is to actively control the number of possible stable states and their reconfiguration paths. Here, we demonstrate how the multistability of origami-inspired structures that are buckled from ferromagnetic composite thin films^{19, 33} can be tailored via creasing and compressive strains. Ribbon structures are chosen as an example for the study because of their very rich nonlinear buckling behavior while having a simple geometry and their potential as basic building blocks for more complicated structures, thus providing an ideal platform to explore our design strategy. The two key control parameters, compression strains and creasing in the ribbon, are selected because they are easy to tune and very effective to alter the multistable behaviors of the structure for real applications. In this work, the experiments are thoroughly complemented with systematic simulations. A computationally efficient discrete shell model,^{34, 35} which is used to simulate non-linear deformations in thin films, is combined with a random search algorithm for energy minimization³⁶⁻³⁸ to construct phase diagrams showing how the available stable states sensitively depend on the compressive assembly strain and the creases of structures. The predictions from the phase diagram are experimentally verified for cases at a representative constant strain (15%) and varying crease numbers, as well as those at a given crease number (3 creases) and varying strains. In addition, reconfiguration paths between the stable states are identified using energy landscape exploration algorithms,^{39,} where the transition states connecting the minima are first located with a double-ended search⁴⁰

method, then the full pathways are computed using the downhill routes to each stable state. Our approach allows the computation of reconfiguration paths with the lowest energy barriers systematically without the need to assume a predefined path for structure morphing.⁴¹ Fast, remote reconfigurations among the multistable states of the ferromagnetic structures are performed experimentally with a portable magnet, the pathways of which are shown to be consistent with those from computational predictions. Finally, guided by tightly integrated numerical and experimental analysis, we demonstrate diverse complex origami-inspired structures, including structure arrays that can display various patterns based on the multistability of the structural unit, a biomimetic insect, and a soft robot.

2. Results and Discussions

2.1 Concept of origami-inspired, multistable 3D magnetic structures

Figure 1 schematically illustrates the assembly process and reconfiguration of origami-inspired structures compressively buckled from ferromagnetic composites.^{19, 42, 43} Ferromagnetic composites are used as the constitutional material of the origami-inspired structures in this study to enable fast, remote reconfiguration among their multistable states.⁴⁴⁻⁴⁶ The scheme begins with the fabrication of soft ferromagnetic composite films (130 μm thick) made from polydimethylsiloxane (PDMS) embedded with magnetic NdFeB (neodymium-iron-boron) microparticles (~ 5 μm in diameter). Laser patterning (VLS 2.30, University Laser System, Norman, OK) of the film defines the geometry and the crease of the 2D precursor with a thickness ratio of 46.15% between the crease- and non-crease regions. The location of the crease region and the reduced thickness of the corresponding segments (2.5 mm of unit length) determine the location of hinges that affect potential multistable reconfigurations.⁴⁷ To assemble origami-inspired structures, the 2D precursor is laminated onto a pre-stretched silicone elastomer substrate (Dragon skin; Smooth-on, Easton, PA), followed by the release of the pre-strain to geometrically transform the 2D precursor into the corresponding 3D structure.

Under an external magnetic field generated by a manually manipulative magnet, the assembled origami-inspired structure can be reconfigured into up to four distinct stable states: state 1 (S1, one center peak), state 2 (S2, one side peak), state 3 (S3, two peaks), and state 4 (S4, twisted two peaks). Remarkably, due to their mechanical stability, the reconfigured states remain stable after the removal of the applied magnetic field.

2.2 Phase diagram of multistable states of magnetically reconfigurable, origami-inspired structures

We first study the effect of two essential parameters, the number of creases and compressive strains, on the number and configurations of stable states by using a ribbon structure as an example. A phase diagram, indicating the stable states of the structure with up to seven creases and at strain levels of 0%-40%, is shown in **Figure 2A** and serves as a theoretical foundation for the multistability design. The phase diagram is constructed computationally by identifying the local minima in the energy landscape of the structure under various conditions of strain levels and crease numbers. To obtain these minima, we use a discrete model combined with a random search algorithm for energy minimization (see the Experimental Section for full details). The discrete model has been widely used to simulate non-linear deformation in thin films and shells, and it has been shown to be in good agreement with more accurate but computationally more expensive finite element method^{39, 48}. In our computational strategy, at selected points (typically 5 different strain levels for each crease number) across the phase diagram, the structure is randomly initialized several hundreds of times, after which it is relaxed to the minima. Once the qualitatively distinct configurations are identified, we systematically vary the compressive strain to observe the full range over which each state is stable. It is worth noting that while it is difficult to guarantee that all possible stable states are obtained, we do not find additional states when more points in the phase diagram are sampled. Hence, we consider the identified stable states to be representative in this study.

As shown in **Figure 2A**, the number of creases (n_{crease}) has notable effects on the number and configurations of stable states. To better illustrate this point, we demonstrate the available states of structures as n_{crease} is increased from 0 to 7 under a constant compressive strain of 15% in **Figure 2B**, with the computational and experimental results shown side by side. When the n_{crease} is zero, i.e., the continuous ribbon structure, only S1 (one center peak) exists at all strain levels (e.g., point i). An additional asymmetric state S2 becomes available when n_{crease} rises to two at a compressive strain of 15% (point ii). A further increase to three creases causes the structure to admit state S3 (two peaks) at a strain of 15% (point iii) and S4 (twisted two peaks) at a higher strain level. As n_{crease} increases above three, the number of stable states begins to decline, with S2 becoming unstable for structures with four creases (point iv). For structures with five creases and above, only S1 remains stable at a compressive strain of 15%, although S3 is still stable under lower strains for $n_{\text{crease}}=5$ and 6. This can be expected because we are approaching the continuous case when the number of creases is large.

The available stable states also depend strongly on the magnitude of the applied compressive strain used in the assembly process of the structure. We illustrate this using a structure with three creases due to its rich phenomena that will be discussed in the following. Based on the number and configurations of stable states, five regimes are identified: a) two distinct stable states (S1 and S2; 0-10% strain), b) three distinct stable states (S1, S2, and S3; 10-17% strain), c) two distinct stable states (S1 and S3; 17-19% strain), d) three distinct stable states (S1, S3, and S4; 19-30% strain), and e) two distinct stable states (S1 and S4; 30-40% strain). **Figure 2C** shows experimental and computational results of distinct stable states at representative strain levels for the five regimes. Under a relatively low compressive strain of 8% (point vi), states S1 (one center peak) and S2 (one side peak) exist, which can be reversibly reconfigured into each other via manually controlling the magnetic force and direction. Increasing the strain to 15% (point iii) leads to the appearance of a third state, S3 with two peaks, which increases the number of stable states to three. However, when the strain is further

increased to 18% (point vii), S2 with one side peak disappears. Further increasing the strain to 24% (point viii) causes the formation of an interesting twisted state (S4) and therefore increases the number of stable states to three (S1, S3 and S4). As the strain becomes even larger, S3 disappears and only S1 and S4 exist at the strain of 34% (point ix). The experimental and computation results shown above agree reasonably well. The discrepancy in the configuration of some stable states (e.g., (v) S1 in Figure 2B) between experiments and modeling likely results from the friction between the structure and the substrate in experiments, which is neglected in computational modeling. The effect of friction will be further discussed in section 2.3. Furthermore, by continuously changing the strain levels from 0% to 40% using the 3-crease structure, we record the dynamic progression of the five regimes and the fast, remote magnetic reconfiguration among the stable states within each regime in **Supplementary Movie S1**, which is highly consistent with the predictions of the phase diagram in Figure 2A. We also show that the states are stable under perturbations perpendicular to the vertical surface (along the height direction) of the ribbon, except in cases where S4 (twisted two peaks) is present. By using S1 as an example, the structure is shown to maintain its S1 configuration after the perturbations caused by a tweezer-induced external mechanical force (Figure S1).

The studies above provide important guidelines for tailoring the number and configurations of stable states in origami-inspired structures by tuning the number of creases and the assembly strain. For example, for applications like digital logics where multiple stable states are desired, structures with three creases may offer more design space and tunability, while structures with a lower or higher number of creases is preferred for applications where a single stable state is needed. Furthermore, from the phase diagram, we observe that structures with two and three creases have multistable states under a wide range of strain (15%-40% strain for the case of two creases and 0%-40% strain for the case of three creases), which can be used for applications of multistable structures that demand a wide working strain range. It is also worth emphasizing that a major advantage of employing the assembly strain as a control

parameter is that varying strain levels and therefore tunable multistability can be repeatedly achieved by using a simple mechanical stage, as we will demonstrate later in **Section 2.4**.

We also study the effects of the crease thickness ratio and the crease length ratio (defined in Figure S2) on the multistability by using the 3-crease ribbon under a strain level of 14% as an example. Table S1 and Table S2 show that both ratios have a significant effect on the multistability of the ribbon structure. In this work, we focus on the study of how the multistability can be tuned by the crease number and the strain levels. More detailed studies on the effects of the crease thickness ratio and the crease length ratio will be pursued elsewhere.

2.3 Reconfiguration paths among distinct stable states of origami-inspired ferromagnetic structures

In addition to locating the stable configurations, we also investigate available pathways that the structure can be reconfigured along among its stable states, which is important for many applications. The pathways are computationally identified by first locating the saddle points that connect the local minima on the energy landscape, also known as the transition states, using the so-called Binary Image Transition State Search model (see the Experimental Section for the description of the algorithm). A full pathway is then given by the steepest-descent paths from the transition state to the energy minima, which are found by tracing the route of a minimization from each downhill side of the transition state.

Here we use the three-crease structure as a representative case for study because of its complexity in the configurations and the number of stable states, which results in a large number of reconfiguration paths. As illustrated in **Figure 3A**, we identify four distinct pathways among the stable states of the structure: P_{1-2} for the transition path between S1 and S2, P_{1-3} between S1 and S3, P_{2-3} between S2 and S3, and P_{3-4} between S3 and S4. It is worth noting that in cases where one or more of those states are not stable, the corresponding individual paths may merge into one, as we will detail below.

Figure 3B shows the available pathways and the associated energy profiles for a representative case in each of the five regimes for a 3-crease ribbon (identified in **Figure 2A**) as the strain is increased from 0% to 40%. In the first regime (0-10% strain), only states S1 and S2 exist, with a single pathway (P_{1-2}) to reconfigure between them, as shown in **Movie S2**. In the second regime (10%-17% strain), state S3 appears, so two additional pathways, P_{1-3} and P_{2-3} , become accessible (**Movie S3**). Our analysis also highlights that there are not only multiple stable states existing in the structure, but also multiple available paths for transforming the structure from one state to another. For example, we can observe that there are two main pathways that can be taken from state S1 to S3. The first path, initially following P_{1-2} to reconfigure S1 to S2, subsequently involves the creation of an asymmetric peak at one side of the structure to form state S3 from S2 (P_{2-3}). Due to symmetry, there are two equivalent scenarios depending on which side the peak is created to form S3. The second path, P_{1-3} , directly reconfigures S1 to S3 by forming two edge peaks simultaneously while maintaining symmetry. As the strain increases to the regime of 17%-19%, state S2 becomes unstable, so P_{1-2} and P_{2-3} merge into a single path P_{1-2^*-3} (**Movie S4**), where 2* denotes that state 2 is no longer stable. Above the strain of 19%, pathway P_{3-4} appears between state S3 and twisted state S4, while the two pathways from S1 to S3 still exist (**Movie S5**). Finally, at the strain of 30% and above, S3 is no longer stable leaving just two merged paths $P_{1-2^*-3^*-4}$ and P_{1-3^*-4} between S1 and S4 (**Movie S6**), where 3* denotes that state S3 is no longer stable.

We further investigate the energy barriers of each pathway as a function of strain. For each pathway, there are two relevant energy barriers, as illustrated in **Figure 3B** using P_{1-2} in the case of 8% strain as an example. We label ΔE_f for the energy required to transition from a lowered numbered state to a higher numbered state in each pathway (here, S1 to S2), while ΔE_b is the energy required for the opposite transition (here, S2 to S1). We summarize the values of the energy barriers for all the available pathways in **Figure 3C**, where ΔE_f and ΔE_b for each

pathway are represented by solid and dotted lines, respectively. We can see that the energy barriers for pathways reconfiguring from S1 to other states including S2, S3 and S4 depending on the strain levels (P_{1-2} , P_{1-2^*-3} , $P_{1-2^*-3^*-4}$, P_{1-3} , P_{1-3^*-4} ; solid blue and orange lines) is much larger than their corresponding reverse barriers (dotted blue and orange lines, respectively). Such difference suggests that state S1 is more stable than the other states (S2, S3 and S4), which is consistent with the phase diagram in **Figure 2A**, where S1 is almost always stable for cases under all crease numbers. It is also seen that the energy barriers of paths P_{2-3} (green lines, transition between S2 and S3) and P_{3-4} (red lines, transition between S3 and S4) are significantly lower than those of pathways involving state S1 represented by solid blue and orange lines. This suggests that reconfigurations among states S2, S3, and S4 are much easier than those between S1 and S2/S3/S4. Correspondingly, the required forces to disturb the reconfiguration paths or trap locally stable states are low. Hence, forces like friction between the structure and the substrate (assembly platform) in experiments may be sufficient to trap the structure along these paths or at states S2, S3 and S4. This may explain why experimentally the structure appears to get trapped in some states which are shown to be unstable in computational results (**Movies S4-6**). For example, in Movie S4, when the structure is reconfigured from S2 to S3, the 2nd edge peak is not fully formed due to possible friction between the structure and the substrate, causing the slight asymmetric configuration of S3.

From **Figure 3C**, we can also see that the energy barriers for the majority of the reconfiguration paths increase monotonically with the strain, implying that it becomes more difficult to reconfigure the states at larger strains. Exceptions occur for reconfiguration paths P_{2-3} (solid green line, transition from S2 to S3) and P_{3-4} (solid red line, transition from S3 to S4), the energy barriers of which decrease with increasing strain levels. Here, the cases when the energy barriers tend to be zero correspond to the instances where S2 and S3 become unstable, i.e., the instability modes of these states. Overall, the energy barrier analysis reinforces the

previous observation that, as the strain is varied from 0% to 40%, state S1 always exists while the availability of states S2, S3 and S4 strongly depends on the strain imposed.

2.4 Origami-inspired multistable ferromagnetic structures of multi-ribbon configurations

The multistable ribbon configurations studied above can serve as building blocks for complicated geometries and diverse types of origami-inspired structures. **Figure 4A** and **Figure S3** show a 3×3 array of ribbons with three creases at different strain levels, which is consistent with the prediction of the phase diagram in **Figure 2A** and demonstrates the scalability and versatility of the technique. Particularly, as predicted by the phase diagram, three distinct stable states exist at the strain levels of 14% (S1, S2, and S3) and 28% (S1, S3, and S4), respectively. In experiments, each individual ribbon unit is separately addressable and therefore the structure array can be magnetically tuned in a sequential manner to display all the three stable states (S1 in row 1, S2 in row 2, and S3 in row 3 at a strain of 14%; S1 in column 1, S3 in column 2, and S4 in column 3 at a strain of 28%). Such capability of dynamically and reversibly tuning the patterns in a structure array represents an important option for applications including digital coding and smart switches, especially when integrated with other functional materials or elements. In addition, the complexity of origami-inspired structures and the number of stable states can be increased by incorporating a larger number of interconnected structural units, like ribbons with two creases. **Figure 4B** presents a structure consisting of two creased table structures connected with a creased ribbon, which can be magnetically reconfigured into six distinct stable states that are enabled by the multistability of the ribbon units. Furthermore, the multistable origami-inspired structures can be extended to diverse geometries. **Figure 4C** and **Figure S4** demonstrate structures that mimic insect flexion, standing states, and a series of biomimetic movements. More examples including those that resemble two stable states of a butterfly structure, a cage and a drug-release system are shown in **Figure S5**.

2.5 Application in soft robotics

Based on the multistability of origami-inspired structures and the flexibility of ferromagnetic actuation, we further assemble two 3-crease ribbon structures (side by side) into a 3D origami robot to achieve fast, remote response to an external magnetic field. **Figure 5A** shows the design concept and assembly process, which begins with two buckled ferromagnetic ribbon structures of 3 creases (150 μm thick) attached to an elastomer substrate (400 μm thick). The center peak of the two structures act as the “feet” of the robot, which can drive the robot to move forward under magnetic actuation. To actuate the robot, a portable magnet is placed directly underneath the structure to bring the front “foot” forward, while the other one as a fulcrum at the back. Once the magnet is removed, the hinge on the front “foot” recovers its original shape, driving the robot forward. The actuation process above is recorded in **Figure 5B** and **Movie S7**. Future opportunities include the fabrication and actuation of freestanding biomimetic structures by using the shape fixing effect of shape memory polymers^{19, 49} or liquid crystal elastomers⁵⁰ for applications including remotely controlled soft robotics.

3. Conclusion

To sum up, we show from experiments and simulations that the multistability and the associated transition paths of origami-inspired, compressively buckled ferromagnetic structures can be tailored by controlling the number of creases and assembly strain. Our constructed phase diagram of a representative creased ribbon structure from the energy landscape analysis is validated by our experiments and provides important guidelines for the targeted number of stable states by varying the two control factors. In addition, transition pathways among the distinct stable states are computed and illustrate how the structure can be manipulated to be reconfigured along different pathways. The experimental results of our origami-inspired ferromagnetic structures show targeted multistable states following designed pathways, which highly agrees with modeling. The fundamental understanding of the multistability of creased

ribbon structures provides important guidelines for the design and application of complex classes of origami-inspired systems that are capable of multiple shape reconfigurations. Demonstrated examples include the arrays of creased ribbon units, a series of biomimetic states of a developed “insect” structure, and a double-ribbon structure that mimics a soft robot. These results highlight potential opportunities in the future to exploit multistable, origami-inspired ferromagnetic structures for intelligent and adaptive systems such as programmable logic array by integrating complex structure design and functional materials like stimuli-responsive polymers and electronics. It will also be interesting to explore the concept of actively manipulating the number of stable states and their reconfiguration paths in the design of other types of functional structures by using alternative control parameters.

4. Experimental Section

Fabrication of 2D ferromagnetic composite precursors: The fabrication of ferromagnetic film began with using a planetary mixer (AR-100, Thinky) to homogeneously mix (2000 rpm for 2 min, then defoaming at 2000 rpm for 1 min) NdFeB (neodymium iron boron) microparticles (average diameter: 5 μm , Neo Magneuch) into uncured PDMS (Polydimethylsiloxane, made with a volume ratio of part A over part B of 5:1) resin at a volume ratio of 1:5. Then the obtained ferromagnetic PDMS composite was spin coated onto a petri-dish at 500 rpm for 15s, and the completely cured ferromagnetic film (thickness=180-200 μm) was obtained after 2 days and laser cut into desired 2D patterns. The raster mode of the laser (VLS 3.50, University Laser System, Norman, OK) was used to create the crease segment of origami structures.

3D assembly: The assembly of origami structures was conducted using the previously introduced 3D buckling technique.⁴² The 2D precursor was transferred onto a prestretched elastomer substrate (1 mm thick, Dragon Skin; Smooth-On, Easton, PA). Strong adhesion was formed at bonding sites by applying a thin layer of superglue. More specifically, a needle tip

was used to apply a tiny drop of the superglue to the center of the bonding site, followed by physical lamination of the film onto the elastomer substrate to spread the superglue into a very thin layer. Releasing the prestrain in the assembly platform transforms the 2D pattern into a 3D structure and completes the assembly process.

Magnetic actuation: A cylinder magnet (D8Y0, K&J magnetics) was used to actuate the targeted structure, and the ferromagnetic field was generated from the circular surface (diameter: 1.27 cm) of the cylinder magnet. The working distance of the magnet for effective actuation was first identified to be 3-22 mm for this specific magnet. Through adjusting the distance within this range and the angle (0-180°) between the circular surface and the targeted part of the targeted structure, the strength and direction of applied ferromagnetic field were controlled to address the needs of reconfigurations. The magnet was moved from one location of the targeted structure to another, and the above operation is repeated to reconfigure the targeted structure from one stable state to another.

Fabrication and assembly of soft robot: 3D buckling technique was used to conduct the fabrication and assembly of soft robot. Two 2D precursors of origami ribbon structures with 3 creases were patterned from ferromagnetic films by using a laser (VLS 3.50, University Laser System, Norman, OK), then was transferred onto a prestretched elastomer substrate (400 μm thick, Dragon Skin; Smooth-On, Easton, PA). Strong adhesion was formed at bonding sites by applying a thin layer of superglue. Releasing the prestrain in the assembly platform transforms the 2D patterns into to an origami structure array in their symmetric one-arc state. Then we used laser to cut the substrate around the structure into a rectangle of 16 mm \times 5 mm. The whole process ended with upside down 2 buckled crease ribbons.

Modeling

The structures are discretized as a 2D triangular mesh using a Delaunay refinement with an optimal mesh size equal to an eighth of the ribbon width. The energy of the structure is calculated by considering contributions from the stretching and bending of the mesh, as well as

a repulsive potential with the substrate. A bar-and-hinge model is used for the stretching and bending components. This involves treating the bonds in the triangulation as elastic springs and with elastic hinges connecting adjacent triangular faces. The resulting expression for the energy is

$$E = \sum_b K_{s,b} (r_b - r_b^0)^2 + \sum_h K_{b,h} (1 + \cos \theta_h), \quad (1)$$

where the summations are over each of the bonds, b , and hinges, h , respectively. For each bond r_b is its length and r_b^0 is the relaxed length when in the flat precursor, while θ_h is the dihedral angle of each hinge. The spring coefficients are obtained by considering the stiffness and flexural rigidities of the individual triangular elements. They are

$$K_{s,i} = \frac{\sqrt{3}}{4} E t_i, \quad (2)$$

$$K_{b,i} = \frac{E t_i^3}{12(1 - \nu^2) A_{i,1} + A_{i,2}}, \quad (3)$$

where E is the Young's modulus, ν is the Poisson ratio, t_i is the thickness, which is smaller at the creases, and $A_{i,1}$ and $A_{i,2}$ are the areas of the triangles either side of the hinge. The values used were a Young's modulus of 1.4 MPa⁵¹ and a thickness of 130 μm (for the ribbon stripes) or 60 μm (for the creases). As to the Poisson ratio in Eq. (3), the current discrete shell leads to a fixed value of $\nu = 1/3$,³⁴ smaller than the usual Poisson ratio for polymeric materials (~ 0.5). However, we do not expect this will significantly influence the results as the thin film deformation is mainly determined by the two stiffnesses (stretching and bending) defined in Eqs. (2) and (3). For the repulsive substrate interaction each node in the triangulation is subject to a Lennard-Jones 9-3 potential which is shifted and cutoff to remove the attractive region,

$$E(r) = \epsilon \left[\frac{2}{15} \left(\frac{\sigma}{r + r_0} \right)^9 - \left(\frac{\sigma}{r + r_0} \right)^3 \right] - E_0 \text{ for } r < 0, \quad (4)$$

where r_0 is the distance at which the unshifted potential is minimal, and E_0 is the value of the potential at that location. The values used are $\sigma = 1 \text{ nm}$ and $\epsilon = 10^{-10} \text{ J}$.

Finding stable states: The stable states correspond to configurations which lie at the local minima in the energy landscape, so they are found by minimizing the energy of the system. The L-BFGS algorithm is used for this because it is efficient for large numbers of degrees of freedom. To enable different states to be obtained, we carefully sample the available states at selected points in the phase diagram, typically at 5 different strain levels for each crease number. At such a point, random forces are applied to each of the creases and the structure is buckled by moving the binding sites according to the strain over the first 10,000 iterations, after which the structure is allowed to relax. This process is repeated several hundred times. Once the qualitatively distinct configurations are identified, the strain is then varied for each configuration to observe the range over which they are stable. To ensure our procedure is robust, we have increased the sampling frequency of each configuration and we reliably find the same states.

Finding transition states: To identify the transition states for use in locating the pathways, the binary-image transition state search (BITSS) method is used. Briefly, this method uses two states, \mathbf{x}_1 and \mathbf{x}_2 , which are initialized at the two minima. The energy of this pair of states is then minimized subject to two constraints. Firstly, the distance between the two states is set to a value d_0 , which is steadily reduced to zero such that the states converge at the transition state. The second constraint requires the energies of the individual states, E_1 and E_2 , to be equal. This prevents one state from passing over the saddle point, which would result in the convergence occurring at one of the minima instead. These two constraints are applied as penalty terms in the total energy to be minimized:

$$E_{tot}(\mathbf{x}_1, \mathbf{x}_2) = E_1 + E_2 + K_e(E_1 - E_2)^2 + K_d(d(\mathbf{x}_1, \mathbf{x}_2) - d_0)^2, \quad (5)$$

where $d(\mathbf{x}_1, \mathbf{x}_2)$ is the distance between the two states, defined by the root mean square separation between corresponding vertices in the two states; and K_e and K_d parametrize the strength of the constraints. These coefficients are computed at regular intervals as the separation

d_0 is reduced so that all the energy terms remain relevant. The coefficient for the energy constraint is set by the expression $K_e = 10/\Delta E$, where ΔE is an estimate for the current energy barrier between \mathbf{x}_1 and \mathbf{x}_2 , obtained by linearly interpolating between them. For a given d_0 , the distance coefficient K_d is initially set to the reciprocal of the separation between the minima. If the states converge with a relative error in distance from d_0 greater than 1%, K_d is increased by a factor of 10. This is repeated until the relative error is within 1%, in which case we then continue with the BITSS method with a smaller distance constraint. Typically, we reduce d_0 by 30%. After finding a transition state at a given strain parameter, a continuation approach can then be used in conjunction with the BITSS method to find the state for nearby parameters. By repeating this process, the transition states, and hence energy barriers, are identified for the whole parameter range of interest.

Acknowledgements

We acknowledge the support of the following grants: NSF-CMMI-2103012 (X.W.), NSF-CMMI-2020476 (T. Z.). S.J.A. is supported by a studentship from the Engineering and Physical Sciences Research Council (EPSRC). Simulations were performed at the facilities of the Hamilton HPC Service of Durham University and the Comet cluster (Award TG-MSS170004 to T.Z.) in The Extreme Science and Engineering Discovery Environment.

Competing interests

The authors declare no competing financial interests.

References

1. Y. Chen, R. Peng and Z. You, *Science*, 2015, **349**, 396.
2. L. H. Dudte, E. Vouga, T. Tachi and L. Mahadevan, *Nature Materials*, 2016, **15**, 583-588.
3. X. Ning, X. Wang, Y. Zhang, X. Yu, D. Choi, N. Zheng, D. S. Kim, Y. Huang, Y. Zhang and J. A. Rogers, *Advanced Materials Interfaces*, 2018, **5**, 1800284.
4. D. Thesiya, A. Srinivas and P. Shukla, *Journal of Astronomical Instrumentation*, 2015, **4**, 1550006.
5. D. Melancon, B. Gorissen, C. J. García-Mora, C. Hoberman and K. Bertoldi, *Nature*, 2021, **592**, 545-550.
6. M. Liu, L. Domino and D. Vella, *Soft Matter*, 2020, **16**, 7739-7750.
7. S. Felton, M. Tolley, E. Demaine, D. Rus and R. Wood, *Science*, 2014, **345**, 644-646.
8. J. L. Silverberg, A. A. Evans, L. McLeod, R. C. Hayward, T. Hull, C. D. Santangelo and I. Cohen, *science*, 2014, **345**, 647-650.
9. T. Chen, M. Pauly and P. M. Reis, *Nature*, 2021, **589**, 386-390.
10. C. Yang, M. Boorugu, A. Dopp, J. Ren, R. Martin, D. Han, W. Choi and H. Lee, *Materials Horizons*, 2019, **6**, 1244-1250.
11. J. Hellmeier, R. Platzer, A. S. Eklund, T. Schlichthaerle, A. Karner, V. Motsch, M. C. Schneider, E. Kurz, V. Bamieh, M. Brameshuber, J. Preiner, R. Jungmann, H. Stockinger, G. J. Schutz, J. B. Huppa and E. Sevcsik, *Proc Natl Acad Sci U S A*, 2021, **118**.
12. K. Miura, *The Institute of Space and Astronautical Science report*, 1985, 1-9.
13. E. T. Filipov, T. Tachi and G. H. Paulino, *Proceedings of the National Academy of Sciences*, 2015, **112**, 12321-12326.
14. J. L. Silverberg, J. H. Na, A. A. Evans, B. Liu, T. C. Hull, C. D. Santangelo, R. J. Lang, R. C. Hayward and I. Cohen, *Nat Mater*, 2015, **14**, 389-393.
15. S. Sadeghi and S. Li, *Extreme Mechanics Letters*, 2020, **40**, 100958.
16. K. Liu, T. Tachi and G. H. Paulino, *Nat Commun*, 2019, **10**, 4238.
17. H. Fang, T.-S. Chang and K. W. Wang, *Smart Materials and Structures*, 2019, **29**, 015026.
18. Z. R. Zhai, Y. Wang and H. Q. Jiang, *P Natl Acad Sci USA*, 2018, **115**, 2032-2037.
19. X. Wang, X. Guo, J. Ye, N. Zheng, P. Kohli, D. Choi, Y. Zhang, Z. Xie, Q. Zhang, H. Luan, K. Nan, B. H. Kim, Y. Xu, X. Shan, W. Bai, R. Sun, Z. Wang, H. Jang, F. Zhang, Y. Ma, Z. Xu, X. Feng, T. Xie, Y. Huang, Y. Zhang and J. A. Rogers, *Adv Mater*, 2019, **31**, e1805615.
20. Y. Liu, B. Shaw, M. D. Dickey and J. Genzer, *Sci Adv*, 2017, **3**, e1602417.
21. Q. Ge, C. K. Dunn, H. Qi, M. J. S. M. Dunn and Structures, 2014, **23**, 094007.
22. S. Janbaz, R. Hedayati and A. A. Zadpoor, *Materials Horizons*, 2016, **3**, 536-547.
23. A. S. Gladman, E. A. Matsumoto, R. G. Nuzzo, L. Mahadevan and J. A. Lewis, *Nat Mater*, 2016, **15**, 413-418.
24. Y. Zhang, X. Le, Y. Jian, W. Lu, J. Zhang and T. Chen, *Advanced Functional Materials*, 2019, **29**, 1905514.
25. A. Kotikian, C. McMahan, E. C. Davidson, J. M. Muhammad, R. D. Weeks, C. Daraio and J. A. Lewis, *Sci Robot*, 2019, **4**.
26. Y. Li, H. Yu, K. Yu, X. Guo and X. Wang, *Advanced Functional Materials*, 2021, 2100338.
27. Y. Kim, H. Yuk, R. Zhao, S. A. Chester and X. Zhao, *Nature*, 2018, **558**, 274-279.
28. M. Jamal, S. S. Kadam, R. Xiao, F. Jivan, T.-M. Onn, R. Fernandes, T. D. Nguyen and D. H. Gracias, 2013, **2**, 1142-1150.

29. S. Chen, J. Chen, X. Zhang, Z.-Y. Li and J. Li, *Light: Science & Applications*, 2020, **9**, 75.
30. L. Xu, T. C. Shyu and N. A. Kotov, *ACS Nano*, 2017, **11**, 7587-7599.
31. L. S. Novelino, Q. Ze, S. Wu, G. H. Paulino and R. Zhao, *Proceedings of the National Academy of Sciences*, 2020, **117**, 24096.
32. W. Xu, Z. Qin, C. T. Chen, H. R. Kwag, Q. Ma, A. Sarkar, M. J. Buehler and D. H. Gracias, *Sci Adv*, 2017, **3**, e1701084.
33. S. Xu, Z. Yan, K.-I. Jang, W. Huang, H. Fu, J. Kim, Z. Wei, M. Flavin, J. McCracken and R. J. S. Wang, 2015, **347**, 154-159.
34. H. Seung and D. R. Nelson, *Physical Review A*, 1988, **38**, 1005.
35. E. Grinspun, A. N. Hirani, M. Desbrun and P. Schröder, 2003.
36. C. J. Pickard and R. J. Needs, *Journal of Physics: Condensed Matter*, 2011, **23**, 053201.
37. J. Chen, G. Schusteritsch, C. J. Pickard, C. G. Salzmann and A. Michaelides, *Physical Review Letters*, 2016, **116**, 025501.
38. H. Zhang, X. Cheng, D. Yan, Y. Zhang, D. J. C. S. Fang and Technology, 2019, **183**, 107822.
39. J. Panter, J. Chen, T. Zhang and H. Kusumaatmaja, *Communications Physics*, 2019, **2**, 1-9.
40. E. Weinan, W. Ren and E. Vanden-Eijnden, *Journal of Chemical Physics*, 2007, **126**, 164103.
41. Y. Li, S. Avis, J. Chen, G. Wu, T. Zhang, H. Kusumaatmaja and X. WANG, 2020.
42. Y. H. Zhang, Z. Yan, K. W. Nan, D. Q. Xiao, Y. H. Liu, H. W. Luan, H. R. Fu, X. Z. Wang, Q. L. Yang, J. C. Wang, W. Ren, H. Z. Si, F. Liu, L. H. Yang, H. J. Li, J. T. Wang, X. L. Guo, H. Y. Luo, L. Wang, Y. G. Huang and J. A. Rogers, *P Natl Acad Sci USA*, 2015, **112**, 11757-11764.
43. Y. Liu, X. Wang, Y. Xu, Z. Xue, Y. Zhang, X. Ning, X. Cheng, Y. Xue, D. Lu, Q. Zhang, F. Zhang, J. Liu, X. Guo, K. C. Hwang, Y. Huang, J. A. Rogers and Y. Zhang, *Proc Natl Acad Sci U S A*, 2019, **116**, 15368-15377.
44. W. Hu, G. Z. Lum, M. Mastrangeli and M. Sitti, *Nature*, 2018, **554**, 81-85.
45. S. Wu, W. Hu, Q. Ze, M. Sitti and R. Zhao, *Multifunctional Materials*, 2020, **3**, 042003.
46. D. Yan, M. Pezzulla, L. Cruveiller, A. Abbasi and P. M. Reis, *Nature Communications*, 2021, **12**, 2831.
47. Y. Tang, Y. Li, Y. Hong, S. Yang and J. Yin, *Proc Natl Acad Sci U S A*, 2019, DOI: 10.1073/pnas.1906435116.
48. W. Huang, Y. Wang, X. Li and M. K. Jawed, *Journal of the Mechanics and Physics of Solids*, 2020, **145**, 104168.
49. Y. Li, C. Luo, K. Yu and X. Wang, *ACS Appl Mater Interfaces*, 2021, **13**, 8929-8939.
50. T. H. Ware, M. E. McConney, J. J. Wie, V. P. Tondiglia and T. J. White, *Science*, 2015, **347**, 982-984.
51. Y. Kim, G. A. Parada, S. Liu and X. Zhao, *Sci Robot*, 2019, **4**.

Figure Captions

Figure 1. Schematic illustration of the assembly and magnetic reconfiguration schemes of multistable origami-inspired ribbon structures.

Figure 2. Multistability of origami-inspired ferromagnetic ribbon structures under varying creases and compressive strains. (A) Design phase diagram showing the effect of the crease number and compressive strain on the number and configurations of distinct stable states of the ribbon. (B) Experimental and computational results of multistable states under a constant strain of 15% and varying crease numbers, corresponding to points i-v labelled in Figure 2A. Scale bars, 2 mm. and (C) Experimental and computational results of multistable states at a constant number of creases ($n_{\text{crease}} = 3$) and varying strain levels, corresponding to points vi-ix in Figure 2A. Scale bars, 2 mm.

Figure 3. Reconfiguration paths among distinct stable states of origami-inspired ferromagnetic ribbon structures. (A) Possible pathways between the stable states. Scale bars, 2 mm. (B) Energy profiles of pathways for the 3-crease ribbon structure at various strain levels. (C) Minimum energy barriers for pathways in Figure 2B as a function of the strain. The solid lines indicate the energy barriers from the lower numbered states to the higher numbered states (illustrated by ΔE_f in Figure 3B), and the dashed lines are the barriers from the higher numbered states to the lowered numbered states (illustrated by ΔE_b in Figure 3B). Here, the line colors follow those of the pathways labelled in Figure 3A. The blue and orange lines also encompass the extended pathways P_{1-2^*-3} , $P_{1-2^*-3^*-4}$, and P_{1-3^*-4} .

Figure 4. Diverse origami-inspired, multistable ferromagnetic structures that can be actuated by magnetic forces. (A) An array of 3-crease ribbon structures showing different patterns formed by the multistable states of the ribbon under the strain of 14% and 28%, respectively. Scale bars, 3 mm. (B) Multistable states and magnetic reconfiguration of a double-table structure composed of creased ribbon segments. (C) A multistable biomimetic “insect” in its flat and standing states, respectively. Scale bars, 2 mm.

Figure 5. An origami-inspired magnetic “robot” composed of two ribbon structures of 3 creases. (A) Fabrication of the “robot”. Scale bars, 2 mm. (B) Motion behaviors of the “robot” under magnetic actuation. Scale bars, 2 mm.

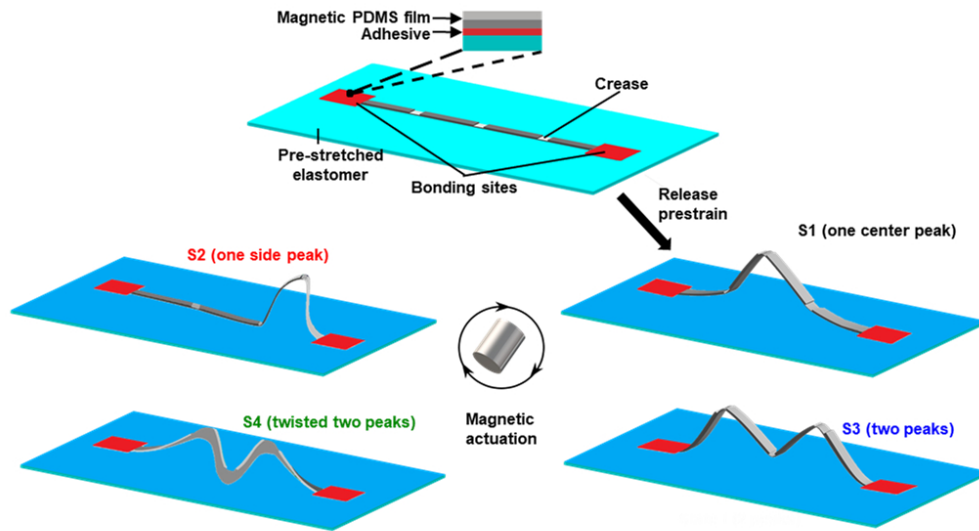


Figure 1. Schematic illustration of the assembly and magnetic reconfiguration schemes of multistable origami-inspired ribbon structures.

216x132mm (120 x 120 DPI)

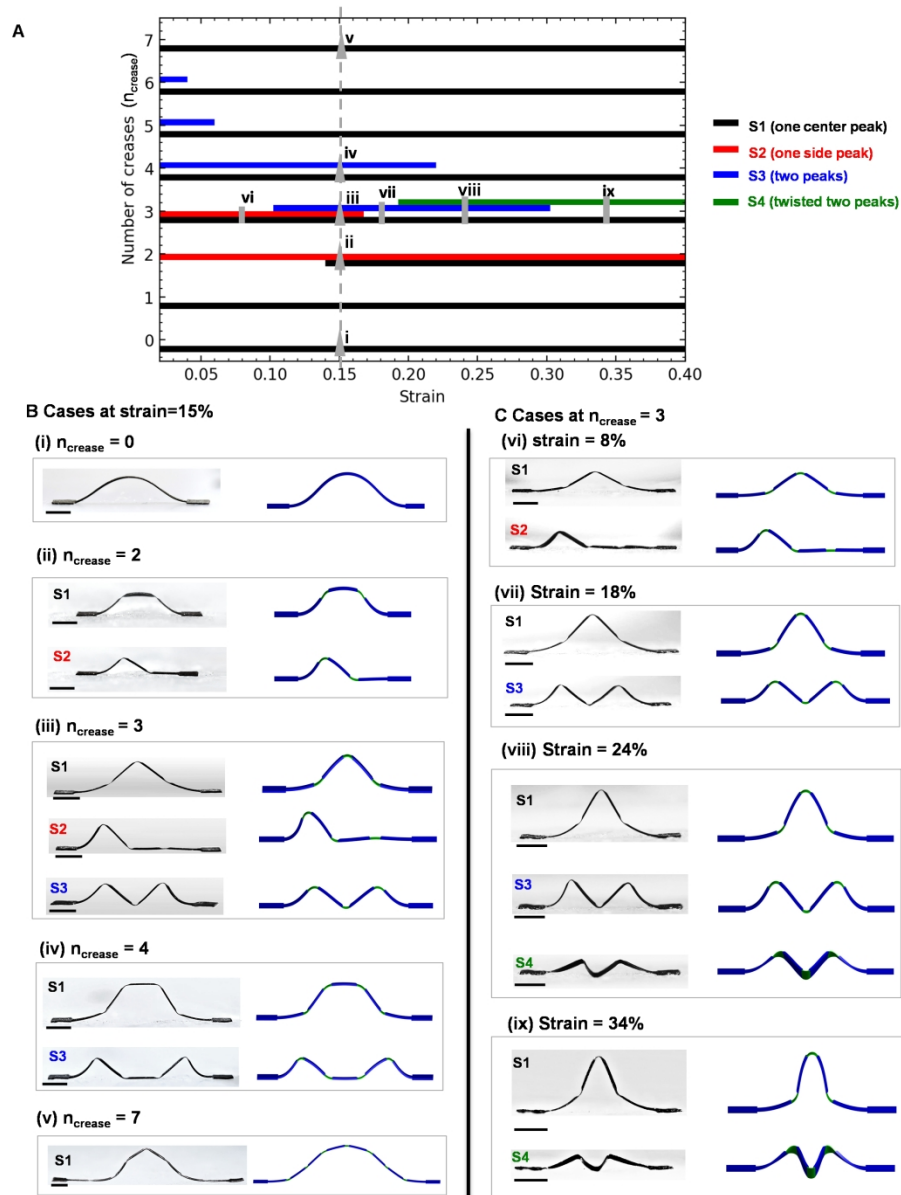


Figure 2. Multistability of origami-inspired ferromagnetic ribbon structures under varying creases and compressive strains. (A) Design phase diagram showing the effect of the crease number and compressive strain on the number and configurations of distinct stable states of the ribbon. (B) Experimental and computational results of multistable states under a constant strain of 15% and varying crease numbers, corresponding to points i-v labelled in Figure 2A. Scale bars, 2 mm. and (C) Experimental and computational results of multistable states at a constant number of creases ($n_{\text{crease}} = 3$) and varying strain levels, corresponding to points vi-ix in Figure 2A. Scale bars, 2 mm.

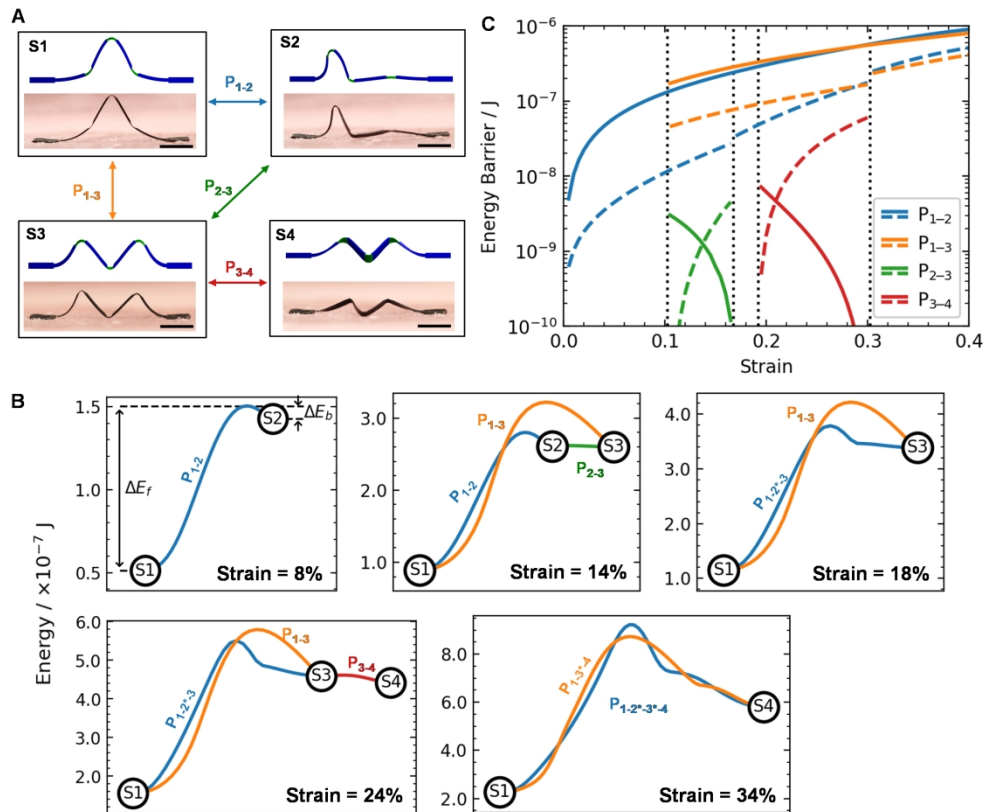


Figure 3. Reconfiguration paths among distinct stable states of origami-inspired ferromagnetic ribbon structures. (A) Possible pathways between the stable states. Scale bars, 2 mm. (B) Energy profiles of pathways for the 3-crease ribbon structure at various strain levels. (C) Minimum energy barriers for pathways in Figure 2B as a function of the strain. The solid lines indicate the energy barriers from the lower numbered states to the higher numbered states (illustrated by ΔE_f in Figure 3B), and the dashed lines are the barriers from the higher numbered states to the lower numbered states (illustrated by ΔE_b in Figure 3B). Here, the line colors follow those of the pathways labeled in Figure 3A. The blue and orange lines also encompass the extended pathways P_{1-2*-3}, P_{1-2*-3*-4}, and P_{1-3*-4}.

498x412mm (120 x 120 DPI)

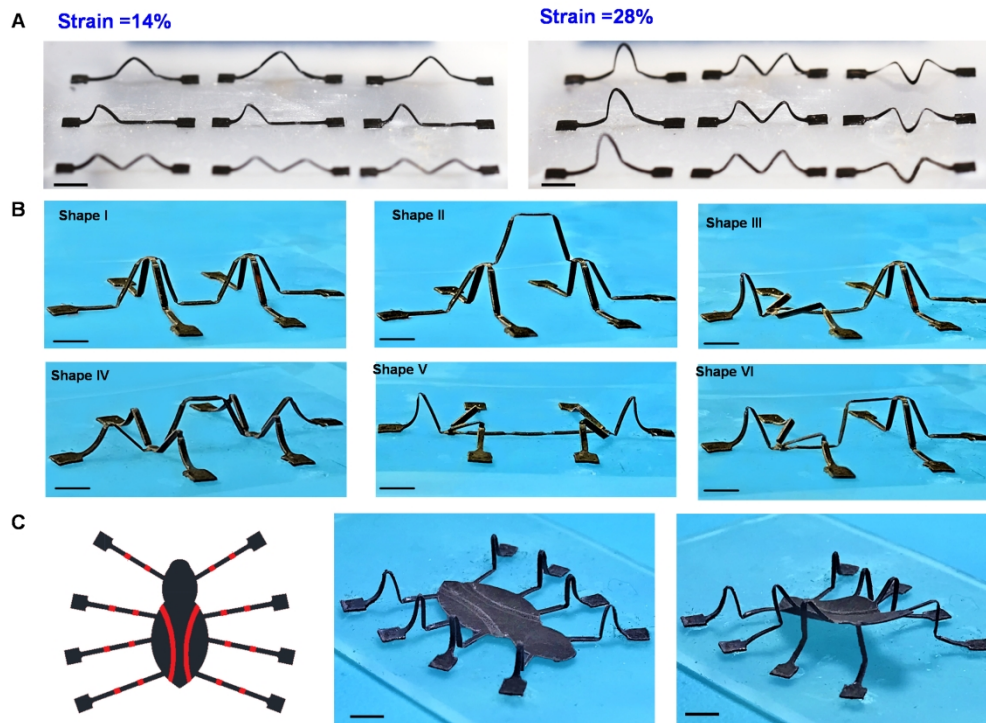


Figure 4. Diverse origami-inspired, multistable ferromagnetic structures that can be actuated by magnetic forces. (A) An array of 3-crease ribbon structures showing different patterns formed by the multistable states of the ribbon under the strain of 14% and 28%, respectively. Scale bars, 3 mm. (B) Multistable states and magnetic reconfiguration of a double-table structure composed of creased ribbon segments. (C) A multistable biomimetic "insect" in its flat and standing states, respectively. Scale bars, 2 mm.

488x356mm (120 x 120 DPI)

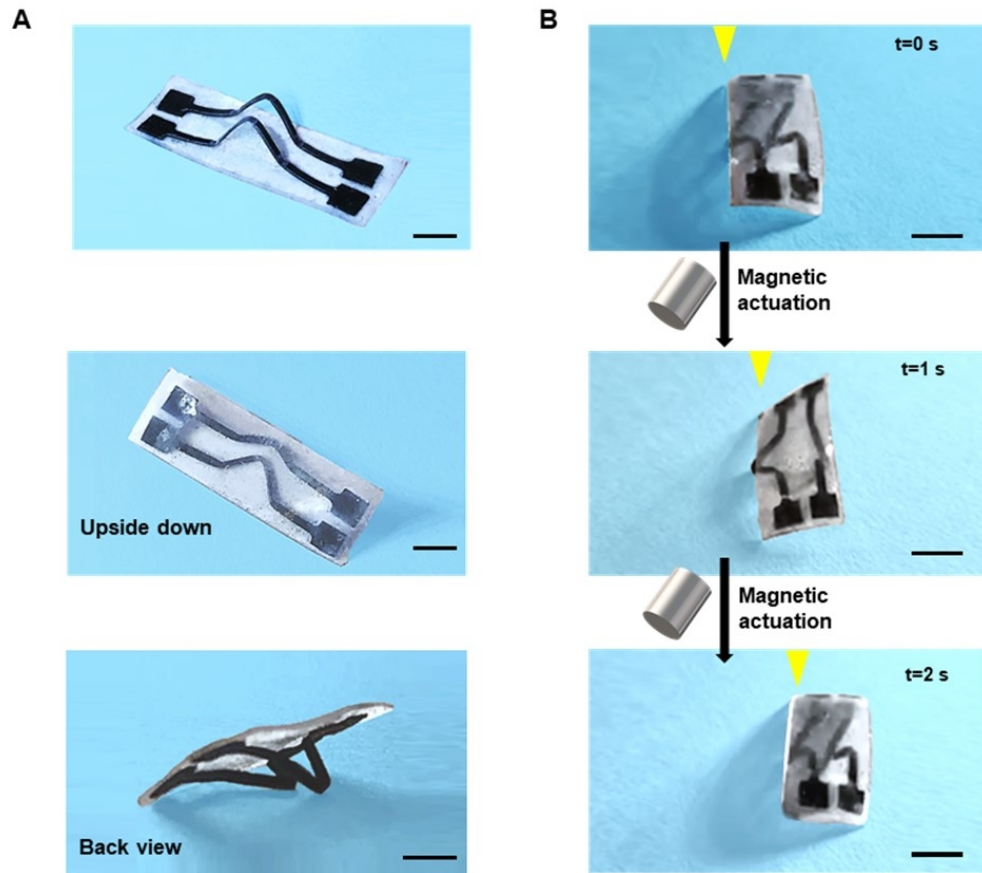


Figure 5. An origami-inspired magnetic "robot" composed of two ribbon structures of 3 creases. (A) Fabrication of the "robot". Scale bars, 2 mm. (B) Motion behaviors of the "robot" under magnetic actuation. Scale bars, 2 mm.

160x141mm (150 x 150 DPI)