



Cite this: *J. Mater. Chem. A*, 2023, 11, 5734

# Hierarchically porous Ni foam-supported Co and Sn doped $\text{Ni}_3\text{S}_2$ nanosheets for oxygen evolution reaction electrocatalysts†

Won Young An,<sup>†a</sup> Hyungwoo Lee,<sup>†b</sup> Sung Ryul Choi,<sup>a</sup> Sungyong Choi,<sup>a</sup> Hyun-Seok Cho,<sup>c</sup> Minseok Choi<sup>b</sup> and Jun-Young Park<sup>\*,a</sup>

To enter the era of a clean and sustainable hydrogen economy, it is crucial to first discover non-noble metal electrocatalysts that can be used for oxygen evolution reactions (OER) of water electrolyzers. Herein, we demonstrate highly active and durable Co- and Sn-co-doped  $\text{Ni}_3\text{S}_2$  catalysts supported on Ni foam ( $\text{CoSn-Ni}_3\text{S}_2@\text{NF}$ ) for the OER in alkaline media. Benefiting from the hierarchically porous nanosheet morphology and synergistic strong electron interaction among Co, Sn, and Ni ions, the  $\text{CoSn-Ni}_3\text{S}_2@\text{NF}$  achieves outstanding OER activity in 1 M KOH with a low overpotential of 321 mV at a current density of  $0.2 \text{ A cm}^{-2}$ . Furthermore, the  $\text{CoSn-Ni}_3\text{S}_2@\text{NF}$  alkaline water electrolysis cell shows a significantly high current density of  $1.367 \text{ A cm}^{-2}$  at a cell voltage of 2.0 V under 80 °C and 30 wt% KOH condition using a nickel–iron layered double hydroxide for the hydrogen evolution reaction and a Zirfon PERL separator (500  $\mu\text{m}$ ). Based on the defect formation energy and electronic structure obtained using density functional theory calculation, the enhanced intrinsic activity of  $\text{CoSn-Ni}_3\text{S}_2@\text{NF}$  can be attributed to the Co and Sn dopants with S vacancies, which increase activation sites (and free electrons) and favorably modify the Ni 3d-band center to be closer to the Fermi level. This work not only demonstrates a highly electrocatalytic active OER catalyst for water electrolyzers, but also provides a new design principle that can be used for high performance materials by tailoring the electronic structure of transition and post transition metal ions.

Received 1st December 2022  
Accepted 16th February 2023

DOI: 10.1039/d2ta09361h

rsc.li/materials-a

## Introduction

Due to the global phenomena of climate change, environmental pollution, and energy crises, eco-friendly hydrogen is attracting substantial attention as a next-generation sustainable energy carrier.<sup>1,2</sup> Hydrogen gas has numerous applications in metallurgy, petrochemical refinery, processing foods, and automobiles, and it is advantageous in various ways, including its high energy density (120–140 MJ kg<sup>−1</sup>), the fact that it is the most abundant element, and its environmental friendliness.<sup>3,4</sup> Currently, natural gas reforming methods based on fossil fuels using high-temperature steam account for the majority of hydrogen production.<sup>5</sup> While gas reforming methods are the cheapest and most common methods, they cause major threats

to the environment and natural resources due to greenhouse gas emissions. More recently, water electrolysis-based hydrogen generation has provided a beneficial opportunity to produce hydrogen gas renewably without affecting nature and natural resources.<sup>6</sup> Among these, alkaline water electrolysis (AWE) is the most industrially mature technology for hydrogen generation that uses an applied electricity.<sup>7</sup> When the direct current is applied to the AWE cells, water is dissociated at the cathode to form  $\text{H}_2$  through hydrogen evolution reactions (HERs), thus releasing hydroxide anions ( $\text{OH}^-$ ) in alkaline solution (e.g., potassium hydroxide). The  $\text{OH}^-$  formed in this way crosses through the membrane separator and then reacts to form  $\text{O}_2$  at the anode by the oxygen evolution reactions (OERs). The OER is the rate-determining step of AWE cells due to the sluggish kinetics with high overpotential, leading to reduced energy efficiency of AWE cells.<sup>8–10</sup> In addition, the use of noble metal OER electrocatalysts such as  $\text{IrO}_2$  and  $\text{RuO}_2$  restricts the large-scale commercialization of AWE cells.<sup>11</sup>

Very recently, transition metal chalcogenides (TMCs) based on group 16 elements such as sulfide, selenide, and telluride have attracted substantial attention as OER catalysts due to their excellent catalytic activity, low price, and good corrosion resistance in the alkaline electrolyte.<sup>12,13</sup> Among chalcogenide materials, comprehensive electrochemical analyses coupled

<sup>a</sup>HMC, Department of Nanotechnology and Advanced Materials Engineering, Sejong University, Seoul 05006, Korea. E-mail: jyoung@sejong.ac.kr; Tel: +82 2 3408 3848

<sup>b</sup>Department of Physics, Inha University, Incheon 22212, Korea. E-mail: minseokchoi.phd@gmail.com

<sup>c</sup>Polymer Electrolyte Fuel Cell Research Center, Hydrogen and Fuel Cell Department, Korea Institute of Energy Research (KIER), Daejeon 34129, Korea

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d2ta09361h>

‡ These authors contributed equally to this work.

with theoretical density functional theory (DFT) calculations have demonstrated that heazlewoodite phase nickel sulfides ( $\text{Ni}_3\text{S}_2$ ) represent one of the best candidates for OER catalysts because of their excellent catalytic activity, high electronic conductivity, and good stability in alkaline solutions, as they benefit from the property of covalency between Ni and S and the 3d orbital electronic structures of Ni.<sup>14–16</sup> In particular, hydrothermally synthesized  $\text{Ni}_3\text{S}_2$  nanostructured catalysts have exhibited similar performance to noble  $\text{RuO}_2$  catalysts, with a low overpotential of 187 mV at 10  $\text{mA cm}^{-2}$  in 0.1 M KOH.<sup>17</sup> However, a facile and reproducible manufacturing process for hierarchically porous nanostructured  $\text{Ni}_3\text{S}_2$  should be established, since nanostructured catalysts have exhibited considerable variations in OER electrochemical performances, even within the same catalyst.<sup>18</sup> Further, there is great potential in enhancing the OER performance of  $\text{Ni}_3\text{S}_2$  catalysts through an atomic surface modification strategy with specific elements.<sup>19,20</sup>

An atomic surface modification with specific elements is an effective method to further boost the OER property by manipulating the electronic structure and charge transport kinetics of electrocatalysts.<sup>21,22</sup> Song *et al.*<sup>23</sup> reported Co-doped  $\text{Ni}_3\text{S}_2$  hierarchical nanoarrays on NF substrate ( $\text{Co-Ni}_3\text{S}_2@\text{NF}$ ) derived from zeolitic imidazolate frameworks with a trunk-branch three-dimensional composite structure. The  $\text{Co-Ni}_3\text{S}_2@\text{NF}$  showed a low overpotential of 120 mV at 10  $\text{mA cm}^{-2}$  (1 M KOH) for the OER and long-term electrochemical durability in alkaline conditions. Yu *et al.*<sup>24</sup> reported that the introduction of Sn element had a significant effect on the structure and morphology of  $\text{Ni}_3\text{S}_2$  nanosheet arrays on Ni foam *via* a simple solvothermal synthesis method. The  $\text{Sn-Ni}_3\text{S}_2@\text{NF}$  exhibited efficient and durable electrocatalytic hydrogen evolution reaction (HER) activity both in acid and alkaline conditions, by providing more exposed active edges and a shorter electron transfer path. Jian *et al.*<sup>25</sup> also demonstrated that  $\text{Ni}_3\text{S}_2$  nanosheet doped with Sn grown on NF ( $\text{Sn-Ni}_3\text{S}_2@\text{NF}$ ) through a hydrothermal procedure had a large current density and high stability for both the HER and the OER. In another study, Cao *et al.*<sup>26</sup> synthesized highly active and durable Fe-doped  $\text{Ni}_3\text{S}_2$  electrocatalysts in the form of vertically oriented nanosheets deposited on three-dimensional Ni foam ( $\text{Fe-Ni}_3\text{S}_2@\text{NF}$ ) for the OER in alkaline media. The introduction of the Fe ions significantly improved the OER activity of  $\text{Ni}_3\text{S}_2$  catalysts (1.54 V at 10  $\text{mA cm}^{-2}$  in 1 M KOH) by increasing the electrochemical surface area and the water adsorption ability with the formation of Ni-Fe (oxy)hydroxide. That is,  $\text{Ni}_3\text{S}_2$  materials can be used through doping of transition metal and post-transition metal ions (*e.g.*, Fe, Co, and Sn) to efficiently modify the surface electron distribution of catalysts and tune the surface adsorption of key active intermediates for the OER, which substantially accelerates the charge transfer kinetics and maximizes the utilization of active sites of catalysts.<sup>27–29</sup>

However, many studies to this point have focused on performance (overpotential or stability) at low current densities of 10  $\text{mA cm}^{-2}$ , which is unsatisfactory for practical applications.<sup>30,31</sup> To secure commercially appropriate hydrogen production capacity, the typical operational current density of a water electrolyzer is preferably above 0.2  $\text{A cm}^{-2}$  with a voltage

between 1.7 and 2.4 V.<sup>32</sup> In addition, along with the measured electrochemical OER performances, the results of theoretical DFT calculations. Such as the analysis of the electronic structures of  $\text{Ni}_3\text{S}_2$  under the doping of transition metal ions, have not been systemically investigated and summarized in mechanistic studies. In particular, although there have been studies on the effect and mechanism of transition metal doping in  $\text{Ni}_3\text{S}_2$ -based catalysts to further boost OER catalyst performances,<sup>33,34</sup> there have been very few mechanistic studies related to the doping of post-transition metals or co-doping with transition metals.

Herein, further OER improvements to the  $\text{Ni}_3\text{S}_2$  catalyst are achieved to take advantage of the feasible benefits of the synergistic structures through co-doping of the multi-valent transition metal (*e.g.*,  $\text{Co}^{2+/3+}$  and  $\text{Fe}^{2+/3+}$ ) and post-transition metal ions (*e.g.*,  $\text{Sn}^{4+}$ ) into the Ni-site. We also investigate an undemanding, scalable, and reproducible synthesis process for hierarchically porous  $\text{Ni}_3\text{S}_2$ -based materials on nickel foam ( $\text{Ni}_3\text{S}_2@\text{NF}$ ), thus enabling the design of highly active, durable, and cost-effective catalysts in alkaline solutions. Moreover, this result is verified by examining the electronic configuration and oxidation state of co-doped  $\text{Ni}_3\text{S}_2$  catalysts critical to their activity and stability for the OERs using theoretical DFT calculations. This work demonstrates new perspectives in developing highly electrocatalytic active OER catalysts for AWE cells with potential applications in the future.

## Experimental

### Synthesis of transition and post transition metal doped-nickel sulfide on Ni foam

Hierarchically porous nickel foam-supported  $\text{Ni}_3\text{S}_2$  ( $\text{Ni}_3\text{S}_2@\text{NF}$ ) was synthesized *via* a simple and scalable hydrothermal synthesis method. To prepare  $\text{Ni}_3\text{S}_2@\text{NF}$  electrocatalysts, 0.6 mmol thiourea ( $\text{CH}_4\text{N}_2\text{S}$ , Alfa Aesar, 99%) was mixed in a solution containing 40 mL of de-ionized (DI) water and stirred for 30 min. Before performing the hydrothermal reaction, the nickel foam (NF,  $1 \times 3 \text{ cm}^2$  in size) was sonicated in 3 M hydrochloric acid (Samchun, 35.0–37.0%) for 30 min, then cleaned with acetone, ethanol, and de-ionized water for 10 min to remove surface impurities. Next, the  $\text{Ni}_3\text{S}_2@\text{NF}$  electrocatalysts were synthesized hydrothermally at 160 °C for 4 h in a stainless-steel autoclave (Ilshin Autoclave, 80 mL Teflon-lined beaker).

The transition (*e.g.*, Co, Fe, and Ni) and post transition metal (*e.g.*, Sn)-doped  $\text{Ni}_3\text{S}_2@\text{NF}$  (Co-, CoSn-, CoFe-, and CoNi- $\text{Ni}_3\text{S}_2@\text{NF}$ ) catalysts were also prepared *via* a one-step hydrothermal synthesis method in the same manner as described above for  $\text{Ni}_3\text{S}_2@\text{NF}$ . To synthesize Co- $\text{Ni}_3\text{S}_2@\text{NF}$  catalysts, 0.3 mmol Co chloride ( $\text{CoCl}_2 \cdot 6\text{H}_2\text{O}$ , Sigma-Aldrich, 98%) precursor and 0.6 mmol thiourea were mixed in a solution containing 40 mL of de-ionized water for 10 min. In the case of CoSn-, CoFe-, and CoNi-doped  $\text{Ni}_3\text{S}_2@\text{NF}$ , 0.25 mmol Co chloride, 0.6 mmol thiourea, and 0.05 mmol Sn chloride ( $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$ , Alfa Aesar, 98.0–103.0%), Fe chloride ( $\text{Cl}_2\text{Fe}$ , Alfa Aesar, 99.5%), and Ni chloride ( $\text{Cl}_2\text{Ni}$ , Alfa Aesar, 98%) were mixed in de-ionized water, respectively. Subsequently, the materials were

hydrothermally synthesized at several different temperatures (120, 140, and 160 °C) and times (1, 4, and 7 h) in an autoclave.

### Characterization of pristine and metal doped-Ni<sub>3</sub>S<sub>2</sub>@NF catalysts

The crystal structures were analyzed using the X-ray diffraction (XRD) technique (Pan Analytical, X'Pert Diffractometer) with filtered Cu-K $\alpha$  radiation source ( $\lambda = 1.5406$  Å wavelength). The XRD patterns were evaluated through step scanning in the  $2\theta$  range of 20–80° with intervals of 0.02°. To characterize the morphologies and crystalline properties of the catalysts, field emission scanning electron microscopy (FE-SEM, S-4700 Hitachi, acceleration voltage of 15 kV) and high-resolution transmission electron microscopy (HR-TEM, JEM-F200, JEOL, acceleration voltage of 200 kV) were conducted with the corresponding energy-dispersive X-ray spectroscopy (EDX) elemental mapping images of the component phases.

The chemical bonding states and electronic structures of the pristine and doped-Ni<sub>3</sub>S<sub>2</sub>@NF catalysts were determined by X-ray photoelectron spectroscopy (XPS, VG Escalab 200i, UK) with an Al K $\alpha$  X-ray source ( $h\nu = 1486.6$  eV). The relative atomic concentrations of Ni 2p, Co 2p, Sn 3d, and S 2p were compared using the peak intensities and integrated area ratios of the catalysts. The surface area (Brunauer–Emmet–Teller, BET) of the pristine and doped-Ni<sub>3</sub>S<sub>2</sub>@NF catalysts was analyzed with a BELSORP-max, BEL instrument while using the N<sub>2</sub> adsorption/desorption isotherms at 77 K. Before the measurements, all of the samples were pre-treated at 80 °C for 3 h. The total pore volume was investigated by converting the adsorbed N<sub>2</sub> gas amount at a relative pressure ( $P/P_0$ ) of 0.99 to the liquid volume of N<sub>2</sub> adsorbate. The Barrett–Joyner–Halenda (BJH) method was used to calculate the pore size distributions in the micropore range from the adsorption branches of the isotherms. The inductively coupled plasma optical emission spectrometry (ICP-OES) experiments were performed with equipment from Spectro (Spectro Arcos II ICP-OES) to analyze the elemental content of catalysts.

### Electrochemical measurements of doped-Ni<sub>3</sub>S<sub>2</sub>@NF catalysts

Electrochemical measurements of the electrocatalysts were carried out using a potentiostat/galvanostat VSP (Biologics, France) with a standard three-electrode system, which uses a Ni<sub>3</sub>S<sub>2</sub>@NF-based catalyst as a working electrode (electrode area =  $1 \times 0.1$  cm<sup>2</sup>), Pt wire as a counter electrode, and Hg/HgO saturated 1 M NaOH as a reference electrode at room temperature. For the electrochemical measurements, the reversible hydrogen electrode (RHE) scale was used to convert all of the potentials. Prior to electrochemical testing, cyclic voltammetry (CV) scans were performed from 0.05 to 1.2 V for 50 cycles (scan rate of 100 mV s<sup>−1</sup>) in 1 M KOH to clean the surfaces of Ni<sub>3</sub>S<sub>2</sub>@NF-based catalysts and stabilize the current. Oxygen evolution reaction (OER) activity measurements were achieved using CV in O<sub>2</sub>-saturated 1 M KOH electrolyte solution at a scan rate of 5 mV s<sup>−1</sup> between 1.2 and 1.7 V. The overpotentials ( $\eta$ ) were ascertained at current densities of 0.1 and 0.2 A cm<sup>−2</sup>. Hydrogen evolution reaction (HER) activity was measured in O<sub>2</sub>-

saturated 1 M KOH solution using the linear sweep voltammetry (LSV) method from −0.6 to 0 V at a scan rate of 5 mV s<sup>−1</sup>.

Electrochemical impedance spectroscopy (EIS) measurements (SP240, BioLogic Science Instruments) were conducted in the range between 100 mHz and 100 kHz at an applied potential of 1.6 V (amplitude at 10 mV). The resistance factors were divided into charge-transport resistance ( $R_{ct}$ ) and mass-transport resistance ( $R_{mt}$ ) from the fitted equivalent circuit model using EC-Lab software. The electrochemical active surface area (ECSA) of the catalysts was investigated by dividing the double-layer capacitances ( $C_{dl}$ ) by the specific capacitance. ECSAs were calculated under different scan rates of 10, 20, 40, 60, and 80 mV s<sup>−1</sup> from 0.05 to 0.25 V. Durability tests were conducted using chronopotentiometry experiments under a constant current density of 0.2 A cm<sup>−2</sup> for 10 and 97 h in O<sub>2</sub>-saturated 1 M KOH solution for the OER.

The electrolysis experiments were conducted with a single cell zero-gap configuration composed of Ni porous transport layers and bipolar plates (single serpentine flow field). The Zirfon Perl membrane (Agfa, thickness of 500  $\mu$ m, for 30 wt% KOH solution) and alkaline exchange membrane (AEM, Fuma-sep FAA-3-50, for 1 M KOH solution) were used as separators for the electrolysis tests. The nickel–iron layered double hydroxide electrode on the nickel foam (NiFe-LDH@NF) and prepared doped-Ni<sub>3</sub>S<sub>2</sub>@NF were used as anodic catalysts for the HER and the OER, respectively. The electrode area of the alkaline water electrolysis (AWE) cells was  $1.65 \times 1.65$  cm<sup>2</sup>. The AWE cells were operated at 55 and 80 °C and 30 wt%, and 1 M KOH electrolyte solutions were circulated to the cell electrode at a flow rate of 200–300 ccm.  $I$ - $V$  polarization curves were measured by a potentiostat (Advanced Power system N7970A, Agilent Technologies) as a function of the current density. EIS analysis was performed in the range between 10 mHz and 100 kHz under the applied current densities of 0.125, 0.5, and 1 A cm<sup>−2</sup>.

### Density functional theory calculation

To address the roles played by Co and Sn doping in catalytic performance, density functional theory (DFT) calculations were made using the projector augmented-wave method and the exchange-correlation functional constructed by the generalized-gradient-approximation in the Perdew–Burke–Ernzerhof scheme,<sup>35</sup> as implemented in the VASP code.<sup>36</sup> A rotationally invariant Hubbard +  $U$  method<sup>37</sup> was applied to Ni 3d ( $U_{\text{eff}} = 6.2$  eV) and Co 3d ( $U_{\text{eff}} = 4.4$  eV) states. The electronic wave functions were described using a plane wave basis set with an energy cut off of 500 eV. All cell parameters were optimized with a residual force cut off of 0.02 eV Å<sup>−1</sup>. A five-atom unit cell and a  $10 \times 10 \times 10$   $k$ -point grid for the Brillouin zone integration were used for pristine Ni<sub>3</sub>S<sub>2</sub>. To investigate the use of metal dopants (*i.e.*, Co and Sn) and its correlation with native defect, several point defects, Ni vacancy ( $V_{\text{Ni}}$ ) and S vacancy ( $V_{\text{S}}$ ), were considered. To simulate the metal-doped and defective Ni<sub>3</sub>S<sub>2</sub>, 135 atom supercells and  $3 \times 3 \times 3$   $k$ -point were employed.

The defect formation energies ( $E_f$ ) of the defects with/without metal dopants were evaluated using the following equation:<sup>38</sup>



$$E_f(D) = E_{\text{tot}}(D) - E_{\text{tot}}(\text{host}) + \sum_i n_i(\mu_i) \quad (1)$$

where  $E_{\text{tot}}(D)$  is the total energy of the supercells containing a defect ( $D = V_{\text{Ni}}$  and  $V_{\text{S}}$ ).  $E_{\text{tot}}(\text{host})$  is the total energy of the pristine or metal-doped  $\text{Ni}_3\text{S}_2$  supercells.  $n_i$  is the number of atoms of type  $i$  (Ni and S) added to ( $n_i > 0$ ) and/or removed ( $n_i < 0$ ) from the perfect supercell to form the defect.  $\mu_i$  is the atomic chemical potential. An extreme case—the Ni-rich ( $\mu_{\text{Ni}} = 1/4E_{\text{tot}}(\text{Ni-metal})$ ) limit—was considered due to the fact that the  $\text{Ni}_3\text{S}_2$  sample was experimentally grown on the Ni foam; then, their OER activities were measured. Thus, the S chemical potential  $\mu_{\text{S}}$  is equal to  $1/2E_{\text{tot}}(\text{S}_2\text{-molecule}) + \Delta\mu$ , where  $\Delta\mu = \frac{1}{2}[\Delta H_f(\text{Ni}_3\text{S}_2)]$ . Here  $\Delta H_f(\text{Ni}_3\text{S}_2)$  is the formation enthalpy of  $\text{Ni}_3\text{S}_2$ . The d-band center is known to be a promising descriptor for understanding catalytic activities, so the metal d-band center ( $\varepsilon_d$ ) is examined using the following equation:

$$\varepsilon_d = \frac{\int_{-\infty}^{E_F} \varepsilon \rho_d d\varepsilon}{\int_{-\infty}^{E_F} \rho_d d\varepsilon} \quad (2)$$

where  $E_F$  represents the Fermi level,  $\rho_d$  denotes the density of states projected onto a single metal d orbital, and  $\varepsilon$  is the energy width of the d orbital.

## Result and discussion

### Physicochemical characterizations of doped nickel sulfides catalysts

Hierarchically structured porous pristine ( $\text{Ni}_3\text{S}_2\text{@NF}$ ), Co ( $\text{Co-Ni}_3\text{S}_2\text{@NF}$ ), CoSn ( $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$ ), CoFe ( $\text{CoFe-Ni}_3\text{S}_2\text{@NF}$ ), and CoNi-doped nickel sulfides ( $\text{CoNi-Ni}_3\text{S}_2\text{@NF}$ ) catalysts on nickel foam (NF) substrate were synthesized using a facile one-step hydrothermal method. To realize high OER performance through the synthesis of hierarchically porous nanostructured catalysts, pristine and doped  $\text{Ni}_3\text{S}_2$  were synthesized under various process conditions [synthesis temperatures (120, 140, and 160 °C) and holding times (1, 4, and 7 h)]. The crystal structures and phase purities of the  $\text{Ni}_3\text{S}_2\text{@NF}$  and doped- $\text{Ni}_3\text{S}_2\text{@NF}$  synthesized at 160 °C for 4 h were characterized through X-ray diffraction (XRD) patterns. As displayed in Fig. 1a, aside from the three main peaks indexed to nickel foam, the five main diffraction peaks of pristine ( $\text{Ni}_3\text{S}_2\text{@NF}$ ) and Co-doped nickel sulfides at 21.8°, 31.1°, 37.8°, 50.1°, and 55.2° were commensurate with those of the heazlewoodite phase of  $\text{Ni}_3\text{S}_2$  (JCPDS no. 44-1418).<sup>39</sup> Moreover, the enlarged portion of  $2\theta$  (in 30° to 33°) evidently indicates the effect of doping as the diffraction peaks shift toward higher (lower)  $2\theta$ , due to the smaller (larger) ionic radii of Co, Fe, and Sn ions, which are doped at host element  $\text{Ni}^{2+}$  site in the four-coordination number, respectively.<sup>40</sup> An additional impurity peak of  $\text{Co}_3\text{Ni}_6\text{S}_8$  in  $\text{Co-Ni}_3\text{S}_2\text{@NF}$  was found at 28° (Fig. S1†), which might be attributable to the side reactions of NF and thiourea ( $\text{CH}_4\text{N}_2\text{S}$ ) with  $\text{CoCl}_2$  during the hydrothermal synthesis.<sup>41</sup> However, in cases of the doping of Sn and Fe for  $\text{Co-Ni}_3\text{S}_2\text{@NF}$  catalysts (synthesized at 160 °C for 4 h), a complete heazlewoodite phase was successfully formed with no specific



Fig. 1 Structural and phase analyses of pristine and doped- $\text{Ni}_3\text{S}_2\text{@NF}$  catalysts using XRD. (a) XRD patterns of  $\text{Ni}_3\text{S}_2\text{@NF}$  and T- $\text{Ni}_3\text{S}_2\text{@NF}$  (T = Co, CoSn, CoFe, and CoNi) catalysts. (b) Heazlewoodite structure of  $\text{CoSn-Ni}_3\text{S}_2$  phase with a space group of  $R32 (155)$ .

impurities, as shown in Fig. 1a. Meanwhile, Fig. 1b shows the crystal structure of  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$ . Heazlewoodite structure  $\text{Ni}_3\text{S}_2$  was described as a rhombohedral structure, and Ni was occupied by a tetrahedral site, which corresponds to the unit cell of  $a = 4.01 \text{ \AA}$  and a space group of  $R32 (155)$ .<sup>42</sup>

The size and morphology of the pristine and doped- $\text{Ni}_3\text{S}_2\text{@NF}$  electrocatalysts were investigated by field emission scanning electron microscopy (FE-SEM, Fig. 2). Fig. S2† shows that the hydrothermal synthesis conditions (temperature and holding time) substantially affected the microstructure of the  $\text{Co-Ni}_3\text{S}_2\text{@NF}$  electrocatalysts. It was found that  $\text{Co-Ni}_3\text{S}_2\text{@NF}$

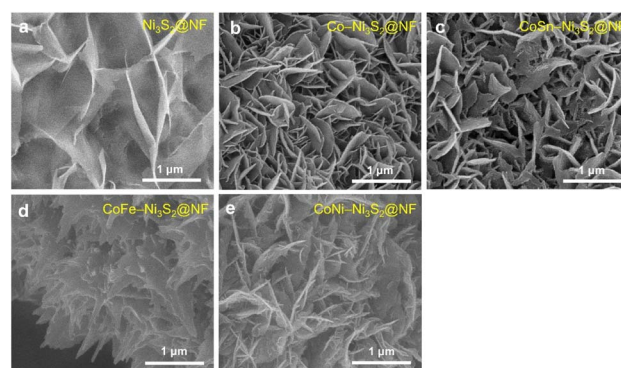


Fig. 2 FE-SEM image of pristine and doped- $\text{Ni}_3\text{S}_2\text{@NF}$  catalysts. (a)  $\text{Ni}_3\text{S}_2\text{@NF}$ , (b)  $\text{Co-Ni}_3\text{S}_2\text{@NF}$ , (c)  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$ , (d)  $\text{CoFe-Ni}_3\text{S}_2\text{@NF}$ , and (e)  $\text{CoNi-Ni}_3\text{S}_2\text{@NF}$ .

synthesized using the hydrothermal method at 160 °C for 4 h exhibited the most optimized morphology of hierarchically porous and ultrathin nanosheets. Accordingly, CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF, CoFe-Ni<sub>3</sub>S<sub>2</sub>@NF, and CoNi-Ni<sub>3</sub>S<sub>2</sub>@NF catalysts were prepared by the same hydrothermal reaction condition at 160 °C and 4 h. For the CoSn-, CoFe-, and CoNi-Ni<sub>3</sub>S<sub>2</sub>@NF catalysts, randomly interconnected and highly porous nickel sulfides flakes are vertically grown on the NF substrate, as shown in Fig. 2.

Fig. 3a and b (Fig. S3a†) shows high resolution-transmission electron microscopy (HR-TEM) images for the and CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF (Ni<sub>3</sub>S<sub>2</sub>@NF and Co-Ni<sub>3</sub>S<sub>2</sub>@NF) arrays. The calculated interplanar d-spacing of CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF (Ni<sub>3</sub>S<sub>2</sub>@NF and Co-Ni<sub>3</sub>S<sub>2</sub>@NF) is about 0.287 nm (0.286 and 0.288 nm, respectively), which is assigned to the (110) crystal plane of Ni<sub>3</sub>S<sub>2</sub>, in accordance with the XRD results (JCPDS no. 44-1418).<sup>43</sup> In the selected area electron diffraction (SAED) pattern analyzed at the [111] zone axis of the HRTEM image (inset of Fig. 3b), representative points located from the center can be identified as (110) and (211) reflections of Ni<sub>3</sub>S<sub>2</sub> nanosheets.<sup>44</sup> Elemental mapping images of the CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF based on energy-

dispersive X-ray spectroscopy (EDS) revealed that all of the composed elements (S, Ni, Co, and Sn) were uniformly coated on the NF surface (Fig. 3c and S3b†). Fig. 3d shows nitrogen adsorption-desorption isotherm results of the pristine and doped-Ni<sub>3</sub>S<sub>2</sub>@NF electrocatalysts. The figure shows similar BET surface areas of 4.56, 7.26, 7.66, 6.34, and 7.66 m<sup>2</sup> g<sup>-1</sup> for Ni<sub>3</sub>S<sub>2</sub>@NF, Co-Ni<sub>3</sub>S<sub>2</sub>@NF, CoNi-Ni<sub>3</sub>S<sub>2</sub>@NF, CoFe-Ni<sub>3</sub>S<sub>2</sub>@NF, and CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF, respectively. The pore volume and size distributions of the catalysts were also calculated from the adsorption-desorption isotherms, as shown in Fig. 3e. The mean pore diameter and total pore volume of the catalysts were 6.2–14.3 nm and 0.011–0.018 cm<sup>3</sup> g<sup>-1</sup>, respectively (Table S1†).

### Oxygen evolution reaction activity and stability

To investigate the electrochemical performances of Ni<sub>3</sub>S<sub>2</sub>@NF, Co-Ni<sub>3</sub>S<sub>2</sub>@NF, CoNi-Ni<sub>3</sub>S<sub>2</sub>@NF, CoFe-Ni<sub>3</sub>S<sub>2</sub>@NF, and CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF, fundamental electrochemical analysis methods such as cyclic voltammetry (CV), linear sweep voltammetry (LSV), electrochemical impedance spectroscopy (EIS) were used.



Fig. 3 Physicochemical analysis of catalysts. (a) HRTEM image and (b) enlarged image with SAED pattern of CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF. The right inset shows an atomic resolution image of yellow dashed box. (c) EDX spectra of each element of CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF. (d) Nitrogen adsorption-desorption isotherms and (e) total pore volume and pore size of Ni<sub>3</sub>S<sub>2</sub>@NF, Co-Ni<sub>3</sub>S<sub>2</sub>@NF, and CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF.

Linear sweep voltammetry (LSV) analysis was conducted in a 1 M KOH solution at a scan rate of  $5 \text{ mV s}^{-1}$  on a three-electrode system. IR compensation (85% IR drop compensation) was carried out to consider the influence of the electrolyte solution resistance during the electrochemical test. Fig. S4a† shows the OER polarization curves of  $\text{Co-Ni}_3\text{S}_2\text{@NF}$  that was synthesized under various hydrothermal conditions ( $120\text{--}160^\circ\text{C}$  for 1–7 h).  $\text{Co-Ni}_3\text{S}_2\text{@NF}$  prepared hydrothermally at  $160^\circ\text{C}$  for 4 h exhibited the best OER activity, with a lower overpotential ( $\eta$ ) of 341 mV at  $0.2 \text{ A cm}^{-2}$  than the other  $\text{Co-Ni}_3\text{S}_2\text{@NF}$  processed at different conditions (120 and  $140^\circ\text{C}$  for 1 and 7 h). Moreover,  $\text{Co-Ni}_3\text{S}_2\text{@NF}$  annealed at  $160^\circ\text{C}$  for 4 h possessed the smallest Tafel slope among all samples with a value of  $97 \text{ mV dec}^{-1}$  (Fig. S4b†), indicating that the hierarchically porous and  $\text{Co-Ni}_3\text{S}_2\text{@NF}$  nanosheet morphology significantly affected the OER performances (Fig. S2b†).

The OER activities of pristine and doped- $\text{Ni}_3\text{S}_2\text{@NF}$  electrocatalysts were evaluated in an  $\text{O}_2$ -saturated 1 M KOH solution at a scan rate of  $5 \text{ mV s}^{-1}$  (Fig. 4a).  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$  exhibited the lowest overpotential of 321 mV at  $0.2 \text{ A cm}^{-2}$  for the OER among all tested samples. In particular, the best OER activity with the lowest  $\eta$  was obtained when the ratio of the amounts of Co and Sn precursors was 5 : 1 among all samples prepared at differing

proportions (Fig. S5a†). The Ir/C catalyst was also tested as the gold standard catalyst for OER under the same conditions. As shown in Fig. 4a,  $\text{CoSn-Ni}_3\text{S}_2$  is even superior to Ir/C (324 mV). More specifically, the  $\eta$  at  $0.2 \text{ A cm}^{-2}$  increased in the following order:  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$  (1.551 V),  $\text{CoFe-Ni}_3\text{S}_2\text{@NF}$  (1.560 V),  $\text{Co-Ni}_3\text{S}_2\text{@NF}$  (1.571 V),  $\text{CoNi-Ni}_3\text{S}_2\text{@NF}$  (1.577 V), and  $\text{Ni}_3\text{S}_2\text{@NF}$  (1.602 V). Namely, doping Co element affects the OER performance of the  $\text{Ni}_3\text{S}_2$  catalyst. It is particularly worth noting that the OER performance of the catalyst substantially improved when Co and Sn were co-doped in  $\text{Ni}_3\text{S}_2$ , and that the  $\eta$  of 298 and 321 mV were required to deliver the current densities of 0.1 and  $0.2 \text{ A cm}^{-2}$ , respectively. To inspect the OER kinetic properties of catalysts, Tafel plots derived from polarization curves (ohmic resistance correct potential,  $E - iR$  vs.  $\log j$ ) are shown in Fig. 4b. The Tafel slopes of  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$ ,  $\text{CoFe-Ni}_3\text{S}_2\text{@NF}$ ,  $\text{CoNi-Ni}_3\text{S}_2\text{@NF}$ ,  $\text{Co-Ni}_3\text{S}_2\text{@NF}$ , and  $\text{Ni}_3\text{S}_2\text{@NF}$  on Ni foam for the OER were 69, 90, 87, 101, and  $125 \text{ mV dec}^{-1}$ , respectively, indicating that the incorporation of Sn (and Fe) atoms into  $\text{Co-Ni}_3\text{S}_2$  triggers an enhancement in OER performance (Table 1). The Tafel slope of Ir/C from the OER polarization curves was  $81 \text{ mV dec}^{-1}$ , indicating the excellent OER kinetics of  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$ .

To assess the scaling-up possibility of water electrolysis, the specific and mass OER activities of the  $\text{Ni}_3\text{S}_2\text{@NF}$ ,  $\text{Co-Ni}_3\text{S}_2\text{@NF}$ , and  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$  catalysts were measured and are shown in Fig. 4c. The specific ( $\text{mA cm}_{\text{BET}}^{-2}$ ) and mass activity ( $\text{A g}^{-1}$ ) were normalized by the BET surface area and the mass loading, respectively. The  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$  achieved an OER specific activity of  $20.7 \text{ mA cm}_{\text{ECSA}}^{-2}$  (and mass activity of  $18.7 \text{ A g}^{-1}$ ) at  $\eta = 370 \text{ mV}$  ( $1.6 \text{ V}$  vs. RHE), which is  $\sim 6.3$  times and  $\sim 3.9$  times that of the  $\text{Ni}_3\text{S}_2\text{@NF}$  ( $4.8 \text{ mA cm}_{\text{ECSA}}^{-2}$  and  $3.0 \text{ A g}^{-1}$ ) and  $\text{Co-Ni}_3\text{S}_2\text{@NF}$  ( $7.1 \text{ mA cm}_{\text{ECSA}}^{-2}$  and  $4.8 \text{ A g}^{-1}$ ), respectively, thus signifying its high feasibility for scalability of electrocatalysts with excellent intrinsic OER activity (Fig. S5b†). More importantly, after an extensive investigation of the activities of other catalysts, the  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$  was found to have a smaller  $\eta$  at  $0.2 \text{ A cm}^{-2}$  than previously reported NF-based OER electrocatalysts in alkaline media (Fig. 4d).<sup>22,28,45–59</sup> The HER catalysis of the  $\text{Ni}_3\text{S}_2\text{@NF}$ ,  $\text{Co-Ni}_3\text{S}_2\text{@NF}$ , and  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$  catalysts was also evaluated together with commercial Pt/C in  $\text{O}_2$ -saturated 1.0 M KOH electrolyte using a typical three-electrode system. As shown in the polarization curve and Tafel plots of Fig. S4c and d,†  $\text{Co-Ni}_3\text{S}_2\text{@NF}$  annealed at  $160^\circ\text{C}$  for 4 h exhibits the smallest  $\eta$  (360 mV at  $0.4 \text{ A cm}^{-2}$  vs. RHE) and Tafel slope ( $119 \text{ mV dec}^{-1}$ ) among all samples, thus confirming that the porous and nanostructured  $\text{Co-Ni}_3\text{S}_2\text{@NF}$  microstructure played an important role in the HER performances. Moreover, doping Sn element into the  $\text{Co-Ni}_3\text{S}_2\text{@NF}$  catalyst contributed to significantly improving the HER performance; the  $\eta$  of  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$  at  $0.4 \text{ A cm}^{-2}$  is nearly 70 and 40 mV lower than that of  $\text{Ni}_3\text{S}_2\text{@NF}$  and  $\text{Co-Ni}_3\text{S}_2\text{@NF}$  (Fig. S6a†). In addition,  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$  provides a lower Tafel slope of  $69 \text{ mV dec}^{-1}$  than those of  $\text{Ni}_3\text{S}_2\text{@NF}$  ( $151 \text{ mV dec}^{-1}$ ) and  $\text{Co-Ni}_3\text{S}_2\text{@NF}$  ( $119 \text{ mV dec}^{-1}$ ), thus indicating enhanced HER kinetics (Fig. S6b†). Further, the  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$  had a lower  $\eta$  at  $0.4 \text{ A cm}^{-2}$  than previously reported NF-based HER electrocatalysts in alkaline media (Fig. S6c†).<sup>50,60–65</sup>

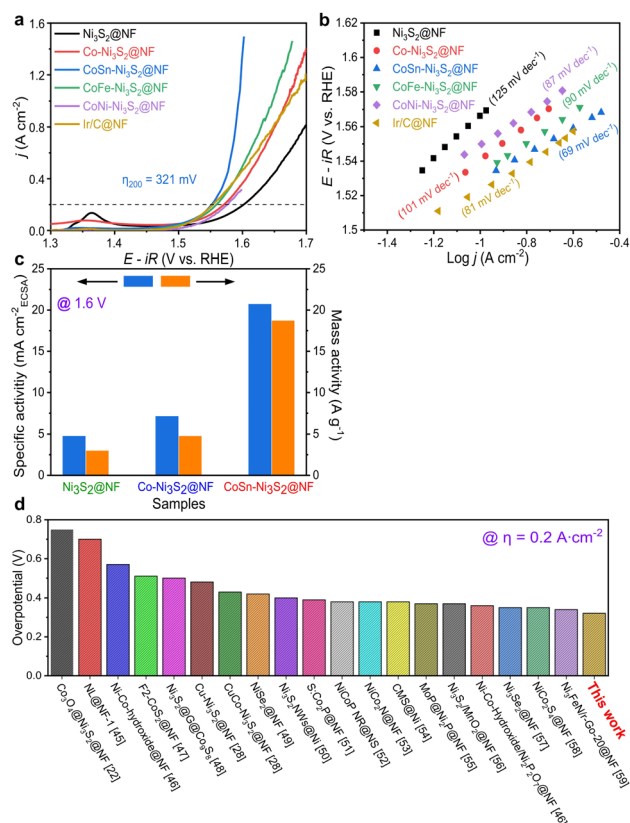


Fig. 4 Electrochemical properties of catalysts for OER. (a) OER polarization curves and (b) Tafel plots of  $\text{Ni}_3\text{S}_2\text{@NF}$  and  $\text{Co-Ni}_3\text{S}_2\text{@NF}$  with Ir/C@NF. (c) Specific activities and mass activities of  $\text{Ni}_3\text{S}_2\text{@NF}$ ,  $\text{Co-Ni}_3\text{S}_2\text{@NF}$ , and  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$ . (d) Comparison of  $\eta$  at  $0.2 \text{ A cm}^{-2}$  for  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$  with previously reported results for other nickel-based catalysts.



**Table 1** Detailed data on electrochemical properties of pristine and doped-Ni<sub>3</sub>S<sub>2</sub>@NF

Catalyst	$\eta$ @ 0.2 A cm <sup>-2</sup> (V)	Tafel slope (mV dec <sup>-1</sup> )	Mass activity @ 1.6 V (A g <sup>-1</sup> )	Specific activity @ 1.6 V (mA cm <sub>ECSA</sub> <sup>-2</sup> )	$R_{ct}$ ( $\Omega$ cm <sup>2</sup> )	ECSA (cm <sup>2</sup> )
Ni <sub>3</sub> S <sub>2</sub> @NF	372	125	3.0	4.8	0.24	37.0
Co-Ni <sub>3</sub> S <sub>2</sub> @NF	341	101	4.8	7.1	0.18	51.5
CoNi-Ni <sub>3</sub> S <sub>2</sub> @NF	347	87	4.0	5.5	0.18	57.8
CoFe-Ni <sub>3</sub> S <sub>2</sub> @NF	330	90	6.2	7.8	0.17	64.3
CoSn-Ni <sub>3</sub> S <sub>2</sub> @NF	321	69	18.7	20.7	0.11	72.3


In electrolysis cell, the operation stability of OER catalysts is an important factor. The long-term stability of catalysts was investigated by the applied constant current in a 1 M O<sub>2</sub>-saturated KOH solution. As shown in Fig. 5a, both Co-Ni<sub>3</sub>S<sub>2</sub>@NF and CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF showed stable potential behavior (1.59 and 1.68 V) with small potential changes under chronopotentiometry at 0.2 A cm<sup>-2</sup> and room temperature for 97 h. In addition, Co-Ni<sub>3</sub>S<sub>2</sub>@NF and CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF present negligible performance degradations (0.3 and 4.5 mV decrease at 0.2 A cm<sup>-2</sup>) during the cycling test between 1.25 and 1.65 V for 1000 cycles (scan rate of 200 mV s<sup>-1</sup>), thus indicating the remarkable stability of nickel sulfides for OER (Fig. 5b). Moreover, the XRD patterns of Co-Ni<sub>3</sub>S<sub>2</sub>@NF and CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF show insignificant change after the stability test (cycling test for 1000 cycles and chronopotentiometry test for 10 h) compared to those of pristine samples (Fig. 5c). The FE-SEM observation results also demonstrate that the morphology of the hierarchically porous CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF nanosheets is well maintained after the OER cycle test, whereas the ends of the nanosheets become rounded in Co-Ni<sub>3</sub>S<sub>2</sub>@NF with a certain degree of agglomeration (Fig. 5d and e). However, the ICP-OES results showed that the atomic ratio (Co : Sn : Ni : S = 1.7 : 0.9 : 91.8 : 5.6) of CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF

electrocatalysts after stability test is somewhat different from that of proportion in the as-prepared sample (Co : Sn : Ni : S = 2.4 : 1.5 : 83.9 : 12.2), indicating some loss of CoSn-Ni<sub>3</sub>S<sub>2</sub> catalysts on the NF during operations. Additional research is need to further improve the stability of Ni<sub>3</sub>S<sub>2</sub>@NF-based catalysts.


### Water-splitting cell performances of electrocatalysts

For industrial applications, AWE cells, which use low-cost power from renewable energy sources, need to satisfy requirements such as the supply of high current density ( $\geq 0.2$  A cm<sup>-2</sup>) at low overpotentials and prolonged durability during oxidizing conditions.<sup>66</sup> Single cell tests were performed using a nickel-iron layered double hydroxide (NiFe-LDH) on nickel foam for the hydrogen evolution reaction (HER, cathode) and OER anodic catalysts with a Zirfon PERL separator (with a thickness of 500  $\mu$ m) (Fig. S7a†).<sup>67,68</sup> Cell performance tests were conducted at a temperature of 80 °C (55 °C) and a flow rate of 30 wt% (1 M) KOH solution equal to 200 ccm (300 ccm).

The *I*-*V* polarization characteristics of the electrolysis cells with Ni<sub>3</sub>S<sub>2</sub>@NF and CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF OER catalysts are shown in Fig. 6. As can be seen in Fig. 6a (55 °C and 1 M KOH), a much higher current density of 0.643 A cm<sup>-2</sup> was reached at a cell

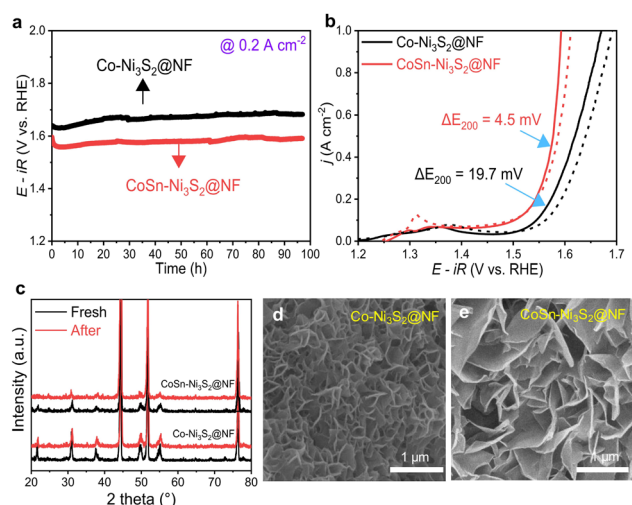

**Fig. 5** Long-term stability of OER catalysts. (a) Durability tests of Co-Ni<sub>3</sub>S<sub>2</sub>@NF and CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF catalysts under 0.2 A cm<sup>-2</sup> for 97 h. (b) Changes of OER activity curves of catalysts after 1000th cycling test between 1.25 V and 1.65 V. (c) XRD patterns of catalysts before and after durability test. FE-SEM image of (d) Co-Ni<sub>3</sub>S<sub>2</sub>@NF and (e) CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF catalysts after durability test.

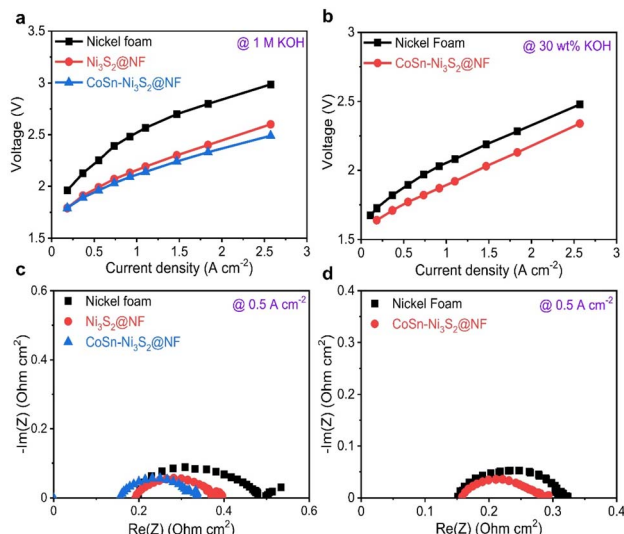

**Fig. 6** Electrochemical results of alkaline water electrolysis cells (with NF, Ni<sub>3</sub>S<sub>2</sub>@NF, and CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF electrodes). Current-voltage curves of alkaline cells under (a) 1 M KOH at 55 °C and (b) 30 wt% KOH solution at 80 °C. EIS curves of alkaline cells at 0.5 A cm<sup>-2</sup> under (c) 1 M KOH at 55 °C and (d) 30 wt% KOH solution at 80 °C.

voltage of 2.0 V for CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF cell, compared to those of the NF (0.227 A cm<sup>-2</sup>) and Ni<sub>3</sub>S<sub>2</sub>@NF (0.551 A cm<sup>-2</sup>) cells, thus indicating the excellent electrocatalytic activity CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF for the OER and showing performance comparable to that of the electrolysis cells composed of any metal oxide catalyst that has been reported to date.<sup>69,70</sup> In addition, the CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF cell showed smaller electrode resistances than the Ni<sub>3</sub>S<sub>2</sub>@NF cell, as specified by the slopes of their *I*-*V* polarization curves. With increasing current density, the difference in the cell voltage between CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF and Ni<sub>3</sub>S<sub>2</sub>@NF (and NF) is more substantial. This result may be attributed to not only the high intrinsic OER activity, but also the effective mass charge transfer. Further, the cell with CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF demonstrated significantly high current densities of 0.7 and 1.367 A cm<sup>-2</sup> at cell voltages of 1.8 and 2.0 V under the conditions of 80 °C and 30 wt% KOH (Fig. 6b). Table S2† summarized the electrochemical performance of recent OER catalysts in the electrolysis cells.

To differentiate the resistance components of the cells in detail, such as ohmic resistance of solution electrolyte (*R*<sub>ohmic</sub>), charge transfer resistance (*R*<sub>ct</sub>), and mass-transfer resistance (*R*<sub>mt</sub>), electrochemical impedance spectroscopy (EIS) was performed under galvanostatic control at 0.125, 0.5, and 1 A cm<sup>-2</sup>. Fig. 6c and d (Fig. S7b-e†) show complex-plane Nyquist plots of NF, Ni<sub>3</sub>S<sub>2</sub>@NF, and CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF at 55 °C (1 M KOH) and 80 °C (30 wt% KOH) for the OER. In the EIS spectra, the high-frequency region indicates the *R*<sub>ohmic</sub>, which is composed of ionic resistance from the electrolyte and electrical connection. The intermediate- and low-frequency regions represent *R*<sub>ct</sub> (electron and ion transfer) and *R*<sub>mt</sub> (ion adsorption, dissociation, and diffusion), respectively.<sup>71</sup> CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF exhibits the lowest *R*<sub>ct</sub> of 0.21, 0.07, and 0.06 Ω cm<sup>2</sup> among all the test samples at 0.125, 0.5, and 1 A cm<sup>-2</sup> (55 °C and 1 M KOH condition) for the OER, respectively. This confirms that doping of Sn and Co for Ni<sub>3</sub>S<sub>2</sub>@NF catalysts contributed significantly to the formation of an effective conducting path for charged ionic/electronic species in the OER.

### Mechanistic study

To identify the decisive factor driving the excellent OER performances of CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF, the surface chemical states and elemental compositions of the catalysts were analyzed by X-ray photoelectron spectroscopy (XPS). Fig. 7a shows the Ni 2p core level XPS spectra of the Ni<sub>3</sub>S<sub>2</sub>@NF, Co-Ni<sub>3</sub>S<sub>2</sub>@NF, and CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF catalysts. Using mixed Gaussian-Lorentzian fitting, the peaks at ~856.4 and ~855.2 eV can be assigned to Ni<sup>3+</sup> and Ni<sup>2+</sup> (2p<sub>3/2</sub>), respectively, while the peaks at ~874.2 and ~872.8 eV can be assigned to Ni<sup>3+</sup> and Ni<sup>2+</sup> (2p<sub>1/2</sub>), respectively. The peaks at 879.4 eV and 861.4 eV can be considered to be satellite peaks of Ni 2p.<sup>72</sup> The relative amount of the oxidation states for Ni ions was assessed from the integrated area ratios of the sub-peaks. Interestingly, the ratio of Ni<sup>2+</sup>/Ni<sup>3+</sup> increased from 0.80 to 0.84 when doped with Co (Co-Ni<sub>3</sub>S<sub>2</sub>@NF) in the heazlewoodite Ni<sub>3</sub>S<sub>2</sub> structure, and it further increased significantly to 1.34 in the case that was co-doped with Sn (CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF). This is because the multivalent Ni ions in Ni<sub>3</sub>S<sub>2</sub> phase can be balanced by modifying higher valence Ni<sup>3+</sup> to



Fig. 7 XPS spectra for (a) Ni 2p and (b) Co 2p of the Ni<sub>3</sub>S<sub>2</sub>@NF, Co-Ni<sub>3</sub>S<sub>2</sub>@NF, and CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF catalysts. (c) EIS analysis of Ni<sub>3</sub>S<sub>2</sub>@NF, Co-Ni<sub>3</sub>S<sub>2</sub>@NF, and CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF catalysts with equivalent circuit model. (d) Linear plots of double layer charging currents with different scan rates (10–80 mV s<sup>-1</sup>) derived from CV diagrams between 0.1–0.2 V (vs. RHE).

lower valence Ni<sup>2+</sup> by increasing the number of electrons (holes) in the Ni<sub>3</sub>S<sub>2</sub> phase to satisfy the electrical neutrality condition.

The same result can be applied in the case of Co ion. The Co 2p XPS spectra of the Co-Ni<sub>3</sub>S<sub>2</sub>@NF and CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF exhibit doublet peaks comprised of two spin orbital lines, Co 2p<sub>3/2</sub> and Co 2p<sub>1/2</sub> at ~780.3 and ~796.7 eV, respectively, thus indicating the coexistence of Co<sup>2+</sup> (~781.6, ~797.4 eV) and Co<sup>3+</sup> (~780.6, ~796.2 eV) oxidation states on the catalyst (Fig. 7b).<sup>73</sup> It should be noted that the ratio of Co<sup>2+</sup>/Co<sup>3+</sup> (in Co-Ni<sub>3</sub>S<sub>2</sub>) also increased from 1.04 to 1.30 when co-doped with Sn (CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF), which endorses that the incorporation of Co and Sn ions in the Ni<sub>3</sub>S<sub>2</sub> converted the electronic configuration of Ni ions with the formation of a highly defective structure. Interactions of multivalent Ni and Co ions with different electronic structures in the heazlewoodite phase could afford plenty of active sites that are beneficial for the OER.<sup>74</sup> Fig. S8a† showed Sn 3d peaks of CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF. In the XPS spectra for Sn 3d, two peaks of Sn 3d<sub>3/2</sub> and Sn 3d<sub>5/2</sub> designate the coexistence of Sn<sup>2+</sup> (~486.0, ~494.5 eV) and Sn<sup>4+</sup> (~486.6, ~495.1 eV) oxidation states, thus indicating that Sn ions were successfully doped into CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF.<sup>24</sup> This phenomenon indicates that Sn doping changed the oxidation state of Co, resulting in some significantly faster charge transfers in CoSn-Ni<sub>3</sub>S<sub>2</sub>@NF. For the S 2p XPS spectra of the pristine and doped Ni<sub>3</sub>S<sub>2</sub>@NF catalysts (Fig. S8b†), the obtained peaks located at ~161.6(8) eV and ~162.9(4) eV respectively corresponded to S 2p<sub>3/2</sub> and S 2p<sub>1/2</sub>, thus revealing the existence of S<sup>2-</sup> species by bonding of metal-sulfur.<sup>75</sup> In particular, the strong peak at a higher value of ~162.4 eV after doping Sn into the Ni<sub>3</sub>S<sub>2</sub> surface is assigned to the sulfur with low coordination, implying the generation of a high density of S vacancies, whereas the peak at ~161.8 eV can be considered to be Ni-S bonds.<sup>72,76</sup>



Electrochemical impedance spectroscopy (EIS) was used in a three-electrode cell configuration to examine the fundamental origin of the high OER activity of  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$ . As shown in Fig. 7c, based on the equivalent circuit model (at 1.6 vs. RHE for OER), the electrode polarization resistance ( $R_{\text{ct}} + R_{\text{mt}}$ ) values were considerably reduced in the order of  $\text{Ni}_3\text{S}_2\text{@NF}$  ( $0.24 \Omega \text{ cm}^2$ ) >  $\text{Co-Ni}_3\text{S}_2\text{@NF}$  ( $0.18 \Omega \text{ cm}^2$ ) >  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$  ( $0.11 \Omega \text{ cm}^2$ ), thus signifying the beneficial effects of the co-doping of Sn and Co on the charge transfer during the OERs. Fig. 7d shows the measured charging current density ( $j_c$ ) plots as a function of scan rates ( $\nu = 10\text{--}80 \text{ mV s}^{-1}$ ) in the non-faradaic range ( $0.05\text{--}0.25 \text{ vs. RHE}$ ) that come from the CV test (Fig. S9†). The double layer capacitance ( $C_{\text{dl}}$ ) was obtained by calculating the slopes of the  $j_c$  plots as a function of  $\nu$  (Fig. S9†).<sup>77</sup> The  $C_{\text{dl}}$  values of  $\text{Ni}_3\text{S}_2\text{@NF}$ ,  $\text{Co-Ni}_3\text{S}_2\text{@NF}$ , and  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$  were 4.7, 20.6, and  $28.9 \text{ mF cm}^{-2}$ , respectively, in 1 M KOH. Further, as a critical indicator of catalysts for OER catalytic activity, the electrochemically active surface area (ECSA) of the catalyst was determined by  $C_{\text{dl}} \times S/C_s$ , where  $C_s$  and  $S$  are the specific capacitance and surface area of the working electrode, respectively. The ECSA of  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$  ( $72.3 \text{ cm}^2$ ) was much higher than those of  $\text{Co-Ni}_3\text{S}_2\text{@NF}$  ( $51.5 \text{ cm}^2$ ) and  $\text{Ni}_3\text{S}_2\text{@NF}$  ( $37.0 \text{ cm}^2$ ), therefore demonstrating that co-doping of Co and Sn in the  $\text{Ni}_3\text{S}_2$  has triggered intrinsic OER catalytic activity with more effective active sites for charged ionic/electronic species.

By combining the experiment and DFT calculations, we attempted to determine the cause of the measured high OER activities of metal doped  $\text{Ni}_3\text{S}_2$ . Our results suggest that this can be understood in terms of (i) defect formation and (ii) Ni 3d-band center. Overall, we find that two dopants, Co and Sn, contribute differently to the OER activity (Table 2); the Co dopant not only becomes an activation site by itself, but it also makes the Ni 3d-band center higher, and the Sn dopant accelerates  $V_s$  formation (that shifts upward Ni 3d-band center) while hardly changing the Ni 3d-band center. Therefore, CoSn co-doping maximizes the OER activities as measured in the experiment.

**(i) Defect formation.** The vacancy formation, which improves the OER performance of oxides and sulfides,<sup>78</sup> is sensitive to whether or not metal is doped as well as which type of metal is doped. As listed in Table 3, although the calculated vacancy formation energies are barely changed with/without Co dopant, those are dramatically reduced after Sn doping and further decrease with CoSn co-doping, possibly due to the fact that the Sn dopant distorts the atomic structure around it (Fig. S10†); hence, the doped structure is less stable, thus leading to easier vacancy formation. The reduced formation

**Table 3** Calculated defect formation energy and Ni 3d-band center. Values in parentheses are responsible for Co 3d band center

Formation energy (eV)	$\text{Ni}_3\text{S}_2$	$\text{Co-Ni}_3\text{S}_2$	$\text{Sn-Ni}_3\text{S}_2$	$\text{CoSn-Ni}_3\text{S}_2$
$V_{\text{Ni}}$	0.785	0.808	−0.105	−0.114
$V_s$	1.681	1.952	−1.245	−1.339
Ni 3d-band center (eV)	$\text{Ni}_3\text{S}_2$	$\text{Co-Ni}_3\text{S}_2$	$\text{Sn-Ni}_3\text{S}_2$	$\text{CoSn-Ni}_3\text{S}_2$
Without vacancies	−3.07	−3.03 (−2.39)	−3.07	−3.06 (−2.76)
$V_{\text{Ni}}$	−3.04	−3.03 (−2.30)	−3.07	−3.06 (−2.76)
$V_s$	−3.00	−3.00 (−2.05)	−3.02	−3.02 (−2.59)

energies indicate that Sn and Co co-doping easily generate vacancies in  $\text{Ni}_3\text{S}_2$ . These results are consistent with the literature reporting the improvement of OER activity after metal doping. For example, Fe-doped  $\text{Ni}_3\text{S}_2$  with rich  $V_s$  shows a reduced OER energy barrier promoted by both Fe doping and the high content of  $V_s$ .<sup>76</sup> Thus,  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$  in our experiment includes affluently generated vacancies and surface oxidation and shows improved OER performance.

Interestingly, Sn and Co co-doping leads to a crossover of the dominant vacancy type. In  $\text{Ni}_3\text{S}_2$  and  $\text{Co-Ni}_3\text{S}_2$ ,  $V_{\text{Ni}}$  is more likely to form than  $V_s$ , since  $E_f(V_{\text{Ni}})$  is calculated to be lower than  $E_f(V_s)$ . On the other hand, after co-doping of Sn and Co, the  $V_s$  formation is much more pronounced than the  $V_{\text{Ni}}$  formation. For example,  $E_f(V_{\text{Ni}})$  is nearly ten times greater than  $E_f(V_s)$  in  $\text{CoSn-Ni}_3\text{S}_2$  (note that, since the calculation of the defect formation energy is based on a thermodynamic equilibrium growth environment whereas our experiment is not, the absolute formation energy is less meaningful in our case). Therefore, although there may exist a  $V_{\text{Ni}}$  with moderate content, the number of electron carriers increases due to a larger content of  $V_s$  (electron supplier) than that of  $V_{\text{Ni}}$  (hole supplier). This is consistent with the experimentally observed ratio of  $\text{Ni}^{2+}/\text{Ni}^{3+}$  (increased from 0.80 in  $\text{Ni}_3\text{S}_2$  to 1.34 in  $\text{CoSn-Ni}_3\text{S}_2$ ) and the ratio of  $\text{Co}^{2+}/\text{Co}^{3+}$  (increased from 1.04 in  $\text{Co-Ni}_3\text{S}_2$  to 1.37 in  $\text{CoSn-Ni}_3\text{S}_2$ ), which possibly result from an increase in electrons relative to holes. More importantly, the observation of higher (greater) OER activity ( $V_s$  content than  $V_{\text{Ni}}$  content) of  $\text{Sn-Ni}_3\text{S}_2\text{@NF}$  and  $\text{CoSn-Ni}_3\text{S}_2\text{@NF}$  compared to  $\text{Co-Ni}_3\text{S}_2\text{@NF}$  indicates that  $V_s$  is more important than  $V_{\text{Ni}}$  in terms of the OER activity.

**(ii) Ni 3d-band center.** It is known that the d-band center indicates an increase in the adsorbates when it shifts close to

**Table 2** Summary of role of dopant and native defect in catalytic activity of  $\text{Ni}_3\text{S}_2$ . + indicates the magnitude of positive contribution to the activity

Contribution	$\text{Co-Ni}_3\text{S}_2$	$\text{Sn-Ni}_3\text{S}_2$	$\text{CoSn-Ni}_3\text{S}_2$
Increasing of activation site	+, Co dopant	+, $V_s$	++, Co dopant & $V_s$
Shift of Ni 3d-band center to $E_F$	+, by Co dopant	+, by $V_s$ (barely changed by Sn)	++, by Co & $V_s$
Increasing of electron carriers		+, by $V_s$	+, by $V_s$
Total	++	+++	++++



**Fig. 8** Calculated DOS for (a)  $\text{Ni}_3\text{S}_2$ , (b)  $\text{Co-Ni}_3\text{S}_2$ , (c)  $\text{Sn-Ni}_3\text{S}_{2-x}$ , and (d)  $\text{CoSn-Ni}_3\text{S}_{2-x}$ . Sn and CoSn-doping leads to  $V_s$  formation in  $\text{Ni}_3\text{S}_2$ , and hence (c) and (d) are responsible for the supercells including one  $V_s$ . Olive and blue dashed lines denote Ni 3d-band center ( $\epsilon_d(\text{Ni})$ ) and Co 3d-band center ( $\epsilon_d(\text{Co})$ ), respectively, and black line indicates Fermi level. DOS values of Co and Sn components are multiplied by ten for easy visualization.

the Fermi level.<sup>79</sup> Thus, the d-band centers of  $\text{Ni}_3\text{S}_2$ ,  $\text{Co-Ni}_3\text{S}_2$ ,  $\text{Sn-Ni}_3\text{S}_2$ , and  $\text{CoSn-Ni}_3\text{S}_2$  were estimated using eqn (2). The position of the Ni 3d-band center was added in the DOS plot of each substance (Fig. 8, S11, and S12<sup>†</sup>), and the estimated values are summarized in Table 3. Our DFT calculations show that Co doping and the  $V_s$  formation shifts the Ni 3d-band center upward and closer to the Fermi level. The Co dopant shifts the Ni 3d-band center upward by 0.04 eV for  $\text{Co-Ni}_3\text{S}_2$  and by 0.01 eV for  $\text{CoSn-Ni}_3\text{S}_2$  compared to  $\text{Ni}_3\text{S}_2$ . The impact of the  $V_s$  formation in the Ni 3d-band center is more significant. The  $V_s$  formation shifts the Ni 3d-band center upward by 0.07 eV ( $\text{Ni}_3\text{S}_2$ ), 0.03 eV ( $\text{Co-Ni}_3\text{S}_2$ ), 0.05 eV ( $\text{Sn-Ni}_3\text{S}_2$ ), and 0.04 eV ( $\text{CoSn-Ni}_3\text{S}_2$ ). These values are comparable to or even greater than the reported d-band center shift of the other metal-doped  $\text{Ni}_3\text{S}_2$  (e.g., 0.03 eV in Cu-doped  $\text{Ni}_3\text{S}_2/\text{Co}_3\text{S}_4$  (ref. 80)). On the other hand, the Sn dopant and  $V_{\text{Ni}}$  either have no effect on the Ni 3d-band center or induce a much smaller change in the Ni 3d-band center than the Co dopant and  $V_s$ .

## Conclusions

With the goal of designing a high-performance, durable, and cost-effective electrocatalyst, we demonstrated that multi-valent transition metal (Co) and post-transition metal (Sn)-co-doped  $\text{Ni}_3\text{S}_2$ @NF are highly active and durable for the OERs in alkaline medium. The hierarchically porous and nanostructured  $\text{CoSn-Ni}_3\text{S}_2$ @NF catalysts were synthesized *via* a facile and reproducible hydrothermal synthesis method.  $\text{CoSn-Ni}_3\text{S}_2$ @NF exhibited better OER activity with a lower  $\eta$  of 321 mV at 0.2 A  $\text{cm}^{-2}$  (Tafel slope of 69 mV  $\text{dec}^{-1}$ ) than the  $\text{CoFe-Ni}_3\text{S}_2$ @NF (330 mV, 90 mV  $\text{dec}^{-1}$ ),  $\text{Co-Ni}_3\text{S}_2$ @NF (341 mV, 101 mV  $\text{dec}^{-1}$ ),

and  $\text{Ni}_3\text{S}_2$ @NF (372 mV, 125 mV  $\text{dec}^{-1}$ ) catalysts. More importantly, the  $\eta$  of  $\text{CoSn-Ni}_3\text{S}_2$ @NF at 0.2 A  $\text{cm}^{-2}$  was smaller than NF-based OER electrocatalysts that have previously been reported, including Ir/C (324 mV, 81 mV  $\text{dec}^{-1}$ ) in alkaline media, which validates that the incorporation of Sn and Co atoms into  $\text{Ni}_3\text{S}_2$  triggers OER performance enhancement. In addition,  $\text{CoSn-Ni}_3\text{S}_2$ @NF presented negligible performance degradations during the constant current (at 0.2 A  $\text{cm}^{-2}$  for 10 h) and voltage cycling test between 1.25 and 1.65 V for 1000 cycles, thus indicating remarkable stability for the OER. Further, the  $\text{CoSn-Ni}_3\text{S}_2$ @NF alkaline water electrolysis cell demonstrated excellent polarization characteristics corresponding to a cell voltage of 2.0 V at a current density of 1.367 A  $\text{cm}^{-2}$ , 80 °C, and 30 wt% KOH condition. Experimental results and DFT calculations revealed that two dopants, Co and Sn, contribute differently to the OER activity of  $\text{CoSn-Ni}_3\text{S}_2$ @NF; the Co dopant becomes an activation site and makes the Ni 3d-band center higher, while the Sn dopant contributes to the OER activity by generating donor-type  $V_s$  that is an activation site, and it also shifts the Ni 3d-band center upward and closer to the Fermi level. Therefore, CoSn co-doping maximizes the OER activities as measured experimentally. This finding provides new possibilities for designing high performance transition and post-transition metal sulfides electrocatalysts for overall water electrolysis technologies.

## Author contributions

Won Young An: conceptualization, methodology, investigation, validation, data acquiring & analysis, visualization, writing – original draft. Hyungwoo Lee: data curation, software, data acquiring & analysis, writing – original draft. Sung Ryul Choi: methodology, investigation, validation, data acquiring & analysis. Sungyong Choi: methodology, investigation, validation, data acquiring & analysis. Hyun-Seok Cho: methodology, resources, supervision, writing – review & editing. Minseok Choi: data curation, software, supervision, writing – review & editing. Jun-Young Park: conceptualization, methodology, funding acquisition, supervision, writing – review & editing.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This research was supported by the Basic Science Research Program through the National Research Foundation of Korea (NRF) funded by the Ministry of Education (NRF-2020R1A6A1A03043435, NRF-2021R1F1A1051716) and Technology Innovation Program (20011633) funded by the Ministry of Trade, Industry & Energy of (MOTIE) Korea.

## References

- 1 H. Zhao and Y. Lei, *Adv. Energy Mater.*, 2020, **10**, 2001460.

- 2 S. R. Choi, M. Lim, D. Y. Kim, W. Y. An, S. W. Lee, S. Choi, S. J. Bae, S.-D. Yim and J.-Y. Park, *Int. J. Hydrogen Energy*, 2022, **47**, 17379–17392.
- 3 F. Qureshi, M. Yusuf, H. Kamyab, S. Zaidi, M. J. Khalil, M. A. Khan, M. A. Alam, F. Masood, L. Bazli and S. Chelliapan, *Sustain. Energy Technol. Assessments*, 2022, **53**, 102677.
- 4 S. Singla, N. P. Shetti, S. Basu, K. Mondal and T. M. Aminabhavi, *J. Environ. Manage.*, 2022, **302**, 113963.
- 5 S. Sadeghi, S. Ghandehariun and M. A. Rosen, *Energy*, 2020, **208**, 118347.
- 6 A. Al-Qahtani, B. Parkinson, K. Hellgardt, N. Shah and G. Guillen-Gosalbez, *Appl. Energy*, 2021, **281**, 115958.
- 7 Z. Y. Yu, Y. Duan, X. Y. Feng, X. Yu, M. R. Gao and S. H. Yu, *Adv. Mater.*, 2021, **33**, 2007100.
- 8 E. Fabbri, A. Habereeder, K. Waltar, R. Kötz and T. J. Schmidt, *Catal. Sci. Technol.*, 2014, **4**, 3800–3821.
- 9 Z. Li, X. Wu, X. Jiang, B. Shen, Z. Teng, D. Sun, G. Fu and Y. Tang, *Advanced Powder Materials*, 2022, **1**, 100020.
- 10 S. Anwar, F. Khan, Y. Zhang and A. Djire, *Int. J. Hydrogen Energy*, 2021, **46**, 32284–32317.
- 11 P. Chen and X. Hu, *Adv. Energy Mater.*, 2020, **10**, 2002285.
- 12 H. M. Amin and U. P. Apfel, *Eur. J. Inorg. Chem.*, 2020, **2020**, 2679–2690.
- 13 X. Wang, X. Huang, W. Gao, Y. Tang, P. Jiang, K. Lan, R. Yang, B. Wang and R. Li, *J. Mater. Chem. A*, 2018, **6**, 3684–3691.
- 14 D. Y. Kim, H. Lee, S. R. Choi, S. Choi, W. Y. An, H.-S. Cho, M. Choi and J.-Y. Park, *J. Alloys Compd.*, 2022, **914**, 165305.
- 15 C. Manjunatha, N. Srinivasa, S. Chaitra, M. Sudeep, R. C. Kumar and S. Ashoka, *Mater. Today Energy*, 2020, **16**, 100414.
- 16 L. Zeng, K. Sun, X. Wang, Y. Liu, Y. Pan, Z. Liu, D. Cao, Y. Song, S. Liu and C. Liu, *Nano Energy*, 2018, **51**, 26–36.
- 17 W. Zhou, X.-J. Wu, X. Cao, X. Huang, C. Tan, J. Tian, H. Liu, J. Wang and H. Zhang, *Energy Environ. Sci.*, 2013, **6**, 2921–2924.
- 18 Q. Lin, Y. Zhu, Z. Hu, Y. Yin, H.-J. Lin, C.-T. Chen, X. Zhang, Z. Shao and H. Wang, *J. Mater. Chem. A*, 2020, **8**, 6480–6486.
- 19 P. Zhang, Z. Wang, X. Hou, J. Lu, X. Xu, C. Stampfl and C. Hu, *Appl. Catal., A*, 2021, **624**, 118324.
- 20 J.-J. Duan, Z. Han, R.-L. Zhang, J.-J. Feng, L. Zhang, Q.-L. Zhang and A.-J. Wang, *J. Colloid Interface Sci.*, 2021, **588**, 248–256.
- 21 S. R. Choi, J.-I. Lee, H. Park, S. W. Lee, D. Y. Kim, W. Y. An, J. H. Kim, J. Kim, H.-S. Cho and J.-Y. Park, *Chem. Eng. J.*, 2021, **409**, 128226.
- 22 Y. Gong, Z. Xu, H. Pan, Y. Lin, Z. Yang and X. Du, *J. Mater. Chem. A*, 2018, **6**, 5098–5106.
- 23 S. Song, Y. Wang, W. Li, P. Tian, S. Zhou, H. Gao, X. Tian and J. Zang, *J. Alloys Compd.*, 2020, **827**, 154299.
- 24 J. Yu, F.-X. Ma, Y. Du, P.-P. Wang, C.-Y. Xu and L. Zhen, *ChemElectroChem*, 2017, **4**, 594–600.
- 25 J. Jian, L. Yuan, H. Qi, X. Sun, L. Zhang, H. Li, H. Yuan and S. Feng, *ACS Appl. Mater. Interfaces*, 2018, **10**, 40568–40576.
- 26 G. Zhang, Y.-S. Feng, W.-T. Lu, D. He, C.-Y. Wang, Y.-K. Li, X.-Y. Wang and F.-F. Cao, *ACS Catal.*, 2018, **8**, 5431–5441.
- 27 B. Fei, Z. Chen, J. Liu, H. Xu, X. Yan, H. Qing, M. Chen and R. Wu, *Adv. Energy Mater.*, 2020, **10**, 2001963.
- 28 J.-F. Qin, M. Yang, S. Hou, B. Dong, T.-S. Chen, X. Ma, J.-Y. Xie, Y.-N. Zhou, J. Nan and Y.-M. Chai, *Appl. Surf. Sci.*, 2020, **502**, 144172.
- 29 X. Wu, T. Zhang, J. Wei, P. Feng, X. Yan and Y. Tang, *Nano Res.*, 2020, **13**, 2130–2135.
- 30 H. Sun, Z. Yan, F. Liu, W. Xu, F. Cheng and J. Chen, *Adv. Mater.*, 2020, **32**, 1806326.
- 31 N. Mahmood, Y. Yao, J. W. Zhang, L. Pan, X. Zhang and J. J. Zou, *Adv. Sci.*, 2018, **5**, 1700464.
- 32 N. Chen, S. Y. Paek, J. Y. Lee, J. H. Park, S. Y. Lee and Y. M. Lee, *Energy Environ. Sci.*, 2021, **14**, 6338–6348.
- 33 X. Luo, P. Ji, P. Wang, R. Cheng, D. Chen, C. Lin, J. Zhang, J. He, Z. Shi and N. Li, *Adv. Energy Mater.*, 2020, **10**, 1903891.
- 34 L. Ma, K. Zhang, S. Wang, L. Gao, Y. Sun, Q. Liu, J. Guo and X. Zhang, *Appl. Surf. Sci.*, 2019, **489**, 815–823.
- 35 J. P. Perdew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, **77**, 3865.
- 36 G. Kresse and J. Hafner, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1993, **47**, 558.
- 37 S. L. Dudarev, G. A. Botton, S. Y. Savrasov, C. Humphreys and A. P. Sutton, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1998, **57**, 1505.
- 38 C. Freysoldt, B. Grabowski, T. Hickel, J. Neugebauer, G. Kresse, A. Janotti and C. G. Van de Walle, *Rev. Mod. Phys.*, 2014, **86**, 253.
- 39 X. Liu, Y. Li, N. Chen, D. Deng, X. Xing and Y. Wang, *Electrochim. Acta*, 2016, **213**, 730–739.
- 40 T. Ai, H. Wang, W. Bao, L. Feng, X. Zou, X. Wei, L. Ding, Z. Deng and B. Rao, *Chem. Eng. J.*, 2022, **450**, 138358.
- 41 A. Ashok, A. Kumar, J. Ponraj and S. A. Mansour, *Carbon*, 2020, **170**, 452–463.
- 42 G. Gibbs, R. Downs, C. Prewitt, K. M. Rosso, N. Ross and D. F. Cox, *J. Phys. Chem. B*, 2005, **109**, 21788–21795.
- 43 Q. Xu, M. Chu, M. Liu, J. Zhang, H. Jiang and C. Li, *Chem. Eng. J.*, 2021, **411**, 128488.
- 44 B. Wu, H. Qian, Z. Nie, Z. Luo, Z. Wu, P. Liu, H. He, J. Wu, S. Chen and F. Zhang, *J. Energy Chem.*, 2020, **46**, 178–186.
- 45 T. Zhu, L. Zhu, J. Wang and G. W. Ho, *J. Mater. Chem. A*, 2016, **4**, 13916–13922.
- 46 N. R. Chodankar, I. V. Bagal, S. W. Ryu, Y. K. Han and D. H. Kim, *ChemCatChem*, 2019, **11**, 4256–4261.
- 47 L. Lei, D. Huang, C. Zhang, R. Deng, S. Chen and Z. Li, *J. Catal.*, 2020, **385**, 129–139.
- 48 Q. Dong, Y. Zhang, Z. Dai, P. Wang, M. Zhao, J. Shao, W. Huang and X. Dong, *Nano Res.*, 2018, **11**, 1389–1398.
- 49 X. Li, G.-Q. Han, Y.-R. Liu, B. Dong, X. Shang, W.-H. Hu, Y.-M. Chai, Y.-Q. Liu and C.-G. Liu, *Electrochim. Acta*, 2016, **205**, 77–84.
- 50 D. Zhang, J. Li, J. Luo, P. Xu, L. Wei, D. Zhou, W. Xu and D. Yuan, *Nanotechnology*, 2018, **29**, 245402.
- 51 M. A. R. Anjum, M. D. Bhatt, M. H. Lee and J. S. Lee, *Chem. Mater.*, 2018, **30**, 8861–8870.
- 52 J.-G. Wang, W. Hua, M. Li, H. Liu, M. Shao and B. Wei, *ACS Appl. Mater. Interfaces*, 2018, **10**, 41237–41245.



- 53 Y. Wang, B. Zhang, W. Pan, H. Ma and J. Zhang, *ChemSusChem*, 2017, **10**, 4170–4177.
- 54 J. Li, W. Xu, J. Luo, D. Zhou, D. Zhang, L. Wei, P. Xu and D. Yuan, *Nano-Micro Lett.*, 2018, **10**, 1–10.
- 55 C. Du, M. Shang, J. Mao and W. Song, *J. Mater. Chem. A*, 2017, **5**, 15940–15949.
- 56 Y. Xiong, L. Xu, C. Jin and Q. Sun, *Appl. Catal., B*, 2019, **254**, 329–338.
- 57 A. Sivanantham and S. Shanmugam, *Appl. Catal., B*, 2017, **203**, 485–493.
- 58 J. Yu, C. Lv, L. Zhao, L. Zhang, Z. Wang and Q. Liu, *Adv. Mater. Interfaces*, 2018, **5**, 1701396.
- 59 Y. Gu, S. Chen, J. Ren, Y. A. Jia, C. Chen, S. Komarneni, D. Yang and X. Yao, *ACS Nano*, 2018, **12**, 245–253.
- 60 K.-L. Yan, J.-F. Qin, Z.-Z. Liu, B. Dong, J.-Q. Chi, W.-K. Gao, J.-H. Lin, Y.-M. Chai and C.-G. Liu, *Chem. Eng. J.*, 2018, **334**, 922–931.
- 61 K. S. Bhat and H. Nagaraja, *Int. J. Hydrogen Energy*, 2018, **43**, 19851–19863.
- 62 X. Wang, R. Liu, Y. Zhang, L. Zeng and A. Liu, *Appl. Surf. Sci.*, 2018, **456**, 164–173.
- 63 S. Shit, S. Chhetri, W. Jang, N. C. Murmu, H. Koo, P. Samanta and T. Kuila, *ACS Appl. Mater. Interfaces*, 2018, **10**, 27712–27722.
- 64 L. Zhang, K. Xiong, S. Chen, L. Li, Z. Deng and Z. Wei, *J. Power Sources*, 2015, **274**, 114–120.
- 65 J. Lin, H. Wang, X. Zheng, Y. Du, C. Zhao, J. Qi, J. Cao, W. Fei and J. Feng, *J. Power Sources*, 2018, **401**, 329–335.
- 66 Y. Li, B. Wei, Z. Yu, O. Bondarchuk, A. Araujo, I. Amorim, N. Zhang, J. Xu, I. C. Neves and L. Liu, *ACS Sustainable Chem. Eng.*, 2020, **8**, 10193–10200.
- 67 Y. Zhu, X. Wang, X. Zhu, Z. Wu, D. Zhao, F. Wang, D. Sun, Y. Tang, H. Li and G. Fu, *Small*, 2022, **19**, 2206531.
- 68 S. Chen, Z. Zheng, Q. Li, H. Wan, G. Chen, N. Zhang, X. Liu and R. Ma, *J. Mater. Chem. A*, 2023, **11**, 1944–1953.
- 69 E. López-Fernández, J. Gil-Rostra, J. P. Espinos, A. R. González-Elipé, F. Yubero and A. de Lucas-Consuegra, *J. Power Sources*, 2019, **415**, 136–144.
- 70 G.-C. Chen, T. H. Wondimu, H.-C. Huang, K.-C. Wang and C.-H. Wang, *Int. J. Hydrogen Energy*, 2019, **44**, 10174–10181.
- 71 J. E. Park, S. Y. Kang, S.-H. Oh, J. K. Kim, M. S. Lim, C.-Y. Ahn, Y.-H. Cho and Y.-E. Sung, *Electrochim. Acta*, 2019, **295**, 99–106.
- 72 F. Lu, M. Zhou, W. Li, Q. Weng, C. Li, Y. Xue, X. Jiang, X. Zeng, Y. Bando and D. Golberg, *Nano Energy*, 2016, **26**, 313–323.
- 73 J. Feng, Y. Meng, Z. Lian, L. Fang, Z. Long, Y. Li and Y. Song, *RSC Adv.*, 2019, **9**, 9729–9736.
- 74 L. Tang, T. Fan, Z. Chen, J. Tian, H. Guo, M. Peng, F. Zuo, X. Fu, M. Li and Y. Bu, *Chem. Eng. J.*, 2021, **417**, 129324.
- 75 Z. Li, D. Zhao, C. Xu, J. Ning, Y. Zhong, Z. Zhang, Y. Wang and Y. Hu, *Electrochim. Acta*, 2018, **278**, 33–41.
- 76 S.-C. Sun, F.-X. Ma, Y. Li, L.-W. Dong, H. Liu, C.-M. Jiang, B. Song, L. Zhen and C.-Y. Xu, *Sustainable Energy Fuels*, 2020, **4**, 3326–3333.
- 77 Y. Liu, X. Liang, L. Gu, Y. Zhang, G.-D. Li, X. Zou and J.-S. Chen, *Nat. Commun.*, 2018, **9**, 1–10.
- 78 Y. Jia, K. Jiang, H. Wang and X. Yao, *Chem*, 2019, **5**, 1371–1397.
- 79 B. Hammer and J. K. Nørskov, *Adv. Catal.*, 2000, **45**, 71–129.
- 80 H. Su, S. Song, S. Li, Y. Gao, L. Ge, W. Song, T. Ma and J. Liu, *Appl. Catal., B*, 2021, **293**, 120225.